

**M. Landowski<sup>1</sup>, M. Budzik<sup>1,2</sup>, K. Imielińska<sup>1</sup>**

<sup>1</sup>*Gdańsk University of Technology, Mechanical Faculty, 80-233 Gdańsk Narutowicza 11/12 Gdańsk, Poland, \* [mlandowski@gmail.com](mailto:mlandowski@gmail.com)*

<sup>2</sup>*Aarhus University, Department of Engineering, 8200 Aarhus C, Dalgas Avenue 2, Denmark*

## **DYNAMIC MECHANICAL BEHAVIOUR OF GFRP COMPOSITES WITH SiO<sub>2</sub> NANO PARTICLES REINFORCED EPOXY MATRIX**

### **ABSTRACT**

Dynamic mechanic (DMA) tests were performed to compare the mechanical behaviour of glass fibre reinforced epoxy laminate composites with SiO<sub>2</sub> nanoparticle reinforced matrix. The selection of the most promising nanoparticle concentrations was considered in terms of elastic modulus and glass transition temperature. The reference specimens (0% nanoparticles) did not contain diluent accordingly the results do not allow the exact comparison with unreinforced composite, nevertheless the ranking of the nanocomposites was made. In terms of stiffness requirements 20% nanoparticles composites offer the best behaviour, 25% higher elastic modulus than 5% nanoparticles. For nano composites the glass transition temperature T<sub>G</sub> is the highest: 80°C, 77°C for 3%, 5% nanoparticles respectively and the lowest 75°C, 72°C, 71°C for 15%, 10% and 20% nanoparticles is respectively.

**Key words:** *Polymer composites, nano composite, DMA, glass transition temperature*

### **INTRODUCTION**

Recently, significant research efforts were invested in improving the toughness of epoxy resin matrices for fibre reinforced composites. As described in ref. [1] various strategies were followed with variable success. According to the recent review, modification of epoxy resin with nano filler - organo-silicates (clay) is known as effective for enhancement of mechanical performance like modulus and strength [2]. As fracture toughness [3,4,] however in some cases no improvement or even a reduction was observed. Some researchers found such modifications of the resin to be effective for increasing the performance of the laminates as well. Specifically bending strength and modulus [5,6] could be enhanced by up to 15 and 30% respectively.

In addition to clay minerals hard nanoparticles such as SiO<sub>2</sub>, SiC i Al<sub>2</sub>O<sub>3</sub> are used as fillers of epoxy resins. The optimum amount of nanoparticles for the best improvement of fracture toughness, as reported by Su Zhao is 10-15% nano Al<sub>2</sub>O<sub>3</sub>. The effect of nanoparticles on other properties is not well known. Accordingly it is essential to accumulate the experimental data obtained on various materials in different laboratories and conditions. The aim of this preliminary study was to compare the effect of nanoparticle modifiers of epoxy resin matrix in GFRP laminates in terms of the mechanical performance and glass transition temperature.

## MATERIALS AND EXPERIMENTS

Glass fibre-reinforced-epoxy (GFRP) laminates were investigated in this study. Epoxy matrix resin Hexion 285 cured with L285 hardener was modified with SiO<sub>2</sub> nano-particles 3wt%, 5wt%, 10wt%, 15wt% 20%. In order to reduce resin viscosity and thus facilitate impregnation of the fibres the nanoparticle modified epoxy resin mixture was diluted by using 5wt% diluent, a (mixture of ethyl benzene and isobutene). Glass fibres were woven fabric: 2 layers 110 g/m<sup>2</sup> and 5 layers 80 g/m<sup>2</sup> (Krosno). The same fibres and resin (without nanoparticles or diluent) were used to produce a laminate plate needed for comparison with nanoparticle composites. All laminates were fabricated using hand lay-up method. Dynamic mechanic (DMA) tests were performed using MetraVib+150 (ACOEM, Limonest, France). Three specimens of each materials were tested so as to consider the selection of the most promising nanoparticle concentrations.

## RESULTS AND DISCUSSION

Figs. 1, 2 illustrate Young modulus and loss angle respectively as a function of temperature for glass fibre reinforced laminates with 5 nano-particle reinforced epoxy matrices. Significant (ca. 25%) enhancement of Young modulus is observed for 20% nanoparticles composites compared with 5%N. 15% nanoparticles gives only slightly lower modulus. For smaller concentrations of nanoparticles (3%,) and 10% the results are similar. 5% N exhibits definitely the lowest modulus. The reference plot for pure GFR epoxy laminates was not considered in the final evaluation since the matrix resin was not diluted. Accordingly only the nanoparticle composites were compared.

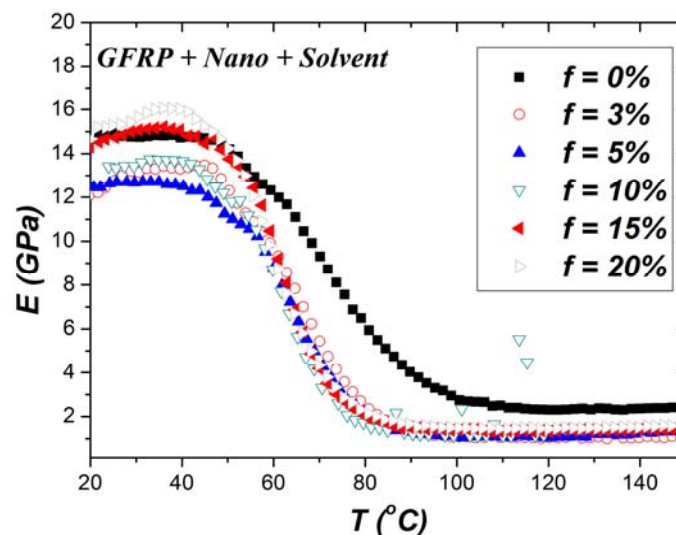
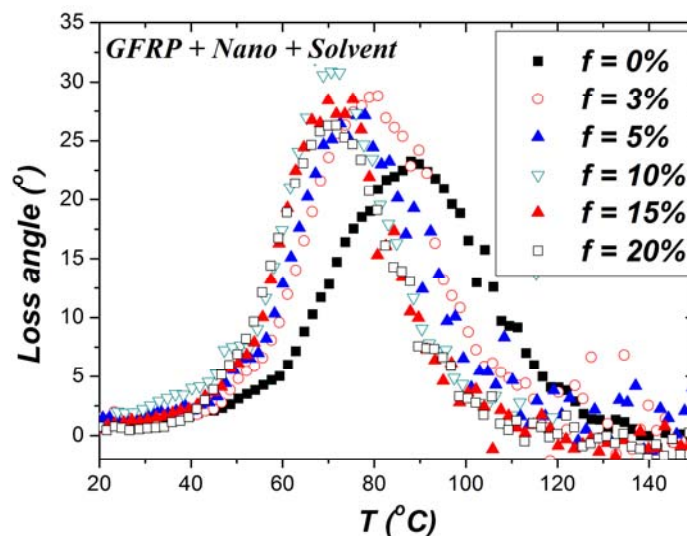


Fig. 1. Young modulus vs. temperature for glass fibre reinforced laminates with 5 nano-particle reinforced epoxy matrices



**Fig. 2.** Loss angle vs. temperature for glass fibre reinforced laminates with 5 nano-particle reinforced epoxy matrices

Loss angle (Fig. 2) is representative of glass transition temperature  $T_G$ . For nano composites the highest value of  $T_G$  is for the lowest (3%, 5%) nanoparticle concentrations - 80°C, 77°C respectively. The glass transition temperature for 15%, 10% and 20% nanoparticles is 75°C, 72°C, 71°C respectively which indicates permanent reduction of the  $T_G$  as nanoparticle concentration grows.

It may be concluded that the preferable concentration of nanoparticles depends on the application. In terms of stiffness requirements the 20% nanoparticles offer the best behaviour while in terms of elevated temperature applications where glass transition temperature is a criterion the results are not conclusive- the effect of nanoparticles is not clear because of the diluent effect. This evidently should be avoided in the future studies.

## CONCLUSIONS

Dynamic mechanical (DMA) tests were performed to compare the mechanical behaviour of glass fibre reinforced epoxy laminate composites with  $\text{SiO}_2$  nanoparticle reinforced matrix. The selection of the most promising nanoparticle concentrations was considered in terms of elastic modulus and glass transition temperature. The reference specimens (0% nanoparticles) did not contain diluent accordingly the results do not allow the exact comparison with unreinforced composite, nevertheless the ranking of the nanocomposites was made.

The following conclusions can be drawn:

- In terms of stiffness requirements 20% nanoparticles composites offer the best behaviour, 25% higher elastic modulus than 5% nanoparticles.
- For nano composites the glass transition temperature  $T_G$  is the highest: 80°C, 77°C for 3%, 5% nanoparticles respectively and the lowest 75°C, 72°C, 71°C for 15%, 10% and 20% nanoparticles is respectively.

## REFERENCES

1. Barbezat M., Brunner AJ, Neola A., Rees M, Gasser Ph., Terassi G., Fracture behaviour of GFRP laminates with nanocomposite epoxy resin matrix: *Journal of composites materials* 43, 9/2009.
2. Hussain F., Hojjati M., Okamoto M., and Gorga RE, Polymer matrix nanocomposites. Processing, manufacturing and Applications: an Overview, *Journal Composite materials* 40 (17) (2006): 1511-1575.
3. Zhou Y., Pervin RF, Biswas MA, Rangari V.K. and Jeelani S., Fabrication and characterization of Montmorillonite Clay filled SC-15 Epoxy, *Materials and Letters*, 60(7) (2006): 869-873.
4. Brunner A.J. Neola A. Rees M., Gasser Ph., Kornmann X., Thomann R., and Barbezat M.: The influence of silicate based nanofiller on the fracture toughness of epoxy resin, *Engineering Fracture Mechanics* , 73(16) (2006) 2336-2345.
5. Haque A., Shamsuzzoha. M. Hussain and Dean D.: S-2Glass.epoxy Polymer nanocomposites: Manufacturing, structures, Thermal and Mechanical Properties *Journal of Composite materials* 37(2003) 1821-1837.
6. Zhao S, Schadler L. S. H. Hillborg H., Auletta T. : Improvements and mechanisms of fracture and fatigue properties of well dispersed alumina /epoxy nanocomposites, *Composites Science and Technology* 68 (2008) 2976-29.
7. Zhao S., Schadler LS, Duncan R., Hillborg H., Auletta T.: Mechanisms leading to improved mechanical performance in nanoscale alumina filled epoxy: *Composites Science and Technology* 68 (2008) 2965-2975.

