

# Sawing Processes as a Way of Determining Fracture Toughness and Shear Yield Stresses of Wood

Lud'ka Hlásková,<sup>a</sup> Kazimierz A. Orłowski,<sup>b</sup> Zdeněk Kopecký,<sup>a,\*</sup> and Michal Jedinák<sup>a</sup>

A new computational model, based on fracture mechanics, was used to determine cutting forces. Unlike traditional computing methods, which depend on many coefficients reflecting the machining of solid wood, the new model uses two main parameters: fracture toughness and shear yield stresses. The aim of this study was to apply this new method to determine these parameters for the tooth cutting edge principal positions and longitudinal and perpendicular cutting speed directions. Samples of beech wood (*Fagus sylvatica* L.) were sawn. The measurements of energetic effects (cutting power and cutting force) while sawing wood were carried out on two laboratory stands: the sash gang saw and the circular sawing machine. The basic relationships between different sawing methods, such as cutting on a frame sawing machine (sash gang saw) and a circular sawing machine, and the fracture toughness and shear yield stresses were recognizable. The data obtained could be applied to the computation of the energetic effects on other wood cutting methods.

*Keywords:* Cutting resistance; Wood sawing process; Fracture mechanics; Shear yield stress; Fracture toughness


*Contact information:* a: Department of Wood Processing, Faculty of Forestry and Wood Technology, Mendel University in Brno, Zemědělská 3, 613 00 Brno, Czech Republic; b: Department of Manufacturing Engineering and Automation, Faculty of Manufacturing Engineering, Gdansk University of Technology, Narutowicza 11/12, 80-233 Gdansk, Poland; \*Corresponding author: kopecky@mendelu.cz

## INTRODUCTION

A number of scientific studies, both theoretical and experimental, have been performed to better understand and predict cutting forces, including those by Naylor and Hackney (2013) and Chuchala *et al.* (2014). Markopoulos (2013) stated that today, most of the research dealing with machining modelling is performed to gain predictive ability. Important machining parameters, such as cutting forces, can be calculated before any cutting is actually performed on a machine tool. In the classical approach (Böllinghaus *et al.* 2009) to the machining process, the energetic effects (cutting forces and cutting power) on metal cutting are based on the specific cutting resistance  $k_c$  (cutting force per unit area of cut). Moreover, the specific cutting resistance  $k_c$  is also extensively applied in wood sawing processes (Fischer 2004; Orłowski 2007; Scholz *et al.* 2009; Orłowski *et al.* 2010). On the other hand, Orłowski *et al.* (2013) demonstrated that cutting power could be considered from a modern fracture mechanics point of view (Atkins 2003, 2009). Elements from this study were taken into account in the calculation models of cutting forces developed by Laternser *et al.* (2003), Stanzl-Tschegg and Navi (2009), Merhar and Bučar (2012), and Hellström *et al.* (2013).

Even though the analyses of energetic effects using cutting models (including the work of separation, plasticity, and friction) corroborated their versatility and revealed the

usefulness for every known type of sawing kinematics (Orlowski *et al.* 2013), there is a general lack of timber data, such as the fracture toughness (specific work of separation) and shear yield stresses in a shear zone. Moreover, the properties of wood, its anisotropy, and disparities in its physical and mechanical properties depend significantly on the direction of the cutting in relation to the grain and on the cutting edge position (Fig. 1).

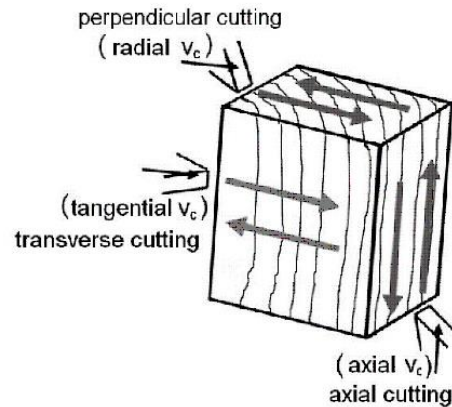


**Fig. 1.** Tooth cutting edge principal positions and cutting speed directions (adapted by authors (Orlowski *et al.* 2013) from Latenser *et al.* 2003)

Nevertheless, the cutting process is a good way to determine the fracture toughness and shear yield stresses of the material being cut (Atkins 2005; Orlowski and Palubicki 2009; Patel *et al.* 2009; Wang *et al.* 2013). Hence, sawing on the sash gang saw, according to the method presented by Orlowski and Palubicki (2009), can be applied to determine the toughness and strength for perpendicular cutting. If a circular saw blade is applied during the cutting process, a similar methodology can be implemented to determine the fracture toughness and shear strength (Kopecky *et al.* 2014); however, it concerns an indirect position of the cutting edges in relation to the wood grain for a distinct direction of cutting speed. The objective of this study was to provide some possible new measurement methods for determining raw material data such as the fracture toughness and shear yield stresses. Combining the two approaches mentioned earlier, which are based on sawing processes, could allow researchers to determine these properties for both the perpendicular and axial cutting directions.

### Sash Gang Saw Cutting Force Model

According to Orlowski *et al.* (2013), the mechanical process of material separation from the sawn workpiece (*i.e.*, chip formation) can be described as an orthogonal process (two-dimensional deformation). The forces acting on the tooth can be represented in the classical approach by Ernst and Merchant's force circle, shown in Fig. 2.

The cutting power for one saw blade during the cutting stroke of a sash gang saw, in which both chip momentum (Orlowski *et al.* 2013) and a ploughing effect caused by tooth cutting edge dullness (Wang *et al.* 2013) are disregarded, follows the equation,

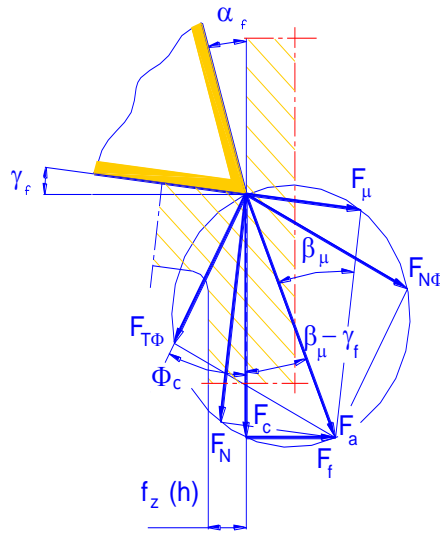

**Fig. 2.** Simplified cutting process model with Ernst and Merchant's force circle (Böllinghaus *et al.* 2009):  $F_a$  – active force,  $F_c$  – cutting force,  $F_f$  – thrust force (passive),  $F_\mu$  – friction force on the rake face,  $F_N$  – normal force to the rake face,  $F_{T\Phi}$  – the force required to shear the wood along the shear plane,  $F_{N\Phi}$  – normal force on the shear plane,  $\alpha_f$  – clearance angle,  $\Phi_c$  – shear angle,  $\gamma_f$  – rake angle, and  $\beta_\mu$  – friction angle (Orlowski *et al.* 2013)

$$\bar{P}_{cw} = F_c v_c = z_a \cdot \frac{\tau_{\gamma\perp} S_t \gamma}{Q_{shear}} v_c f_z + z_a \cdot \frac{R_\perp S_t}{Q_{shear}} v_c \quad (1)$$

where  $z_a = \left( \frac{H_p}{P} \right)$  is the number of teeth in contact with the kerf (on average),  $H_p$  is the workpiece height (cutting depth);  $\tau_{\gamma\perp}$  is the shear yield stress for the perpendicular cutting speed direction; and  $\gamma$  is the shear strain along the shear plane, given by,

$$\gamma = \frac{\cos \gamma_f}{\cos(\Phi_c - \gamma_f) \sin \Phi_c} \quad (2)$$

where  $f_z$  is the feed per tooth (uncut chip thickness  $h$ );  $S_t$  is a kerf (the width of the orthogonal cut);  $\beta_\mu$  is the friction angle given by  $\tan^{-1} \mu = \beta_\mu$ ;  $\mu$  is the coefficient of friction;  $\gamma_f$  is the rake angle;  $\Phi_c$  is the shear angle which defines the orientation of the shear plane with respect to the cut surface;  $R_\perp$  is the specific work of surface separation/formation (fracture toughness); and  $Q_{shear}$  is the friction correction,

$$Q_{shear} = [1 - (\sin \beta_\mu \sin \Phi_c / \cos(\beta_\mu - \gamma_f) \cos(\Phi_c - \gamma_f))] \quad (3)$$

The shear angle  $\Phi_c$ , for the necessary aim of this study, can be calculated for larger values of feed per tooth  $f_z$  with the Merchant's equation (because for large uncut chip values  $\Phi_c$  is constant) (Atkins 2003),


$$\Phi_c = (\pi/4) - (1/2)(\beta_\mu - \gamma_f) \quad (4)$$

The quantity  $\Phi_c$  does not actually follow Eq. 4 and is dependent on the ratio of  $R$  to  $\tau_\gamma$  (Atkins 2003). The values of  $\Phi_c$  obtained from Eq. 3 are always greater than the experimental  $\Phi_c$  (Atkins 2003); however, there is a lack of material-dependent data for sawing, except for some published results for Polish pine wood sawing (Orlowski and Ochrymiuk 2013; Orlowski *et al.* 2013).

Based on sawing results obtained on the sash gang saw (frame sawing machine) PRW-15M, it was possible to determine sawn material data, such as the specific work of surface formation (toughness) and the shear yield stresses, for the perpendicular cutting speed direction (Orlowski and Atkins 2007; Orlowski and Palubicki 2009). Since the kinematics of the cutting process during bandsawing has features of the perpendicular cutting, the same methodology of determining  $R_\perp$  and  $\tau_{\gamma\perp}$  could be possible during sawing processing on a band sawing machine, which is equipped with a similar measuring system, as described in the paper by Moradpour *et al.* (2013).

### Circular Sawing Machine Cutting Force Model

The kinematics of sawing on circular sawing machines (Fig. 3) differs from the kinematics of cutting on sash gang saws and bandsawing machines.

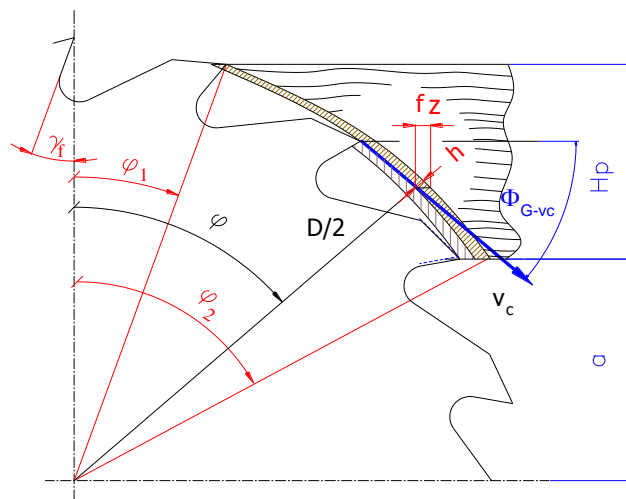

**Fig. 3.** Sawing kinematics on circular sawing machine:  $f_z$  – feed per tooth,  $D$  – circular saw blade diameter,  $h$  – uncut chip thickness,  $H_p$  – workpiece height (depth of cut),  $a$  – position of the workpiece,  $\varphi$  – angular tooth position,  $\Phi_{G-vc}$  – an angle between grains and the cutting speed direction (Orlowski *et al.* 2013)

In the case of cutting with circular saw blades, uncut chip thickness  $\bar{h}$  (an average value) should be taken into account instead of the feed per tooth  $f_z$ ; hence, the cutting power may be expressed as (Orlowski *et al.* 2013),

$$\bar{P}_{cw} = z_a \cdot \frac{\tau_{\gamma\perp} S_t \gamma}{Q_{shear}} v_c \bar{h} + z_a \cdot \frac{R_{\perp} S_t}{Q_{shear}} v_c \quad (5)$$

where  $z_a = \left( \frac{\varphi_2 - \varphi_1}{\varphi_t} \right)$  is the number of teeth in the contact with the kerf (on average);  $\varphi_1$  is the angle of tooth entrance given by  $\varphi_1 = \arccos \frac{2(H_p + a)}{D_{cs}}$ ;  $\varphi_2$  is an exit angle which can be determined as  $\varphi_2 = \arccos \frac{2a}{D_{cs}}$ ;  $D_{cs}$  is the diameter of the circular saw blade; an average uncut chip thickness is given by  $\bar{h} = f_z \sin \varphi$ ; an average angle of tooth contact with a workpiece  $\varphi$  is calculated as  $\varphi = \frac{\varphi_1 + \varphi_2}{2}$ ;  $R_{\perp}$  is the fracture toughness for indirect position of cutting speed, defined by  $\varphi$ ; and  $\tau_{\gamma\perp}$  is the shear yield stress for the indirect cutting speed direction, also defined by  $\varphi$ . In Eq. 5, it was assumed that teeth of the circular saw are sharp, and because of rather intermediate feed speeds values in tests, both the ploughing effect and chip momentum are disregarded.

Kopecký *et al.* (2014) developed methodology for determining raw material data including  $\tau_{\gamma\perp}$  and  $R_{\perp}$  for the indirect cutting speed direction. However, it must be emphasized that the values obtained are valid only at the position of the tooth cutting edge oriented by the average angle of tooth contact with a workpiece  $\varphi$ .

The results of using both methodologies to determine raw material features on the basis of sawing processes are described by Orłowski and Palubicki (2009), for the case of sawing on the sash gang saw and Kopecký *et al.* (2014), for circular sawing. By combining these methodologies, it is possible to compute the fracture toughness  $R_{\parallel}$  and shear stress  $\tau_{\gamma\parallel}$ .

Taking into account the position of the cutting edge in relation to the grain, for indirect positions of the cutting edge (cutting speed direction is in disagreement with the principal axes of wood), the fracture toughness  $R_{\perp}$  and the shear yield stress  $\tau_{\gamma\perp}$  may be calculated from formulae known from the strength of materials (Orlicz 1988). For example, for cutting on circular sawing machines (a case of axial-perpendicular cutting), these material features are as follows,

$$R_{\perp} = R_{\parallel} \cos^2 \Phi_{G-vc} + R_{\perp} \sin^2 \Phi_{G-vc} \quad (6)$$

and

$$\tau_{\gamma\perp} = \tau_{\gamma\parallel} \cos^2 \Phi_{G-vc} + \tau_{\gamma\perp} \sin^2 \Phi_{G-vc} \quad (7)$$

where  $\Phi_{G-vc}$  is the angle between the grain and the cutting speed direction (Fig. 3), which in this approach equals  $\varphi$ . In the present approach of combining the two described sawing technologies to determine the fracture toughness  $R_{\parallel}$  and shear stress  $\tau_{\gamma\parallel}$ , Equations 6 and 7 can be transformed as follows,

$$R_{\parallel} = \frac{R_{\perp} (\Phi_{G-vc} = \varphi) - R_{\perp} \sin^2 (\Phi_{G-vc} = \varphi)}{\cos^2 (\Phi_{G-vc} = \varphi)} \quad (8)$$

and



$$\tau_{\gamma\parallel} = \frac{\tau_{\gamma\perp}(\Phi_{G-vc} = \varphi) - \tau_{\gamma\perp} \sin^2(\Phi_{G-vc} = \varphi)}{\cos^2(\Phi_{G-vc} = \varphi)} \quad (9)$$

## EXPERIMENTAL

### Materials

Beech wood (*Fagus sylvatica* L.) samples originating from the Training Forest Enterprise Masaryk Forest Křtiny (TFE), an organizational part of the Mendel University of Agriculture and Forestry in Brno (CZ), were used as experimental samples. They were in the shape of rectangular blocks with dimensions of 55 mm (H) × 55 mm (W) × 564 mm (L) and a density of 691 kg/m<sup>3</sup> and were conditioned to 8% to 12% moisture content (MC).

### Methods


#### *Sash gang saw: Determination of cutting forces (cutting power)*

In this part, the methodology of determining cutting forces (cutting power) as proposed in the work of Chuchala *et al.* (2014) was applied. A series of cutting tests to empirically determine the cutting power was carried out on a PRW15M sash gang saw (a prototype designed at the Gdansk University of Technology, PL, and manufactured by the firm REMA-Reszel, PL), a frame sawing system with elliptical tooth trajectory and a hybrid, dynamically-balanced drive, as described by Wasielewski and Orłowski (2002). The machine settings were as follows: number of strokes of saw frame per min ( $n_F$ ), 685 spm; saw frame stroke ( $H_F$ ), 162 mm; number of saws in the gang ( $n$ ), 5; and average cutting speed ( $v_c$ ), 3.69 m/s. The saw blades had stellite tipped teeth: overall set (kerf width) ( $S_t$ ), 2 mm; saw blade thickness ( $s$ ), 0.9 mm; free length of the saw blade ( $L_0$ ), 318 mm; tension stresses of saws in the gang ( $\sigma_N$ ), 300 MPa; blade width ( $b$ ), 30 mm; tooth pitch ( $P$ ), 13 mm; tool side rake ( $\gamma_f$ ), 8.46° (measured value); and tool side clearance ( $\alpha_f$ ), 9.3° (measured value). Even though the saw blades were new, the tooth cutting edge radius had an average value ( $\rho_{CE}$ ) of around 55 μm (measured with a system for image analysis and processing NIS – Elements AR (ver. 2.3), equipped with the digital camera Nikon DS – Fi1, 5 Mpix, with macrolens Navitar, in Brno, CZ), meaning that it was not the normal “sharp” tool (Orlicz 1988; Blackman *et al.* 2013). The only varying cutting parameter was the feed speed, which was applied at two levels:  $v_{f1} \approx 0.4$  m/min and  $v_{f2} \approx 1.1$  m/min. Lamellae with thicknesses of  $5 \pm 0.2$  mm were obtained as a result of the re-sawing process. The friction coefficient value  $\mu = 0.8$  for dry beech wood was taken from the work of Kopecký *et al.* (2014).

The corresponding cutting forces ( $F_c$ ) (related to one tooth of the saw blade) were calculated according to the method described by Orłowski and Palubicki (2009) and Orłowski (2010). The average idle power ( $\bar{P}_I$ ) was measured immediately before and after cutting (Fig. 4). The total power of the main driving system ( $\bar{P}_{cT}$ ) was recorded during all wood sawing tests with a sampling frequency of 80 Hz (number of samples = 8192). Subsequently, the average cutting power ( $\bar{P}_c$ ) and the mean cutting force in the working stroke ( $\bar{F}_{cw}$ ), per tooth, were determined. Eventually, all of the resulting cutting forces were calculated by linear regression using a function of feed per tooth (uncut chip thickness). The linear regressions, Pearson’s  $r$  coefficients, and their significances (t-test)



were computed with Statistica 8.0 software (StatSoft Inc., USA) (StatSoft 2015). Statistical analyses were done for the confidence level  $\alpha = 0.05$ .

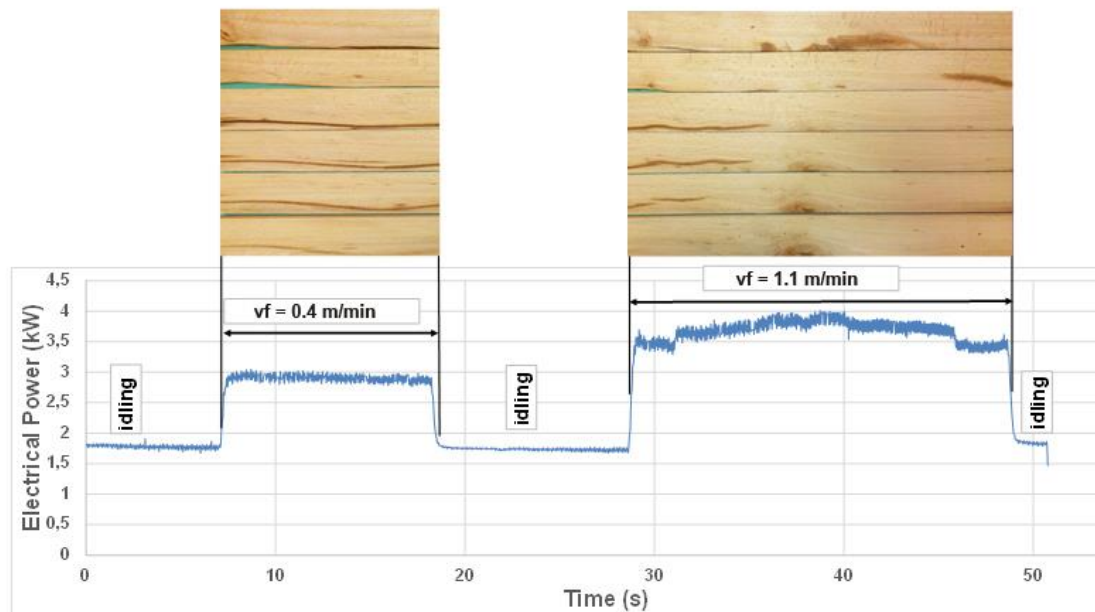


**Fig. 4.** Change of electrical power consumption over time while sawing beech wood at two feed speeds on the sash gang saw

#### *Circular sawing machine: Determination of cutting forces*

The series of cutting tests to empirically determine the cutting force was carried out on a test rig for research *via* cutting with circular saw blades at the laboratory of the Department of Wood Processing of the Faculty of Forestry and Wood Technology of Mendel University in Brno (Kopecký and Rousek 2012). This stand simulated, as closely as possible, the conditions of a circular sawing machine (CSM) in actual operation. During the cutting process, the cutting moment (cutting force  $F_c$ ; feed force  $F_f$ ; spindle rotational speed, and feed speed  $v_f$ ) was measured. Signals from the sensors were transferred to the Spider 8 (f. Hottinger Baldwin Messtechnik, D), and they were subsequently processed into tables and graphs using Conmes Spider software (f. Consymea s.r.o.). The machine settings were as follows: optimum operating rotational speed = 3800 rpm (Veselý *et al.* 2012) for the applied circular saw blade (*i.e.*, operating at the cutting speed  $v_c = 69.6$  m/s); and the feed rate ( $v_f$ ) varied between 2 and 22 m/min with a step size of 2 m/min. This corresponded to changing of the feed per tooth  $f_z$  (uncut chip thickness  $\bar{h}$ ). The circular saw blade (f. Flury Systems AG, CH) had straight, sharp, carbide-tipped teeth; the diameter of the circular saw blade ( $D_{cs}$ ) was 350 mm. The diameter of the hole ( $d$ ) was 30 mm; the overall set (kerf width) ( $S_t$ ) was 3.5 mm; the teeth number ( $z$ ) was 28; the saw blade thickness ( $s$ ) was 2.5 mm; the tool side rake ( $\gamma_f$ ) was  $20^\circ$ ; and the tool side clearance ( $\alpha_f$ ) was  $15^\circ$ . The tooth cutting edge radius had an average value ( $\rho_{CE}$ ) of around  $8 \mu\text{m}$  meaning that it was a normal “sharp” tool (Orlicz 1988; Blackman *et al.* 2013). The friction coefficient value  $\mu = 0.83$  for dry beech wood was taken from the work of Kopecký *et al.* (2014). The linear regressions, Pearson’s  $r$  coefficients, and their significances (t-test) were computed with Statistica 8.0 software (StatSoft Inc., USA) (StatSoft 2015). Statistical analyses were done for the confidence level  $\alpha = 0.05$ .

Figure 5 presents the recorded signals of the cutting moment (cutting force  $F_c$ ) during sawing with feed speed  $v_f = 19$  m/min.

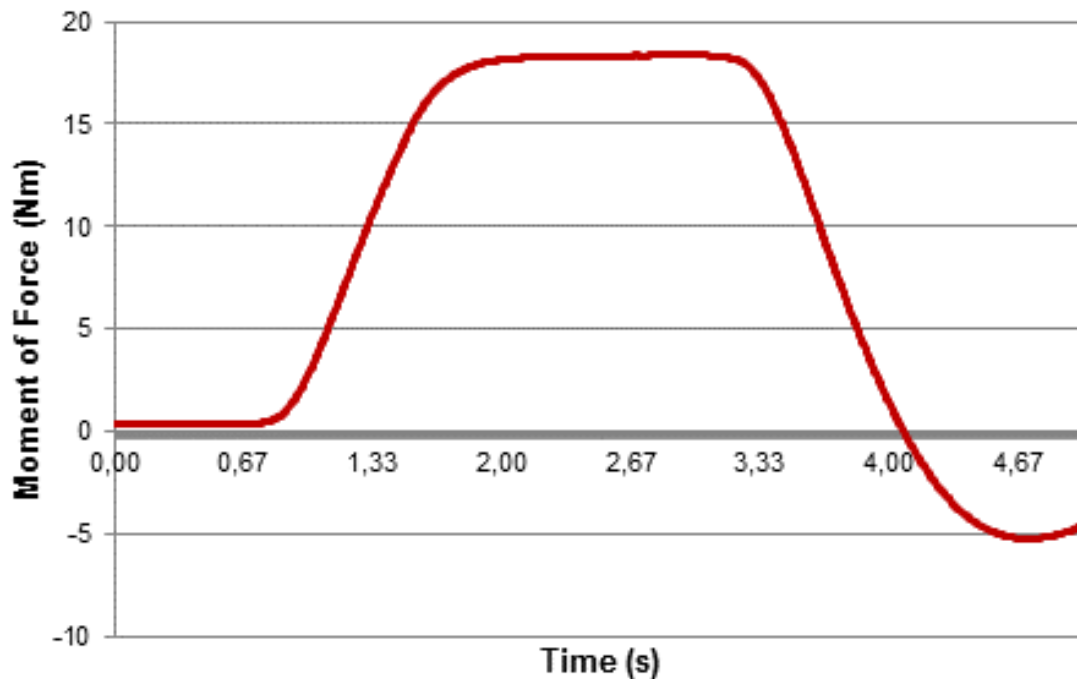

**Fig. 5.** Change of cutting moment (Moment) over time while sawing beech wood with a circular saw blade at feed speed  $v_f = 19$  m/min

## RESULTS AND DISCUSSION

The obtained regression models of the cutting force per tooth, as a function of the uncut chip thicknesses, are presented in Fig. 6 for cutting on the sash gang saw and Fig. 7 for processing with the circular saw blade. The models were characterized by Pearson's  $r$  values of 0.945 (for sash gang saw) and 0.996 (circular sawing machine), respectively. Both cutting force trends were linear, and they were in the form as expressed in Eqs. 1 and 5, respectively.

The cutting force per tooth for the sash gang saw, in N, for kerf width ( $S_t$ ) 2 mm is as follows,

$$F_c^1 = 328060f_z + 7.77 \text{ (N)} \quad (10)$$

The average (medium) cutting force per tooth for processing with the circular saw blade, for the kerf width ( $S_t$ ) 3.5 mm, for a tooth position defined by the average angle of tooth contact with the workpiece  $\bar{\varphi} = 37.47^\circ$ , is described as,

$$F_c^1(\bar{\varphi} = 37.47^\circ) = 301816\bar{h} + 3.792 \text{ (N)} \quad (11)$$


In the first step, characteristic data for other materials and cutting processes were estimated according to Atkins (2005). The value of the slope was determined as 328060 (N/m) for sash gang saw (Eqs. 1 and 10) and 301816 (N/m) for circular saw blade (Eqs. 5 and 11). Application of the mechanics approach to the sawing processes of beech on both



the sash gang saw and the circular sawing machine yielded fracture toughnesses  $R_{\perp}$ ,  $R_{\perp\perp}(\bar{\varphi} = 37.47^{\circ})$ , and  $R_{\perp\perp}$  and shear yield stresses  $\tau_{\gamma\perp}$ ,  $\tau_{\gamma\perp\perp}(\bar{\varphi} = 37.47^{\circ})$ , and  $\tau_{\gamma\parallel}$ . Additionally, calculations determining shear yield stresses  $\tau_{\gamma}$  were conducted for uncut chip thicknesses  $h > 0.12$  mm, when the cutting resistance is practically constant (Orlowski 2003). The orientation of the shear plane with regard to the cut surface could be calculated with Eq. 4. The computed data input, such as the shear strain along the shear plane  $\gamma$  (Eq. 2); the shear angle  $\Phi_c$  (Eq. 4); the friction correction  $Q_{shear}$  (Eq. 3); and the friction angle  $\beta_{\mu}$ , given by  $\tan^{-1}\mu = \beta_{\mu}$ , are presented in Table 1.

**Table 1.** Sawing Processes Characteristic Data


Machine Tool	$\gamma_f$ (°)	$\mu$ (-)	$\beta_{\mu}$ (°)	$\Phi_c$ (°)	$\gamma$ (-)	$Q_{shear}$ (-)
PRW15M	8.46	0.8	38.65	29.90	2.2952	0.6129
CSM	20	0.8	38.65	35.67	1.7006	0.6007

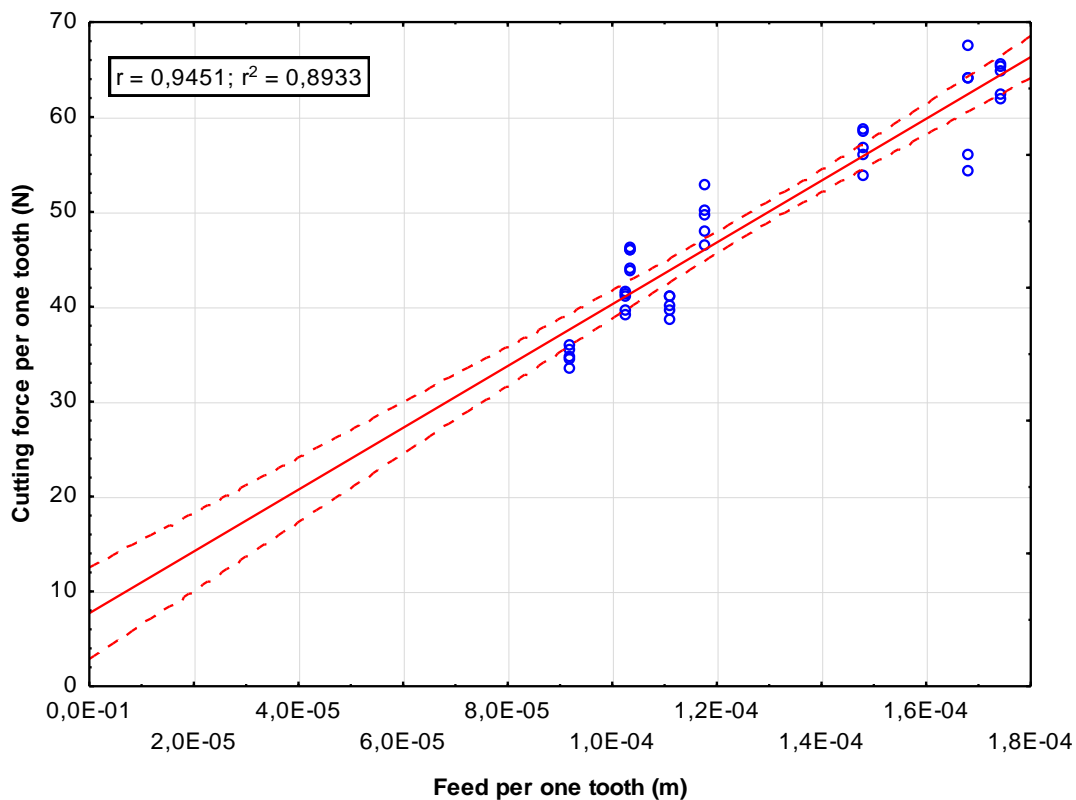

**Fig. 6.** Cutting force per one tooth in a function of feed per tooth with 95% confidence intervals while sawing beech wood on the sash gang saw

The toughness  $R_{\perp}$  was determined from the experimental ordinate intercept, where value of the intercept was 7.77 (N) (Eq. 10) for sash gang saw and  $R_{\perp\perp}(\bar{\varphi} = 37.47^{\circ})$  was determined from the value of experimental ordinate intercept 3.792 (N) (Eq. 11) for circular saw blade. In both cases, the friction correction in these calculations was assumed to be  $Q_{shear} = 1$ , since the uncut chip thickness is equal to 0 and simultaneously

$\Phi_c = 0$  (Orlowski and Atkins 2007; Orlowski and Palubicki 2009; Orlowski 2010). Since the tool cannot be perfectly sharp, the lower portion of the tool tip can result in a ploughing of the testing material during the cutting process (Blackman *et al.* 2013; Wang *et al.* 2013). Thus, the fracture toughness from measurement results could be an overestimate, especially in case of processing on the sash gang saw with stellite tipped teeth, which were not “sharp”.

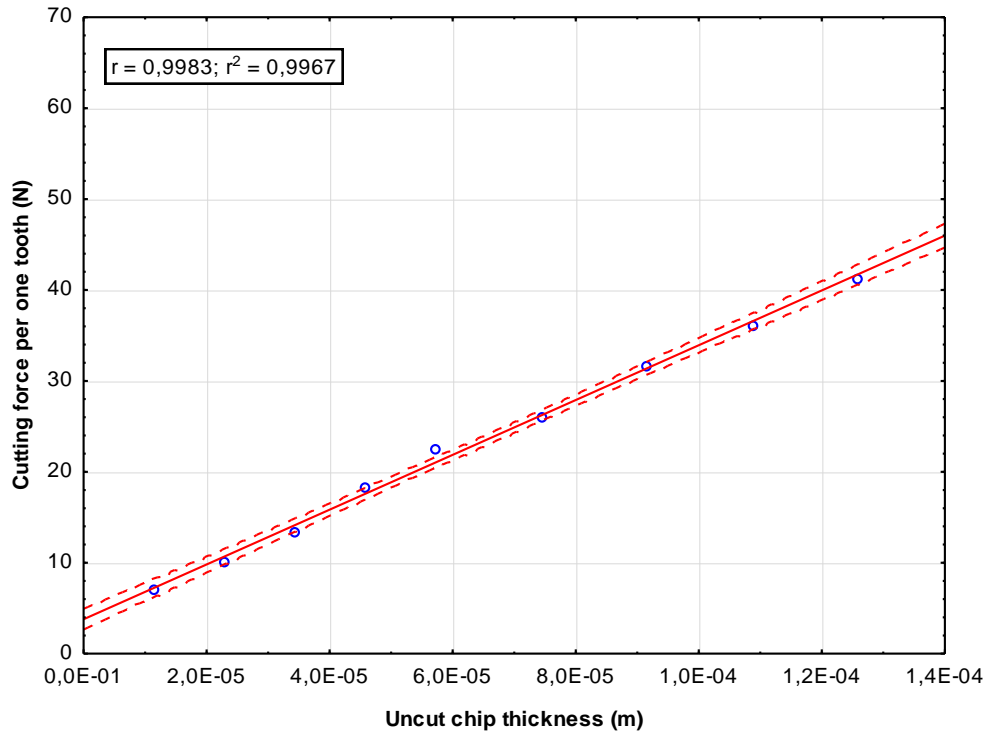

**Fig. 7.** Cutting force per tooth versus uncut chip thickness, with 95% confidence intervals, while sawing beech wood on circular sawing machine

According to Blackman *et al.* (2013), it was assumed that half of the size of the tip radius  $\rho_{CE}$  contributed to the ploughing process, such that the fracture toughness overestimated by ploughing could be approximated by,

$$R_p = 0.5\rho_{CE}\tau_\gamma \quad (12)$$

where  $\tau_\gamma$  is the shear yield stress determined from the cutting test.

The computed shear stresses  $\tau_\gamma$ , fracture toughnesses from experiments  $R'$ , fracture toughness reductions  $R_p$ , and  $R_{||}$  and  $\tau_{\gamma||}$  as calculated from Eqs. 8 and 9 are shown in Table 2.

**Table 2.** Shear Yield Stress and Fracture Toughness of Beech Wood (*Fagus sylvatica* L.)

$T_{\gamma\perp}$	$T_{\gamma  }^*$	$T_{\gamma  }$	$R_{\perp}$	$R_{\perp p}$	$R_{\perp}$	$R'_{  \perp}^*$	$R_{  \perp p}^*$	$R_{  \perp}^*$	$R_{  }$
MPa	MPa	MPa	J/m <sup>2</sup>	J/m <sup>2</sup>	J/m <sup>2</sup>	J/m <sup>2</sup>	J/m <sup>2</sup>	J/m <sup>2</sup>	J/m <sup>2</sup>
43.86	30.46	22.62	3886	1204	2682	1083	76.1	1007	23.3

\*data for indirect position of the cutting edge defined by the average angle of tooth contact with a workpiece,  $\bar{\varphi} = 37.47^\circ$

Determined on the basis of empirical results from the sawing process (on the sash gang saw), the fracture toughness  $R_{\perp}$  for beech wood is about 2 times larger than the average values for Polish pine wood (*Pinus sylvestris* L.) (Orlowski and Ochrymiuk 2013). Moreover, the fracture toughness  $R_{\parallel}$  obtained from the results of cutting processes (on the sash gang saw and the circular sawing machine) on basis of the proposed, combined method was several times lower than  $R_{\perp}$ . Additionally, the ratio of  $R_{\parallel}/R_{\perp}$  was calculated, and the value achieved for beech wood was  $R_{\parallel}/R_{\perp} = 0.009$ , whereas for pine fir this ratio is about 0.035 (Aydin *et al.* 2007).

Furthermore, when comparing the shear stresses  $\tau_{\gamma\perp}$  of Polish pine wood (Orlowski and Ochrymiuk 2013; Orlowski *et al.* 2014) and beech wood, the latter value is around 2 times higher. The calculated ratio  $\tau_{\gamma\parallel}/\tau_{\gamma\perp}$  for beech wood was 0.52, whereas for Polish pine wood it is 0.23 (Orlowski *et al.* 2013). It should be emphasized that in case, of Polish pine wood, a shear strength value for the axial cutting direction (Orlowski *et al.* 2013, 2014) was estimated on the basis of the MOR (modulus of rupture in bending).

The determined values of sawn beech wood properties could be useful in forecasting the energetic effects using cutting models that include the work of separation, plasticity, and friction for every known type of sawing kinematics.

## CONCLUSIONS

1. The application of the results obtained by experimental cutting on both the sash gang saw and the circular sawing machine allowed for the determination of the toughness and shear yield strength of sawn wood for both the perpendicular and axial cutting directions.
2. The toughness and shear yield stresses of the cut wood depended strongly on the cutting speed direction as related to the grain.
3. It must be emphasized that the fracture toughness values obtained from sawing processes could be affected by dull teeth and that the toughness may have been overestimated. In this case, the phenomenon of ploughing must be taken into account.

## ACKNOWLEDGMENTS

The authors are grateful for the support of the project “The Establishment of an International Research Team for the Development of New Wood-based Materials,” Reg. No. CZ.1.07 / 2 March 00 / 20.0269 and “Postdoctoral positions in technical and economic fields on MENDELU,” Reg. No. CZ.1.07 / 2 March 00/30003, which have been co-financed by the European Social Fund and the budget of the Czech Republic. Parts of the experiments were conducted at the Department of Manufacturing Engineering and Automation of the Gdansk University of Technology (Poland).

## REFERENCES CITED

- Atkins, A. G. (2003). "Modelling metal cutting using modern ductile fracture mechanics: quantitative explanations for some longstanding problems," *International Journal of Mechanical Sciences* 45(2), 373-396. DOI: 10.1016/S0020-7403(03)00040-7
- Atkins, A. G. (2005). "Toughness and cutting: A new way of simultaneously determining ductile fracture toughness and strength," *Engineering Fracture Mechanics* 72(6), 849-860. DOI: 10.1016/j.engfracmech.2004.07.014
- Atkins, A. G. (2009). *The Science and Engineering of Cutting. The Mechanics and Process of Separating, Scratching and Puncturing Biomaterials, Metals and Non-Metals*, Butterworth-Heinemann, Oxford, UK.
- Aydin, S., Yardimci, M. Y., and Ramyar, K. (2007). "Mechanical properties of four timber species commonly used in Turkey," *Turkish Journal of Engineering and Environmental Sciences*, 31(1), 19-27.
- Blackman, B. R. K., Hoult, T. R., Patel, Y., and Williams, J. G. (2013). "Tool sharpness as a factor in machining tests to determine toughness," *Engineering Fracture Mechanics* 101, 47-58. DOI: 10.1016/j.engfracmech.2012.09.020
- Böllinghaus, T., Byrne, G., Cherpakov, B. I., Chlebus, E., Cross, C. E., Denkena, B., Dilthey, U., Hatsuzawa, T., Herfurth, K., Herold, H., et al. (2009). "Manufacturing engineering," in: *Springer Handbook of Mechanical Engineering*, K.-H. Grote and E. K. Antonsson (eds.), Springer, Würzburg, pp. 609-656. DOI: 10.1007/978-3-540-30738-9\_7
- Chuchala, D., Orłowski, K., Sandak, A., Sandak, J., Pauliny, D., and Barański, J. (2014). "The effect of wood provenance and density on cutting forces while sawing Scots pine (*Pinus sylvestris* L.)," *BioResources* 9(3), 5349-5361. DOI: 10.15376/biores.9.3.5349-5361
- Fischer, R. (2004). "Micro processes at cutting edge - Some basics of machining wood," in: *Proceedings of the 2<sup>nd</sup> International Symposium on Wood Machining*, Vienna, Austria, pp. 191-202.
- Hellström, L. M., Biller, S.-O., Edvardsson, S., and Gradin, P. (2013). "A theoretical and experimental study of the circular sawing process," *Holzforschung* 68(3), 307-312. DOI: 10.1515/hf-2013-0066
- Kopecký, Z., and Rousek, M. (2012) "Impact of dominant vibrations on noise level of dimension circular sawblades," *Wood Research* 57(1), 151-160.
- Kopecký, Z., Hlaskova, L., and Orłowski, K. (2014). "An innovative approach to prediction energetic effects of wood cutting process with circular-saw blades," *Wood Research* 59(5), 827-834.
- Latenser, R., Gänser, H.P., Taenzer, L., and Hartmaier, A. (2003). "Chip formation in cellular materials," *Journal of Engineering Materials and Technology* 125(1), 44-49. DOI: 10.1115/1.1526126
- Naylor, A., and Hackney, P. (2013) "A review of wood machining literature with a special focus on sawing," *BioResources* 8(2), 3122-3135. DOI: 10.15376/biores.8.2.3122-3135
- Markopoulos, A. P. (2013). "Cutting mechanics and analytical modeling," in: *Finite Element Method in Machining Processes*, Springer, London, UK, pp. 11-27. DOI: 10.1007/978-1-4471-4330-7\_2



- Merhar, M., and Bučar, B. (2012). “Cutting force variability as a consequence of exchangeable cleavage fracture and compressive breakdown of wood tissue,” *Wood Science and Technology* 46(5), 965-977. DOI: 10.1007/s00226-011-0457-4
- Moradpour, P., Doosthoseini, K., Scholz, F., and Tarmian, A. (2013). “Cutting forces in bandsaw processing of oak and beech wood as affected by wood moisture content and cutting directions,” *European Journal of Wood and Wood Products* 71(6), 747-754. DOI: 10.1007/s00107-013-0734-z
- Orlicz, T. (1988). *Obróbka drewna narzędziami tnącymi*. (In Polish: *Wood machining with cutting tools*), Skrypty SGGW-AR w Warszawie, Wydawnictwo SGGW-AR, Warszawa.
- Orłowski, K. (2003). *Materialooszczędne i Dokładne Przecinananie Drewna Pilami*. (in Polish: *Narrow-kerf and Accurate Sawing of Wood*), Monografie Nr 40, Politechnika Gdańska, Gdańsk.
- Orłowski, K. (2007). “Experimental studies on specific cutting resistance while cutting with narrow-kerf saws,” *Advances in Manufacturing Science and Technology* 31(1), 49-63.
- Orłowski, K. A. (2010). *The Fundamentals of Narrow-Kerf Sawing: The Mechanics and Quality of Cutting*, Publishing House of the Technical University in Zvolen, Technical University in Zvolen
- Orłowski, K. A., and Atkins, A. (2007). “Determination of the cutting power of the sawing process using both preliminary sawing data and modern fracture mechanics,” in: *Proceedings of the Third International Symposium on Wood Machining. Fracture Mechanics and Micromechanics of Wood and Wood Composites with Regard to Wood Machining*, P. Navi and A. Guidoum (eds.), 21-23 May, Lausanne, Switzerland, Presses Polytechniques et Universitaires Romandes, Lausanne, pp. 171-174.
- Orłowski, K. A., and Ochrymiuk, T. (2013) “Prognozowanie maksymalnych granicznych wartości prędkości posuwu dla procesu przecinania drewna na pilarkach ramowych,” (In Polish: “Forecasting of maximum boundary feed speeds for the rip sawing process of wood on frame sawing machines”) *Inżynieria Maszyn* 18(2), 20-31.
- Orłowski, K. A., and Pałubicki, B. (2009). “Recent progress in research on the cutting process of wood. A review COST Action E35 2004-2008: Wood machining- Micromechanics and fracture,” *Holzforschung* 63(2), 181-185. DOI: 10.1515/HF.2009.015
- Orłowski, K. A., Ochrymiuk, T., and Atkins, A. (2010). “Specific cutting resistance while sawing of wood - the size effect,” *Ann. WULS-SGGW, Forestry, and Wood Technology* 72, 103-107.
- Orłowski, K., Ochrymiuk, T., Atkins, A., and Chuchala, D. (2013). “Application of fracture mechanics for energetic effects predictions while wood sawing,” *Wood Science and Technology* 47(5), 949-963. DOI: 10.1007/s00226-013-0551-x
- Orłowski, K. A., Ochrymiuk, T., and Atkins, A. (2014). “An innovative approach to the forecasting of energetic effects while wood sawing,” *Drvna Industrija* 65(4), 273-281. DOI: 10.5552/drind.2014.1341
- Patel, Y., Blackman, B. R. K., and Williams, J. G. (2009). “Measuring fracture toughness from machining tests,” *Proceedings of the Institution of Mechanical Engineers, Part C: Journal of Mechanical Engineering Science* 223(12), 2861-2869. DOI: 10.1243/09544062JMES1497

- Scholz, F., Duss, R., Hasslinger, R., and Ratnasingam, J. (2009). "Integrated model for the prediction of cutting forces," in: *Proceedings of 19<sup>th</sup> International Wood Machining Seminar*, H. D. Zhou, N. F. Zhu, and T. Ding (eds.), October 21-23, Nanjing, China, Nanjing Forestry University, pp. 183-190.
- Stanzl-Tschegg, S. E., and Navi, P. (2009). "Fracture behaviour of wood and its composites. A review COST Action E35 2004 - 2008: Wood machining - Micromechanics and fracture," *Holzforschung* 63(2), 139-149. DOI: 10.1515/HF.2009.012
- StatSoft (2015). *StatSoft Electronic Statistics Textbook*, [www.statsoft.com/Textbook/Basic-Statistics#Correlationsc](http://www.statsoft.com/Textbook/Basic-Statistics#Correlationsc) (accessed March 2015)
- Vesely, P., Kopecký, Z., Hejmal, Z., and Pokorny, P. (2012). "Diagnostics of circular sawblade vibration by displacement sensors," *Drvna Industrija* 63(2), 81-86. DOI:10.5552/drind.2012.1130
- Wang, H., Chang, L., Ye, L., and Williams, J. G. (2013). "Micro-cutting tests: A new way to measure the fracture toughness and yield stress of polymeric nanocomposites," in: *Proceedings of the 13th International Conference on Fracture*, June 16-21, 2013, Beijing, China. <http://www.gruppofrattura.it/ocs/index.php/ICF/icf13/paper/viewFile/11399/10778> Accessed 20 March 2015.
- Wasielewski, R., and Orłowski, K. (2002). "Hybrid dynamically balanced saw frame drive," *Holz Holz als Roh- und Werkstoff* 60(3), 202-206. DOI: 10.1007/s00107-002-0290-4

Article submitted: April 13, 2015; Peer review completed: June 20, 2015; Revised version received and accepted: June 30, 2015; Published: July 15, 2015.  
DOI: 10.15376/biores.10.3.5381-5394