

# WILEY

## Online Proofing System


### Enabling the Adobe PDF Viewer

In order to proof your article Adobe Reader or Adobe Acrobat needs to be your browser's default PDF viewer. See how to set this up for Internet Explorer, Firefox, and Safari at <https://helpx.adobe.com/acrobat/using/display-pdf-in-browser.html>


Google Chrome and Microsoft Edge do not support Adobe Reader or Adobe Acrobat as a PDF Viewer. We recommend using Internet Explorer, Firefox, or Safari.

**1.** Mark your corrections, changes, and query responses using the Annotation Tools outlined on the next 2 pages.

**2.** Save your proof corrections by clicking the “Publish Comments” button in the yellow banner above. Corrections don’t have to be marked in one sitting. You can publish comments and log back in at a later time to add and publish more comments before you click the “Complete Proof Review” button.



**3.** When your proof review is complete we recommend you download a copy of your annotated proof for reference in any future correspondence concerning the article before publication. You can do this by clicking on the icon to the right of the ‘Publish Comments’ button and selecting ‘Save as Archive Copy...’.

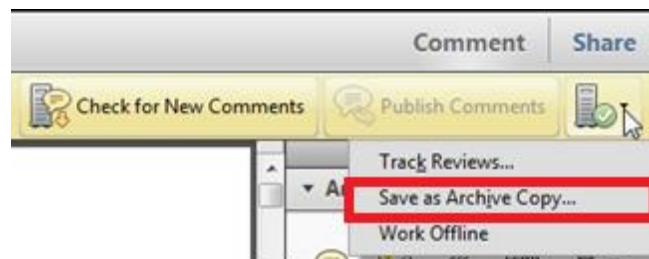

**IMPORTANT:** Did you reply to all queries listed on the Author Query Form appearing before your proof?

**IMPORTANT:** Did you click the “Publish Comments” button to save all your corrections? Any unpublished comments will be lost.

**IMPORTANT:** Once you click “Complete Proof Review” you will not be able to add or publish additional corrections.

**4.** When your proof review is complete and all corrections have been published to the server by clicking the “Publish Comments” button, please click the “Complete Proof Review” button appearing above the proof in your web browser window.



Finalize PDF Comments

## Author Query Form

Journal: JFBC

Article: 12494









Dear Author,

During the copyediting of your manuscript the following queries arose.

Please refer to the query reference callout numbers in the page proofs and respond to each by marking the necessary comments using the PDF annotation tools.

Please remember illegible or unclear comments and corrections may delay publication.

Many thanks for your assistance.

Query References	Query	Remarks
AQ1	AUTHOR: Please note that all strikethrough text present in the manuscript have been removed. Please check.	
AQ2	AUTHOR: Please check that the hierarchy of ALL section heads and subheads in the manuscript are correct.	
AQ3	AUTHOR: Please note that "Gousterova et al., 2012" has been changed to "Gousterova et al., 2011" in accordance with the reference list. Please check if it is OK as amended.	
AQ4	AUTHOR: Please note that "Maclaren & Mulligans, 1981" has been changed to "Maclaren & Milligan, 1995" in accordance with the reference list. Please check if it is OK as amended.	
AQ5	AUTHOR: Please provide complete details for "de Guzman et al., 2011" in the reference list or delete the citations from the text.	
AQ6	AUTHOR: There is no mention of "Wrześniewska-Tosik et al., 2015" in the text. Please insert a citation in the text or delete the reference as appropriate.	
AQ7	AUTHOR: Please note that "Muhsin et al., 2000" has been changed to "Muhsin & Aubaid, 2001" in accordance with the reference list. Please check if it is OK as amended.	
AQ8	AUTHOR: Please confirm that given names (red) and surnames/family names (green) have been identified correctly.	



# Solubilization of keratins and functional properties of their isolates and hydrolysates

Izabela Sinkiewicz  | Hanna Staroszczyk | Agata Śliwińska

Department of Food Chemistry, Technology and Biotechnology, Gdansk University of Technology, G. Narutowicza 11/12, 80-233 Gdańsk, Poland

## Correspondence

Department of Food Chemistry, Technology and Biotechnology, Gdansk University of Technology, G. Narutowicza 11/12, 80-233 Gdańsk, Poland.  
Email: izabela.sinkiewicz@pg.edu.pl

## Abstract

The keratinous wastes of the textile industry and poultry slaughterhouses may be used as sources of soluble keratins or hydrolysates. This review presents methods for processing raw keratin-based materials into bioproducts with functional and bioactive properties suitable for biomedical, cosmetic, food, and agricultural applications. Soluble keratin can be obtained by thermal treatment in some organic solvents, reduction, or oxidation of the disulfide bonds. Recent studies have shown that keratins contain amino acid sequences with high biological activities such as antioxidant, angiotensin I converting enzyme inhibitory, dipeptidyl peptidase IV inhibitory, and antimicrobial. Peptides containing these sequences may find numerous applications as value-added products in the food industry. More research devoted to development of methods for conversion of animal by-products to novel products is needed. Further technological investigations to create large-scale production methods are also necessary.

## Practical applications

The keratinous wastes represent a problematic by-product to the wool textile industry and poultry slaughterhouses due to the large volumes and their high pollutant load. They are usually incinerated or used for low value purposes such as fertilizers. This review focuses on the trends of application of keratin recovered from animal by-products. Biomaterials for regenerative medicine, cosmetic formulations, and biodegradable food packaging can be obtained as a result of keratin self-assembly. Several peptide sequences released by hydrolysis as bioactive peptides should be studied further for their in vivo antihypertensive, and antidiabetic effects, as well as functional ingredients in foods.

## KEYWORDS

bioactive peptides, functional properties, keratin hydrolysates, keratin isolates

## 1 | INTRODUCTION

Keratins have biological activity, biocompatibility, biodegradability, and mechanical durability (Cardamone, 2010; Ferraro, Anton, & Santé-Lhoutellier, 2016; Reddy, Chen, & Yang, 2013) and are also capable of facilitating cell adhesion and proliferation (Rouse & Van Dyke, 2010). These properties have led to the development of keratin-based materials which can be suitable for numerous applications: biomedical (wound healing, drug delivery, tissue engineering, and medical devices) (Rouse & Van Dyke, 2010; Vasconcelos, Freddi, & Cavaco-Paulo, 2008), cosmetic materials (Nomura et al., 2005; Vermelho, Villa, De Almeida, de Souza Dias, & Dos Santos, 2008), food products (Goodwin, 1976), and

agricultural uses (Vesela & Friedrich, 2009), as well as for food packaging (Song, Lee, Al Mijan, & Song, 2014).

The industrial applications of keratin-rich materials are limited due to difficulty in dissolving it due to the high level of cross-linking of the protein and tightly packed microfibrils (Reddy, Jiang, et al., 2013). In recent years, bioactive properties related to antioxidant (Ohba et al., 2003), angiotensin I converting enzyme (ACE) inhibitory (Karamać, Flaczyk, Wanasundara, & Amarowicz, 2005), dipeptidyl peptidase IV (DPP IV) inhibitory (Fontoura et al., 2014), antifungal (Gousterova et al., 2011), and antibacterial activity (Sundaram, Legadevi, Banu, Gayathri, & Palanisamy, 2015) have been found in keratin hydrolysates. Production of enzymatic hydrolysates as a source of bioactive peptides can contribute to develop

54 nutritional or pharmaceutical applications (Di Bernardini et al., 2011;  
55 Gómez-Guillén, Giménez, López-Caballero, & Montero, 2011).

56 This paper reviews the processing and applications of keratin. The  
57 great potential of keratin as a fibrous protein with supramolecular orga-  
58 nization in the form of  $\alpha$ -helix which is an important factor affecting  
59 the characteristic mechanical properties and functionality, is discussed.  
60 The potential of keratin as a store house of bioactive peptides is also  
61 discussed.

## 62 2 | STRUCTURE AND OCCURANCE OF 63 KERATINS

64 Keratins (gr. keras—horn) are major structural proteins of vertebrate  
65 epithelia. They occur in hair, bristles, wool, feathers, claws, and horns.  
66 They perform various functions such as waterproof, excretion of  
67 wastes and regulation of temperature, cushion to protect the deeper  
68 tissues against mechanical shock and infection (Ferraro et al., 2016).  
69 Keratins are very hard, visco-elastic, and resilient (Bonser, 1996). They  
70 undergo bundling and have higher Young's modulus than collagen  
71 (Eslahi, Dadashian, & Nejad, 2013). They are insoluble in water, weak  
72 acids, and alkalis, as well as in organic solvents (Ferraro et al., 2016).  
73 Keratins belong to the superfamily of intermediate filament (IF)  
74 proteins forming the cytoskeleton (Korniłowicz-Kowalska & Bohacz,  
75 2011). Their subunits consist of a central domain with  $\alpha$ -helical  
76 structure and globular N- and C-terminal domains composed of 15–30  
77 amino acid residues, and  $\beta$ -sheet regions (Fraser, MacRae, Parry, &

Suzuki, 1986). The highly conserved central domains contain 310–315  
residues arranged in repeating sequences (Bragulla & Homberger,  
2009). Keratin subunits associate in a high-order structure forming a  
double-stranded superhelix, microfibrils, and macrofibrils embedded in  
an amorphous matrix (McKittrick et al., 2012). The right-handed  $\alpha$ -helix  
of  $\alpha$ -keratin is stabilized by hydrogen bonds and numerous disulfide  
bridges formed by cysteine residues that cause the insolubility of kera-  
tin. Therefore it is not easily degradable by common proteolytic  
enzymes such as trypsin, pepsin, and papain. A high cystine content  
amounting to 7–20% of the total amino acid residues is characteristic  
of keratins. They also contain about 0.5% methionine residues, as well  
as large proportion of glycine, serine, leucine, and glutamic acid. The  
amino acid sequence of keratin is very similar in different species  
(Bragulla & Homberger, 2009).

Keratins are heterogeneous proteins due to variation in amino  
acids composition (Table 1) and type of secondary structure. Twenty  
isoforms have been identified with molecular weights ranging from 40  
to 70 kDa in human epithelial cells (Rodziewicz & Łaba, 2006). Wool,  
hair, and skin keratins with cystine content between 10 and 14% are  
soft and flexible, but keratins extracted from feathers, beaks, claws,  
and horns are hard, rigid, inflexible, and inextensible due to higher cys-  
tine content up to 22% (Cardamone, 2010). Keratin polypeptide chains  
can curl into two configurations:  $\alpha$ -helix and  $\beta$ -sheet. Thus, keratins are  
also classified into four groups:  $\alpha$ -keratin,  $\beta$ -keratin, feather keratin,  
and amorphous keratin (McKittrick et al., 2012).  $\alpha$ -Keratins occur in  
mammals as the primary constituent of hair (fiber cortex), nails, hooves, 103

TABLE 1 Amino acid composition (% of total amino acid residues) of keratin from different sources

Amino acid	Buffalo horn and hoof (Noda, Imai, Kida, & Otagiri, 1996)	Cow hair (Coward-Kelly, Chang, Agbogbo, & Holtzapfle, 2006)	Feathers (Moore, Martelli, Gandolfo, Pires, & Laurindo, 2006)	Wool (Cardamone, 2010)
Alanine	6.3	4.5	3.6	5.8
Arginine	6.8	11.0	5.4	7.8
Aspartic acid	6.7	6.6	4.7	4.1
Cysteine	3.7	nd	7.7	6.1
Glutamic acid	12.6	14.5	7.7	11.4
Glycine	12.3	5.5	6.2	2.9
Histidine	0.6	1.3	-	-
Isoleucine	3.0	4.2	4.3	3.9
Leucine	8.2	9.8	7.0	11.9
Lysine	2.7	5.5	0.6	2.9
Methionine	0.6	0.7	1.3	0.2
Phenylalanine	2.9	3.1	4.2	1.9
Proline	6.8	7.7	8.7	4.1
Serine	10.8	8.9	9.3	8.3
Threonine	5.6	7.5	3.5	5.6
Tyrosine	5.9	2.4	2.0	2.4
Valine	4.1	6.8	6.9	6.1

nd = not determined.

104 horns, quills, and the epidermal layer of the skin. They have  $\alpha$ -helical  
105 tertiary structure and are rich in cystine residues ranging from 10 to  
106 22%. They are divided into two subfamilies, the type I acidic microfibril-  
107 lar component of ca. 40–50 kDa and the type II neutral/basic mem-  
108 branes of ca. 55–65 kDa (Marchisio, 2000).  $\beta$ -Keratins are found in  
109 reptiles and birds in scales, claws, beaks, feathers, and cuticle hair. They  
110 are difficult to extract and they do not form useful reconstituted struc-  
111 tures such as gels, films, coatings, and fibers suitable for medical appli-  
112 cations (wound healing, bone generation, hemostasis, and peripheral  
113 nerve repair (Ferraro et al., 2016; Hill, Brantley, & Van Dyke, 2010).  
114 They are rich in glycine, alanine, serine, and proline residues, but lack  
115 cysteine, thus the structure is stabilized only by hydrogen bonds. In  
116 feather keratin  $\beta$ -sheet and  $\alpha$ -helix occur in 1/3 and 2/3, respectively  
117 (Marchisio, 2000). Feather keratins from various birds are similar with  
118 molecular weight of about 10 kDa and cystine content of about 8%  
119 which is lower than that in keratin from nail and hair (Akhatar &  
120 Edwards, 1997). They are composed of about 20 different types which  
121 vary only by few amino acids (Saravanan, 2012). The basic and acid  
122 residues are positioned in the N- and C-terminal regions, whereas the  
123 hydrophobic residues are located in the central portion. The chemical  
124 or enzymatic process of feather keratin degradation is not uniform due  
125 to its complex hierarchical structure (Ferraro et al., 2016). Amorphous  
126 keratins, so-called  $\gamma$ -keratins are a part of the matrix. These are globu-  
127 lar proteins with high cystine content and molecular weight of about  
128 15 kDa.  $\gamma$ -Keratins occur in the external layer of the hair cuticle (Hill  
129 et al., 2010).

130 The content and structure of various forms of keratin depend on  
131 the physiological function and type of organism in which the protein  
132 occurs (Wang, Yang, McKittrick, & Meyers, 2016). Structural diversity  
133 of keratins also occurs within the same skin appendages. An example  
134 of this is the hair in which the external layer of the cuticle contains  
135 more cystine than the internal layers which are less resistant to  
136 proteolytic enzymes (Korniłowicz-Kowalska & Bohacz, 2011).

137 The physicochemical and biological features of keratins isolated  
138 from different sources are reflected in various functionalities of these  
139 proteins of which self-assembly is the most important (Dickerson et al.,  
140 2013). During thermodynamic equilibrium, the keratin molecules  
141 spontaneously arrange forming well-defined networks stabilized by  
142 noncovalent interactions. As a result of self-assembly, keratins can  
143 provide biomaterials for medicine, bioactive peptides, cosmetic formu-  
144 lations, and biodegradable films (Ferraro et al., 2016).

### 145 3 | SOLUBILIZATION OF KERATINS

#### 146 3.1 | Introduction


147 The method of processing raw keratin-based materials depends on the  
148 intended use of the product of keratin solubilization. These include  
149 thermal treatment in some organic solvents, reduction or oxidation of  
150 the disulfide bonds, alkaline, acid or enzymatic hydrolysis, various  
151 hydrothermal methods, and a combination of thermo-chemical and  
152 enzymatic treatments (Chojnacka, Górecka, Michalak, & Górecki, 2011;  
153 Ferraro et al., 2016; Wolski, 1979).

#### 3.2 | Production of keratin isolates

154

155 Obtaining keratin isolates containing native keratin is difficult in prac-  
156 tice due to insolubility of the protein in solutions which do not cause  
157 its degradation (Yin, Li, He, Wang, & Wang, 2013). A method of solubi-  
158 lization of keratin was developed using organic solvents, for example,  
159 N,N-dimethylformamide (DMF) or dimethyl sulfoxide (DMSO). For  
160 extraction with DMSO, precipitation of dissolved protein with acetone  
161 or benzene is needed. When both solvents are removed, a sediment is  
162 dried for dietary purposes as protein preparation (Wolski, 1985). This  
163 method requires a long extraction time and high cost caused by the  
164 need for solvent recovery (Wolski, 1979). There are no changes in pro-  
165 tein structure caused by this procedure and is often used by many  
166 researchers on laboratory scale to obtain a substrate for determination  
167 of keratinolytic activity (Wawrzkiwicz, Lobarzewski, & Wolski, 1987).

168 Reduction and oxidation of disulfide bonds belong to the common  
169 methods for keratin isolation. Reduction of keratin involves use of 2-  
170 mercaptoethanol (Balaji et al., 2012; Fujii & Li, 2008; Kakkar, Madhan,  
171 & Shanmugam, 2014; Reichl, 2009; Schrooyen, Dijkstra, Oberthür,  
172 Bantjes, & Feijen, 2001; Tanabe, Okitsu, & Yamauchi, 2004; Yamauchi,  
173 Yamauchi, Kusunoki, Kohda, & Konishi, 1996), dithiothreitol (DTT),  
174 dithioerythritol (Vasconcelos et al., 2008; Yang, Zhang, Yuan, & Cui,  
175 2009), thioglycolic acid (Hill et al., 2010; Zabashta, Kasprova,  
176 Senchurov, & Grabovskii, 2012), glutathione (Schrooyen, Dijkstra,  
177 Oberthür, Bantjes, & Feijen, 2000), salts of hydrocyanic acid (Arai,  
178 Sakamoto, Naito, & Takahashi, 1989), bisulfites (Tonin et al., 2007), and  
179 *m*-bisulphites (Aluigi et al., 2007; Vasconcelos et al., 2008) to solubilize  
180 the protein. Many keratins can remain trapped within the protective  
181 structure, and usually a hydrogen-bond breaking agent, such as urea,  
182 thiourea, transition metal hydroxides, surfactants, and combinations  
183 thereof, are included in the extractant to unfold or denature the protein  
184 (Torchinsky, 1981). Aqueous solutions of tris(hydroxymethyl)amino-  
185 methane in concentrations between 0.1 and 1.0 M, and urea solutions  
186 0.1–10 M are used (Schrooyen et al., 2000). The keratin solution is  
187 dialyzed to remove the reagents. During dialysis, extensive protein  
188 aggregation may occur but is often prevented by addition of sodium  
189 dodecylsulfate (SDS) (Schrooyen et al., 2001). Upon reduction, the  
190 disulfide bonds are broken to give cysteine thiol (reduced keratin) and  
191 cysteine-S-sulphonate (Bunte salt) residues:



192 where keratin-Cys-S- is the reduced keratin and keratin-Cys-SSO<sub>3</sub><sup>-</sup> is  
193 the Bunte salt (Maclaren & Milligan, 1995). If keratins are extracted by  
194 reduction, the resulting products are referred to as kerateines which  
195 are less polar, less soluble in water, but more stable in acidic and alka-  
196 line solutions. They can re-cross-link, and remain in vivo for weeks to  
197 months longer than the oxidized derivatives (Hill et al., 2010).

198 When oxidation is applied to extract keratin, strong oxidants are  
199 used, such as hydrogen peroxide (Breinl & Baudisch, 1907), potassium  
200 permanganate (Lissizin, 1928), ammonium copper hydroxide (Nagai &  
201 Nishikawa, 1970), and organic peracids (de Guzman et al., 2011). The  
202 disulfide bonds are converted to sulfonic acid groups and cysteic acid  
203 derivatives are formed, which are referred to as "keratoses":






203 These keratases are hygroscopic, water soluble, nondisulfide  
204 cross-linkable, and degrade relatively quickly in vivo in days to weeks  
205 (Hill et al., 2010).

### 206 3.3 | Chemical hydrolysis


207 During chemical hydrolysis, some amino acids are lost (Zhang, Li, et al.,  
208 2013). Keratins can be easily solubilized by hydrolysis in strong acids or  
209 alkalis, but they cannot be recovered except as amino acids or peptides,  
210 peptones, and proteoses, the properties of which differ significantly  
211 from those of the native keratin. The thermo-chemical treatment of  
212 keratinous materials with alkali leads to degradation of asparagine,  
213 arginine, serine, threonine, and glutamine (Chojnacka et al., 2011). The  
214 solubilization of keratin wool at temperatures above 70°C in a pH  
215 range of 9–11 for 4–12 hr in the presence of excess alkali can cause  
216 conversion of disulfide groups to cystyl residues (CysS<sup>-</sup>):



217 and subsequently the conversion of the cystyl residues into thioether  
218 groups, giving lanthionyl residues (Cys-S-Cys) (Cardamone, 2010). Pre-  
219 liminary alkaline treatment of wool in the sheep skin unhairing process  
220 also leads to the formation of two unnatural amino acids lysinoalanine  
221 and ornithinoalanine (Money, 1996). These products are a result of ker-  
222 atin hydrolysis under alkaline conditions during unhairing by the lime-  
223 sulfide method. Moreover, the treatment of keratins with reducing  
224 agents in strong alkaline solutions creates conditions that destroy the  
225 cystine and hydroxy amino acid residues (Koleva, Danalev, Ivanova,  
226 Vezenkov, & Vassilev, 2009).

227 Keratins can also be solubilized in alkaline solutions of metallic sul-  
228 fides. These reagents are generally used in cosmetic depilatories and  
229 removal of hair from hides in the tanning industry (Jones & Mechem,  
230 1948). Furthermore, alkaline hydrolysis with prolonged exposure at ele-  
231 vated temperature produces low molecular weight peptide fragments  
232 with poor mechanical properties. This product has limited biomedical  
233 application (Smith, Blanchard, & Lankford, 1994).

234 Acidic hydrolysis is highly efficient, but it is not recommended  
235 because of the loss of some amino acids, for example, serine, threonine,  
236 tyrosine, and cystine, as well as conversion of asparagine, glutamine,  
237 and tryptophan to other products. Furthermore, the bonds between  
238 valine and isoleucine are gradually disrupted (Chojnacka et al., 2011).  
239 Keratin can be solubilized in formic acid (Aluigi et al., 2007), hydrochlo-  
240 ric acid (Zhang, Li, et al., 2013), and sulfuric acid (Kurbanoglu &  
241 Kurbanoglu, 2007) using appropriately high temperature. During acid  
242 hydrolysis of wool keratin, disulfide, and partial peptide bonds are  
243 destroyed:




244 The degree of acid hydrolysis of keratin ranges from about 33 to  
245 46% (Karamać et al., 2005; Zhang, Li, et al., 2013). Acid-derived keratin  
246 hydrolysates have higher glass transition and lower decomposition

temperatures than pristine wool fibers (Katoh, Shibayama, Tanabe, & 247  
Yamauchi, 2004; Vasconcelos et al., 2008). They are nontoxic and bio- 248  
compatible and therefore can have potential application as biomaterials 249  
for wound healing and drug delivery. During acid hydrolysis of wool 250  
keratin, most of the hydrogen bonds are broken down which results in 251  
the amorphous structure of wool keratin polypeptides (Tung & Daoud, 252  
2009). Hence the content of both  $\alpha$ -helix and  $\beta$ -sheet structures in 253  
wool keratin are decreased as the total crystallinity of wool is the sum 254  
of  $\alpha$ - and  $\beta$ -crystallinity (Cao & Billows, 1999). The products of acid 255  
hydrolysis are more amorphous keratin polypeptides than alkaline- 256  
derived keratin hydrolysates (Zhang, Li, et al., 2013). 257

The hydrothermal methods for obtaining soluble keratin are expen- 258  
sive and destroy certain amino acids, for example, lysine, methionine, 259  
and tryptophan (Grazziotin, Pimentel, De Jong, & Brandelli, 2006). They 260  
result in products with poor digestibility and variable nutritional quality 261  
(Chojnacka et al., 2011). These processes are performed at 100–150°C 262  
and  $1.5 \times 10^5$  Pa (Grazziotin et al., 2006) and alkali or acid are often 263  
added. These hydrolysates have been used in feeding of poultry, rain- 264  
bow trout, shrimp, and salmon after supplementation with essential 265  
amino acids (Bertsch & Coello, 2005). 266

### 267 3.4 | Enzymatic hydrolysis

The enzymatic and/or microbiological methods for solubilization of ker- 268  
atin waste are cheap and run under mild conditions (Chojnacka et al., 269  
2011). These methods are an alternative to environmentally harmful 270  
chemical methods used most often in keratin isolation. Keratinases are 271  
extracellular serine proteases or metalloproteases produced by bacte- 272  
ria, actinomycetes, and fungi (Brandelli, 2008). The characteristics of 273  
keratinases produced by some microorganisms are shown in Table 2. 274  
These enzymes convert insoluble keratin to feedstuffs, fertilizers, and 275  
films, and also materials suitable for cosmetic and pharmaceutical appli- 276  
cations (Brandelli, Daroit, & Riffel, 2010). The mechanism of microbial 277  
keratinolysis is not completely known. The process of keratin degrada- 278  
tion proposed by Kunert (1976) is for dermatophytes and consists of 279  
sulfitolysis and proteolysis: 280



In the first stage, disulfide bonds are disrupted by sulfite produced 281  
by the fungus which leads to protein denaturation (Kunert, 1976) and 282  
proteolysis by endopeptidases. On the other hand, Yamamura, Morita, 283  
Hasan, Yokoyama, and Tamiya (2002) proposed a two-stage process of 284  
keratin degradation involving disulfide reductase and serine protease 285  
produced by *Stenotrophomonas* sp. D-1 from deer fur. Keratin reduced 286  
by disulfide reductase is hydrolyzed by protease to amino acids and 287  
peptides. Some bacteria, actinomycetes, keratinophilic fungi, and larvae 288  
of the common clothes moth (*Tineola bisselliella* Hummel) use native 289  
keratin as the sole source of carbon, nitrogen, sulfur, and energy 290  
(Kornitowicz-Kowalska & Bohacz, 2011). *Bacillus licheniformis*, *Bacillus* 291  
*pumilus*, *Bacillus cereus*, and *Bacillus subtilis*, and *Stenotrophomonas* sp., 292  
*Fervidobacterium pannavorans*, and *Fervidobacterium islandicum* were 293  
isolated from plumage and bird feathers, and fermented feather waste 294

TABLE 2 Characteristic of keratinases from some microorganisms

Source of keratinase	Molecular mass (kDa)	Optimum pH	Optimum temperature (°C)	References
<i>Aspergillus fumigatus</i> TKF1	24	6.0	50	Paul et al. (2014)
<i>Aspergillus parasiticus</i>	36	7.0	50	Anitha and Palanivelu (2013)
<i>Bacillus licheniformis</i> PWD-1	33	7.5	50	Lin, Lee, Casale, and Shih (1992)
<i>Bacillus pumilus</i> A1	–	9.0	55–60	Fakhfakh-Zouari, Haddar, Hmidet, Frikha, and Nasri (2010)
<i>Bacillus subtilis</i> S14	–	8.0	50	Silva, Macedo, and Termignoni (2014)
<i>Brevibacillus</i> sp.	83.2	12.5–13.0	45	Rai and Mukherjee (2011)
<i>Chryseobacterium indologenes</i> A22	–	7.5	45	Bach, Daroit, Corrêa, and Brandelli (2011)
<i>Chryseobacterium</i> sp. kr6	64	8.5	50	Riffel et al. (2007)
<i>Fervidobacterium islandicum</i> AW-1	>200	9.0	100	Nam et al. (2002)
<i>Microsporum canis</i>	33	8.0	35–45	Descamps et al. (2003)
<i>Microsporum gypseum</i>	33	8.0	35	Raju, Neogi, Saumya, and Goud (2007)
<i>Stenotrophomonas</i> sp. D-1	40	7.0	30	Yamamura et al. (2002)
<i>Streptomyces fradiae</i>	24	8.0	50	Galas and Kałużewska (1991)
<i>Streptomyces gulbargensis</i>	46	9.0	45	Syed, Lee, Li, Kim, and Agasar (2009)
<i>Streptomyces thermoviolaceus</i> SD8	40	8.0	55	Chitte, Nalawade, and Dey (1999)
<i>Trichophyton mentagrophytes</i>	38	5.5	55	Muhsin and Aubaid (2001)

AQ7

295 (Burt & Ichida, 1999; Ichida et al., 2001; Williams & Shih, 1989).  
 296 Keratinolytic species of actinomycetes, particularly from the genus  
 297 *Streptomyces*, and some species from *Thermoactinomyces* occur in  
 298 feathers, hairs, nails, and horns. The keratinophilic fungi live in the soil,  
 299 birds, mammals, avian nests, bird plumage, mammalian hair, communal  
 300 waste water, waste sediments, communal waste, and polluted water.  
 301 They are represented by dermatophytes (some species of *Trichophyton*  
 302 and *Microsporum*), and two genera: *Chryso sporium* and *Myceliophthora*  
 303 (Korniłowicz-Kowalska & Bohacz, 2011).

304 Another method used to dissolve keratins is a combination of  
 305 enzymatic and chemical treatment (Mokrejs, Svoboda, Hrcirik,  
 306 Janacova, & Vasek, 2011). Reports on application of thermo-chemical  
 307 treatment of keratins have appeared recently, however these methods  
 308 occur in different experimental layout, aimed in aiding subsequent  
 309 enzymatic digestion (Łaba et al., 2015).

## 310 4 | BIOACTIVE PROPERTIES OF KERATIN 311 PRODUCTS

### 312 4.1 | Introduction

313 Hydrolyzed proteins from many sources such as milk casein, soybean,  
 314 rice bran, quinoa seed protein, canola, egg yolk protein, and muscle  
 315 proteins have been reported to be sources of biologically active pep-  
 316 tides (Gómez-Guillén et al., 2011) (Table 3). These peptides, sequences  
 317 of 2–30 amino acids, are inactive in the parent protein and can be  
 318 released during gastrointestinal digestion, enzymatic processing or  
 319 microbial fermentation (Di Bernardini et al., 2011; Ferraro et al., 2016;

Gómez-Guillén et al., 2011). After liberation, they display biological  
 320 activities, for example, antioxidant, ACE inhibitory, and antimicrobial.  
 321 Keratins have also been shown to be a source of bioactive peptides by  
 322 Ferraro et al. (2016) and Lasekan, Bakar, and Hashim (2013).  
 323

### 324 4.2 | Antioxidant activity

325 Reports on the antioxidant properties of hydrolysates or peptides from  
 326 various proteins are abundant, but only a few from keratin. The antioxi-  
 327 dant peptides often contain hydrophobic amino acid residues, proline,  
 328 histidine, tyrosine, and tryptophan (Brandelli, Daroit, & Corrêa, 2015).  
 329 Ohba et al. (2003) reported high antioxidant activity in the enzymatic  
 330 hydrolysate of a mixture of horn and hoof, and chicken feather. They  
 331 suggested that the large amounts of cysteine in keratin were responsi-  
 332 ble for this activity. Fakhfakh et al. (2011) also found high antioxidant  
 333 activity in the hydrolysate obtained after fermentation of chicken  
 334 feather with the bacterium *Bacillus pumilus* A1. The keratin wastes  
 335 showed stronger antioxidant activity than the collagen wastes using  
 336 the DPPH radical scavenging assay. The authors suggested that the use  
 337 of feather protein hydrolysate in fish feed formulations could be  
 338 suitable for improving the biological properties of the feed. Kumar  
 339 et al. (2012) produced feather protein hydrolysate with a high DPPH  
 340 free radical-scavenging activity which was similar to that shown by  
 341 Fakhfakh et al. (2011) using the strain *Bacillus pumilus* A1. Fontoura  
 342 et al. (2014) obtained hydrolysates from raw chicken feathers with the  
 343 bacterium *Chryseobacterium* sp. kr6 which displayed in vitro antioxidant  
 344 properties. These hydrolysates might be used as a source of bioactive  
 345 constituent for feed, food, and drug production. An antioxidative

TABLE 3 Bioactive peptides from different proteins

Source	Antioxidant peptides	Reference	ACE inhibitory peptides	Reference
Bovine casein	Tyr-Phe-Tyr-Pro-Glu-Leu	Suetsuna, Ukeda, and Ochi (2000)	Arg-Tyr-Leu-Gly-Tyr  Ala-Tyr-Phe-Tyr-Pro-Glu-Leu Tyr-Gln-Lys-Phe-Pro-Gln-Tyr	Contreras et al. (2009)
Bovine $\alpha$ -lactalbumin	Ile-Asn-Tyr-Trp	Sadat et al. (2011)	Leu-Ala-His-Lys-Ala-Leu  Trp-Leu-Ala-His-Lys  Val-Gly-Ile-Asn-Tyr-Trp-Leu-Ala-His-Lys	Pihlanto-Leppälä et al. (1998) Pihlanto-Leppälä, Koskinen, Piilola, Tupasela, and Korhonen (2000)
Bovine $\beta$ -lactoglobulin	Phe-Asn-Pro-Thr-Gln  Leu-Gln-Lys-Trp Leu-Asp-Thr-Asp-Tyr-Lys-Lys Val-Ala-Gly-Thr-Trp-Tyr Trp-Tyr-Ser-Leu	Contreras, Hernández-Ledesma, Amigo, Martín-Álvarez, and Recio (2011)  Power et al. (2014) Zhang, Wu, Ling, and Lu (2013)	Ile-Ile-Ala-Glu-Lys  Ile-Pro-Ala-Val-Phe-Lys Ala-Leu-Pro-Met-His-Ile-Arg	Power, Fernández, Norris, Riera, and FitzGerald (2014) Mullally, Meisel, and FitzGerald (1997)
Bovine skin gelatin	Gly-Pro-Hyp-Gly-Pro-Hyp-Gly-Pro-Hyp-Gly	Kim, Byun, Park, and Shahidi (2001) and Kim, Kim, Byun, Park, and Ito (2001)	Gly-Pro-Val  Gly-Pro-Leu	Kim, Byun, et al. (2001) and Kim, Kim, et al. (2001)
Chicken feather keratin	Ser-Asn-Leu-Cys-Arg-Pro-Cys-Gly	Wan et al. (2016)	-	-
Chicken leg collagen	-	-	Gly-Ala-Hyp-Gly-Leu-Hyp-Gly-Pro	Saiga et al. (2008)
Egg yolk protein	Leu-Met-Ser-Tyr-Met-Trp-Ser-Thr-Ser-Met  Leu-Glu-Leu-His-Lys-Leu-Arg-Ser-Ser-His-Trp-Phe-Ser-Arg-Arg	Park, Jung, Nam, Shahidi, and Kim (2001)	-	-
Egg white protein	Ala-His  Val-His-His  Val-His-His-Ala-Asn-Glu-Asn	Tsuge, Eikawa, Nomura, Yamamoto, and Sugisawa (1991)	Arg-Ala-Asp-His-Pro-Phe-Leu  Tyr-Ala-Glu-Glu-Arg-Tyr-Pro-Ile-Leu	Miguel, Recio, Gómez-Ruiz, Ramos, and Lopez-Fandino (2004)
Fish skin gelatin ( <i>Jonius belengerii</i> )	His-Gly-Pro-Leu-Gly-Pro-Leu	Mendis, Rajapakse, and Kim (2005)	-	-
Pacific codfish gelatin	-	-	Thr-Cys-Ser-Pro Thr-Gly-Gly-Gly-Asn-Val	Ngo et al. (2011)
Porcine actomyosin	Asp-Leu-Tyr-Ala Ser-Leu-Tyr-Ala Val-Trp	Arihara (2006)	-	-
Porcine skin collagen	Gln-Gly-Ala-Arg	Li, Chen, Wang, Ji, and Wu (2007)	-	-
Porcine skin gelatin	-	-	Gly-Phe-Hyp-Gly-Pro	Ichimura, Yamanaka, Otsuka, Yamashita, and Maruyama (2009)



346 peptide had been isolated from chicken feather hydrolysate obtained  
347 by bacterial fermentation and identified as Ser-Asn-Leu-Cys-Arg-Pro-  
348 Cys-Gly (Wan, Dong, Yang, & Feng, 2016). Polypeptides from bovine  
349 hair exhibited significant antioxidant activity and remarkable food  
350 protection. These polypeptides could be a new natural antioxidant  
351 used in oil and oil-rich food (Zeng, Zhang, Zhang, & Shi, 2013).

### 352 4.3 | ACE inhibitory activity

353 Antihypertensive peptides can lower blood pressure through inhibition  
354 ACE. Many years of research have been devoted to the synthesis of  
355 ACE inhibitors used widely for therapeutic purposes to prevent hyper-  
356 tension (Gómez-Guillén et al., 2011). However, they have side effects  
357 such as coughing, poor taste, skin rashes, and angioneurotic edema  
358 (Atkinson & Robertson, 1979). Therefore, research has focused on  
359 identifying natural sources of ACE inhibitors with no side effects. Many  
360 antihypertensive/ACE inhibitory peptides have been isolated from  
361 casein, collagen, lactalbumin, myosin, ovalbumin, and serum albumin  
362 (Brandelli et al., 2015; Contreras, Carrón, Montero, Ramos, & Recio,  
363 2009; Pihlanto-Leppälä, Rokka, & Korhonen, 1998; Saiga et al., 2008).

364 Keratin has also been shown to be a source of ACE inhibitory pep-  
365 tides, although it has not been studied with regard to this activity as  
366 much as other proteins. ACE inhibitory activity has been shown in  
367 keratin hydrolysates from poultry feathers (Karamać et al., 2005). The  
368 activity of acid hydrolysates from keratin waste was lower (49.6% inhi-  
369 bition) than that of collagen hydrolysates (72.3% inhibition). Increase in  
370 ACE inhibitory activity with increase of the concentration of proline  
371 and hydroxyproline had been observed (Gómez-Guillén et al., 2011).  
372 Ohba et al. (2003) reported that the enzymatic hydrolysate of a mixture  
373 of horn and hoof also exhibited low ACE inhibitory activity. ACE inhi-  
374 bitory activity increased with decreasing molecular weight of hydroly-  
375 sates. The hydrolysates obtained from raw chicken feathers with the  
376 bacterium *Chryseobacterium* sp. kr6 also had ACE inhibitory activity  
377 (Fontoura et al., 2014). The keratin hydrolysates were able to inhibit  
378 65% ACE activity and was comparable to ACE inhibitory activity of  
379 soybean hydrolysates and milk protein hydrolysates. Enzyme specificity  
380 influences the biological activity of protein hydrolysates (Gómez-  
381 Guillén et al., 2011). High hydrophobic and aromatic amino acid  
382 residues content of 50–60% of the total amino acid residues is charac-  
383 teristic of keratins (Fontoura et al., 2014). Hydrophobic amino acids at  
384 the C-terminal tripeptide sequence contribute to the ACE inhibitory  
385 activity of peptides (Haque & Chand, 2008).

### 386 4.4 | Other activities

387 Keratins have also been shown to be a source of bioactive peptides  
388 with other biological activities. Fontoura et al. (2014) showed that the  
389 hydrolysates obtained from raw chicken feathers had the ability to  
390 inhibit DPP IV activity by 44%. This activity was found only in whey  
391 hydrolysates which positively affect blood glucose control and insulino-  
392 tropic responses in humans. Bioactive peptides from whey proteins  
393 stimulate the secretion gut hormones, and also act as DPP IV inhibitors  
394 in vivo (Jakubowicz & Froy, 2013).

Gousterova et al. (2011) found that feather hydrolysate obtained 395  
using a mixed culture of *Thermoactinomyces* strains showed good activ- 396  
ity against plant pathogenic fungi *Fusarium solani*, *Fusarium oxysporum*, 397  
*Mucor* sp., and *Aspergillus niger*. It was suggested that the feather 398  
hydrolysate could be used as an alternative soil amendment for restor- 399  
ing contaminated soils, accelerating ryegrass growth, and improving the 400  
quality of agricultural soils. 401

Sundaram et al. (2015) observed antibacterial activity of keratin 402  
hydrolysate and keratin nanoparticles. The radius of inhibition zone for 403  
keratin hydrolysate against *Staphylococcus aureus* and *Escherichia coli* 404  
was 7.5 mm and 9 mm, respectively, at 100 µg/mL. They reported that 405  
the inhibition zone formulated for keratin nanoparticles was higher 406  
than that for keratin hydrolysates. 407

## 5 | CONCLUSIONS AND PERSPECTIVES 408

Keratin extracted from waste is a source of bioactive compounds for 409  
biological, food, and biomaterial applications. There is more information 410  
on the nonbiological functions of keratins than bioactive properties. 411  
Thus there is a need for further research devoted to selecting enzyme 412  
systems that convert keratin waste into bioactive peptides which could 413  
be used for formation of useful novel bioproducts. Literature shows an 414  
increasing number of reports on the use of various enzymes and 415  
conditions to obtain bioactive peptides from keratin. The peptides with 416  
antioxidant and antimicrobial activities could possibly be used as addi- 417  
tives in functional food products. Similarly, the fragments of keratin 418  
with ACE inhibitory and DPP IV inhibitory activity could be suitable for 419  
food and pharmaceutical applications. Therefore, advanced research on 420  
safety of these future bioproducts, maintenance of their bioactivity in 421  
humans mechanism of action, and industrial production are necessary. 422

### ORCID 423

Izabela Sinkiewicz  <http://orcid.org/0000-0001-5221-552X> 424

### REFERENCES 425

- Akhtar, W., & Edwards, H. G. M. (1997). Fourier-transform Raman 426  
spectroscopy of mammalian and avian keratotic biopolymers. *Spectro-* 427  
*chimica Acta A*, 53(1), 81–90. 428
- Aluigi, A., Zoccola, M., Vineis, C., Tonin, C., Ferrero, F., & Canetti, M. 429  
(2007). Study on the structure and properties of wool keratin regen- 430  
erated from formic acid. *International Journal of Biological Macromole-* 431  
*cules*, 41(3), 266–273. 432
- Anitha, T. S., & Palanivelu, P. (2013). Purification and characterization of 433  
an extracellular keratinolytic protease from a new isolate of *Aspergil-* 434  
*lus parasiticus*. *Protein Expression and Purification*, 88(2), 214–220. 435
- Arai, K., Sakamoto, M., Naito, S., & Takahashi, T. (1989). Crosslinking 436  
structure of keratin. II. Intermolecular and intramolecular crosslinks in 437  
potassium-cyanide-treated wool fibers. *Journal of Applied Polymer* 438  
*Science*, 38(1), 29–44. 439
- Arihara, K. (2006). Strategies for designing novel functional meat 440  
products. *Meat Science*, 74(1), 219–229. 441
- Atkinson, A. B., & Robertson, J. I. S. (1979). Captopril in the treatment of 442  
clinical hypertension and cardiac failure. *Lancet*, 314(8147), 836–839. 443

- 444 Bach, E., Daroit, D. J., Corrêa, A. P. F., & Brandelli, A. (2011). Production  
445 and properties of keratinolytic proteases from three novel Gram-  
446 negative feather-degrading bacteria isolated from Brazilian soils.  
447 *Biodegradation*, 22(6), 1191.
- 448 Balaji, S., Kumar, R., Sripriya, R., Kakkar, P., Ramesh, D. V., Reddy, P. N.  
449 K., & Sehgal, P. K. (2012). Preparation and comparative characteriza-  
450 tion of keratin-chitosan and keratin-gelatin composite scaffolds for  
451 tissue engineering applications. *Materials Science and Engineering: C*,  
452 32(4), 975–982.
- 453 Bertsch, A., & Coello, N. (2005). A biotechnological process for treatment  
454 and recycling poultry feathers as a feed ingredient. *Bioresource*  
455 *Technology*, 96(15), 1703–1708.
- 456 Bonser, R. H. C. (1996). The mechanical properties of feathers keratin.  
457 *Journal of Zoology*, 239(3), 477–484.
- 458 Bragulla, H. H., & Homberger, D. G. (2009). Structure and functions of  
459 keratin proteins in simple, stratified, keratinized and cornified  
460 epithelia. *Journal of Anatomy*, 214(4), 516–559.
- 461 Brandelli, A. (2008). Bacterial keratinases: Useful enzymes for bioproc-  
462 essing agroindustrial wastes and beyond. *Food and Bioprocess*  
463 *Technology*, 1(2), 105–116.
- 464 Brandelli, A., Daroit, D. J., & Corrêa, A. P. F. (2015). Whey as a source of  
465 peptides with remarkable biological activities. *Food Research*  
466 *International*, 73, 149–161.
- 467 Brandelli, A., Daroit, D. J., & Riffel, A. (2010). Biochemical features of  
468 microbial keratinases and their production and applications. *Applied*  
469 *Microbiology and Biotechnology*, 85(6), 1735–1750.
- 470 Breinl, F., & Baudisch, O. (1907). The oxidative breaking up of keratin  
471 through treatment with hydrogen peroxide. *Zeitschrift für Physiologi-*  
472 *sche Chemie*, 52(1–2), 158–169.
- 473 Burt, E. H. Jr., & Ichida, J. M. (1999). Occurrence of feather-degrading  
474 bacilli in the plumage of birds. *The Auk*, 116(2), 364–372.
- 475 Cao, J., & Billows, C. A. (1999). Crystallinity determination of native and  
476 stretched wool by X-ray diffraction. *Polymer International*, 48(10),  
477 1027–1033.
- 478 Cardamone, J. M. (2010). Investigating the microstructure of keratin  
479 extracted from wool: Peptide sequence (MALDI-TOF/TOF) and  
480 protein conformation (FTIR). *Journal of Molecular Structure*, 969(1),  
481 97–105.
- 482 Chitte, R. R., Nalawade, V. K., & Dey, S. (1999). Keratinolytic activity  
483 from the broth of a feather-degrading thermophilic *Streptomyces*  
484 *thermophilaceus* strain SD8. *Letters in Applied Microbiology*, 28(2),  
485 131–136.
- 486 Chojnacka, K., Górecka, H., Michalak, I., & Górecki, H. (2011). A review:  
487 Valorization of keratinous materials. *Waste and Biomass Valorization*,  
488 2(3), 317–321.
- 489 Contreras, M., Carrón, R., Montero, M. J., Ramos, M., & Recio, I. (2009).  
490 Novel casein-derived peptides with antihypertensive activity. *Interna-*  
491 *tional Dairy Journal*, 19(10), 566–573.
- 492 Contreras, M., Hernández-Ledesma, B., Amigo, L., Martín-Álvarez, P. J., &  
493 Recio, I. (2011). Production of antioxidant hydrolyzates from a whey  
494 protein concentrate with thermolysin: Optimization by response sur-  
495 face methodology. *LWT-Food Science and Technology*, 44(1), 9–15.
- 496 Coward-Kelly, G. U., Chang, V. S., Agbogbo, F. K., & Holtzapple, M. T.  
497 (2006). Lime treatment of keratinous materials for the generation of  
498 highly digestible animal feed: 2. Animal hair. *Bioresource Technology*,  
499 117(11), 1344–1352.
- 500 Descamps, F., Brouta, F., Vermout, S., Monod, M., Losson, B., & Mignon,  
501 B. (2003). Recombinant expression and antigenic properties of a  
502 31.5-kDa keratinolytic subtilisin-like serine protease from *Microspo-*  
503 *rum canis*. *FEMS Immunology & Medical Microbiology*, 38(1), 29–34.
- Di Bernardini, R., Harnedy, P., Bolton, D., Kerry, J., O'Neill, E., Mullen, A. 504  
M., & Hayes, M. (2011). Antioxidant and antimicrobial peptide hydro- 505  
lysates from muscle protein sources and by-products. *Food Chemistry*, 506  
124(4), 1296–1307. 507
- Dickerson, M. B., Sierra, A. A., Bedford, N. M., Lyon, W. J., Gruner, W. 508  
E., Mirau, P. A., & Naik, R. R. (2013). Keratin-based antimicrobial 509  
textiles, films, and nanofibers. *Journal of Materials Chemistry B*, 40, 510  
5505–5514. 511
- Eslahi, N., Dadashian, F., & Nejad, N. H. (2013). An investigation on kera- 512  
tin extraction from wool and feathers waste by enzymatic hydrolysis. 513  
*Preparative Biochemistry and Biotechnology*, 43(7), 624–648. 514
- Fakhfakh, N., Ktari, N., Haddar, A., Mnif, I. H., Dahmen, I., & Nasri, M. 515  
(2011). Total solubilisation of the chicken feathers by fermentation 516  
with a keratinolytic bacterium, *Bacillus pumilus* A1, and the produc- 517  
tion of protein hydrolysate with high antioxidative activity. *Process* 518  
*Biochemistry*, 46(9), 1731–1737. 519
- Fakhfakh-Zouari, N., Haddar, A., Hmidet, N., Frikha, F., & Nasri, M. 520  
(2010). Application of statistical experimental design for optimization 521  
of keratinases production by *Bacillus pumilus* A1 grown on chicken 522  
feather and some biochemical properties. *Process Biochemistry*, 45(5), 523  
617–626. 524
- Ferraro, V., Anton, M., & Santé-Lhoutellier, V. (2016). The “sisters” 525  
 $\alpha$ -helices of collagen, elastin and keratin recovered from animal by- 526  
products: Functionality, bioactivity and trends of application. *Trends* 527  
*in Food Science & Technology*, 51, 65–75. 528
- Fontoura, R., Daroit, D. J., Correa, A. P., Meira, S. M., Mosquera, M., & 529  
Brandelli, A. (2014). Production of feather hydrolysates with antioxi- 530  
dant, angiotensin-I converting enzyme-and dipeptidyl peptidase-IV- 531  
inhibitory activities. *New Biotechnology*, 31(5), 506–513. 532
- Fraser, R. D., MacRae, T. P., Parry, D. A., & Suzuki, E. (1986). Intermedi- 533  
ate filaments in alpha-keratins. *Proceedings of the National Academy* 534  
*of Sciences*, 83(5), 1179–1183. 535
- Fujii, T., & Li, D. (2008). Preparation and properties of protein films and 536  
particles from chicken feather. *International Journal of Biological* 537  
*Macromolecules*, 8(2), 48–55. 538
- Galas, E., & Kałużewska, M. (1991). Proteinases of *Streptomyces fradiae*. 539  
III. Catalytic and some physico-chemical properties of keratinolytic 540  
proteinase. *Acta Microbiologica Polonica*, 41(3–4), 169–177. 541
- Gómez-Guillén, M. C., Giménez, B., López-Caballero, M. E., & Montero, 542  
M. P. (2011). Functional and bioactive properties of collagen and 543  
gelatin from alternative sources: A review. *Food Hydrocolloids*, 25(8), 544  
1813–1827. 545
- Goodwin, W. D. (1976). Nutrient protein from keratinaceous material 546  
solubilized with N, N-dimethylformamide. *U.S. Patent No. 3,970,614*. 547  
Washington, DC: U.S. Patent and Trademark Office. 548
- Gousterova, A., Nustorova, M., Paskaleva, D., Naydenov, M., Neshev, G., 549  
& Vasileva-Tonkova, E. (2011). Assessment of feather hydrolysate 550  
from thermophilic actinomycetes for soil amendment and biological 551  
control application. *International Journal of Environmental Research*, 5  
4(4), 1065–1070. 552
- Grazziotin, A., Pimentel, F. A., De Jong, E. V., & Brandelli, A. (2006). 554  
Nutritional improvement of feather protein by treatment with micro- 555  
bial keratinase. *Animal Feed Science and Technology*, 126(1), 135–144. 556
- Haque, E., & Chand, R. (2008). Antihypertensive and antimicrobial 557  
bioactive peptides from milk proteins. *European Food Research and* 558  
*Technology*, 227(1), 7–15. 559
- Hill, P., Brantley, H., & Van Dyke, M. (2010). Some properties of keratin 560  
biomaterials: Kerateines. *Biomaterials*, 31(4), 585–593. 561
- Ichida, J. M., Krizova, L., Lefevre, C. A., Keener, H. M., Elwell, D. L., & 562  
Burt, E. H. Jr. (2001). Bacterial inoculum enhances keratin 563

- 564 degradation and biofilm formation in poultry compost. *Journal of*  
565 *Microbiological Methods*, 47(2), 199–208.
- 566 Ichimura, T., Yamanaka, A., Otsuka, T., Yamashita, E., & Maruyama, S.  
567 (2009). Antihypertensive effect of enzymatic hydrolysate of collagen  
568 and Gly-Pro in spontaneously hypertensive rats. *Bioscience, Biotech-*  
569 *nology, and Biochemistry*, 73(10), 2317–2319.
- 570 Jakubowicz, D., & Froy, O. (2013). Biochemical and metabolic mecha-  
571 nisms by which dietary whey protein may combat obesity and type 2  
572 diabetes. *The Journal of Nutritional Biochemistry*, 24(1), 1–5.
- 573 Jones, C. B., & Mecham, D. K. (1948). Method of dispersing keratin  
574 proteins with amides and the composition resulting therefrom. U.S.  
575 Patent No. 2,445,028. Washington, DC: U.S. Patent and Trademark  
576 Office.
- 577 Kakkar, P., Madhan, B., & Shanmugam, G. (2014). Extraction and charac-  
578 terization of keratin from bovine hoof: A potential material for  
579 biomedical applications. *SpringerPlus*, 3(1), 596.
- 580 Karamać, M., Flaczyk, E., Wanasundara, P. K. J. P. D., & Amarowicz, R.  
581 (2005). Angiotensin I-converting enzyme (ACE) inhibitory activity of  
582 hydrolysates obtained from muscle food industry by-products—a short  
583 report. *Polish Journal of Food and Nutrition Sciences*, 14, 133–137.
- 584 Katoh, K., Shibayama, M., Tanabe, T., & Yamauchi, K. (2004). Preparation  
585 and physicochemical properties of compression-molded keratin films.  
586 *Biomaterials*, 25(12), 2265–2272.
- 587 Kim, S. K., Byun, H. G., Park, P. J., & Shahidi, F. (2001). Angiotensin I  
588 converting enzyme inhibitory peptides purified from bovine skin gela-  
589 tin hydrolysate. *Journal of Agricultural and Food Chemistry*, 49(6),  
590 2992–2997.
- 591 Kim, S. K., Kim, Y. T., Byun, H. G., Park, P. J., & Ito, H. (2001). Purifica-  
592 tion and characterization of antioxidative peptides from bovine skin.  
593 *BMB Reports*, 34(3), 219–224.
- 594 Koleva, M., Danalev, D., Ivanova, D., Vezenkov, L., & Vassilev, N. (2009).  
595 Synthesis of two peptide mimetics as markers for chemical changes  
596 of wool's keratin during skin unhairing process and comparison of  
597 the wool quality obtained by ecological methods for skins unhairing.  
598 *Bulgarian Chemical Communications*, 41, 160–164.
- 599 Kornitowicz-Kowalska, T., & Bohacz, J. (2011). Biodegradation of keratin  
600 waste: Theory and practical aspects. *Waste Management*, 31(8),  
601 1689–1701.
- 602 Kumar, D. M., Priya, P., Balasundari, S. N., Devi, G. S. D. N., Rebecca, A. I.  
603 N., & Kalaichelvan, P. T. (2012). Production and optimization of feather  
604 protein hydrolysate from *Bacillus* sp. MPTK6 and its antioxidant poten-  
605 tial. *Middle-East Journal of Scientific Research*, 11(7), 900–907.
- 606 Kunert, J. (1976). Keratin decomposition by dermatophytes II. Presence  
607 of S-sulfocysteine and cysteic acid in soluble decomposition prod-  
608 ucts. *Zeitschrift für Allgemeine Mikrobiologie*, 16(2), 97–105.
- 609 Kurbanoglu, E. B., & Kurbanoglu, N. I. (2007). Ram horn hydrolysate as  
610 enhancer of xanthan production in batch culture of *Xanthomonas*  
611 *campestris* EBK-4 isolate. *Process Biochemistry*, 42(7), 1146–1149.
- 612 Łaba, W., Kopeć, W., Chorążyk, D., Kancelista, A., Piegza, M., & Malik, K.  
613 (2015). Biodegradation of pretreated pig bristles by *Bacillus cereus*  
614 B5esz. *International Biodeterioration & Biodegradation*, 100, 116–123.
- 615 Lasekan, A., Bakar, F. A., & Hashim, D. (2013). Potential of chicken by-  
616 products as sources of useful biological resources. *Waste Manage-*  
617 *ment*, 33(3), 552–565.
- 618 Li, B., Chen, F., Wang, X., Ji, B., & Wu, Y. (2007). Isolation and identifica-  
619 tion of antioxidative peptides from porcine collagen hydrolysate by  
620 consecutive chromatography and electrospray ionization–mass spec-  
621 trometry. *Food Chemistry*, 102(4), 1135–1143.
- 622 Lin, X., Lee, C. G., Casale, E. S., & Shih, J. C. (1992). Purification and char-  
623 acterization of a keratinase from a feather-degrading *Bacillus*  
*licheniformis* strain. *Applied and Environmental Microbiology*, 58(10), 624  
3271–3275. 625
- Lissizin, T. (1928). The oxidation products of keratin by oxidation with  
626 permanganate II. *Zeitschrift für Physiologische Chemie*, 173(5–6),  
627 309–311. 628
- Maclaren, J. A., & Milligan, B. (1995). The chemical reactivity of the wool  
629 fiber. *Wool Science*, 3, 45–49. 630
- Marchisio, V. F. (2000). Keratinophilic fungi: Their role in nature and deg-  
631 radation of keratinic substrates. In R. K. S. Kushawaha & J. Guarro  
632 (Eds.), *Biology of dermatophytes and other keratinophilic fungi* (Vol. 17,  
633 pp. 86–92). Bilbao, Spain: Revista Iberoamericana de Micología. 634
- McKittrick, J., Chen, P. Y., Bodde, S. G., Yang, W., Novitskaya, E. E., &  
635 Meyers, M. A. (2012). The structure, functions, and mechanical  
636 properties of keratin. *JOM*, 64(4), 449–468. 637
- Mendis, E., Rajapakse, N., & Kim, S. K. (2005). Antioxidant properties of  
638 a radical-scavenging peptide purified from enzymatically prepared  
639 fish skin gelatin hydrolysate. *Journal of Agricultural and Food*  
640 *Chemistry*, 53(3), 581–587. 641
- Miguel, M., Recio, I., Gómez-Ruiz, J. A., Ramos, M., & Lopez-Fandino, R.  
642 (2004). Angiotensin I-converting enzyme inhibitory activity of  
643 peptides derived from egg white proteins by enzymatic hydrolysis.  
644 *Journal of Food Protection*, 67(9), 1914–1920. 645
- Mokrejs, P., Svoboda, P., Hrcirik, J., Janacova, D., & Vasek, V. (2011).  
646 Processing poultry feathers into keratin hydrolysate through  
647 alkaline-enzymatic hydrolysis. *Waste Management & Research*, 29(3),  
648 260–267. 649
- Money, C. A. (1996). Unhairing and dewooling – Requirements for  
650 quality and the environment. *Journal of the Society of Leather Technol-*  
651 *ogists & Chemists*, 80, 175–186. 652
- Moore, G. R., Martelli, S. M., Gandolfo, C. A., Pires, A. T., & Laurindo, J.  
653 B. (2006). Queratina de penas de frango: Extração, caracterização e  
654 obtenção de filmes. *Ciência e Tecnologia de Alimentos*, 26(2), 421. 655
- Muhsin, T. M., & Aubaid, A. H. (2001). Partial purification and some bio-  
656 chemical characteristics of exocellular keratinase from *Trichophyton*  
657 *mentagrophytes* var. *erinacei*. *Mycopathologia*, 150(3), 121–125. 658
- Mullally, M. M., Meisel, H., & FitzGerald, R. J. (1997). Identification of a  
659 novel angiotensin-I-converting enzyme inhibitory peptide correspond-  
660 ing to a tryptic fragment of bovine  $\beta$ -lactoglobulin. *FEBS Letters*, 402  
661 (2–3), 99–101. 662
- Nagai, Y., & Nishikawa, T. (1970). Solubilization of chicken feather  
663 keratin by ammonium copper hydroxide (Schweitzer's reagent).  
664 *Agricultural and Biological Chemistry*, 34(4), 575–584. 665
- Nam, G. W., Lee, D. W., Lee, H. S., Lee, N. J., Kim, B. C., Choe, E. A., ...  
666 Pyun, Y. R. (2002). Native-feather degradation by *Fervidobacterium*  
667 *islandicum* AW-1, a newly isolated keratinase-producing thermophilic  
668 anaerobe. *Archives of Microbiology*, 178(6), 538–547. 669
- Ngo, D. H., Ryu, B., Vo, T. S., Himaya, S. W. A., Wijesekara, I., & Kim, S. K.  
670 (2011). Free radical scavenging and angiotensin-I converting enzyme  
671 inhibitory peptides from Pacific cod (*Gadus macrocephalus*) skin gelatin.  
672 *International Journal of Biological Macromolecules*, 49(5), 1110–1116. 673
- Noda, J., Imai, T., Kida, K., & Otagiri, M. (1996). The physicochemical and  
674 biopharmaceutical properties of fragmented keratin as a new drug  
675 carrier. *Biological & Pharmaceutical Bulletin*, 19(3), 466–473. 676
- Nomura, Y., Aihara, M., Nakajima, D., Kenjou, S., Tsukuda, M., & Tsuda,  
677 Y. (2005). Process for producing solubilized keratin. U.S. Patent  
678 Application No. 10/594,758. 679
- Ohba, R., Deguchi, T., Kishikawa, M., Arsyad, F., Morimura, S., & Kida, K.  
680 (2003). Physiological functions of enzymatic hydrolysates of collagen  
681 or keratin contained in livestock and fish waste. *Food Science and*  
682 *Technology Research*, 9(1), 91–93. 683

- 684 Park, P. J., Jung, W. K., Nam, K. S., Shahidi, F., & Kim, S. K. (2001). Purifi- 744  
 685 cation and characterization of antioxidative peptides from protein 745  
 686 hydrolysate of lecithin-free egg yolk. *Journal of the American Oil 746*  
 687 *Chemists' Society*, 78(6), 651–656.
- 688 Paul, T., Das, A., Mandal, A., Halder, S. K., DasMohapatra, P. K., Pati, B. 747  
 689 R., & Mondal, K. C. (2014). Production and purification of keratinase 748  
 690 using chicken feather bioconversion by a newly isolated *Aspergillus 749*  
 691 *fumigatus* TKF1: Detection of valuable metabolites. *Biomass Conver- 750*  
 692 *sion and Biorefinery*, 4(2), 137–148. 751
- 693 Pihlanto-Leppälä, A., Koskinen, P., Piilola, K., Tupasela, T., & Korhonen, 752  
 694 H. (2000). Angiotensin I-converting enzyme inhibitory properties of 753  
 695 whey protein digests: Concentration and characterization of active 754  
 696 peptides. *Journal of Dairy Research*, 67(1), 53–64. 755
- 697 Pihlanto-Leppälä, A., Rokka, T., & Korhonen, H. (1998). Angiotensin I 756  
 698 converting enzyme inhibitory peptides derived from bovine milk pro- 757  
 699 teins. *International Dairy Journal*, 8(4), 325–331. 758
- 700 Power, O., Fernández, A., Norris, R., Riera, F. A., & FitzGerald, R. J. (2014). 759  
 701 Selective enrichment of bioactive properties during ultrafiltration of a 760  
 702 tryptic digest of  $\beta$ -lactoglobulin. *Journal of Functional Foods*, 9, 38–47. 761
- 703 Rai, S. K., & Mukherjee, A. K. (2011). Optimization of production of an 762  
 704 oxidant and detergent-stable alkaline  $\beta$ -keratinase from *Brevibacillus 763*  
 705 sp. strain AS-S10-II: Application of enzyme in laundry detergent for- 764  
 706 mulations and in leather industry. *Biochemical Engineering Journal*, 54 765  
 707 (1), 47–56. 766
- 708 Raju, K. C., Neogi, U., Saunmya, R., & Goud, N. R. (2007). Studies on extra 767  
 709 cellular enzyme keratinase from dermatophyte *Microsporum gypseum*. 768  
 710 *International Journal of Biological Chemistry*, 1(3), 174–178. 769
- 711 Reddy, N., Chen, L., & Yang, Y. (2013). Biothermoplastics from hydro- 770  
 712 lyzed and citric acid crosslinked chicken feathers. *Materials Science & 771*  
 713 *Engineering: C, Materials for Biological Applications*, 33(3), 1203–1208. 772
- 714 Reddy, N., Jiang, Q., Jin, E., Shi, Z., Hou, X., & Yang, Y. (2013). Bio-ther- 773  
 715 moplastics from grafted chicken feathers for potential biomedical 774  
 716 applications. *Colloids and Surfaces B: Biointerfaces*, 110, 51–58. 775
- 717 Reichl, S. (2009). Films based on human hair keratin as substrates for cell 776  
 718 culture and tissue engineering. *Biomaterials*, 30(36), 6854–6866. 777
- 719 Riffel, A., Brandelli, A., Bellato, C. D. M., Souza, G. H., Eberlin, M. N., & 778  
 720 Tavares, F. C. (2007). Purification and characterization of a keratino- 779  
 721 lytic metalloprotease from *Chryseobacterium* sp. kr6. *Journal of 780*  
 722 *Biotechnology*, 128(3), 693–703. 781
- 723 Rodziewicz, A., & Łaba, W. (2006). Keratins and their biodegradation. 782  
 724 *Biotechnology*, 2(73), 130–147. 783
- 725 Rouse, J. G., & Van Dyke, M. E. (2010). A review of keratin-based bioma- 784  
 726 terials for biomedical applications. *Materials*, 3(2), 999–1014. 785
- 727 Sadat, L., Cakir-Kiefer, C., N'Negue, M. A., Gaillard, J. L., Girardet, J. M., & 786  
 728 Miclo, L. (2011). Isolation and identification of antioxidative peptides 787  
 729 from bovine  $\alpha$ -lactalbumin. *International Dairy Journal*, 21(4), 214–221. 788
- 730 Saiga, A. I., Iwai, K., Hayakawa, T., Takahata, Y., Kitamura, S., Nishimura, 789  
 731 T., & Morimatsu, F. (2008). Angiotensin I-converting enzyme-inhibi- 790  
 732 tory peptides obtained from chicken collagen hydrolysate. *Journal of 791*  
 733 *Agricultural and Food Chemistry*, 56(20), 9586–9591. 792
- 734 Saravanan, K. (2012). Exploration of amino acids content and morpholog- 793  
 735 ical structure in chicken feather fiber. *Journal of Textile and Apparel, 794*  
 736 *Technology and Management*, 7(3), 1–6. 795
- 737 Schrooyen, P. M., Dijkstra, P. J., Oberthür, R. C., Bantjes, A., & Feijen, J. 796  
 738 (2001). Stabilization of solutions of feather keratins by sodium dodecyl 797  
 739 sulfate. *Journal of Colloid and Interface Science*, 240(1), 30–39. 798
- 740 Schrooyen, P. M., Dijkstra, P. J., Oberthür, R. C., Bantjes, A., & Feijen, J. 799  
 741 (2000). Partially carboxymethylated feather keratins. 1. Properties in 800  
 742 aqueous systems. *Journal of Agricultural and Food Chemistry*, 48(9), 801  
 743 4326–4334. 802
- Silva, L. A. D., Macedo, A. J., & Termignoni, C. (2014). Production of 803  
 keratinase by *Bacillus subtilis* S14. *Annals of Microbiology*, 64(4), 804  
 1725–1733. 805
- Smith, R. A., Blanchard, C. R., & Lankford, J. Jr. (1994). Nonantigenic 806  
 keratinous protein material. *U.S. Patent No. 5,358,935*. Washington, 807  
 DC: U.S. Patent and Trademark Office. 808
- Song, N. B., Lee, J. H., Al Mijan, M., & Song, K. B. (2014). Development 809  
 of a chicken feather protein film containing clove oil and its applica- 810  
 tion in smoked salmon packaging. *LWT-Food Science and Technology*, 811  
 57(2), 453–460. 812
- Suetsuna, K., Ukeda, H., & Ochi, H. (2000). Isolation and characterization 813  
 of free radical scavenging activities peptides derived from casein. *The 814*  
*Journal of Nutritional Biochemistry*, 11(3), 128–131. 815
- Sundaram, M., Legadevi, R., Banu, N. A., Gayathri, V., & Palanisamy, A. 816  
 (2015). A study on anti bacterial activity of keratin nanoparticles 817  
 from chicken feather waste against *Staphylococcus aureus* (Bovine 818  
 mastitis bacteria) and its anti oxidant activity. *European Journal of 819*  
*Biotechnology and Bioscience*, 6, 1–5. 820
- Syed, D. G., Lee, J. C., Li, W. J., Kim, C. J., & Agasar, D. (2009). Produc- 821  
 tion, characterization and application of keratinase from *Streptomyces 822*  
*gulbargensis*. *Bioresource Technology*, 100(5), 1868–1871. 823
- Tanabe, T., Okitsu, N., & Yamauchi, K. (2004). Fabrication and characteri- 824  
 zation of chemically crosslinked keratin films. *Materials Science and 825*  
*Engineering: C*, 24(3), 441–446. 826
- Tonin, C., Aluigi, A., Vineis, C., Varesano, A., Montarsolo, A., & Ferrero, F. 827  
 (2007). Thermal and structural characterization of poly (ethylene- 828  
 oxide)/keratin blend films. *Journal of Thermal Analysis and Calorimetry*, 829  
 89(2), 601–608. 830
- Torchinsky, Y. M. (1981). *Sulfur in proteins*. Oxford: Pergamon Press. 831
- Tsuge, N., Eikawa, Y., Nomura, Y., Yamamoto, M., & Sugisawa, K. (1991). 832  
 Antioxidative activity of peptides prepared by enzymatic hydrolysis 833  
 of egg-white albumin. *Nippon Nogeikagaku Kuishi*, 65(11), 1635–1641. 834
- Tung, W. S., & Daoud, W. A. (2009). Photocatalytic self-cleaning keratins: 835  
 A feasibility study. *Acta Biomaterialia*, 5(1), 50–56. 836
- Vasconcelos, A., Freddi, G., & Cavaco-Paulo, A. (2008). Biodegradable 837  
 materials based on silk fibroin and keratin. *Biomacromolecules*, 9(4), 838  
 1299–1305. 839
- Vermelho, A. B., Villa, A. L. V., De Almeida, A. M. M., de Souza Dias, E. 840  
 P., & Dos Santos, E. P. (2008). Keratin hydrolysates, process for their 841  
 production and cosmetic composition containing the same. *U.S. 842*  
*Patent Application No. 12/666,409*. 843
- Veselá, M., & Friedrich, J. (2009). Amino acid and soluble protein cocktail 844  
 from waste keratin hydrolysed by a fungal keratinase of *Paecilomyces 845*  
*marquandii*. *Biotechnology and Bioprocess Engineering*, 14(1), 84–90. 846
- Wan, M. Y., Dong, G., Yang, B. Q., & Feng, H. (2016). Identification and 847  
 characterization of a novel antioxidant peptide from feather keratin 848  
 hydrolysate. *Biotechnology Letters*, 38(4), 643–649. 849
- Wang, B., Yang, W., McKittrick, J., & Meyers, M. A. (2016). Keratin: 850  
 Structure, mechanical properties, occurrence in biological organisms, 851  
 and efforts at bioinspiration. *Progress in Materials Science*, 76, 852  
 229–318. 853
- Wawrzkiwicz, K., Lobarzewski, J., & Wolski, T. (1987). Intracellular kera- 854  
 tinase of *Trichophyton gallinae*. *Journal of Medical and Veterinary 855*  
*Mycology: Bi-Monthly Publication of the International Society for Human 856*  
*and Animal Mycology*, 25(4), 261–268. 857
- Williams, C. M., & Shih, J. C. H. (1989). Enumeration of some microbial 858  
 groups in termophilic poultry waste digestors and enrichment of a 859  
 feather-degrading culture. *Journal of Applied Bacteriology*, 67(1), 25–35. 860
- Wolski, T. (1979). Urea granulates obtained from feathers for use in 861  
 feeds. *Food Industry*, 33, 302–303. 862

- 804 Wolski, T. (1985). *Modified keratin proteins, their physicochemical proper-*  
805 *ties, analysis and application* (DSc Dissertation). Medical Academy,  
806 Lublin, Poland.
- 807 Wrześniewska-Tosik, K., Zajchowski, S., Ryszkowska, J., Tomaszewska,  
808 J., Mirowski, J., & Szota, K. (2015). Influence of preparation  
809 method of keratin fibers from poultry feathers on the properties of  
810 composites from recycled high density polyethylene. *Polimery*, 60(2),  
AQ6 811 109–117.
- 812 Yamamura, S., Morita, Y., Hasan, Q., Yokoyama, K., & Tamiya, E. (2002).  
813 Keratin degradation: A cooperative action of two enzymes from  
814 *Stenotrophomonas* sp. *Biochemical and Biophysical Research Communi-*  
815 *cations*, 294(5), 1138–1143.
- 816 Yamauchi, K., Yamauchi, A., Kusunoki, T., Kohda, A., & Konishi, Y. (1996).  
817 Preparation of stable aqueous solution of keratins, and physiochemi-  
818 cal and biodegradational properties of films. *Journal of Biomedical*  
819 *Materials Research Part Research*, 31(4), 439–444.
- 820 Yang, X., Zhang, H., Yuan, X., & Cui, S. (2009). Wool keratin: A novel  
821 building block for layer-by-layer self-assembly. *Journal of Colloid and*  
822 *Interface Science*, 336(2), 756–760.
- 823 Yin, X. C., Li, F. Y., He, Y. F., Wang, Y., & Wang, R. M. (2013). Study on  
824 effective extraction of chicken feather keratins and their films for  
825 controlling drug release. *Biomaterials Science*, 1(5), 528–536.
- Zabashta, Y. F., Kasprova, A. V., Senchurov, S. P., & Grabovskii, Y. E. 826  
(2012). The location of the thioglycolic acid molecules in intrafibrillar 827  
unordered areas of the human hair keratin structure. *International* 828  
*Journal of Cosmetic Science*, 34(3), 223–225. 829
- Zeng, W. C., Zhang, W. C., Zhang, W. H., & Shi, B. (2013). Antioxidant 830  
activity and characterization of bioactive polypeptides from bovine 831  
hair. *Reactive and Functional Polymers*, 73(3), 573–578. 832
- Zhang, J., Li, Y., Li, J., Zhao, Z., Liu, X., Li, Z., . . . Chen, A. (2013). Isolation 833  
and characterization of biofunctional keratin particles extracted from 834  
wool wastes. *Powder Technology*, 246, 356–362. 835
- Zhang, Q. X., Wu, H., Ling, Y. F., & Lu, R. R. (2013). Isolation and identifi- 836  
cation of antioxidant peptides derived from whey protein enzymatic 837  
hydrolysate by consecutive chromatography and Q-TOF MS. *Journal* 838  
*of Dairy Research*, 80(3), 367–373. 839

**How to cite this article:** Sinkiewicz I, Staroszczyk H, Śliwińska 841  
A. Solubilization of keratins and functional properties of their 842  
isolates and hydrolysates. *J Food Biochem.* 2017;e12494. 843  
<https://doi.org/10.1111/jfbc.12494> 844

AQ1

845

WILEY  
Author Proof

