

1 **Asphalt concrete subjected to long-time loading at low temperatures –**
2 **deviations from the time-temperature superposition principle**

3 Mariusz Jaczewski, Jozef Judycki, Piotr Jaskuła

4 *Highway and Transportation Engineering Department, Faculty of Civil and*
5 *Environmental Engineering, Gdansk University of Technology, Gdansk, Poland*

6 Gdansk University of Technology, Faculty of Civil and Environmental Engineering

7 Narutowicza Street 11/12

8 Gdansk, PL 80-233

9 tel.:+48 58 347 27 82

10 e-mail: mariusz.jaczewski@pg.edu.pl

11 **Abstract**

12 The article presents the observed deviations from the time-temperature
13 superposition principle of asphalt concretes, tested in the bending beam creep test at low
14 temperatures for a long time of loading. In almost all tested asphalt concretes,
15 deviations appeared after 500 seconds of loading at the temperature of -10°C . Some
16 types of bitumen presented deviations at other temperatures – usually the harder the
17 grade of the bitumen, the higher was the temperature of appearance of deviation. The
18 article investigates also the impact of the following factors on the described deviations:
19 type of bitumen, assumed time of loading and level of loading.

20 **Keywords:** low-temperature properties; master curve; viscoelasticity; creep;
21 deviations from time-temperature superposition principle

22 **1. Introduction**

23 1.1. Background

24 The time-temperature superposition and thermo-rheological simplicity principles
25 belong to the basic assumptions in the linear viscoelastic analysis of bitumen and
26 asphalt mixtures. Since the first applications of these principles for polymers [1] and,
27 later, bitumen and asphalt mixtures in the 1960s [2], they have been commonly used [3].
28 The concept of a single curve to describe the behaviour of the tested material for the
29 whole temperature and time range is very useful. In most cases, especially normalised
30 test procedures, bitumen and asphalt mixtures comply with the aforementioned
31 principles. However, in some cases both bitumen and asphalt mixtures show results
32 different than predicted on the basis of the time-temperature superposition principle. A
33 few different types of deviations from these principles are known and described in the
34 literature.

35 In the case of bitumen, deviations from one straight curve may be visible,
36 especially in the case of bitumen modification with different kinds of polymers [4–11]
37 or as a results of ageing of the bitumen [12]. These deviations are especially apparent in
38 the black diagram as separate lines for different temperatures. Some researchers even
39 describe this kind of behaviour, where it is possible to create one unique curve for
40 stiffness modulus, but not in the case of phase angle, as “partial time-temperature
41 superposition principle” [11,13]. Deviations from the thermo-rheological simplicity
42 were also reported by [14]. Stiffness moduli of the tested bitumen predicted in the
43 research were slightly higher than those obtained directly from the laboratory tests.

44 In the case of bitumen-filler mastics and asphalt mixtures it is generally accepted
45 that materials comply with the time-temperature superposition principle and thermo-



46 rheological simplicity. Deviations from those principles are not commonly described.
47 Nevertheless, some researchers [15–20] reported behaviour which was not completely
48 consistent with the commonly accepted rheological models. Laboratory tests described
49 in the mentioned studies were conducted at moderate or elevated temperatures.

50 The authors of this paper observed that for long times of loading at low
51 temperatures asphalt concretes exhibited evident deviations from thermo-rheological
52 simplicity. In the creep test conducted on beam specimens, tested asphalt concretes
53 behaved similarly to solid elastic materials – their creep under constant load either
54 stopped or strongly decreased. The value of stiffness modulus in some tested cases for a
55 long loading time was almost constant and it seemed to be independent of the time of
56 loading. The probable explanation of this case was that the time of loading was still too
57 short. For long loading times, when the value of stiffness modulus is almost
58 independent from the time of loading, the validity of the time-temperature superposition
59 principle is doubtful. While the experimental results obtained at the three tested
60 temperatures can be shifted and the first parts of the stiffness curves (until around 500
61 seconds) comply completely with the time-temperature superposition principle, the
62 values obtained for longer times will not coincide with the rest of the results. They will
63 usually present either asymptotic behaviour (in the case of hard grade bitumen) or slope
64 different than the stiffness modulus master curve (in the case of softer bitumen). For
65 these longer times of loading, values determined from the constructed master curve will
66 be much lower than those obtained from the laboratory investigation. Moreover, the
67 deviation from the master curve increases with the increase in the time of loading [21–
68 23]. This kind of deviation can result in generating large errors in computational
69 analyses performed on the basis of master curve models, when long times of loading are
70 taken into consideration [24]. Interestingly, this kind of behaviour was not noted in the

71 long time creep tests conducted on asphalt concretes at higher temperatures [25], even
72 when laboratory tests were made in the range of strain which strongly exceeded the
73 assumed limit of linear behaviour.

74 1.2. Modelling of asphalt concrete


75 Literature presents numerous models used for description of behaviour of
76 asphalt concrete under static loading [26], such as series-parallel models, spectral
77 response functions, ladder models and mathematical models. In this analysis only the
78 two most commonly used types of models were taken into consideration: series-parallel
79 Burgers models and different mathematical models of master curves. In further studies
80 application of 2S2P1D [27] for description of test data is planned.

81 It was assumed that materials presented and analysed in this paper can be
82 modelled as linear-viscoelastic materials, i.e. relation between stress and strain is linear
83 and material properties are not dependent on the level of load used or deformation of the
84 tested specimen. Limit of application of linear viscoelasticity is given in the literature in
85 different approaches: [28–32] suggested that the limit of linear behaviour depends on
86 the applied stress, the test temperature and time of loading. On the other hand, [5,11,33]
87 gave the limiting values of strain up to which behaviour of bitumen and asphalt mixture
88 is assumed as linear. In the case of temperatures below 0°C, the tested asphalt mixture
89 specimens complied with both of the stated requirements. At the temperature of 0°C the
90 tested materials exceeded the limit given by Di Benedetto [11], but still presented the
91 steady flow stage, without any signs of tertiary flow or destruction of the test specimen.

92

93 1.2.1. Series-parallel Burgers model

94 The Burgers series-parallel model, which was used in this paper, is presented in
 95 Fig. 1. It comprises of 2 dashpots and 2 springs. It is a linear connection of two simple
 96 viscoelastic models: Maxwell model and Kelvin-Voight model. Despite its simplicity,
 97 recent research shows that it can be used in prediction of thermal stresses with very
 98 good reliability [24,34].

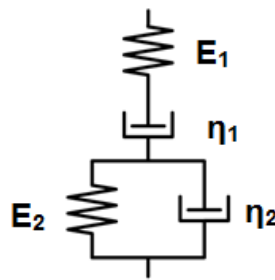

100
101 Fig. 1. The analysed series-parallel Burgers model.
102

103 The general stress-strain relationship of the model is given by the following
 104 differential equation [35]:

$$\left[\frac{d^2}{dt^2} \cdot \frac{\eta_1 \eta_2}{E_1 E_2} + \frac{d}{dt} \left(\frac{\eta_1}{E_1} + \frac{\eta_2}{E_2} + \frac{\eta_1}{E_2} \right) + 1 \right] \cdot \sigma(t) = \left[\frac{d^2}{dt^2} \frac{\eta_1 \eta_2}{E_2} + \frac{d}{dt} \eta_1 \right] \cdot \varepsilon(t) \quad (1)$$

106 where: E_1 – instantaneous modulus of elasticity, MPa, E_2 – modulus of retarded
 107 elasticity, MPa, η_1 – coefficient of viscosity of steady flow, MPa·s, η_2 – coefficient of
 108 viscosity of retarded flow, MPa·s, t – time of loading, s.

109 Solution of equation (1) for the case of constant load is given by equation (2).

$$\varepsilon(t) = \sigma_0 \left\{ \frac{1}{E_1} + \frac{t}{\eta_1} + \frac{1}{E_2} \left[1 - e^{\left(-t/\lambda_2\right)} \right] \right\} \quad (2)$$

111 where: σ_0 – constant load, MPa, $\lambda_2 = \text{retardation time } (\lambda_2 = \eta_2 / E_2), \text{ s.}$

112 1.2.2. Master curve mathematical models

113 Assuming that the material complies with the time-temperature superposition
114 principle and presents linear viscoelastic behaviour, the conception of master curve
115 enables creation of one line to describe the whole spectrum of temperatures and times of
116 loading. Master curve is created by shifting separate stiffness curves along the time axis.
117 The relationship between these curves is described by shift factor α_T . Master curve
118 mathematical models used for the description of asphalt concrete are mostly sigmoidal,
119 sinusoidal or polynomial functions, both symmetrical and nonsymmetrical [26,36].
120 Every function can be applied with slight modifications for both time and frequency
121 domains. All of the commonly used master curve functions are phenomenological
122 equations, which give the best fitting to the available laboratory test data. It is the main
123 reason why most of them are still subject to corrections and improvements.

124 Shift factor α_T , which describes relationships between separate stiffness curves
125 obtained for different temperatures, can be determined using two major approaches –
126 free shifting or using one of the equations, such as WLF [37][38], logarithmic
127 polynomial or Kaelble [38].

128 One of the most difficult issues in creation of master curves for asphalt concrete
129 is the upper stiffness modulus asymptote, due to complex behaviour of the material. In
130 case of bitumen, limiting value of stiffness modulus is constant and independent of the
131 used type of bitumen – it ranges from 3 to 6 MPa [4,39]. For asphalt mixtures, either
132 Witczak [40] or Hirsh [41,42] equations are usually taken into consideration for the
133 assumption of the maximum modulus. This approach uses basic asphalt mixture

134 properties and maximum value of bitumen stiffness for determination of the modulus.
 135 However, in the case of asphalt mixtures designed according to the Polish technical
 136 requirements, results obtained from laboratory tests very often exceeded those
 137 calculated from mathematical equations, probably due to the use of hard grade bitumen
 138 (usually 35/50 and even 20/30) in the mixture. In this study, results from laboratory
 139 tests (ITSM test) conducted at the temperature of -30°C were assumed as the maximum
 140 values of stiffness modulus.

141 Two different master curve equations were selected for the study. One of them
 142 was the CAM model [36,39,43,44], which was originally used for description of
 143 bitumen behaviour. Its basic function is given by equation (3).

$$144 \quad S(\xi) = S_{\text{glassy}} \left[1 + \left(\frac{\xi}{\lambda} \right)^{\beta} \right]^{\frac{\kappa}{\beta}} \quad (3)$$

145 where: S_{glassy} – glassy state modulus (maximum stiffness modulus), ξ –
 146 reduced time, β , λ , κ – fitting parameters.

147 Second model selected for the analysis was the Richards function described in
 148 [38]. It is a minor modification of the equation used for Simple Performance Test [45].
 149 Both functions differ by one parameter λ , which changes the equation into a
 150 nonsymmetrical function. In this study, instead of using Kaelble shift factor, free
 151 shifting was used to connect stiffness curves obtained at different temperatures.
 152 Richards model function modified for the purpose of this study is given by:

$$153 \quad \log |E^*| = \delta + \frac{\alpha - \delta}{\left[1 + \lambda e^{\beta + \gamma \log(t/t_1)} \right]^{\frac{1}{\lambda}}} \quad (4)$$

154 where: $|E^*|$ – complex stiffness modulus, psi/MPa, t – reduced time, δ – value of
155 the lower asymptote (minimum value of stiffness modulus; treated as a fitting
156 parameter), α – the value of the upper asymptote (determined from laboratory test
157 conducted at the temperature of -30°C), λ , β , γ – fitting parameters responsible for the
158 shape of the function.


159 In both cases, fitting parameters of the master curve equations were determined
160 using SOLVER package of MS Excel software. The target function was selected
161 according to the minimal value of the root mean square error.

162 **2. Outline of the deviations from thermo-rheological simplicity**

163 Figs. 2a, 2b and 2c present results typical of an asphalt mix whose behaviour is
164 inconsistent with the principle of time-temperature superposition. Fig. 2a shows the
165 creep curve of the mix which, after a long time of constant loading, reaches a constant
166 (or nearly constant) value of strain or exhibits very slow viscous flow. Such behaviour
167 is typical of “solid-type” materials and can be described with the Zener model. Most of
168 the tested asphalt concretes showed such behaviour at low temperatures equal to or less
169 than -10°C . Fig. 2b shows stiffness curves for such materials on a logarithmic scale. It
170 can be seen that after long loading time the stiffness of the mix reaches a constant value
171 for a given temperature T_1 or T_2 . After shifting along the time axis, the stiffness curves
172 at T_1 and T_2 only partly coincide at short time of loading and do not coincide for long
173 time of loading. Master curve obtained from the shifted stiffness curves is presented in
174 Fig. 2c. It does not present one smooth curve, but branches into several characteristic
175 “tails” for each testing temperature below or equal to -10°C . The described deviations
176 from the thermo-rheologically simple behaviour were observed by the authors in most
177 of the tested materials, regardless of the used mineral mixture or bitumen type. Some

178 exceptions were also observed. First, in the case of hard grade 20/30 neat bitumen,
 179 where the deviations appeared at the temperature of 0°C. Second, in the case of hard
 180 grade 20/30 multigrade bitumen, in which the deviations appeared only at the
 181 temperature of -20°C.

182

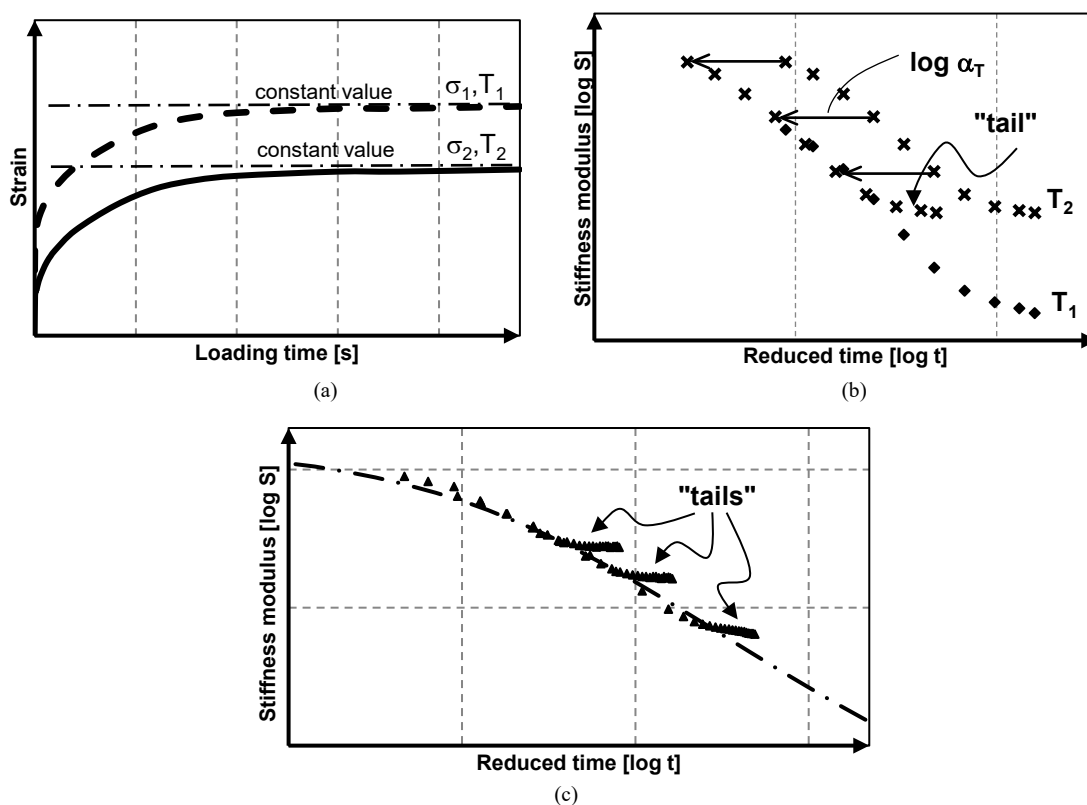

185
186
187
188

Fig. 2. The outline of the deviations from thermo-rheological simplicity: (a) creep curves, (b) stiffness moduli, (c) master curves of stiffness moduli, after [21].

189

3. Materials and methods

190

3.1. Materials and preparation

191

192

193

194

195

196

Two types of asphalt concretes were used for the purpose of this study – high modulus asphalt concrete (HMAC) used for the binder and base course with three types of bitumen (neat, polymer modified and multigrade) and, for the sake of comparison, a typical asphalt concrete (AC) used for the binder course. Finally, four different mixtures were evaluated (AC 16W 35/50; HMAC16 20/30; HMAC16 PMB 25/55-60; HMAC16 20/30 MG). All of the materials were designed in accordance with the Polish technical

197 requirements and appropriate EN standards. Gneiss aggregate, crushed sand and
 198 limestone filler were used for the production of the mixtures. No additives were added
 199 to the asphalt mixtures. Before the compaction of the test specimens, all asphalt
 200 mixtures were subjected to the procedure of short-term ageing (acc. to SHRP-007
 201 standard). Basic properties of the bitumen and asphalt mixtures used are presented in
 202 Tables 1 and 2 respectively. Properties presented in Table 2 were determined during the
 203 design of the asphalt mixture.

204 **Table 1.** Basic properties of the bitumen used

Property:	Type of bitumen			
	35/50	20/30	PMB 25/55-60	20/30 MG
	neat	neat	SBS-polymer modified	multigrade
Properties before TFOT ageing				
Penetration, 25°C, 0.1 mm, acc. to EN 1426	48	23	28	24
R&B temperature, °C acc. to EN 1427	53	58	62	68
Dynamic viscosity, Pa·s, acc. To EN 12596 at temp.:				
• 60°C	659.3	3063.0	not tested	not tested
• 90°C	15.9	48.5	66.6	137.0
• 135°C	0.6	1.3	1.6	2.0
• 160°C	not tested	0.4	0.5	0.5
Properties after TFOT ageing				
Penetration, 25°C, 0.1 mm, acc. to EN 1426,	45	21	26	24
R&B temperature, °C acc. to EN 1427	57	64	68	72

205
206

Table 2. Basic properties of the asphalt mixtures used

Property	Designation of the asphalt mixture			
	AC 16W 35/50	HMAC16 20/30	HMAC16 PMB 25/55-60	HMAC16 20/30 MG
Grading				
(passes # [mm], %)				
31.5	100	100	100	100
22.4	100	100	100	100
16	97.3	97.8	97.8	97.8
11.2	78.0	81.7	81.7	81.7
8	57.7	62.5	62.5	62.5
5	44.5	49.4	49.4	49.4
2	27.4	32.0	32.0	32.0
0.125	7.1	9.2	9.2	9.2
0.063	5.5	7.3	7.3	7.3
Binder content %, m/m	4.6	5.0	5.0	5.0
Air void content, acc. to EN 12697-8, %	4.3	3.6	3.5	3.5
VMA, %	15.2	15.5	15.4	15.4

VFA, %	71.8	76.9	77.3	77.3
Rutting Resistance, acc. to EN 12697-22, WTS _{Air}	0.10	0.10	0.07	0.04
PRD _{Air}	6.9	4.8	5.3	4.0

207

208

209

210

211

212

The tests were conducted on beam specimens (50 x 50 x 300 mm). Beam specimens were cut from asphalt mixture slabs (300 x 300 x 50 mm) compacted using a standard Cooper laboratory compactor. The target degree of compaction was determined in the range of 98-100% of Marshall specimen bulk density. Five specimens were cut from each compacted slab.

213

214

215

216

217

218

219

220

221

222

223

Preliminary flexural strength test for each test temperature (0°C, -10°C, -20°C) was performed on five beam specimens. The bending beam creep test for each test temperature (0°C, -10°C, -20°C) was performed on at least three specimens. Two remaining specimens from the slab were kept as a reserve for unpredictable situations (for example, if the test machine stopped due to an energy outage). For the entire planned experiment, at least six slabs of each mixture were needed (three for determination of flexural strength and three for bending beam creep test). Before the tests, specimens cut from all the six slabs of a given mixture were mixed and random five beams were chosen for specific test at each temperature. For each beam specimen, air void content was determined, in order to verify whether it was in the range of air void content determined on Marshall specimen.

224

3.2. Methods

225

226

227

228

229

To evaluate the long-time load stiffness modulus, the three point bending beam test (Fig. 3) was used [46,47]. The test was performed in a standard hydraulic press. The test consisted of two phases: in the first phase beams were subjected to constant static load for a time of 2400 seconds; in the second phase beams were left unloaded for a time of 1200 seconds. The applied load depended on the temperature at which the test


230 was conducted. Load values were assigned as about 30% of the flexural strength. In one
 231 case (HMAC 20/30), two additional levels of loads were tested. Applied values of load
 232 are presented in Table 3. Values of applied load vary for different mixtures, depending
 233 on flexural strength determined in laboratory test. For all beams the test temperatures
 234 were -20°C , -10°C and 0°C . All specimens were conditioned at the selected
 235 temperature for 24 hours before the test. The time of conditioning was strictly
 236 controlled to avoid the influence of physical hardening [48–52] on the values of test
 237 results. The strain at the bottom of the specimen was measured with an LVDT sensor.
 238 Coefficient of variation for the measured strain test results equalled up to 20% [46,47].

239 **Table 3.** Applied values of static load

Test temperature	Flexural strength [MPa]	Value of applied stress [MPa]	Value of applied load [kN]
0°C	4.17–7.21 (mean 5.80)	1.7–2.2	0.55–0.71
-10°C	5.49–7.85 (mean 6.65)	2.7	0.86
-20°C	6.02–7.82 (mean 6.75)	2.7	0.86

240

241

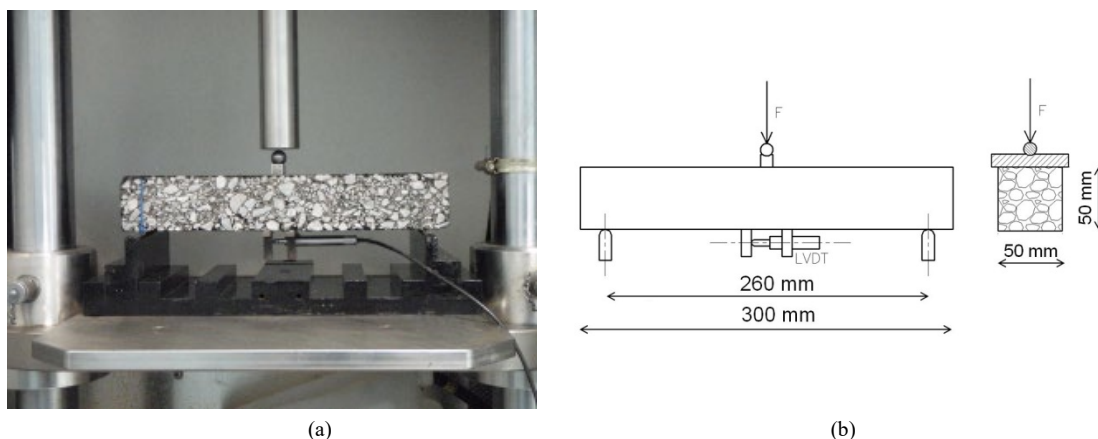

242

243

244

245

Fig. 3. Bending beam creep test of asphalt concrete: (a) the specimen before the test; (b) scheme of the specimen.


246

4. Results and discussion

247

4.1. Bending beam creep test results


248 Typical creep curves obtained from laboratory tests for the temperatures of 0°C,
 249 -10°C and -20°C are presented in Fig. 4. The results for each temperature are presented
 250 for a single specimen from the whole batch of a chosen mixture type. In this case,
 251 HMAC16 with 20/30 neat bitumen was used as an example. Apart from isolated results
 252 obtained at the temperature of 0°C, the strain values remained within the linear
 253 viscoelasticity limit given by Di Benedetto [11]. However, even in the case of the
 254 temperature of 0°C, when the limit was slightly exceeded, tested specimens showed
 255 steady flow, without any sign of tertiary flow or specimen destruction.

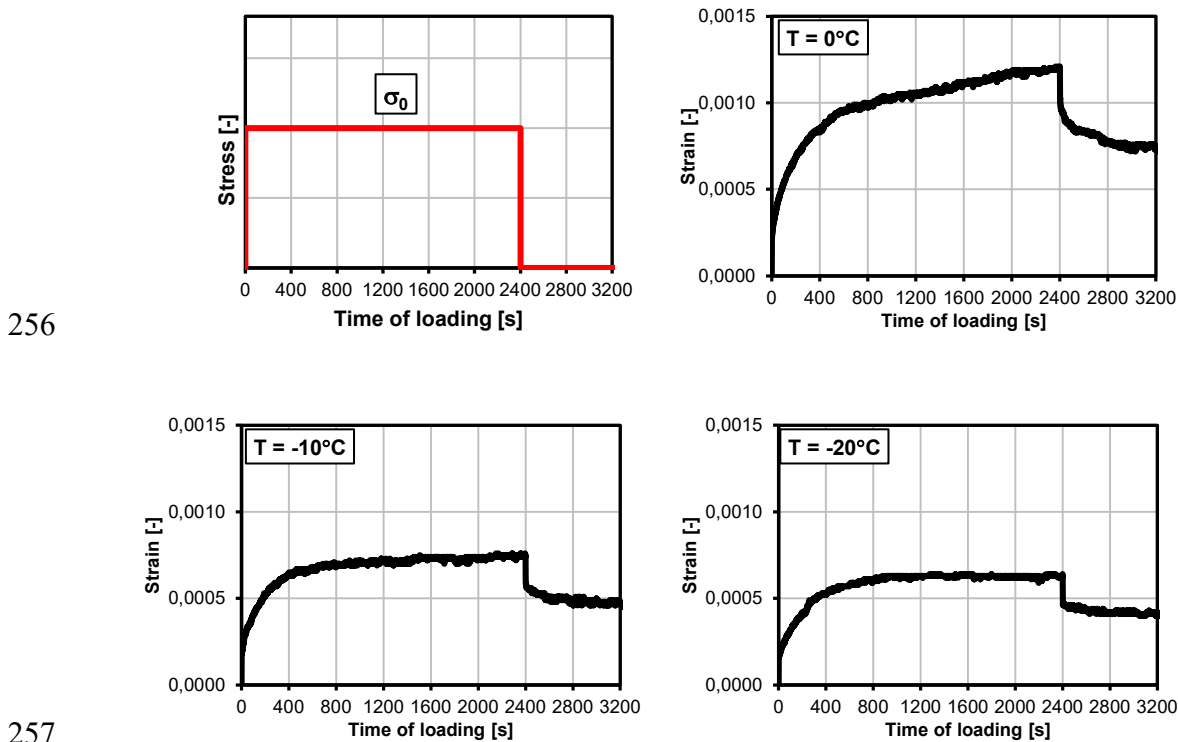

257
 258 **Fig. 4.** (a) Applied load; (b), (c), (d) typical creep curves obtained from bending beam creep test of
 259 asphalt concrete for the temperatures of 0°C, -10°C and -20°C.

260 Additionally, to confirm the assumption of linear viscoelasticity, one mixture –
 261 HMAC16 with 20/30 neat bitumen – was tested at the temperature of -20°C with three
 262 different levels of stress. The results for four selected time points (8, 60, 360 and 2400
 263 seconds) are presented in Fig. 5. Taking into consideration the variability of the test
 264 results (up to 20% [46,47]), all the results for specific time points, apart from selected


265 results for 8 seconds for the highest applied stress, present similar values of stiffness
 266 modulus regardless of the stress used.

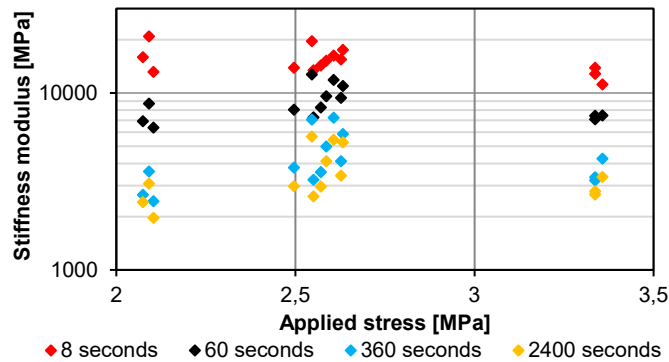

267

268 **Fig. 5.** Verification of the linear viscoelasticity of tested mixtures. Results for the mixture HMAC16
 269 with 20/30 neat bitumen, test temperature -20°C , three levels of applied load.

270 Fig. 6 presents results obtained at the temperature of -10°C for all the asphalt
 271 mixtures analysed in this paper.

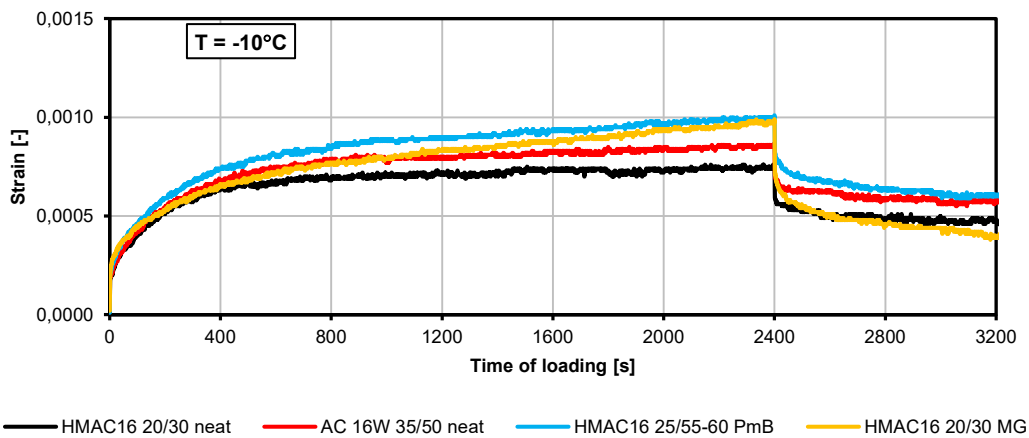

272

273 **Fig. 6.** Creep curves obtained from the bending beam creep test of asphalt concrete for the
 274 temperature of -10°C for all the tested mixtures.

275 As can be seen in Fig. 6, all the tested mixtures comply with Burgers rheological
 276 model, with all its phases: instant elastic strain and steady creep state for the loaded
 277 phase, and instant return and steady relaxation during the unloaded phase. All the tested
 278 mixtures present steady creep with time of loading. In the case of hard grade neat
 279 bitumen (20/30 neat bitumen, black line), it might seem that the steady flow stage of the


280 creep curve flattens and almost reaches horizontal asymptote. An elongated test, which
281 lasted 8 hours, showed that the specimen still creeps, but the rate of creep is very slow,
282 similar to the rate typical of elastic materials, such as cement concrete.

283 4.2. Modelling of asphalt concrete using laboratory test results

284 Test results obtained from the bending beam creep test were later described
285 using two groups of mathematical models: rheological series-parallel model and master
286 curve mathematical models using procedures developed at the Department of Highway
287 Engineering of the Gdansk University of Technology. In all cases the fitting was
288 performed on the basis of root mean square error criterion.

289 4.2.1. Modelling using rheological series-parallel model


290 Modelling using rheological model was based on the fitting of equation (2)
291 using root mean square error. Three of the four Burgers model parameters were treated
292 as fitting parameters: E_2 , η_1 and η_2 . In the case of the E_1 elastic modulus, it was
293 obtained from the unloaded phase of the creep curve, as seen in Fig. 7. E_1 elastic
294 modulus was calculated as $E_1 = \varepsilon_1 / \sigma_0$.

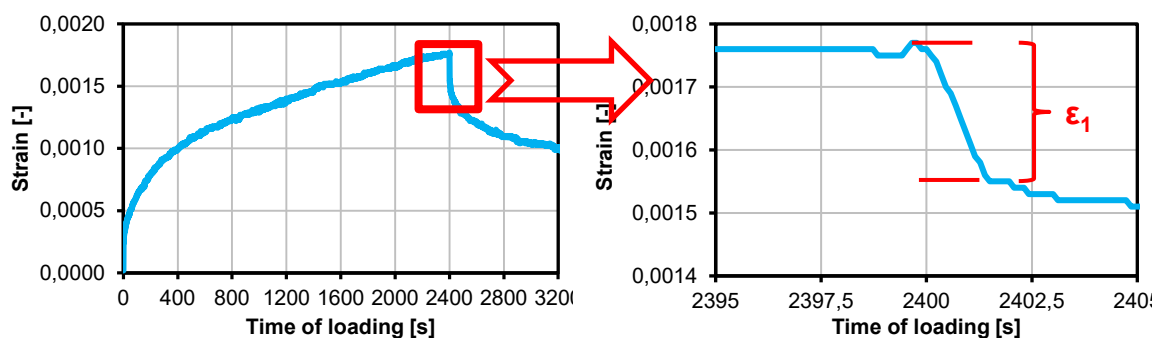

295 **Fig. 7.** Determination of the E_1 elastic modulus of Burgers model.

296 Such a way of calculation of the E_1 parameter resulted in higher homogeneity of
297 the obtained results and eliminated random deviations coming from the factors

298 associated with the loading phase (especially from the fitting of steel beam used for
 299 centring of the load on the specimen). Fitting of the test results for different
 300 temperatures using described methodology is presented in Fig. 8. The determined
 301 parameters of Burgers model for all the tested asphalt mixtures are presented in Table 4.
 302

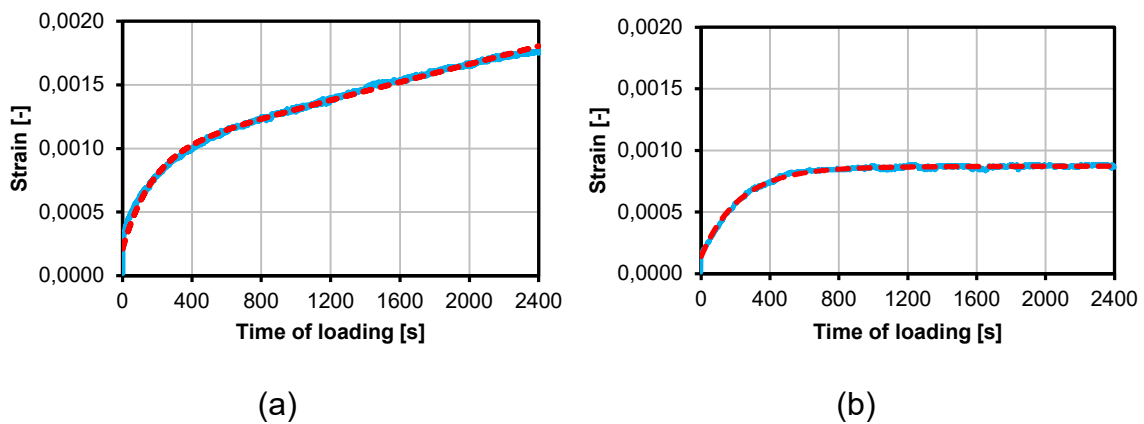

303 **Fig. 8.** Fitting of the creep curves using Burgers model: (a) temperature of 0°C, (b) temperature of
 304 -20°C (continuous line – experimental results, dashed line – fitting using Burgers model).
 305

306 **Table 4.** Burgers model parameters for all the tested mixtures

Asphalt mixture	Temperature °C	Burgers model rheological parameters			
		E ₁ MPa	E ₂ MPa	η ₁ MPa·s	η ₂ MPa·s
HMAC16 20/30	0	11 666	1 811	19 303 852	327 299
	-10	16 338	4 437	128 667 390	1 000 705
	-20	20 243	7 950	261 050 362	1 801 012
HMAC16 PMB 25/55-60	0	8 107	1 989	4 512 138	434 479
	-10	13 417	4 017	32 637 170	798 762
	-20	17 514	4 331	98 703 764	890 505
HMAC16 20/30 MG	0	4 966	2 423	3 201 052	444 497
	-10	7 048	5 520	8 699 462	1 097 785
	-20	14 328	7 138	194 646 646	1 850 407
AC 16W 35/50	0	7 891	1 469	5 646 589	325 605
	-10	15 609	3 901	55 355 791	783 953
	-20	17 241	4 761	91 268 648	933 607

307 As can be seen in Fig. 6, the obtained creep curves are consistent with the
 308 Burgers rheological model and the obtained values are similar to those observed in other
 309 creep tests conducted for asphalt mixtures [46,53,54]. Nevertheless, some discrepancies
 310 are visible in comparison to the parameters obtained from cyclic tests, such as Simple
 311 Performance Tester. While both elastic moduli are quite similar, the biggest
 312 discrepancies are visible in the case of the η₁ parameter – coefficient of viscosity of


313 steady flow. Results determined from cyclic tests [55–57] differ up to three orders of
314 magnitude from the results obtained from creep tests. The reason for this discrepancy is
315 still under research. Nevertheless, Burgers model parameters determined in this study
316 were recently successfully used for calculation of thermal stresses in [24].

317 4.2.2. Modelling using master curves

318 Master curves were determined using the authors' modifications of the
319 procedures used for Bending Beam Rheometer (BBR) and its later variant for testing of
320 asphalt concrete [58–61]. In comparison to the aforementioned studies, the time of
321 loading was extended to 2400 seconds, instead of typical 1000 seconds. Master curves
322 were obtained on the basis of free shift of specific stiffness curves determined for the
323 temperatures of 0°C, –10°C
324 and –20°C. The temperature of 0°C was selected as the reference temperature. Each
325 stiffness curve is the mean value of 3 different stiffness curves obtained from each
326 tested specimen for a selected temperature. Each obtained master curve was later
327 described using CAM and Richards models, under assumption that results comply with
328 the thermo-rheological simplicity principle. During construction of the master curve, the
329 observed deviations were not taken into consideration so as not to influence the shifting,
330 and data points only up to 500 seconds were utilized. Master curves were constructed on
331 the basis of results directly from the creep test, but also, separately, from the results
332 back-calculated from rheological model parameters. The developed master curves,
333 obtained from both direct and back-calculated results, along with mathematical
334 description using CAM and modified Richards equations are presented in Fig. 9.

335



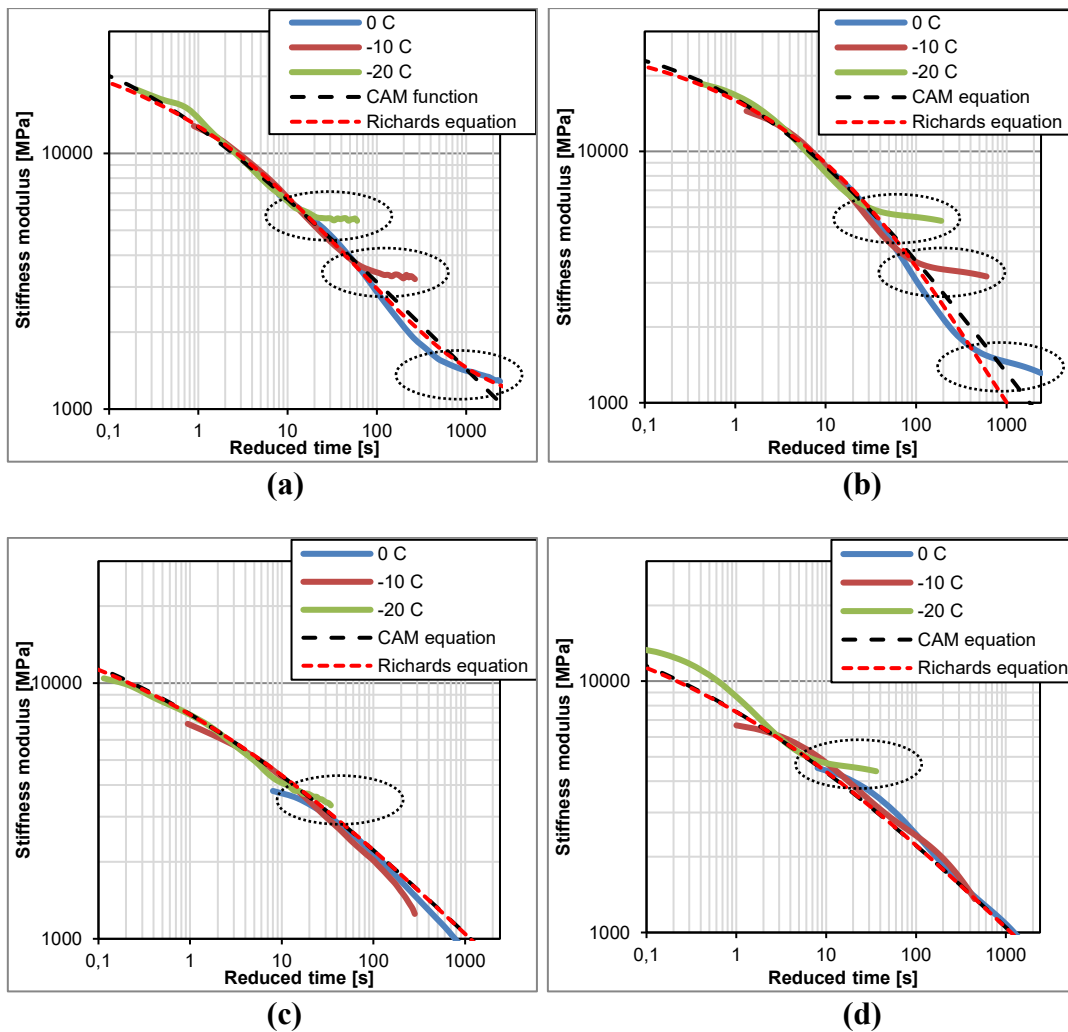

336
337
338

339
340
341
342
343

Fig. 9. Shifted stiffness curves (free shifting): (a), (c) direct results from the bending beam creep test; (b), (d) results back-calculated from the Burgers model. Deviations from the master curves are highlighted with ovals. Mixtures used: (a), (b) HMAC 20/30; (c), (d) HMAC 20/30 MG.

344

345

346

347

348

349

350

351

352

As can be seen in Fig. 9, for both types of data (directly from the creep test and back-calculated from the Burgers model) master curves obtained after free shifting are very similar. Nevertheless, in all cases, there are visible deviations from one continuous curve. In Fig. 9, two extreme cases are presented. In case of HMAC with 20/30 neat bitumen (Figs. 9a, 9b), horizontal deviation is visible at all the tested temperatures (from 0°C down to -20°C). In the case of HMAC with 20/30 MG, the horizontal deviation appeared only at the temperature of -20°C. In other tested cases – conventional AC and HMAC with polymer modified bitumen – the horizontal deviation appeared at the temperature of -10°C and lower.

353 Parameters of master curves (CAM and Richards models) of all the tested
 354 materials are presented in Table 5.

355 **Table 5.** Master curve model parameters for all the tested mixtures

Asphalt mixture	Parameters of model				
	CAM model				
	E_{max} [MPa]	λ	β	κ	
HMAC 20/30	29 723	0.168	0.506	0.348	
HMAC 25/55-60	27 018	0.203	0.587	0.360	
HMAC 20/30 MG	22 799	0.399	0.283	0.376	
AC 16W 35/50	29 885	0.044	0.857	0.332	
	Richards model				
	Max	$\delta^a)$	λ	β	γ
HMAC 20/30	4.473	3.027	0.001	-9.095	-0.696
HMAC 25/55-60	4.431	0.000	5.934	-0.443	-0.826
HMAC 20/30 MG	4.358	0.038	3.760	-0.582	-0.564
AC 16W 35/50	4.475	0.000	8.726	0.463	-0.980

356 Remarks: a) δ parameter is responsible for the lower asymptote of the master curve. As can be seen
 357 from the values presented in tables, for a very long time of loading the stiffness modulus will be
 358 approaching the value of 0 MPa. While in the case of beam specimens subjected to bending this kind of
 359 situation is possible (it would be equivalent to the destruction of the specimen), from the physical point
 360 of view it is an impossibility. Therefore, values presented in the table are in this case treated as fitting
 361 parameters for the best description of the model at temperatures below 0°C and not as a physically
 362 sound general description of material's behaviour across the full spectrum of times and temperatures.

363 4.3. Discussion of test results


364 As can be seen in Fig. 8, both models gave very similar results, with similar
 365 fitting quality. Nevertheless, there are two main visible differences:

- 366 • in the case of very short reduced times, Richards model gives values lower than
 367 those obtained from the laboratory test;
- 368 • in the case of HMAC with 20/30 neat bitumen, CAM model (in contrast to
 369 Richards model), does not give any opportunity to describe the deviation from
 370 the straight section of the master curve line, as visible near the 1000s reduced
 371 time.

372 In one case it was also observed that for very long reduced times CAM model
 373 gave values higher than those obtained from laboratory tests. Regardless of the used
 374 model, for temperatures lower than 0°C and long times of loading, values obtained from

375 the models are much lower than values determined from laboratory test. This situation
 376 is presented in Figs. 10b and 10d.

377

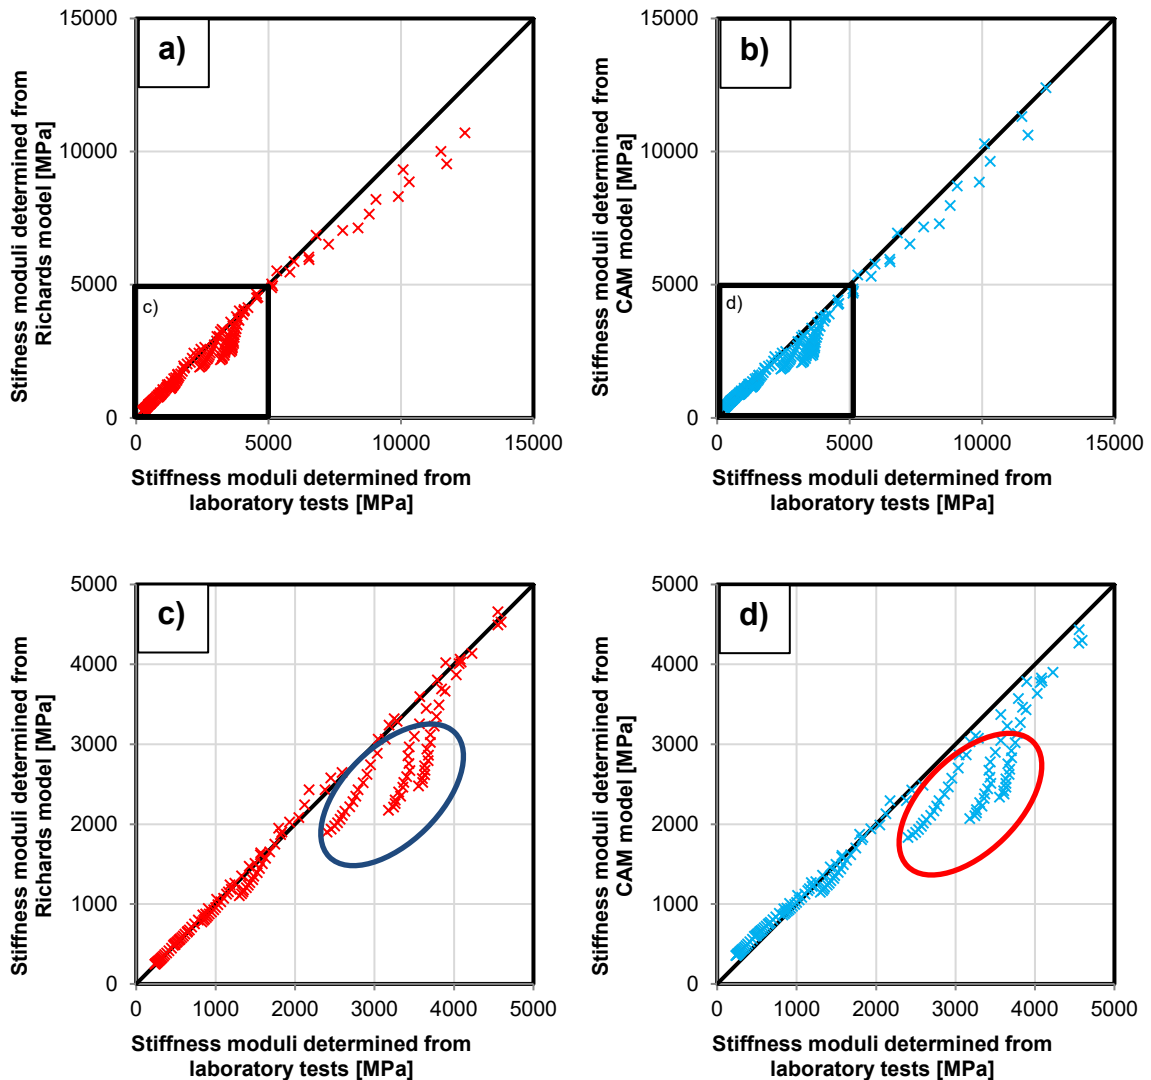

378 Remark: in figures c) and d) values obtained from both master curve models that were lower in
 379 comparison to laboratory test data are highlighted with an oval

380
 381
 382

Fig. 10. The correctness of the modelling of laboratory test data (HMAC 20/30) using two master curve models: a), c) Richards model; b), d) CAM model.

383 Both of the used master curve models gave similar and very good fitting of the
 384 test data, but only in the case of assumption that tested materials are thermo-
 385 rheologically simple and comply with time-temperature superposition, and time of
 386 loading used for determination of the master curve was reduced to 1000 seconds. This
 387 kind of assumption will give correct results when short-time load phenomena are


388 modelled. In the case of long-time load phenomena, such as development of thermal
389 stresses in asphalt pavements, values determined from the master curve will be much
390 lower and will have strong impact on computational analyses. For example, thermal
391 stresses calculated using that kind of data will present much lower values than those
392 measured in the field or in the laboratory.

393 Authors tried to determine the main aspect which influences the appearance of
394 the described deviations from the models used. At this stage of the research, influence
395 of the assumed time of loading, type of bitumen and asphalt mixture composition were
396 taken into consideration.


397 4.3.1. The impact of the assumed time of loading on modelling of asphalt concrete

398 As stated above, deviations from the models used appear at temperatures below
399 0°C, when the time of loading is long, usually after around 500 seconds of loading. On
400 the other hand, typical laboratory creep test methods assume the maximum time of
401 loading in the range from 100 to 1000 seconds [58,62,63]. As shown in Fig. 11, even
402 when the time of loading is assumed as 1000 seconds, the deviations do not have strong
403 impact on development of the master curve. The problem intensifies when the time of
404 loading increases above 1000 seconds. The longer the time of loading, the more
405 noticeable the deviations that appear. This fact is very important when master curve
406 mathematical models are used for calculation of low temperature processes, such as
407 thermal stresses induced in real pavements, where very long times of loading are
408 needed, sometimes exceeding 10000 seconds. In such a case, shifted stiffness curves
409 would be branching into multiple separate curves.


410

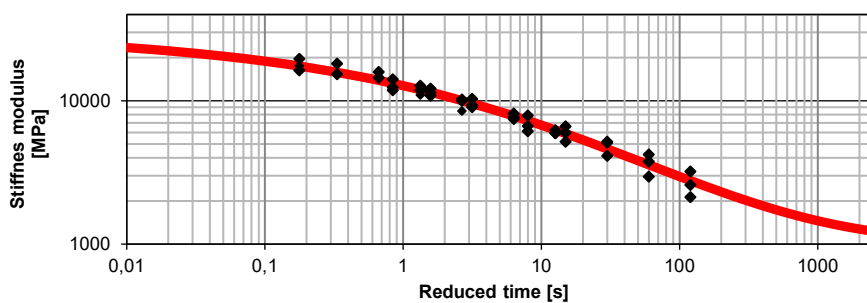

(a)

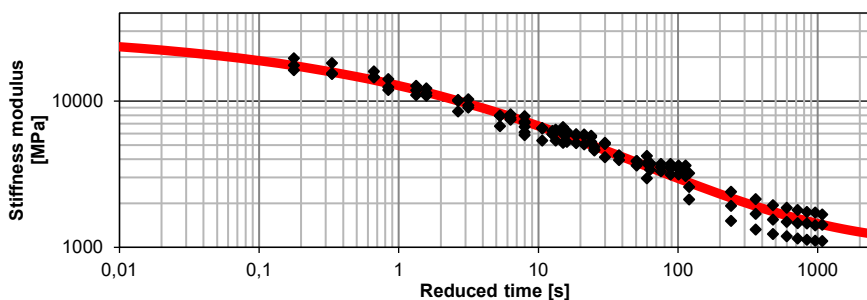

(b)

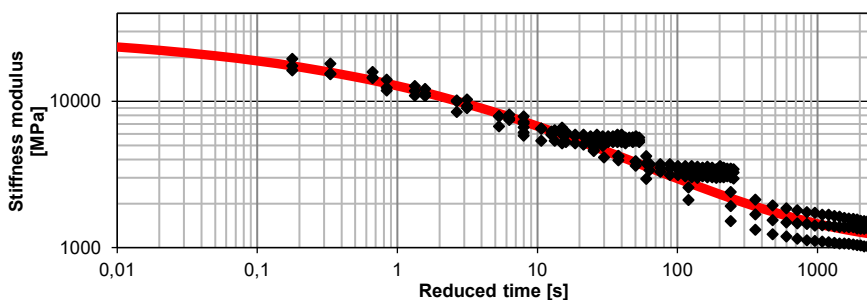

(c)

411 **Fig. 11.** The influence of time of loading on modelling of the master curve: a) 100 seconds; b) 1000
412 seconds; c) 2400 seconds.

413 In the case of temperatures higher than 0°C, deviations from the models used
414 were not observed, even for times of loading equal to 2400 seconds. At lower
415 temperatures, the appearance of deviation is strongly connected to the assumed time of
416 loading. In the case of 100 seconds or even 1000 seconds, after appropriate shifting,
417 deviations do not influence the creation of master curve. “Branching problem” appears
418 after around 500 seconds of loading and its impact is strongly visible after 1000 seconds

419 of loading. The type of bitumen or type of asphalt mixture did not have strong impact
420 on the time when the “branching” of the master curve occurred.


421 4.3.2. Determination of the limit of the time-temperature superposition principle

422 To determine the time limit of application of the time-temperature superposition
423 principle in analysis of creep test data, each of the stiffness curves was described using
424 two logarithmic functions (see Fig. 12):

- 425 • Second order curve – for the time range from 0 to around 500 seconds, (based
426 on an assumption that within this range the stiffness curve is mostly consistent
427 with the time-temperature superposition principle); this part of the curve
428 overlaps with the developed master curve for the analysed asphalt mixture.
- 429 • First order curve – for the time range in which the stiffness curve does not
430 comply with the time-temperature superposition principle. In most cases this
431 part of the curve approaches the horizontal asymptote.

432 The intersection of the two aforementioned logarithmic curves was assumed to
433 be the time limit of the time-temperature superposition principle. Determined times
434 (rounded up to full 20 seconds) of all the tested materials are presented in Table 6.

435

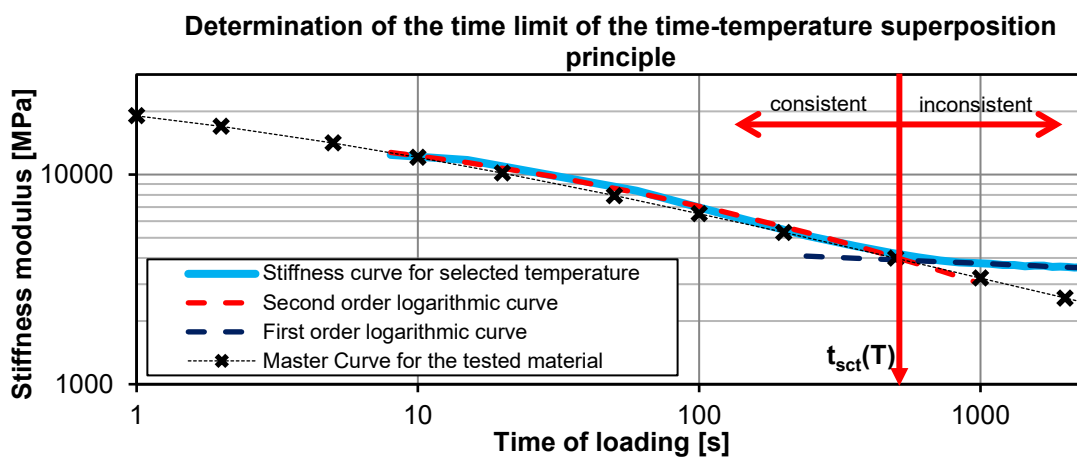

436
437

Fig. 12. Method used for determination of the limit of the time-temperature superposition principle

438
439
440

Table 6. The determined limit loading times in which tested materials comply with the time-temperature superposition principle

Temperature [°C]	HMAC 20/30	HMAC 25/55-60	HMAC 20/30 MG	AC 16W 35/50	AC 16W 50/70
-20	520	520	580	460	500
-10	600	440	- ^{a)}	580	460
0	420	- ^{a)}	- ^{a)}	- ^{a)}	- ^{a)}

441
442

a) tested specimens did not show deviation from the time-temperature superposition principle up to 2400 seconds

443

444

445

446

447

Time limit up to which test results were consistent with the time-temperature superposition principle at the temperature of -10°C and lower lies within the range from 400 to 600 seconds. In the described cases, master curve model covered only around 20-25% of the whole time range of the test, which is not enough for proper material description in terms of low temperature impact on asphalt mixtures.

448

4.3.3. The impact of type of asphalt mixture and bitumen used in asphalt concrete

449

450

451

452

453

454

Apart from the research presented in this paper, similar bending beam creep tests were conducted under other research projects carried out at the Gdansk University of Technology. Regardless of the used type of test machine or asphalt mixture [47,64] – asphalt concrete, high modulus asphalt concrete, stone matrix asphalt, porous asphalt – in all the tested cases at temperatures lower than 0°C deviations appeared after a time of loading longer than approx. 500 seconds.

455

456

457

458

459


460

461

It was noted that the particular type and grade of bitumen used in the asphalt mixture had a relatively strong impact on the moment of appearance of the deviations. In most cases, the first deviations appeared at the temperature of -10°C , regardless if neat or polymer modified bitumen was used. Some discrepancies were observed for two types of hard grade bitumen. First, in the case of neat hard grade 20/30 bitumen, the deviation appeared at the temperature of 0°C . This type of bitumen is characterized by a relatively high viscosity even at higher temperatures, which probably resulted in faster

462 “stiffening” of the tested asphalt mixtures. Second case was the hard grade multigrade
 463 bitumen. In this instance, the deviation appeared much later, at the temperature of
 464 -20°C . The latter phenomenon, however, cannot be explained by the values of
 465 viscosity, as the results are similar to the values obtained for a typical polymer-modified
 466 bitumen. A probable explanation is that the viscoelastic temperature range of this type
 467 of bitumen is wider, and its behaviour is close to viscoelastic even at the temperature
 468 near 0°C . All cases are presented in Fig. 13.

469
 470
 471

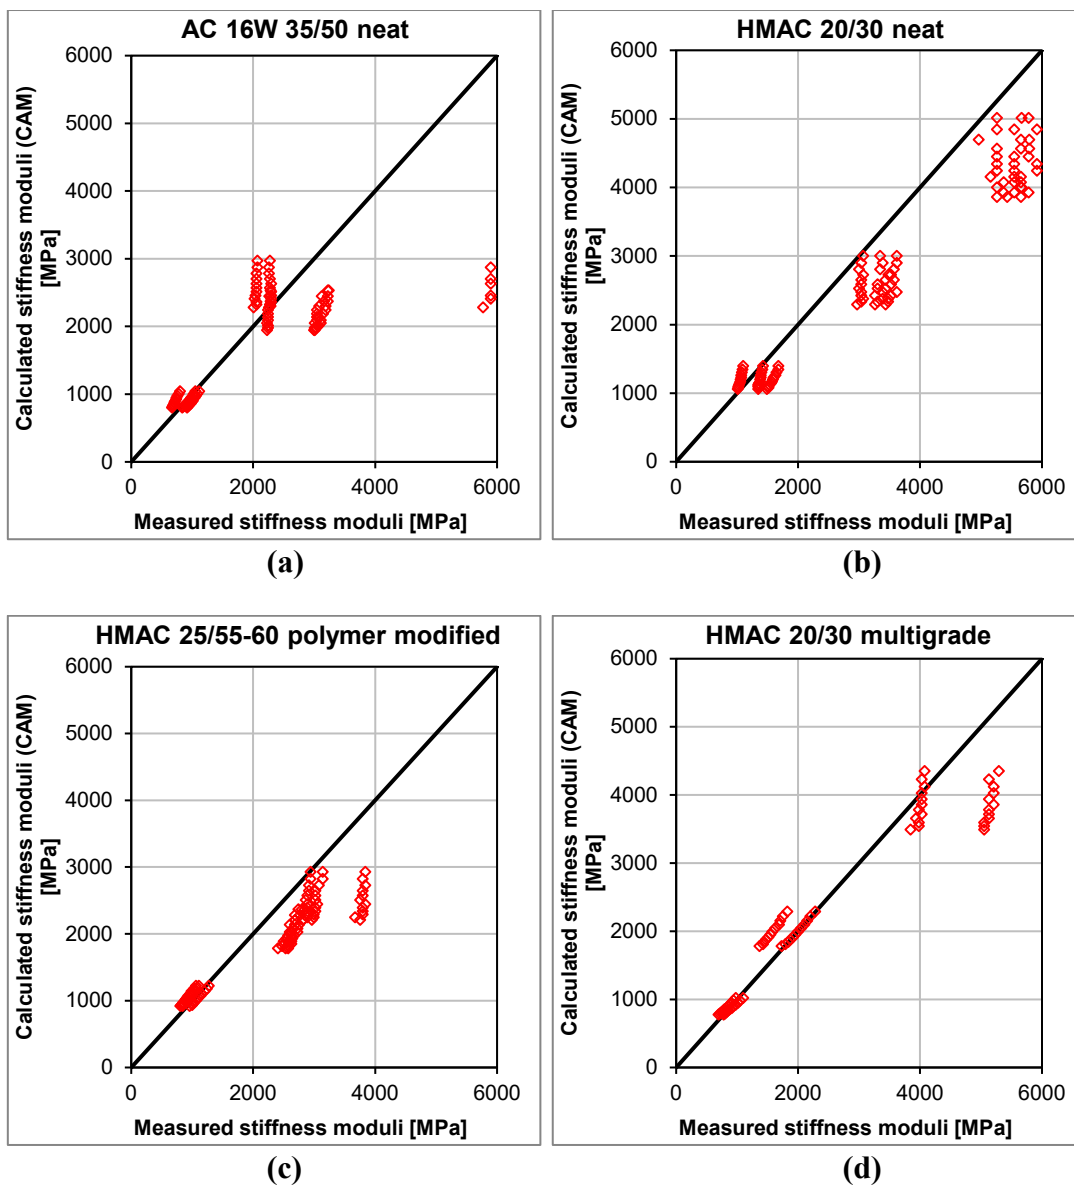


472
 473
 474
 475
 476
 477

Fig. 13. Differences between calculated and measured stiffness moduli for times of loading longer than 1000 seconds: (a) AC 16W 35/50 neat bitumen, (b) HMAC 20/30 neat bitumen, (c) HMAC 25/55-60 polymer modified bitumen, (d) HMAC 20/30 multigrade bitumen.

478 4.3.4. The impact of the level of static loading

479 In most cases the value of around 30% of flexural strength was used as the
480 constant stress that the specimen was subjected to. It was worthwhile to analyse whether
481 the applied stress was too small to induce viscous flow. Tests with higher static load (up
482 to 50% of flexural strength) were conducted to examine such possibility in additional
483 research. Results of these tests are presented in Fig. 14. Creep curves measured under
484 three static load levels (32%, 38% and 50% of flexural strength) show different limits of
485 strain at long time of loading. For each load level two to five specimens were used.
486 Limit of strain for static load of 50% of flexural strength is higher than for lower static
487 loads – 32% and 38% of flexural strength – but it also reaches constant value after time
488 of loading of about 600 to 1000 seconds. In the case of the two lower static load levels,
489 the results of the test overlap with each other. This preliminary study on one mixture at
490 one temperature showed that the time at which strain reaches constant limit depends on
491 the load level and increases with higher levels of static load. A detailed investigation on
492 different load levels at different temperatures is planned in further analyses.

493

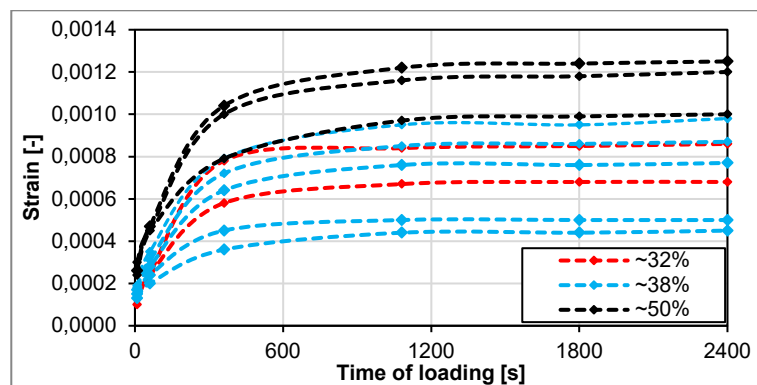

494
495
496

Fig. 14. Impact of different levels of static load on behaviour of asphalt mix at creep (creep curves for HMAC 20/30 neat bitumen at the temperature of -20°C), after [21] and supplemented.

497 **5. Conclusions and further studies**

498 The described deviations from the material models used can have strong impact
499 on computational analyses conducted on the basis of master curves. Values of stiffness
500 modulus determined from master curves for long times of loading are significantly
501 lowered in comparison to the real values determined from laboratory tests. For example,
502 in the case of calculation of thermal stresses, the calculated values can be significantly
503 lowered or even unacceptably underestimated if only the thermo-rheologically simple
504 part of master curve is taken into consideration. Based on the analysis, the following
505 conclusions can be made:

- 506 • Series-parallel rheological models described each of the tested materials
507 correctly at every tested temperature. Burgers model did not present any
508 problems during modelling of the test data. Correctness of the data was
509 confirmed in other studies [24].
- 510 • Neither of the master curve models described the tested materials correctly. The
511 deviations were visible in the case of long times of loading. Under assumption
512 of short time of loading, laboratory test data allowed to create master curves
513 without any problems.
- 514 • It was determined that the time-temperature superposition principle limit lied
515 within the range from 420 to 600 seconds.
- 516 • The appearance of the described deviations depended strongly on the type of
517 bitumen used (production process and grade). The type of asphalt mixture used
518 did not influence the appearance of the deviations.

- 519 • The level of static loading does not have strong impact on the occurrence of
520 deviations from thermo-rheological simplicity. For the higher levels of loading
521 the time limit of thermo-rheological simplicity principle is slightly higher.
- 522 • “Branching” model of the master curve should be created to model the complex
523 behaviour of asphalt mixtures at low temperatures for long times of loading.

524 **Acknowledgement**

525 It is gratefully acknowledged that the presented research was performed under a
526 research project sponsored by the Polish General Directorate for National Roads and
527 Motorways.

528 **References**

- 529 [1] J.D. Ferry, *Viscoelastic Properties of Polymers*, 3rd Edition, 1980.
- 530 [2] C.L. Monismith, R.L. Alexander, K.E. Secor, *Rheologic Behavior of Asphalt*
531 *Concrete*, *J. Assoc. Asph. Paving Technol.* 35 (1966) 400–450.
- 532 [3] Y.R. Kim, *Modeling of Asphalt Concrete*, American Society of Civil Engineers,
533 2009.
- 534 [4] G.D. Airey, *Use of Black Diagrams to Identify Inconsistencies in Rheological*
535 *Data*, *Road Mater. Pavement Des.* 3 (2002) 403–424.
- 536 [5] G. Airey, *Rheological properties of styrene butadiene styrene polymer modified*
537 *road bitumens**, *Fuel.* 82 (2003) 1709–1719. doi:10.1016/S0016-2361(03)00146-
538 7.
- 539 [6] H. Di Benedetto, F. Olard, C. Sauzéat, B. Delaporte, *Linear viscoelastic*

- 540 behaviour of bituminous materials: From binders to mixes, *Road Mater.*
541 *Pavement Des.* 5 (2004) 163–202. doi:10.1080/14680629.2004.9689992.
- 542 [7] G.D. Airey, M.H. Mohammed, Rheological properties of polyacrylates used as
543 synthetic road binders, *Rheol. Acta.* 47 (2008) 751–763. doi:10.1007/s00397-
544 007-0250-3.
- 545 [8] G. Airey, M. Mohammed, A.C. Collop, C.J. Hayes, T. Parry, Linear Viscoelastic
546 Behaviour of Polyacrylate Binders and Bitumen Blends, *Road Mater. Pavement*
547 *Des.* 9 (2008) 13–35. doi:10.1080/14680629.2008.9690157.
- 548 [9] N.I.M. Yusoff, E. Chailleux, G.D. Airey, A Comparative Study of the Influence
549 of Shift Factor Equations on Master Curve Construction, *Int. J. Pavement Res.*
550 *Technol.* 4 (2011) 324–336.
- 551 [10] E. Santagata, O. Baglieri, L. Tsantilis, D. Dalmazzo, Rheological
552 Characterization of Bituminous Binders Modified with Carbon Nanotubes,
553 *Procedia - Soc. Behav. Sci.* 53 (2012) 546–555.
554 doi:10.1016/j.sbspro.2012.09.905.
- 555 [11] H. Di Benedetto, C. Sauzeat, K. Bilodeau, M. Buannic, S. Mangiafico, Q.T.
556 Nguyen, S. Pouget, N. Tapsoba, J. Van Rompu, General overview of the time-
557 temperature superposition principle validity for materials containing bituminous
558 binder, *Int. J. Roads Airports.* 1 (2011) 35–52.
- 559 [12] Y. Ruan, R.R. Davison, C.J. Glover, The effect of long-term oxidation on the
560 rheological properties of polymer modified asphalts, *Fuel.* 82 (2003) 1763–1773.
561 doi:10.1016/S0016-2361(03)00144-3.

- 562 [13] F. Olard, H. Di Benedetto, A. Dony, J.-C. Vaniscote, Properties of bituminous
563 mixtures at low temperatures and relations with binder characteristics, *Mater.*
564 *Struct.* 38 (2005) 121–126. doi:10.1007/BF02480584.
- 565 [14] M.O. Marasteanu, A. Basu, S.A.M. Hesp, V. Voller, Time–Temperature
566 Superposition and AASHTO MP1a Critical Temperature for Low-temperature
567 Cracking, *Int. J. Pavement Eng.* 5 (2004) 31–38.
568 doi:10.1080/10298430410001720792.
- 569 [15] A.F. Stock, *Alternative Modified Binders for Airfield Pavements*, Report no.
570 AD-A197 902, 1988.
- 571 [16] L.-I. Palade, P. Attané, S. Camaro, Linear viscoelastic behavior of asphalt and
572 asphalt based mastic, *Rheol. Acta.* 39 (2000) 180–190.
573 doi:10.1007/s003970050018.
- 574 [17] C.W. Schwartz, N. Gibson, R.A. Schapery, Time-Temperature Superposition of
575 Asphalt Concrete at Large Compressive Strains, *Transp. Res. Rec. J. Transp.*
576 *Res. Board.* 1789 (2002) 101–112.
- 577 [18] C.W. Schwartz, N.H. Gibson, R.A. Schapery, M.W. Witczak, Viscoplasticity
578 Modeling of Asphalt Concrete Behavior, in: *Recent Adv. Mater. Charact. Model.*
579 *Pavement Syst.*, American Society of Civil Engineers, Reston, VA, 2003: pp.
580 144–159. doi:10.1061/40709(257)10.
- 581 [19] Y. Zhao, Y. Kim, Time-Temperature Superposition for Asphalt Mixtures with
582 Growing Damage and Permanent Deformation in Compression, *Transp. Res.*
583 *Rec. J. Transp. Res. Board.* 1832 (2003) 161–172. doi:10.3141/1832-20.

- 584 [20] N.I.M. Yusoff, M.T. Shaw, G.D. Airey, Modelling the linear viscoelastic
585 rheological properties of bituminous binders, *Constr. Build. Mater.* 25 (2011)
586 2171–2189. doi:10.1016/j.conbuildmat.2010.11.086.
- 587 [21] M. Jaczewski, J. Judycki, Effects of deviations from thermo-rheologically simple
588 behavior of asphalt mixes in creep on developing of master curves of their
589 stiffness modulus, in: 9th Int. Conf. “Environmental Eng. 2014,” Vilnius
590 Gediminas Technical University Press “Technika” 2014, Vilnius, Lithuania,
591 2014. doi:10.3846/enviro.2014.157.
- 592 [22] M. Jaczewski, J. Judycki, P. Jaskuła, Modelling of Asphalt Mixes under Long
593 Time Creep at Low Temperatures, in: *Transp. Res. Procedia*, 2016: pp. 3527 –
594 3535. doi:10.1016/j.trpro.2016.05.323.
- 595 [23] M. Jaczewski, Wpływ zastosowania betonu asfaltowego o wysokim module
596 sztywności na spękania niskotemperaturowe nawierzchni, Gdansk University of
597 Technology, 2016.
- 598 [24] J. Judycki, Verification of the new viscoelastic method of thermal stress
599 calculation in asphalt layers of pavements, *Int. J. Pavement Eng.* (2016) 1–13.
600 doi:10.1080/10298436.2016.1199883.
- 601 [25] J. Sohm, T. Gabet, P. Horny, J.-M. Piau, H. Di Benedetto, Creep tests on
602 bituminous mixtures and modelling, *Road Mater. Pavement Des.* 13 (2012) 832–
603 849. doi:10.1080/14680629.2012.735795.
- 604 [26] N.W. Tschoegl, *The Phenomenological Theory of Linear Viscoelastic Behavior*,
605 Springer Berlin Heidelberg, Berlin, Heidelberg, 1989. doi:10.1007/978-3-642-
606 73602-5.



- 607 [27] F. Olard, H. Di Benedetto, General “2S2P1D” Model and Relation Between the
608 Linear Viscoelastic Behaviours of Bituminous Binders and Mixes, *Road Mater.*
609 *Pavement Des.* 4 (2003) 185–224. doi:10.1080/14680629.2003.9689946.
- 610 [28] J. Judycki, Analysis of selected rheological properties of asphalt concrete
611 subjected to static load (in Polish), Gdansk University of Technology, 1975.
- 612 [29] J. Judycki, Non-linear viscoelastic behaviour of conventional and modified
613 asphaltic concrete under creep, *Mater. Struct.* 25 (1992) 95–101.
- 614 [30] Y.R. Kim, Y.C. Lee, H.J. Lee, Correspondence Principle for Characterization of
615 Asphalt Concrete, *J. Mater. Civ. Eng.* 7 (1995) 59–68. doi:10.1061/(ASCE)0899-
616 1561(1995)7:1(59).
- 617 [31] C.Y. Cheung, D. Cebon, Experimental study of pure bitumens in tension,
618 compression, and shear, *J. Rheol.* (N. Y. N. Y.) 41 (1997) 45–74.
619 doi:10.1122/1.550858.
- 620 [32] H. Soenen, J. De Visscher, T. Tanghe, A. Vanelstraete, P. Redelius, R. Davis, R.
621 Kluttz, M. Dunning, K. Chatti, Selection of binder performance indicators for
622 asphalt rutting based on triaxial and wheel tracking tests, *J. Assoc. Asph. Paving*
623 *Technol.* 75 (2006) 165–202.
- 624 [33] P. Des Croix, H. Di Benedetto, Binder-mix rheology: Limits of linear domain,
625 non linear behaviour, in: *Proceeding Euroasphalt Eurobitume Congr. Strasbourg,*
626 *Fr.* 7-10 May, 1996.
- 627 [34] J. Judycki, A new viscoelastic method of calculation of low-temperature thermal
628 stresses in asphalt layers of pavements, *Int. J. Pavement Eng.* 19 (2018) 24–36.

- 629 doi:10.1080/10298436.2016.1149840.
- 630 [35] J. Skrzypek, Plasticity and creep, theory, application, excercises (in Polish),
631 PWN, Warsaw, 1986.
- 632 [36] G.M. Rowe, M.J. Sharrock, M.G. Bouldin, R.N. Dongre, Advanced Techniques
633 to Develop Asphalt Master Curves from the Bending Beam Rheometer, *Pet.*
634 *Coal.* 43 (2001) 54–59.
- 635 [37] M. Williams, R.F. Landel, J.D. Ferry, The Temperature Dependance of
636 Relaxation Mechanisms in Amorphous Polymers and Other Glass-forming
637 Liquids, *J. Am. Chem. Soc.* 77 (1955) 3701–3707.
- 638 [38] G.M. Rowe, M.J. Sharrock, Alternate Shift Factor Relationship for Describing
639 the Temperature Dependency of the Visco-Elastic Behaviour of Asphalt
640 Materials, *Transp. Res. Rec. J. Transp. Res. Board.* 2207 (2011) 125–135.
- 641 [39] D.W. Christensen, D.A. Anderson, Interpretation of Dynamic Mechanical Test
642 Data for Paving Grade Asphalt Cements, *J. Assoc. Asph. Paving Technol.* 61
643 (1992) 68–116.
- 644 [40] Guide for Mechanistic-Empirical Design of New and Rehabilitated Pavement
645 Structures, Final Report, Part 3 – Design and Analysis, 2004.
- 646 [41] D.W. Christensen, T. Pellinen, R.F. Bonaquist, Hirsh Model for Estimating the
647 Modulus of Asphalt Concrete, *J. Assoc. Asph. Paving Technol.* 72 (2003) 121 –
648 151.
- 649 [42] T. Pellinen, A. Zofka, M. Marasteanu, N. Funk, Asphalt Mixture Stiffness
650 Predictive Models, *J. Assoc. Asph. Paving Technol.* 76 (2007) 575–625.



- 651 [43] M.O. Marasteanu, D.A. Anderson, Improved Model for Bitumens Rheological
652 Characterization, in: Eurobitume Work. Performance-Related Prop. Bitum. Bind.,
653 Luxembourg, 1999: p. Paper No. 133.
- 654 [44] M. Cholewińska, M. Iwański, G. Mazurek, The Impact of Ageing on the Bitumen
655 Stiffness Modulus Using the CAM Model, *Balt. J. Road Bridg. Eng.* 13 (2018)
656 34–39. doi:10.3846/bjrbe.2018.386.
- 657 [45] Refining the Simple Performance Tester for Use in Routine Practice,
658 Washington, D.C., 2008.
- 659 [46] M. Pszczoła, J. Judycki, Testing of low temperature behaviour of asphalt
660 mixtures in bending creep test, in: 7th Int. RILEM Symp. Adv. Test. Charact.
661 Bitum. Mater. Adv. Test. Charact. Bitum. Mater., Rhodes, 2009: pp. 303–312.
- 662 [47] M. Pszczoła, M. Jaczewski, D. Rys, P. Jaskula, C. Szydłowski, Evaluation of
663 Asphalt Mixture Low-Temperature Performance in Bending Beam Creep Test,
664 *Materials (Basel)*. 11 (2018) 100. doi:10.3390/ma11010100.
- 665 [48] D.A. Anderson, D.W. Christensen, H.U. Bahia, R. Dongre, M.G. Sharma, C.E.
666 Antle, Binder characterization and evaluation. In: Physical characterization, vol.
667 3. Publication SHRP-A-369, Washington D.C., 1994.
- 668 [49] D.A. Anderson, M.O. Marasteanu, Physical hardening of asphalt binders relative
669 to their glass transition temperature, *Transp. Res. Rec. J. Transp. Res. Board.*
670 1661 (1999) 27–34.
- 671 [50] X. Lu, U. Isacsson, Laboratory study on the low temperature physical hardening
672 of conventional and polymer modified bitumens, *Constr. Build. Mater.* 14 (2000)

- 673 79–88.
- 674 [51] S.A.M. Hesp, S. Iliuta, J.W. Shirokoff, Reversible aging in asphalt binders,
675 Energy Fuel. 21 (2007) 1112–1121.
- 676 [52] J. Judycki, Influence of low-temperature physical hardening on stiffness and
677 tensile strength of asphalt concrete and stone mastic asphalt, Constr. Build.
678 Mater. 61 (2014) 191–199. doi:10.1016/j.conbuildmat.2014.03.011.
- 679 [53] J. Judycki, Bending test of asphaltic mixtures under statical loading, in: Proc.
680 Fourth Int. RILEM Symp. Mech. Tests Bitum. Mix. Charact. Des. Qual. Control,
681 Budapest, 1990: pp. 207–227.
- 682 [54] M. Pszczoła, J. Judycki, Comparison of calculated and measured thermal stresses
683 in asphalt concrete, Balt. J. ROAD Bridg. Eng. 10 (2015) 39–45.
684 doi:10.3846/bjrbe.2015.05.
- 685 [55] R. Kleizienė, A. Vaitkus, D. Čygas, Influence of asphalt visco-elastic properties
686 on flexible pavement performance, Balt. J. Road Bridg. Eng. 11 (2016) 313–323.
687 doi:10.3846/bjrbe.2016.36.
- 688 [56] Ł. Mejłun, J. Judycki, B. Dołżycki, Comparison of Elastic and Viscoelastic
689 Analysis of Asphalt Pavement at High Temperature, Procedia Eng. 172 (2017)
690 746–753. doi:10.1016/j.proeng.2017.02.095.
- 691 [57] B. Świeczko-Żurek, P. Jaskuła, J.A. Ejsmont, A. Kędzierska, P. Czajkowski,
692 Rolling resistance and tyre/road noise on rubberised asphalt pavement in Poland,
693 Road Mater. Pavement Des. 18 (2017) 151–167.
694 doi:10.1080/14680629.2016.1159245.



- 695 [58] AASHTO T 322-03 Standard Method of Test for Determining the Creep
696 Compliance and Strength of Hot-Mix Asphalt (HMA) Using the Indirect Tensile
697 Test Device, (n.d.) 2006.
- 698 [59] M.O. Marasteanu, R. Velasquez, A.C. Falchetto, A. Zofka, Development of a
699 Simple Test to Determine the Low Temperature Creep Compliance of Asphalt
700 Mixtures, Final Report for Highway IDEA Project 133, 2009.
- 701 [60] A. Zofka, M. Marasteanu, M. Turos, Investigation of Asphalt Mixture Creep
702 Compliance at Low Temperatures, Road Mater. Pavement Des. 9 (2008) 269–
703 285. doi:10.1080/14680629.2008.9690169.
- 704 [61] A. Zofka, M. Marasteanu, M. Turos, Determination of Asphalt Mixture Creep
705 Compliance at Low Temperatures by Using Thin Beam Specimens, Transp. Res.
706 Rec. J. Transp. Res. Board. 2057 (2008) 134–139. doi:10.3141/2057-16.
- 707 [62] R. Velasquez, M. Marasteanu, J. Labuz, M. Turos, Evaluation of Bending Beam
708 Rheometer for Characterization of Asphalt Mixtures, J. Assoc. Asph. Paving
709 Technol. 79 (2010) 295–324.
- 710 [63] R. Velasquez, A. Zofka, M. Turos, M.O. Marasteanu, Bending beam rheometer
711 testing of asphalt mixtures, Int. J. Pavement Eng. 12 (2011) 461–474.
712 doi:10.1080/10298430903289956.
- 713 [64] M. Pszczoła, M. Jaczewski, C. Szydłowski, J. Judycki, B. Dołżycki, Evaluation
714 of Low Temperature Properties of Rubberized Asphalt Mixtures, Procedia Eng.
715 172 (2017) 897–904. doi:10.1016/j.proeng.2017.02.098.
- 716