



Urchin-like TiO₂ structures decorated with lanthanide-doped Bi₂S₃ quantum dots to boost hydrogen photogeneration performance

Magdalena Miodyńska^a, Alicja Mikołajczyk^{a,b}, Beata Bajorowicz^a, Julia Zwara^a, Tomasz Klimczuk^c, Wojciech Lisowski^d, Grzegorz Trykowski^e, Henry P. Pinto^f, Adriana Zaleska-Medynska^{a,*}

^a Department of Environmental Technology, Faculty of Chemistry, University of Gdansk, 80-308, Gdansk, Poland

^b Laboratory of Environmental Chemometrics, University of Gdansk, 80-308, Gdansk, Poland

^c Department of Solid State Physics, Faculty of Applied Physics and Mathematics, Gdansk University of Technology, 80-233, Gdansk, Poland

^d Institute of Physical Chemistry, Polish Academy of Science, 01-224, Warsaw, Poland

^e Faculty of Chemistry, Nicolaus Copernicus University, 87-100, Torun, Poland

^f CompNano Group, School of Physical Sciences and Nanotechnology, Yachay Tech University, 100119, Urcuqui, Ecuador

ARTICLE INFO

Keywords:

Heterogeneous photocatalysis
Hydrogen generation
Bismuth sulfide quantum dots
Doped quantum dots

ABSTRACT

The formation of heterojunctions between wide- and narrow-bandgap photocatalysts is commonly employed to boost the efficiency of photocatalytic hydrogen generation. Herein, the photoactivity of urchin-like rutile particles is increased by decorating with pristine as well as Er- or Yb-doped Bi₂S₃ quantum dots (QDs) at varied QD loadings (1–20 wt%) and doping degrees (1–15 mol%), and the best hydrogen evolution performance is achieved at Er and Yb contents of 10 mol%. Specifically, a hydrogen productivity of 1576.7 μmol g_{cat}⁻¹ is achieved after 20-h irradiation for TiO₂ decorated by 10 mol% Yb-doped Bi₂S₃ QDs. Theoretical calculations show that the introduction of defects into the Bi₂S₃ lattice through Er/Yb doping promotes the creation of new energy levels and facilitates the transport of photogenerated charges during photocatalysis.

1. Introduction

Heterogeneous photocatalysis is one of the most promising methods of obtaining molecular hydrogen, a prospective future energy carrier, additionally allowing for the decomposition of contaminants in liquid and gas phases [1–6]. To date, the upscaling of heterogeneous photocatalytic processes is mainly hindered by their low efficiency, especially in the case of hydrogen generation. Hence, much effort has been made to find ways of circumventing this problem, as exemplified by the modification of wide-bandgap (wide-BG) semiconductor matrices with narrow-BG quantum dots (QDs) to simultaneously enhance efficiency and utilise visible (as opposed to ultraviolet (UV)) light. QDs are semiconductor nanocrystals with sizes of 2–10 nm that experience the quantum confinement effect [7,8] and hence feature unique properties not observed for their macro- or micro-counterparts [9]. For example, the size-dependent optical properties of QDs allow for broadband radiation absorption, especially in the visible-light region. Furthermore, as the extremely high surface-to-volume ratio of QDs can be used to promote photocatalytic reactions at the catalyst surface [7], QDs have been explored as photocatalytic reaction promoters.

Among the broad range of QDs, those comprising Cd and Pb compounds such as CdS, CdO, CdSe, CdTe, and PbS are used most often because of their advantageous conduction and valence band edge positions as well as the narrow BG and ease of synthesis [10–13]. In particular, these QDs have been used for visible light-induced pollutant degradation [14–20] and photocatalytic hydrogen generation [21–26]. Unfortunately, the toxicity of Pb-/Cd- based QDs limits their practical applications, especially those associated with environmental remediation [27,28], which necessitates the search for less harmful and more stable QDs. To date, diverse QDs have been synthesised, characterised, and evaluated in terms of photoactivity, as exemplified by carbon [29–32], AgBr [33], ZnO [34], graphene [35], black P [36], InP [37], MoS₂ [38], CuInS₂ [39,40], CeO₂ [41], In₂S₃ [42], CuO [43], Cu₂O [44], Ag₃PO₄ [45], Bi₂WO₆ [46], BiVO₄ [47], SnS [48], Ag₂S [49], and Bi₂S₃ [44,50,51] QDs, which have been used for the photocatalytic degradation of organic pollutants and/or hydrogen production via photocatalytic water splitting. In most cases, QDs are deposited at the surface of three-dimensional semiconductor structures to create photoactive composites, as this hybridisation allows one to hinder the rapid recombination of photogenerated charges observed for pristine QDs and

* Corresponding author.

E-mail address: adriana.zaleska-medynska@ug.edu.pl (A. Zaleska-Medynska).

<https://doi.org/10.1016/j.apcatb.2020.118962>

Received 19 February 2020; Received in revised form 30 March 2020; Accepted 1 April 2020

Available online 10 April 2020

0926-3373/ © 2020 The Author(s). Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license

(<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

thus increase the efficiency of QD usage in photocatalytic reactions [7].

Herein, Bi₂S₃ QDs were selected because of their appropriate conduction band (CB) edge position (sufficient for the reduction of protons to molecular hydrogen during the photocatalytic process) and narrow BG (1.3–1.7 eV) [52]. Previous works revealed that the introduction of rare earth (RE) ions into a foreign crystal lattice creates additional electronic states to indirectly promote both near-infrared (NIR) radiation absorption and emission in the visible or UV range [53,54]. In this case, an effective conversion of visible and NIR light energy can afford UV light (via the so-called upconversion), which can then excite broadband semiconductors [55]. Hence, the introduction of RE ions (Er³⁺ and Yb³⁺) into the crystal lattice of Bi₂S₃ QDs was expected to increase the photocatalytic activity of the resulting RE-Bi₂S₃ QD/TiO₂ hybrids. Previous research largely focused on the doping of TiO₂ with lanthanides [56–59] and confirmed the resulting photoactivity increase; however, lanthanide doping has also been shown to increase the photoactivity of CdS, ZnS, and ZnO QDs [8,60]. To the best of our knowledge, only one paper has dealt with the doping of Bi₂S₃ with lanthanides, describing the modification of flower-like Bi₂S₃ with Eu ions and the application of the resulting hybrids for pollutant photodegradation [61].

In contrast, Bi₂S₃ QD-decorated rutile hybrids have not been applied to hydrogen evolution; moreover, Er- and Yb-doped Bi₂S₃ QDs (and hence, their composites) have not even been synthesised. In view of the above, the present study probes the effect of Bi₂S₃ QD loading onto urchin-like rutile particles as well as the influence of Er and Yb doping on the photoactivity of doped-Bi₂S₃ QD/TiO₂ composites, providing experimental and theoretical evidence concerning the mechanism of hydrogen evolution over as-prepared hybrids. The above-mentioned composites with well dispersed Bi₂S₃ QDs (pristine and Er- or Yb-doped) at the surface of urchin-like rutile particles are synthesised by a combination of solvothermal and direct adsorption methods, and the hydrogen evolution performances of these composites are evaluated in electrolytes containing Na₂S/Na₂SO₃ or triethanolamine (TEOA) as a sacrificial agent under UV-vis and visible-light (> 420 nm) irradiation. Furthermore, density functional theory (DFT) calculations are applied to assess the effects of RE ion introduction into the crystal structure of Bi₂S₃. The usefulness of our contribution lies in the development of Cd-free QDs and in the deepening of our understanding of the interactions between Bi₂S₃-based QDs and the rutile matrix and related reagents during hydrogen evolution.

The formation of RE-Bi₂S₃/TiO₂ hybrids is confirmed by structural (powder X-ray diffraction, pXRD) and surface (X-ray photoelectron spectroscopy, XPS) analyses, and the obtained samples are shown to exhibit higher photocatalytic activity for the water splitting reaction than their individual components (Bi₂S₃ QDs and rutile TiO₂). Computer simulations of Bi₂S₃ QDs doped with Yb³⁺ and Er³⁺ are used to determine the resulting changes in Bi₂S₃ crystal lattice and, in combination with experiments, help to elucidate the photocatalytic mechanism. The highest activity is observed for the composite containing 10 mol% Yb-doped Bi₂S₃ QDs at a loading of 10 wt%, in which case hydrogen productivity after 4 h reaches 376.4 μmol g_{cat}⁻¹. This enhanced activity is ascribed to (i) the introduction of Yb³⁺ into the interstitial space of QDs to reduce the BG to 0.4 eV, as indicated by theoretical studies; (ii) the use of an optimal sulphur-containing electrolyte to stabilise the exposure system; and (iii) the facilitated transport of photogenerated charges due to the creation of an effective TiO₂-Bi₂O₃-RE-doped Bi₂S₃ semiconductor connection via surface oxidation of Bi₂S₃ during thermal treatment in the last step of composite synthesis.

2. Experimental

2.1. Materials and instruments

Ti(IV) butoxide (TBOT; Sigma-Aldrich) and concentrated HCl

(35–38%, STANLAB) were used for the preparation of TiO₂ spheres. Pristine and RE-doped Bi₂S₃ QDs were prepared from Bi(NO₃)₃·5 H₂O (analytical grade, STANLAB), Na₂S₂O₃·5 H₂O (pure, POCH S.A.), Er(NO₃)₃·5 H₂O (99.99%, Sigma-Aldrich), Yb(NO₃)₃·5 H₂O (99.99%, Sigma-Aldrich), and acetone (STANLAB). Deionised water and ethanol (96 vol%, POCH S.A.) were used to purify the obtained photocatalysts. The electrolytes used for photocatalytic measurements were prepared from Na₂S·9 H₂O (analytical grade, EUROCHEM BGD), Na₂SO₃ (analytical grade, POCH S.A.), NaOH (analytical grade, STANLAB), and TEOA (C₆H₁₅NO₃, > 99%, Carl Roth GmbH + Co. KG). All chemicals were used as received without further purification.

Diffuse reflectance spectra were recorded on a UV-vis spectrophotometer (UV 2600, Shimadzu) equipped with an integrating 4 sphere in the range of 200–800 nm using a BaSO₄ reference. Phase composition was probed by pXRD using a Bruker D8 Advance Eco diffractometer (Cu K_α) equipped with a LynxEye-XE detector. The collected data were analysed by the Le Bail method using HighScore Plus ver. 3.0e software. The morphology and size of TiO₂ particles and QDs were probed by field-emission scanning electron microscopy (FE-SEM; JEOL JSM-7610 F) and transmission electron microscopy (TEM; STEM-EDX, FEI Europe, TecnaiF20 X-Twin). Photoluminescence (PL) measurements were carried out at 20 °C using an LS-50B luminescence spectrophotometer equipped with a Xe discharge lamp as an excitation source and an R928 photomultiplier as a detector. Excitation radiation (λ = 325 nm) was directed on the sample surface at an angle of 90°. The elemental compositions of QD nanocomposite surfaces were evaluated by XPS (PHI 5000 VersaProbe, ULVAC-PHI) using monochromatic Al K_α radiation (hν = 1486.6 eV).

2.2. TiO₂ preparation

TiO₂ particles were hydrothermally prepared as described elsewhere [62]. Briefly, TBOT (68 g) was added to concentrated HCl (60 mL) upon stirring over 10 min, and the mixture was then transferred into a Teflon-lined stainless steel autoclave and heated at 170 °C for 24 h. The reactor was cooled to room temperature, and the TiO₂ precipitate was sequentially washed with water and ethanol for three times, dried at 70 °C until complete liquid evaporation, and calcined at 300 °C for 1 h.

2.3. Preparation of pristine and RE-doped Bi₂S₃ QDs

Bi₂S₃ QDs were synthesised using a refined solvothermal method [63]. Briefly, Bi(NO₃)₃·5 H₂O was dissolved in acetone (140 mL) to a concentration of 4.77 mM upon vigorous stirring over 30 min. The solution was treated with Na₂S₂O₃·5 H₂O (0.248 g), stirred for 30 min, and the obtained yellowish suspension was transferred into a Teflon-lined stainless steel autoclave and heated at 180 °C for 24 h. After cooling to room temperature, the dark brown powder of QDs was sequentially washed with water and ethanol (three times each, with centrifugation (6000 rpm) after each wash) and dried at 80 °C overnight. For the synthesis of RE-doped Bi₂S₃ QDs, Er or Yb nitrate was introduced at the stage of Bi(NO₃)₃ solution preparation. RE ions were assumed to be incorporated into the QD crystal structure instead of Bi; therefore, the extent of doping was expressed as mol% RE with respect to Bi, and the sum of Bi + RE nitrate amounts was held constant. In this way, Bi₂S₃ QDs doped with Er or Yb at levels of x = 1, 5, 10, and 15 mol% were obtained (xRE-Bi₂S₃).

2.4. Combination of QDs with TiO₂

Composites with different amounts of QDs deposited on TiO₂ were prepared by a physical adsorption method. For this purpose, a beaker filled with doubly distilled water (25 mL) was charged with TiO₂ (1 g) and an appropriate amount of QDs (corresponding to loadings of 1, 3, 5, 10, 15, or 20 wt%) or 10RE-Bi₂S₃ powder and placed in an ultrasonic

bath for 10 min. The obtained suspension was magnetically stirred for 1 h and then evaporated to dryness at 70 °C overnight. For better QD anchoring on TiO₂, the composites were calcined at 300 °C for 1 h at a ramp rate of 5 °C min⁻¹. The photocatalyst exhibiting the highest activity for hydrogen evolution, namely 10Yb_10Bi₂S₃/TiO₂ was also calcined at 350 and 400 °C for 1 h.

2.5. Photocatalytic activity measurements

Typically, a cylindrical quartz reactor was charged with the photocatalyst (100 mg) and aqueous electrolyte (80 mL; 10 wt% TEOA or 0.1 M Na₂S/0.5 M Na₂SO₃/1 M NaOH) and tightly closed with a silicone septum. The suspension was stirred at 700 rpm and a constant temperature of 10 °C. For the first 30 min, the process was run without irradiation to establish an adsorption-desorption equilibrium between the photocatalyst and the solution, and the space above the suspension was purged with nitrogen. Then, a reference air sample from the suspension was collected by a syringe and analysed. The system was subsequently irradiated by a 1000-W Xe lamp (Oriel), and control air samples were collected every hour. The total exposure time was 4 h (or 20 h for the stability testing of the most photoactive composite). The hydrogen content of collected air samples was determined by a gas chromatograph equipped with a Thermal Conductivity Detector. For measurements of visible-light photocatalytic activity, a long-pass filter with a cut-off of 420 nm was employed.

2.6. Theoretical calculations

DFT calculations were performed using the plane-wave-basis Vienna *ab initio* simulation package (VASP) [64–66]. Core electrons were described by projected augmented wave potentials, with potentials for S, Bi, Er, and Yb atoms generated in [Ne]3s²3p⁴, [Xe, 4f¹⁴]5d¹⁰6s²6p³, [Kr, 4d¹⁰5s²4f¹¹]5p⁶6s²5d¹, and [Kr, 4d¹⁰5s²4f¹⁴]5p⁶6s² electron configurations, respectively, where square brackets denote core electron configurations. The optimal bulk crystal structures of Bi₂S₃ and RE-Bi₂S₃ QDs were computed using the strongly constrained and appropriately normed (SCAN) meta-generalised gradient approximation [67,68] with long-range van der Waals interactions from the revised Vydrov–van Voorhis nonlocal correlation functional (SCAN + rVV10) [69]. The total energy was converged to < 1 meV atom⁻¹ using a kinetic cut-off energy of 600 eV and an appropriate Γ -centred Monkhorst–Pack *k*-point mesh with a separation of 0.035 Å⁻¹. Finally, ionic optimisations were performed until all the forces were below 0.01 eV Å⁻¹. The electronic structure of RE-Bi₂S₃ was studied using a 1 × 3 × 1 supercell considering the presence of either S or Bi vacancies as well as RE_S, RE_{Bi}, and RE_{int} sites. The band structure of pristine Bi₂S₃ was computed using the hybrid Hartree–Fock DFT functional (Heyd–Scuseria–Ernzerhof hybrid functional HSE12 [70]) using the optimal atomic structure obtained by SCAN + rVV10.

3. Results and discussion

To investigate the effect of QD loading and doping degree on photocatalyst properties, we prepared a range of RE-Bi₂S₃ QD/TiO₂ composites (Table 1) as well as bare TiO₂ and pristine Bi₂S₃ QDs as references.

3.1. Morphology

The shape and size of TiO₂ particles and (RE)-Bi₂S₃ QDs as well as the distribution of QDs on the TiO₂ surface were probed by SEM and TEM (Fig. 1). SEM imaging (Figs. 1a and b) revealed that TiO₂ particles were spherical (diameter = 6–7 μm) and comprised individual rods, thus resembling sea urchins. Fig. 1c presents a TEM image of a non-modified TiO₂ particle fragment, revealing that the constituent rods with a diameter of ~50 nm had a defect-free smooth surface. The size

Table 1

Compositions of the prepared photocatalysts.

Sample label	Loading of (RE)-Bi ₂ S ₃ QDs on the TiO ₂ matrix	Type and amount of dopant introduced into QDs
TiO ₂	–	–
Bi ₂ S ₃ QDs	–	–
1Bi ₂ S ₃ /TiO ₂	1 wt%	–
3Bi ₂ S ₃ /TiO ₂	3 wt%	–
5Bi ₂ S ₃ /TiO ₂	5 wt%	–
10Bi ₂ S ₃ /TiO ₂	10 wt%	–
15Bi ₂ S ₃ /TiO ₂	15 wt%	–
20Bi ₂ S ₃ /TiO ₂	20 wt%	–
1Er_10Bi ₂ S ₃ /TiO ₂	10 wt%	1 mol% Er
5Er_10Bi ₂ S ₃ /TiO ₂	10 wt%	5 mol% Er
10Er_10Bi ₂ S ₃ /TiO ₂	10 wt%	10 mol% Er
15Er_10Bi ₂ S ₃ /TiO ₂	10 wt%	15 mol% Er
1Yb_10Bi ₂ S ₃ /TiO ₂	10 wt%	1 mol% Yb
5Yb_10Bi ₂ S ₃ /TiO ₂	10 wt%	5 mol% Yb
10Yb_10Bi ₂ S ₃ /TiO ₂	10 wt%	10 mol% Yb
15Yb_10Bi ₂ S ₃ /TiO ₂	10 wt%	15 mol% Yb

distribution of spherical QDs was estimated by TEM imaging of bulk QDs (Fig. 1d) and composites (Fig. 1f–n). The main fraction (~73%) of QDs had diameters of 3–6 nm, while ~32% of QDs had diameters of 4–5 nm (see details in Fig. 1d). Fig. 1f–i indicates the homogenous distribution of QDs at the TiO₂ surface. Moreover, the increase in QD loading resulted in a higher surface density of QDs distributed at TiO₂ facets, which was particularly noticeable when the loading increased from 5 to 10 wt% (Fig. 1f–g). TEM imaging of hybrids containing Er- or Yb-doped Bi₂S₃ QDs (Figs. 1j–n) demonstrated that doping did not affect the shape, size, and surface distribution of Bi₂S₃ QDs. Sample elemental compositions were examined by TEM/EDX (Transmission Electron Microscope/Energy Dispersive X-Ray Analysis) (Fig. 1o) to confirm the presence of Er, while Yb was invisible at this characterisation stage.

Furthermore, during TEM analysis, it was possible to capture the moment of QD movement on the TiO₂ surface due to the interaction of matter with high-energy electrons from the electron beam (Video S1 in the Supplementary Information, SI). This movement was attributable to heating induced by electron beam focusing and vacuum conditions in the TEM chamber. A similar phenomenon was reported by Wang et al. for Bi₂S₃ nanorods [71].

3.2. Optical properties

The absorption and emission spectra of photocatalysts are presented in Fig. 2 and 3, respectively. Fig. 2a shows that whereas bare TiO₂ absorbed radiation with wavelengths of up to 400 nm, decoration with Bi₂S₃ QDs allowed the absorption range to be extended into the visible region. The BG of pristine TiO₂ was calculated as 3–3.1 eV from its absorption range and was in line with the formation of the rutile phase. The QD content of composites (1–20 wt%) was positively correlated with the intensity of visible-light ($\lambda > 400$ nm) absorbance. In contrast, no such correlation was observed between visible-light absorption intensity and the Er/Yb content of QDs (Fig. 2b).

Among Er-doped photocatalysts, the composite with 10 mol% Er-doped QDs featured the highest intensity of visible-light absorption and activity for photocatalytic hydrogen production (Fig. 9 and 10d). Similarly, among the synthesised QDs, those doped with 10 mol% Er showed the highest absorption intensity (Fig. 2c). However, no such trend was observed for Yb-containing samples, in which case the highest composite absorbance intensity was observed for 5Yb_10Bi₂S₃/TiO₂ (Fig. 2b), while among Yb-doped Bi₂S₃ QDs, the strongest absorbance was observed for those doped with 15 mol% Yb (Fig. 2d).

Fig. 3 presents photocatalyst PL spectra (excitation wavelength = 315 nm), revealing a correlation between the decrease in luminescence intensity (in relation to that of bare TiO₂) and the increase in the

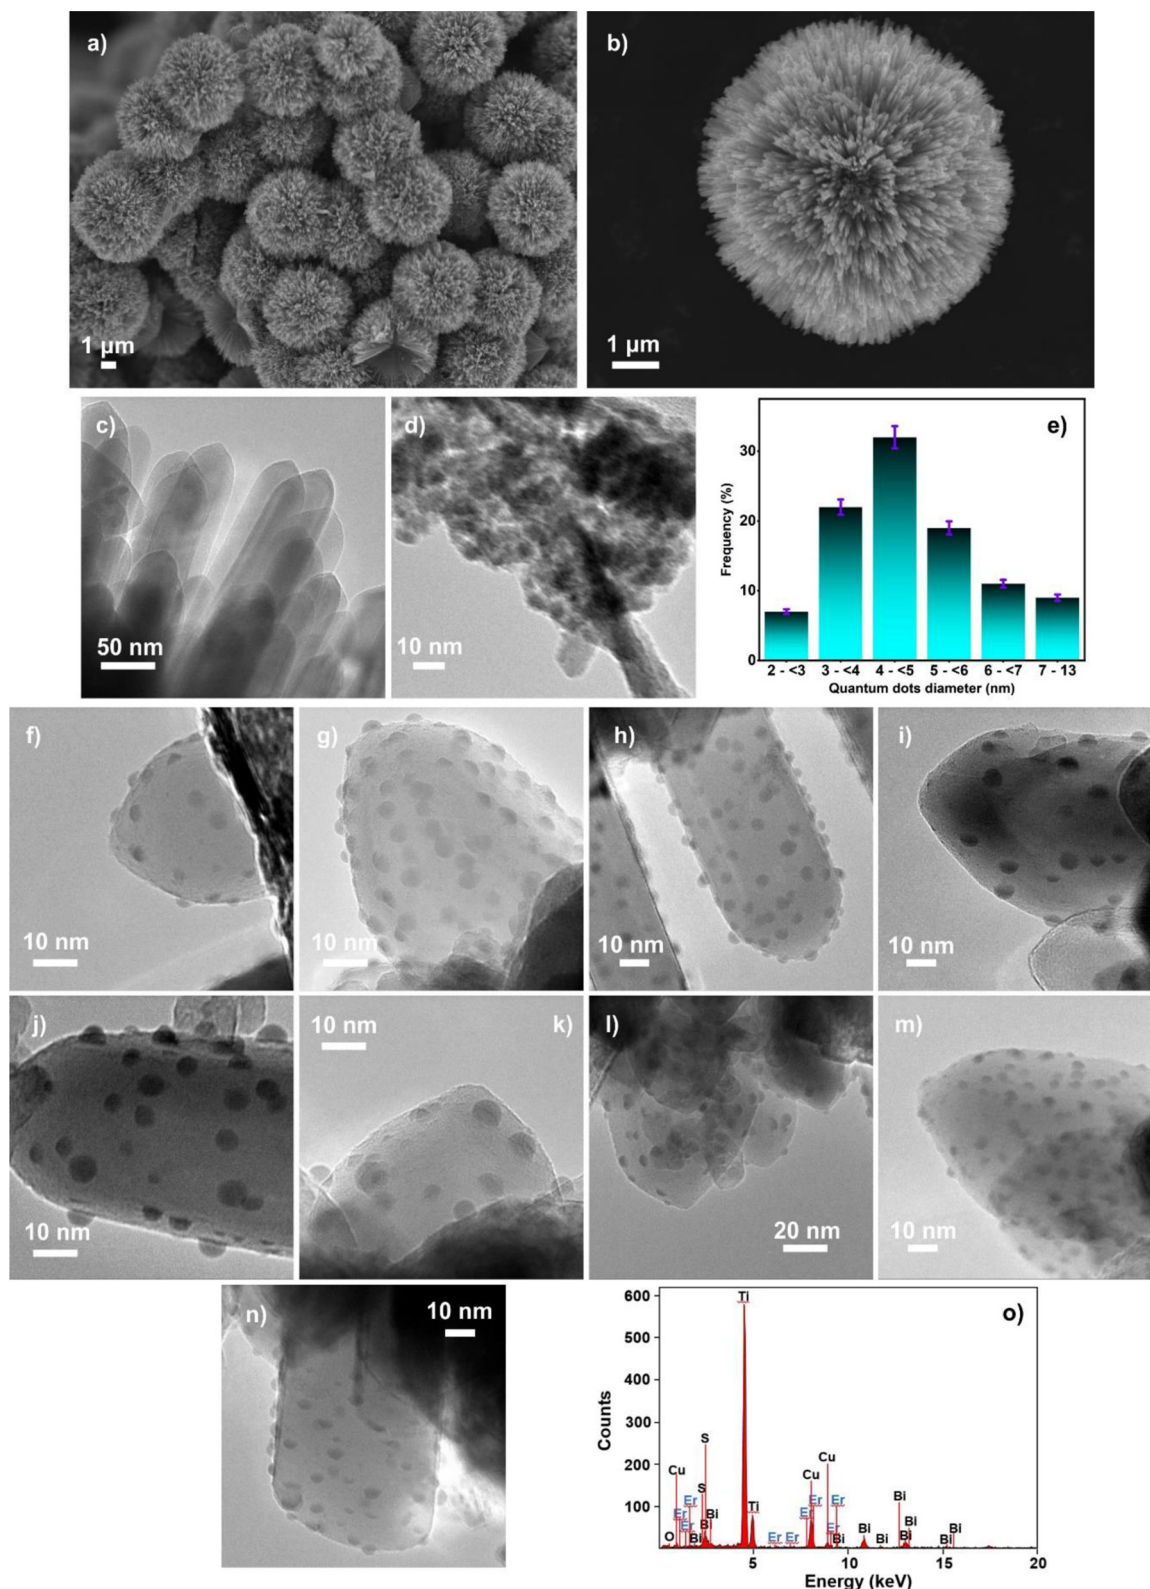


Fig. 1. SEM (a, b) and TEM (c) images of urchin-like TiO_2 structures. (d) TEM image of Bi_2S_3 QDs. (e) Size distribution of $\text{Bi}_2\text{S}_3/\text{RE-Bi}_2\text{S}_3$ QDs. TEM images of (f) $5\text{Bi}_2\text{S}_3/\text{TiO}_2$, (g) $10\text{Bi}_2\text{S}_3/\text{TiO}_2$, (h) $15\text{Bi}_2\text{S}_3/\text{TiO}_2$, (i) $20\text{Bi}_2\text{S}_3/\text{TiO}_2$, (j) $1\text{Er}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$, (k) $5\text{Er}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$, (l) $10\text{Er}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$, (m) $5\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$, and (n) $10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$. (o) EDX analysis of $10\text{Er}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$.

QD content of composites. A significant decrease in luminescence was also detected for composites containing RE-doped Bi_2S_3 QDs. The simultaneous decrease in luminescence and an increase in photocatalytic activity were ascribed to the inhibition of photogenerated charge

recombination [44,72]. Additionally, all PL spectra featured four characteristic emission bands of TiO_2 at 421, 449, 484, and 530 nm. The band at 421 nm was ascribed to the existence of self-trapped excitons from TiO_6^{8-} octahedra [73,74], while those at 449 and 484 nm

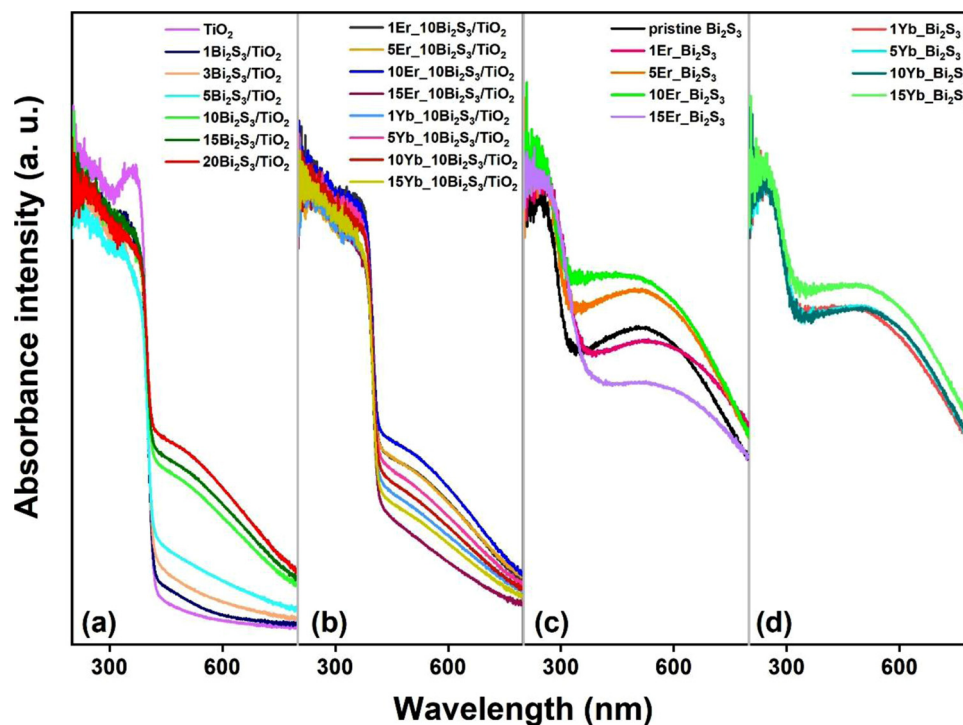


Fig. 2. UV-vis/diffuse reflectance spectra of the prepared photocatalysts: a) bare TiO_2 and $\text{Bi}_2\text{S}_3/\text{TiO}_2$ composites; b) RE- $\text{Bi}_2\text{S}_3/\text{TiO}_2$; c) Er- Bi_2S_3 QDs and d) Yb- Bi_2S_3 QDs.

were attributed to the presence of surface defects such as oxygen vacancies, which formed intermediate energy states below the CB and could therefore trap electrons. Finally, the peak at 530 nm was ascribed to the radiative recombination of charge carriers [73,75].

3.3. XPS

The surface elemental compositions of bare TiO_2 and QD/ TiO_2 hybrids were probed by XPS (Table 2).

Because of the overlap between Bi 4d/Ti 2p and Bi 4f/S 2p spectra, Bi and Ti contents were evaluated using the combination of Bi 3p_{3/2}

spectra and deconvoluted Bi 4d + Ti 2p and Bi 4f spectra. S content was determined from S 2s spectra. An exemplary set of these spectra collected for 10 $\text{Bi}_2\text{S}_3/\text{TiO}_2$ is shown in Fig. 4a and b.

The Ti 2p spectrum of 10 $\text{Bi}_2\text{S}_3/\text{TiO}_2$ confirmed the presence of TiO_2 (Fig. 4a, main Ti 2p_{3/2} signal at 458.8 eV [68]). The dominant Bi 4f_{7/2} signal at 159.4 eV (Bi 4f + S 2p spectrum, Fig. 4a) evidenced the presence of Bi(+3) due to Bi_2S_3 deposition [76], while signals located at lower binding energies indicated the coexistence of Bi(+3-x) and Bi(0) surface states [76,77], the contribution of which was relatively large for TiO_2 doped with 1–3 wt% Bi_2S_3 (Table 2 and Bi 4f spectra in Fig. 5).

The S 2s spectrum of 10 $\text{Bi}_2\text{S}_3/\text{TiO}_2$ (Fig. 4b) was well fitted by two

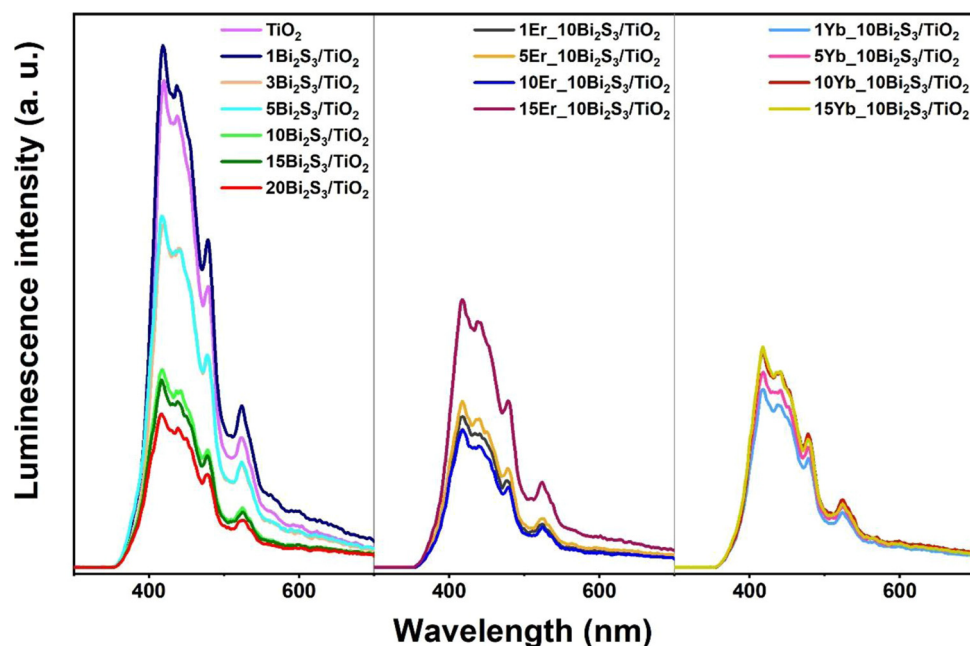


Fig. 3. PL spectra of the prepared photocatalysts ($\lambda_{\text{exc}} = 315$ nm).

Table 2
Elemental contents and Bi valence states in the surface layer of QD/TiO₂ samples.

Sample	Ti (at%)	Bi ^a (at%)			Fraction of Bi4f _{7/2} state (%)			O (at%)	S (at%)	Other (C N Cl) (at%)			
		Bi(0) 156.7 eV			Bi(+3-x) 157.5 ± 0.2 eV						Bi(+3) 159.4 ± 0.2 eV		
TiO ₂	24.9	0	0	0	0	0	65.7	0	9.4				
Bi ₂ S ₃ QDs	0	17.3	0	17.2	82.8		48.1	12.4	22.2				
1Bi ₂ S ₃ /TiO ₂	24.4	0.1	60.3	11.2	28.5		67.2	0.3	8.0				
3Bi ₂ S ₃ /TiO ₂	22.8	1.1	19.7	36.9	43.4		65.0	1.1	10.0				
5Bi ₂ S ₃ /TiO ₂	17.9	5.6	0	11.2	88.8		61.6	1.8	13.1				
10Bi ₂ S ₃ /TiO ₂	14.3	8.3	0	13.9	86.1		62.8	4.3	10.3				
15Bi ₂ S ₃ /TiO ₂	11.4	10.5	0	10.2	89.8		62.1	5.4	10.6				
20Bi ₂ S ₃ /TiO ₂	9.1	12.1	0	4.1	95.9		63.9	5.8	9.1				

^a Average values determined from Bi 4p_{3/2} and Bi 4d/Bi 4f deconvoluted X-ray photoelectron spectra.

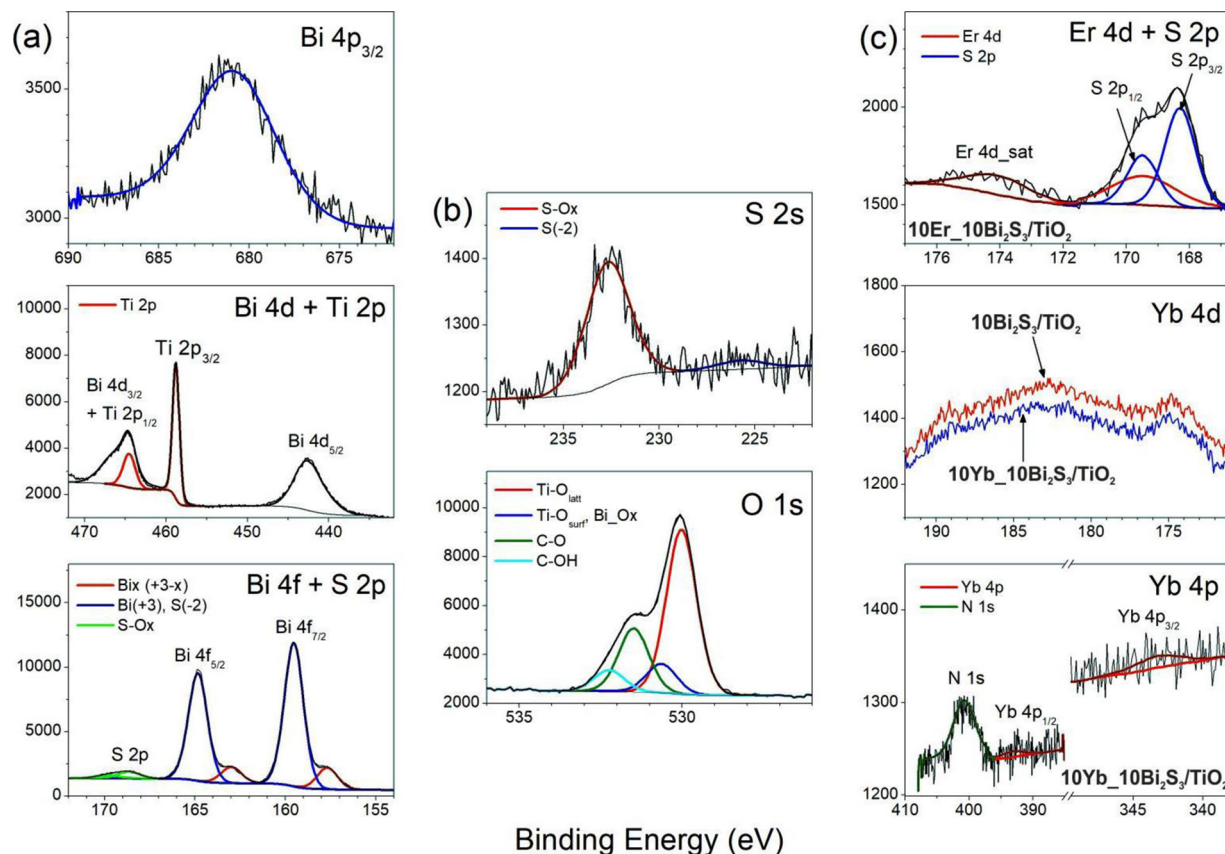


Fig. 4. High-resolution X-ray photoelectron spectra of 10Bi₂S₃/TiO₂: (a) Bi 4p_{3/2}, Bi 4d + Ti 2p, Bi 4f + S 2p; (b) S 2s, O 1s. (c) X-ray photoelectron spectra of doped elements: Er 4d overlapping with S 2p, Yb 4d, and Yb 4p.

peaks at 232.4 and 225.2 eV, attributed to surface sulphates and sulphides, respectively [76,77].

The presence of Er and Yb at the surface of RE-doped Bi₂S₃ QDs was confirmed by analysis of Er 4d and Yb 4d core level spectra, with representative spectra collected for 10Er_10Bi₂S₃/TiO₂ and 10Yb_10Bi₂S₃/TiO₂ presented in Fig. 4c. Unfortunately, Er 3d spectra overlapped with S 2p ones, while Yb 4d signals were too weak to be detected because of the overlap with relatively strong plasmonic Bi 4f signals (see Yb 4d region in the spectra of 10Bi₂S₃/TiO₂ and 10Yb_10Bi₂S₃/TiO₂). However, the effective doping of Er(+3) was confirmed by observation of Er 4d and Er 4d satellite signals at 169.4 and 174.0 eV, respectively [78,79]. The presence of Yb was confirmed by analysis of high-resolution Yb 4p spectra (Fig. 4c). Despite the very low signal/noise ratio, two signals at 343.2 and 393.2 eV, attributable to Yb 4p_{3/2} and Yb 4p_{1/2}, respectively, could be distinguished [76]. However, the suitability of these spectra for Yb content evaluation was doubtful. In fact, the amounts of Er and Yb species at the surface of all

RE-doped samples were much smaller than nominal values (Table 3).

10Yb_10Bi₂S₃/TiO₂ exhibited the highest photocatalytic activity, and its pristine-state surface chemical composition was therefore compared with that obtained after photocatalytic processing in different electrolytes (0.1 M Na₂S/0.5 M Na₂SO₃/1 M NaOH and 10 wt% TEOA). The corresponding XPS data are presented in Table 3 and Fig. 6, with 10Yb_10Bi₂S₃/TiO₂_20h_TEOA and 10Yb_10Bi₂S₃/TiO₂_20h_ES denoting samples subjected to prolonged irradiation (20 h) in TEOA and Na₂S/Na₂SO₃ electrolytes, respectively.

The Bi 4f spectrum recorded for the sample processed in TEOA (Fig. 6) revealed a much smaller content of Bi(+3) species than that of the sample processed in the Na₂S/Na₂SO₃ electrolyte. Moreover, the surface content of Bi significantly decreased after photocatalytic processing in TEOA solution (Table 3), which indicated the advanced decomposition of Yb-doped Bi₂S₃ QDs. In contrast, this process was inhibited when 0.1 M Na₂S/0.5 M Na₂SO₃/1 M NaOH was used as an electrolyte.

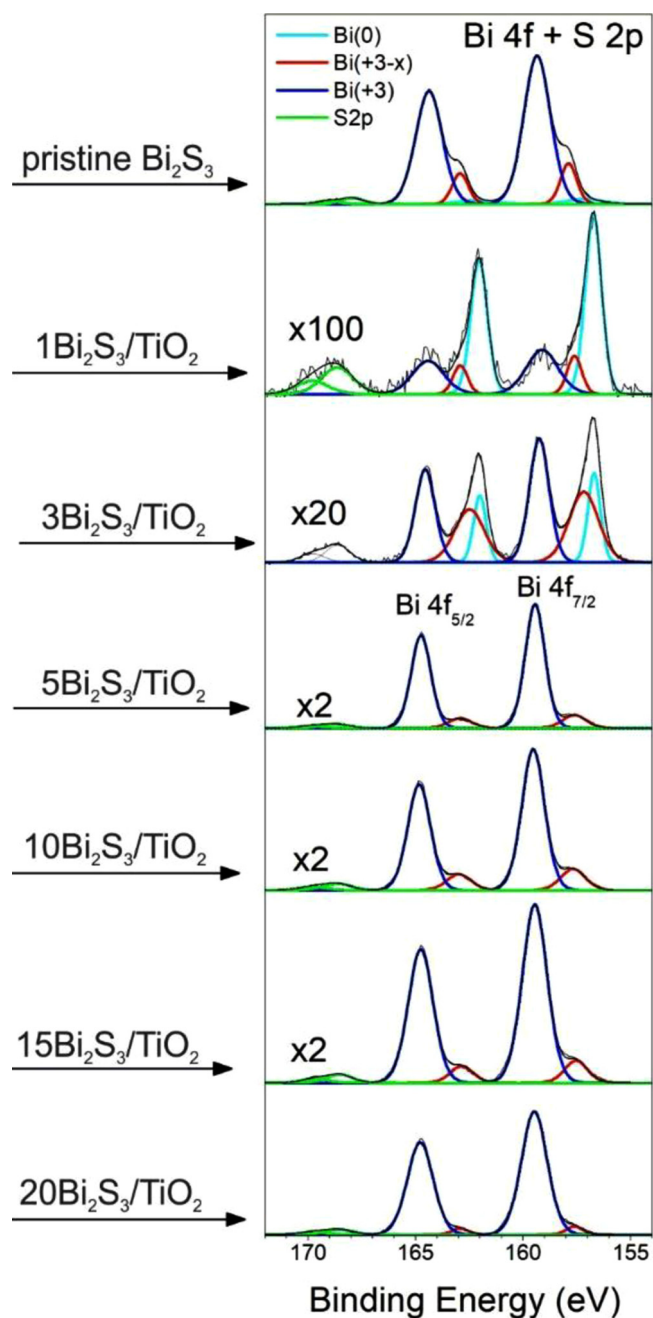


Fig. 5. Bi 4f X-ray photoelectron spectra of $\text{Bi}_2\text{S}_3/\text{TiO}_2$ samples with different Bi_2S_3 contents.

3.4. XRD

Fig. 7 presents the powder X-ray diffraction (pXRD) patterns of bare TiO_2 , Bi_2S_3 QDs, and selected composites. In the case of bare TiO_2 , all signals originated from TiO_2 (rutile), with the strongest peak at $2\theta = 27^\circ$ corresponding to reflection from the (110) plane. We also provide the Miller indices for the strongest peaks. The peaks expected for TiO_2 are shown by black vertical bars. Contrary to that of TiO_2 , the pattern of Bi_2S_3 QDs featured weak peaks barely discernible from the amorphous-like background. The pXRD pattern with a broad maximum at around 30° is similar to reported in ref. [80–82]. The low intensity reflections can be indexed by an orthorhombic Bi_2S_3 phase (red vertical bars) [83], but Le Bail analysis was not performed. Notably, the above pattern contained no peaks of $\text{Bi}(\text{NO}_3)_3$ or $\text{Na}_2\text{S}_2\text{O}_3$.

In the pattern of $10\text{Bi}_2\text{S}_3/\text{TiO}_2$ (Fig. 7c), the strongest reflections

were attributable to the rutile phase, whereas weak peaks marked by arrows probably indicated the presence of Bi_2O_3 (monoclinic P21/c) phase. Doping with 10 mol% Er or Yb had no influence on pXRD patterns.

The Le Bail method was used to estimate the lattice parameters of the rutile structure (P42/mnm), affording values of $a = 4.5955(1) \text{ \AA}$ and $c = 2.9581(1) \text{ \AA}$ for bare TiO_2 , which were very close to those ($a = 4.5924 \text{ \AA}$ and $c = 2.9575 \text{ \AA}$) reported in ref. [84]. The lattice parameters of composites differed from those of the pristine sample by less than 0.03%, i.e., were essentially the same.

In contrast to XPS, pXRD did not confirm the presence of Bi_2S_3 and instead might suggested the presence of Bi_2O_3 in composites. As no Er and Yb oxides were detected (Figs. 7d and e), this may finding indirectly supported the hypothesis that Er and Yb ions substituted other ions in the QD phase.

Furthermore, the composite with the highest photoactivity, $10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$, was probed by pXRD after a 20-h photocatalytic process in TEOA and sulphide/sulphite electrolytes (Fig. 8). The pattern recorded after irradiation in the TEOA electrolyte indicated the absence of Bi-based QDs, as opposed to that of the pristine sample (Fig. 8c), demonstrating the destructive effect of the reaction environment during photocatalysis. This effect was also observed in the images of samples and electrolytes before and after photocatalysis (Fig. 11).

The pXRD pattern recorded after irradiation in the sulphide/sulphite electrolyte (Fig. 8b) featured weak peaks (marked by arrows) that could not be indexed to monoclinic Bi_2O_3 and were instead ascribed to the cubic (I23.s.g. #197) phases of $\gamma\text{-Bi}_2\text{O}_3$ ($a = 10.267 \text{ \AA}$) and $\text{NaBi}_{12}\text{O}_{18.5}$ ($a = 10.2635 \text{ \AA}$). However, more detailed crystallographic studies are required to characterise the unknown phase.

3.5. Photocatalytic activity

The performances of as-prepared samples for photocatalytic water splitting are presented in Fig. 9 and 10. Specifically, Fig. 9 shows the time course of hydrogen generation under UV–vis irradiation in the presence of the sulphide/sulphite electrolyte. First, the effect of QD loading was assessed, and the highest activity was observed at a loading of 10 wt%. In particular, 4-h irradiation resulted in the formation of 239.9 and 296.7 $\mu\text{mol hydrogen g}_{\text{cat}}^{-1}$ in the presence of non-modified and 10 wt%-QD-decorated TiO_2 , respectively. Thus, the effects of QD doping by Er/Yb were further investigated for hybrids with a QD loading of 10 wt% (Fig. 9). The highest hydrogen productivity was observed in the presence of $10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$. Moreover, doping with both Er and Yb at 10 mol% benefitted hydrogen production, with hydrogen yields of 376.4 and 339 $\mu\text{mol g}_{\text{cat}}^{-1}$ observed after 4-h irradiation for $10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$ and $10\text{Er}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$ samples, respectively. Interestingly, pristine Bi_2S_3 QDs featured a low hydrogen generation activity ($72.4 \mu\text{mol g}_{\text{cat}}^{-1}$ after 4 h), probably due to the rapid recombination of photogenerated electron-hole pairs therein.

The most active composite ($10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$) was selected to investigate the effect of calcination temperature on photocatalytic activity. For this investigation, an additional batch of this composite was synthesised, divided into three parts in the final preparation stage, and annealed at 300, 350 or 400 $^\circ\text{C}$ for 1 h. Photocatalytic activity measurements revealed that the initially chosen calcination temperature (300 $^\circ\text{C}$) was optimal, while a temperature increase to 400 $^\circ\text{C}$ resulted in decreased photoactivity (Fig. 10a). This photoactivity loss was ascribed to the complete oxidation of Bi_2S_3 to Bi_2O_3 at $\geq 350 \text{ }^\circ\text{C}$, as reported previously [85]. The CB edge of Bi_2O_3 is more positive (+0.33 eV [86]) than that of Bi_2S_3 (−0.76 eV [86]), and the reduction potential of the former is too low to reduce hydrogen, which results in the suppression of hydrogen evolution in the presence of a Bi_2O_3 -containing composite. Thus, we concluded that photocatalyst annealing at 300 $^\circ\text{C}$ causes the surface oxidation of Bi_2S_3 to Bi_2O_3 (confirmed by XPS analysis and described in section 3.3), while annealing at higher temperatures leads to complete oxidation. Consequently, the presence of both sulphide and

Table 3
Contents and valence states of elements in the surface layer of RE-doped Bi₂S₃/TiO₂ samples.

Sample	Ti (at%)	Bi (at%)		Fraction of Bi _{4f_{7/2}} state (%)			O (at%)	S (at%)	Er (at%)	Yb (at%)	Other (C N Cl) (at%)
		Bi(0)	Bi(+3-x)	Bi(+3)							
					156.4 ± 0.2 eV	157.6 ± 0.1 eV					
10Bi ₂ S ₃ /TiO ₂	14.3	8.3	0	13.9	86.1	62.8	4.3	0	0	10.3	
1Er_10Bi ₂ S ₃ /TiO ₂	14.1	7.1	0	12.0	88.0	62.1	4.7	0.5	0	11.5	
5Er_10Bi ₂ S ₃ /TiO ₂	13.1	8.1	0	6.7	93.3	62.3	4.8	0.5	0	11.2	
10Er_10Bi ₂ S ₃ /TiO ₂	14.3	7.0	0	9.8	90.1	64.1	4.8	0.7	0	9.1	
15Er_10Bi ₂ S ₃ /TiO ₂	14.5	7.3	0	4.9	95.1	64.9	4.1	0.8	0	8.4	
1Yb_10Bi ₂ S ₃ /TiO ₂	14.1	10.2	0	10.9	89.1	61.7	3.7	0	0.1	10.3	
5Yb_10Bi ₂ S ₃ /TiO ₂	13.9	10.3	0	7.4	92.6	63.1	4.1	0	0.1	8.5	
10Yb_10Bi ₂ S ₃ /TiO ₂	14.0	10.1	0	6.2	93.8	60.3	4.4	0	0.1	11.1	
15Yb_10Bi ₂ S ₃ /TiO ₂	14.3	9.9	0	16.2	83.8	62.2	3.8	0	0.1	9.7	
10Er_Bi ₂ S ₃ QDs	0	22.3	3.6	14.1	82.3	42.0	14.8	0.6	0	20.3	
10Yb_Bi ₂ S ₃ QDs	0	23.9	2.3	10.8	86.9	46.0	12.4	0	0.2	17.5	
10Yb_10Bi ₂ S ₃ /TiO ₂ _20h_TEOA	21.5	1.8	54.7	13.8	31.5	59.2	0.4	0	0.1	17.0	
10Yb_10Bi ₂ S ₃ /TiO ₂ _20h_ES	19.2	5.9	23.2	9.4	67.4	64.1	1.1	0	0.1	9.6	

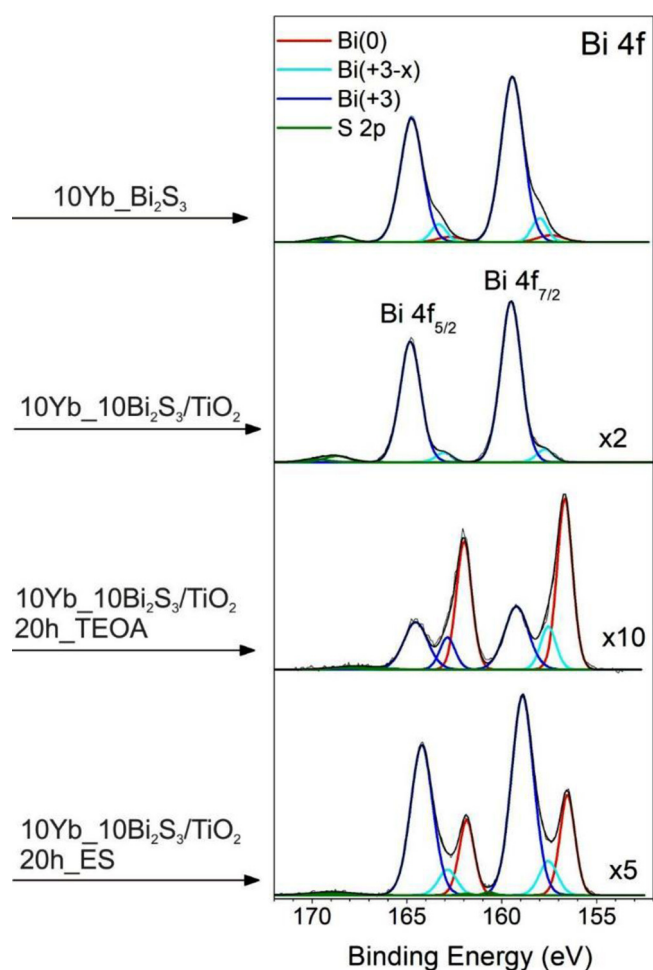


Fig. 6. Bi 4f X-ray photoelectron spectra of 10Yb_10Bi₂S₃/TiO₂ before and after photocatalytic processing in 0.1 M Na₂S/0.5 M Na₂SO₃/1 M NaOH and 10 wt% TEOA. The corresponding Bi 4f spectrum for 10Yb_10Bi₂S₃ QDs without the TiO₂ matrix is shown for comparison.

oxide phases in QDs could improve the transport of photogenerated charges. Moreover, Bi₂S₃ facilitated hydrogen generation because of the appropriate position of the Bi₂S₃ CB edge, while the exclusive presence of Bi₂O₃ was undesirable. The reaction mechanism involving such a composite is comprehensively described in section 3.7.

Blank experiments indicated that a certain amount of hydrogen is generated in the absence of photocatalysts via direct photolysis of the

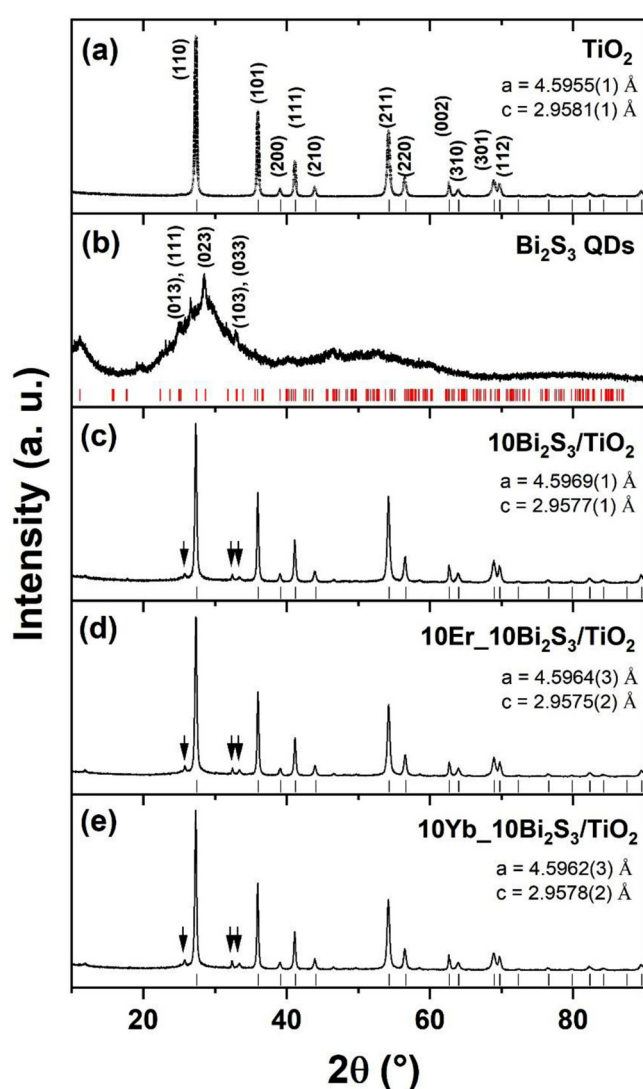


Fig. 7. pXRD patterns of (a) bare TiO₂, (b) Bi₂S₃ QDs, (c) 10Bi₂S₃/TiO₂, (d) 10Er_10Bi₂S₃/TiO₂, and (e) 10Yb_10Bi₂S₃/TiO₂. Vertical bars show the expected peak positions for rutile TiO₂ (black) and Bi₂S₃ (red). Arrows in (c–e) indicate peaks of monoclinic Bi₂O₃. The depicted lattice parameters of rutile TiO₂ were estimated by the Le Bail method. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

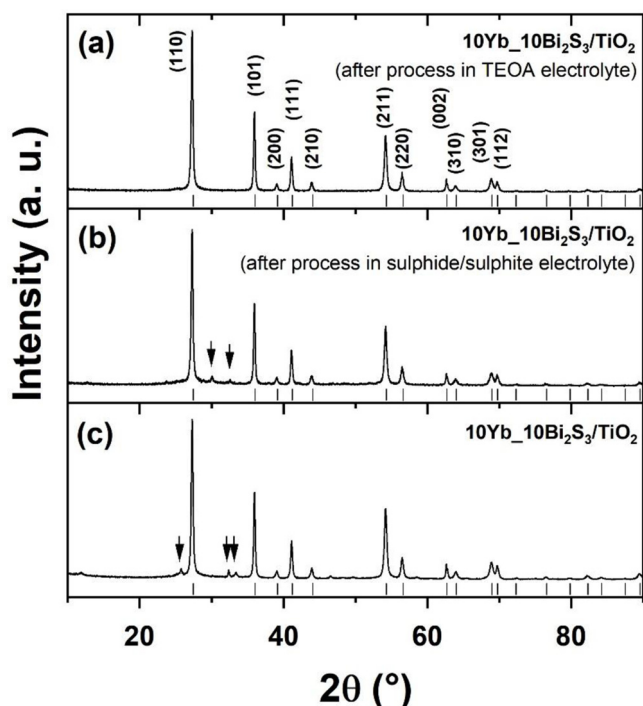


Fig. 8. pXRD patterns of (c) pristine $10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$ and the same composite after the photocatalytic process in (a) TEOA and (b) sulphide/sulphite electrolytes. Arrows in (b) and (c) indicate the peaks of an unknown phase and monoclinic Bi_2O_3 , respectively.

$\text{Na}_2\text{S}/\text{Na}_2\text{SO}_3$ electrolyte [87], as discussed in detail in section 3.7. To minimise the effect of sacrificial agent hydrolysis, we used 10 wt% aqueous triethanolamine (TEOA) as an appropriate sacrificial agent for sulphide and oxide-based photocatalysts. However, no hydrogen evolution was previously observed during TEOA irradiation in the absence of a photocatalyst [87]. The efficiencies of hydrogen generation in the presence of $\text{Na}_2\text{S}/\text{Na}_2\text{SO}_3$ and TEOA with and without photocatalysts

over 4 and 20 h are presented in Fig. 10. The results obtained for the TEOA electrolyte were consistent with those reported previously [87] and confirmed that hydrogen is not generated during irradiation in the absence of a photocatalyst. On the other hand, H_2 was generated when the Yb-doped Bi_2S_3 QD/rutile composite was introduced into this system, although the hydrogen yield dropped from $376.4\text{--}72.2\ \mu\text{mol g}_{\text{cat}}^{-1}$ when TEOA was used as a sacrificial agent instead of $\text{Na}_2\text{S}/\text{Na}_2\text{SO}_3$. Catalyst stability was probed by a long-term (20-h) hydrogen evolution test in the presence of the most active sample ($10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$) and both sacrificial agents (Fig. 10c). As a result, hydrogen was constantly produced in the presence of both $\text{Na}_2\text{S}/\text{Na}_2\text{SO}_3$ and TEOA, although the yield observed after 20-h irradiation in the former case ($1576.7\ \mu\text{mol g}_{\text{cat}}^{-1}$) was much higher than that in the latter case ($264.2\ \mu\text{mol g}_{\text{cat}}^{-1}$). After these tests, the spent photocatalyst was collected and characterised by XPS and XRD. Both techniques revealed the destructive effect of TEOA on the Yb- Bi_2S_3 QD/ TiO_2 photocatalyst (see detailed discussion in section 3.3 and 3.4). On the other hand, the catalyst was stable during irradiation in the sulphide/sulphite electrolyte. Furthermore, XRD analysis indicated the incorporation of sodium derived from the sulphide/sulphite electrolyte (1 M NaOH) and the creation of a new crystalline phase, which could not be matched to any pattern of crystallographic databases (Fig. 8b). The available literature presents some reports on the photocatalytic activity increase of various photocatalysts [88–90]. Fig. 11 shows images of $10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$ before and after processing in two different electrolytes and the colours of these electrolytes before and after processing. Notably, the originally colourless TEOA electrolyte became yellow-brown after the photocatalytic process, while the photocatalyst powder simultaneously turned from brown-yellow to light yellow. This behaviour suggested the dissolution of brown Bi_2S_3 QDs in the electrolyte during irradiation. In contrast, the sulphide/sulphite electrolyte remained colourless after 20-h irradiation, even though the photocatalyst became darker, probably because of sodium incorporation.

Finally, all photocatalysts were tested for hydrogen evolution activity in the sulphide/sulphite electrolyte under visible-light irradiation. Notably, hydrogen production after 4-h irradiation was observed only for three samples, but hydrogen yields were much lower than those observed in UV-vis tests (Fig. 10d). Thus, only $10\text{Bi}_2\text{S}_3/\text{TiO}_2$,

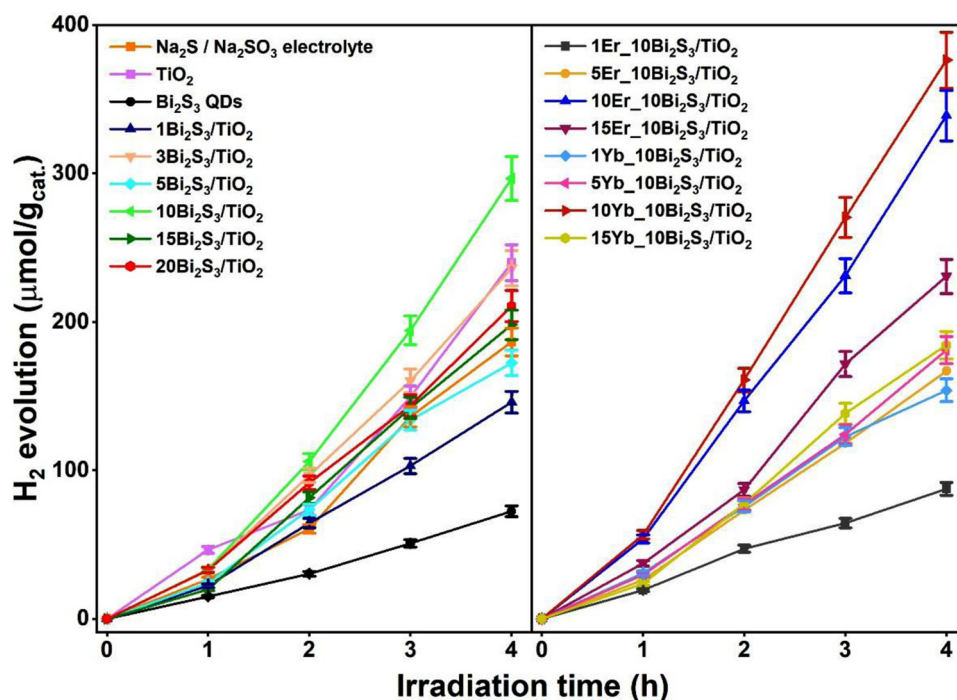


Fig. 9. Profiles of photocatalytic hydrogen evolution under UV-vis irradiation.

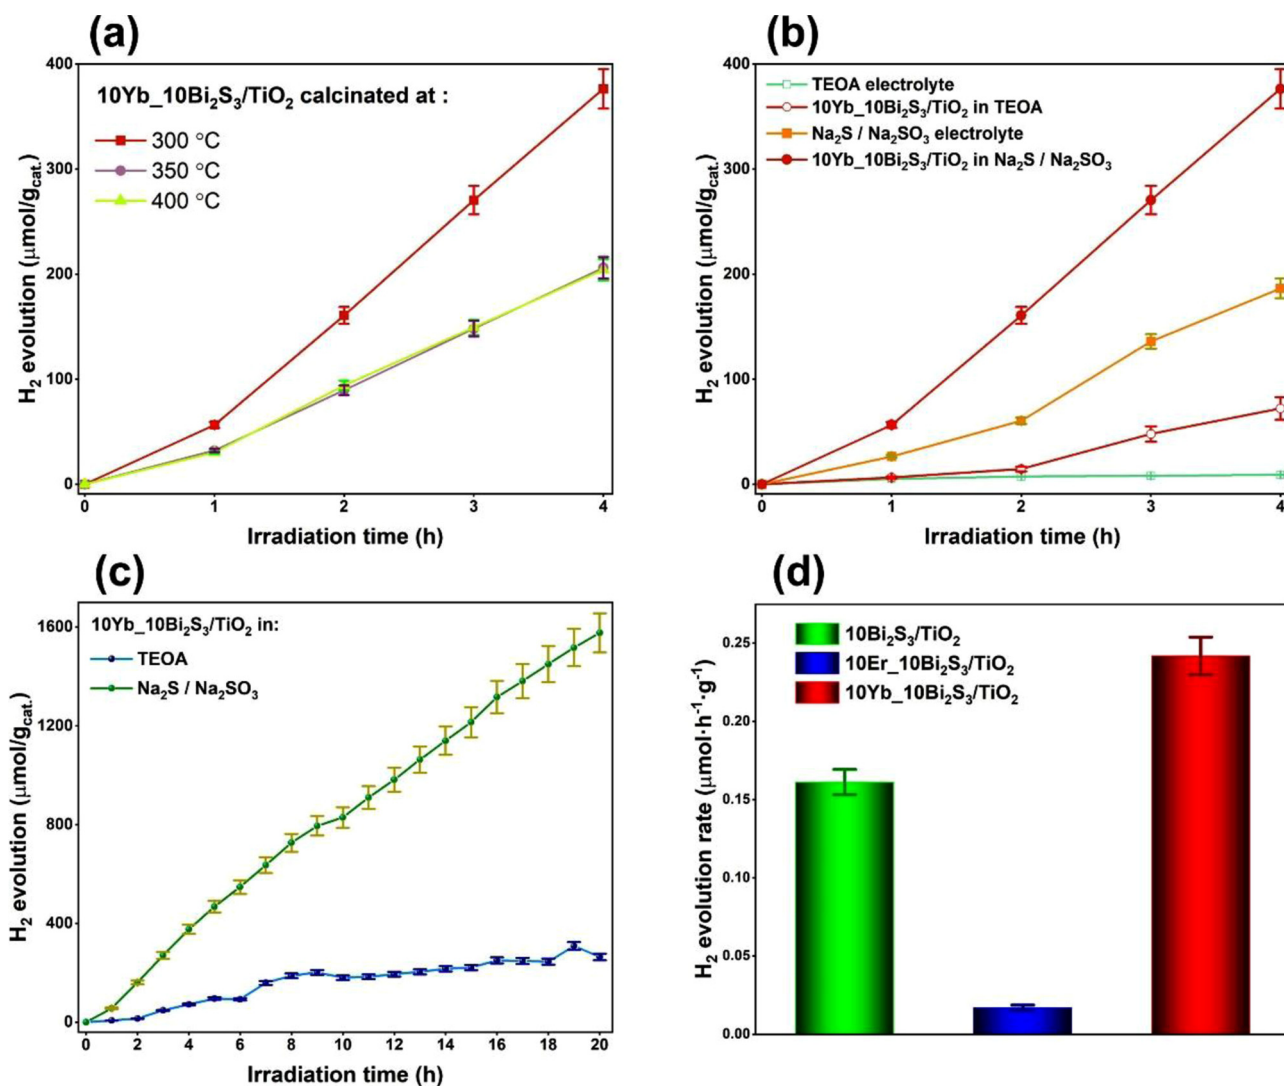


Fig. 10. Photocatalytic hydrogen evolution (a) under UV–vis irradiation in the sulphide/sulphite electrolyte in the presence of 10Yb₁₀Bi₂S₃/TiO₂ calcined at different temperatures; (b) under UV–vis irradiation in the presence of 10Yb₁₀Bi₂S₃/TiO₂ in two different electrolytes; (c) under long-term UV–vis irradiation in the presence of 10Yb₁₀Bi₂S₃/TiO₂ in two different electrolytes; (d) under 4-h visible-light irradiation in the presence of 10Yb₁₀Bi₂S₃/TiO₂ in the sulphide/sulphite electrolyte.

10Er₁₀Bi₂S₃/TiO₂, and 10Yb₁₀Bi₂S₃/TiO₂ samples featured measurable visible light–induced photoactivity. A reference test revealed that no hydrogen was produced in the sulphur-based electrolyte under visible-light irradiation in the absence of a photocatalyst.

3.6. Theoretical calculations

The effect of doping on the photocatalytic activity of RE-Bi₂S₃ QDs was probed by DFT-based electronic structure calculations. Pristine Bi₂S₃ has an orthorhombic structure that belongs to the *Pbnm* space group (symmetry No. 62), with its crystals having a layered structure across the *a* lattice vector (Fig. 12 and Table 4). The crystal structure and physical properties of Bi₂S₃ computed by SCAN + rVV10 are presented in Table 4.

The band structure of pristine Bi₂S₃ was computed using both SCAN + rVV10 and hybrid HSE12 functionals. The simulations suggested a system with an indirect BG of 1.4 eV (1.98 eV for HSE12) (cf. Fig. 13), in good agreement with experimental data [91]. Furthermore, according to the computed partial density of states (PDOS), the upper valence band comprised S 2p states with a small contribution of Bi 6s and Bi 6p states, while the lower CB comprised Bi 6p and S 2p states (Fig. 13b).

The SCAN + rVV10-computed PDOS for defects in a (1 × 3 × 1) Bi₂S₃ supercell with V_S and V_{Bi} vacancies (Fig. 14a) are displayed in Fig. 14b and Table 5. V_S defects showed the formation of a defective level within the BG that features contributions of S 2p and Bi 6p states, while V_{Bi} defects showed the formation of a hole state above the VB (cf. Fig. 14b).

The electronic properties of RE-Bi₂S₃ QDs were simulated using a 1 × 3 × 1 supercell of Bi₂S₃ containing 60 atoms (i.e., 24 Bi atoms and 36 S atoms), which corresponds to an RE content of ~33 mg per gram Bi₂S₃. Within this supercell, we first investigated the formation of S and Bi vacancies (V_S and V_{Bi}, respectively) and then, based on the obtained results, considered RE doping on V_S(3) (RE_S) and V_{Bi}(2) (RE_{Bi}) sites as well as RE interstitials (RE_{int}). The crystal symmetry of Bi₂S₃ suggests that it has three S and two Bi non-equivalent sites, as displayed in Fig. 14a. DFT calculations were performed for each vacancy type (V_S and V_{Bi}), with the computed formation energies of neutral defects listed in Table 5. The most stable vacancy formation site for S (Bi) was identified as V_S(3), with the corresponding formation energy equalling 4.66 eV [7.36 eV for V_{Bi}(2)] (cf. Fig. 14a, Table 5).

Then, we investigated the doping of RE on V_S(3) and V_{Bi}(2) sites and the computed formation energies of different configurations, with results listed in Table 5. In addition, we also considered RE interstitials

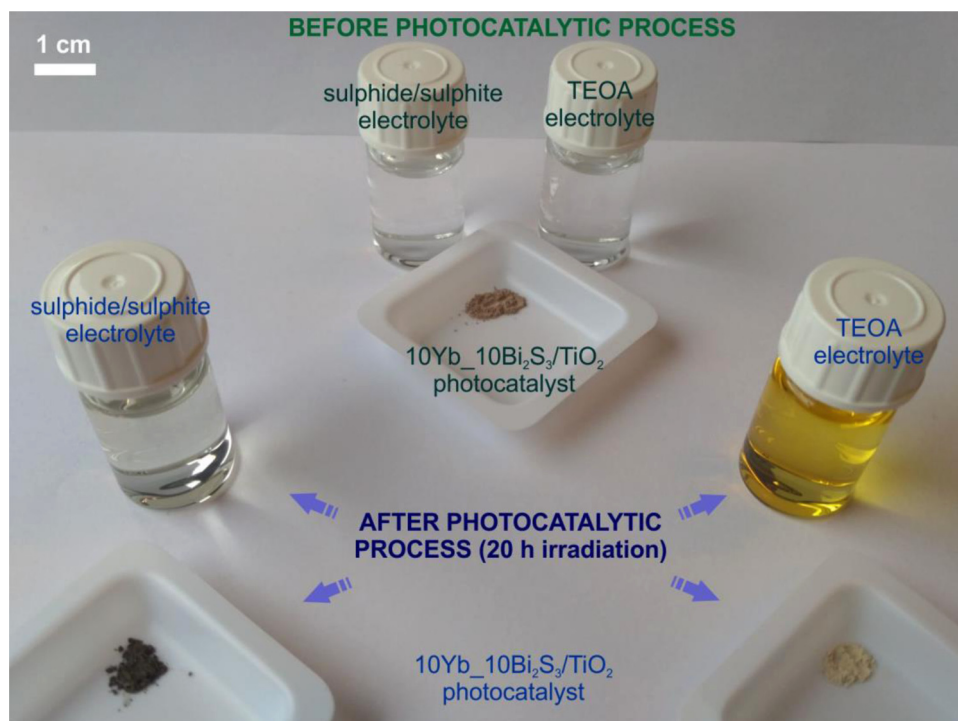


Fig. 11. Images of electrolytes and photocatalysts before and after prolonged (20-h) photocatalytic hydrogen generation.

located on the RE_{int} site, as displayed in Fig. 14a. Fig. 15 displays the electronic structure computed for RE_S , RE_{Bi} , and RE_{int} . The calculations yielded Er_S and Er_{int} with a Fermi level within the CB, while Yb_S and Yb_{int} showed a defective level within the BG with S 2p + Bi 6p character. Finally, Er_{Bi} and Yb_{Bi} had a hole defect state at the VB. Considering the results for RE occupying S sites, Bi sites, and interstitials, our SCAN + rVV10 calculations suggested that for Er, the most likely defect site location is Er_{Bi} with a formation energy of -6.40 eV (Table 5). In the case of Yb, Yb_{int} is the most likely site with a formation energy of -3.45 eV (Table 5). The electronic structures computed for the most stable defect location of Er (Er_{Bi}) and Yb (Yb_{int}) are displayed in Fig. 16. The computed PDOS show that Er_{Bi} - Bi_2S_3 QDs have a BG of 1.4 eV, while the BG of Yb_{int} - Bi_2S_3 QDs equals 0.4 eV.

The computed PDOS for Er_{Bi} show no defective level within the BG, while Yb_{int} presents a defect level with S 2p + Bi 6p character within the BG (Fig. 16). The electronic structures computed for other cases yield Er_S and Er_{int} with the Fermi level within the CB. Yb_S and Yb_{int} show a defect level with S 2p + Bi 6p character within the BG. Finally, Er_{Bi} and Yb_{Bi} have a hole defect state at the VB (cf. Fig. 15). Doping with Yb_{int} and Er_{int} was calculated to decrease the BG from 1.4 (1.98) to 0.4 and 0.7 eV, respectively. Interestingly, the RE_S defective site in RE - Bi_2S_3 QDs also decreased the BG, while the RE_{Bi} defective site had no

Table 4

Crystallographic data and physical properties of pristine Bi_2S_3 computed by SCAN + rVV10. The values correspond to those of the predicted unit cell, with u , v and w being fractional coordinates. The atomic sites correspond to those in Fig. 12. The E_g value in parentheses is the one predicted by HSE12.

Property	Calculated (SCAN + rVV10)	Sites			
		u	v	w	
Space group	<i>Pbnm</i>	Bi(1)	0.0128	0.2500	0.1735
a (Å)	11.366	Bi(2)	0.1598	0.7500	0.4654
b (Å)	3.985	S(1)	0.1223	0.7500	0.0569
c (Å)	11.103	S(2)	0.0505	0.2500	0.6297
$\alpha = \beta = \gamma$ (°)	90	S(3)	0.2147	0.2500	0.3059
Volume (Å ³)	502.91				
B_0 (GPa)	34.0				
E_g (eV)	1.4 (1.98)				

significant influence on the BG (Table 5).

3.7. Mechanism of photocatalytic reaction

Based on experimental and theoretical studies as well as on literature data [92,93], we proposed a mechanism for photocatalytic

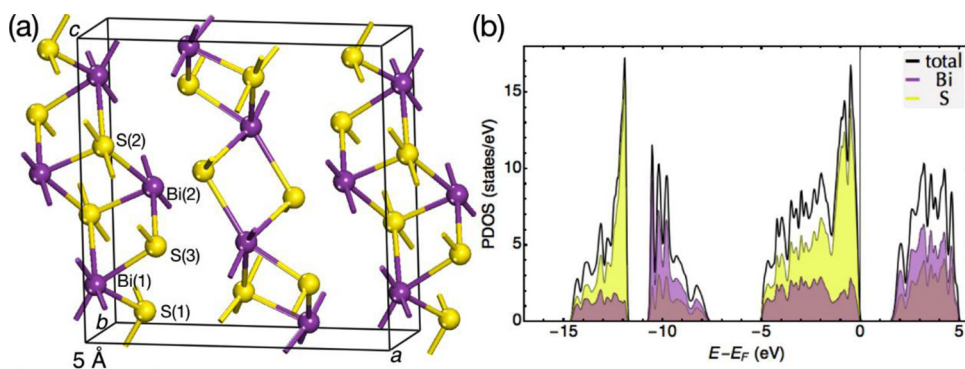


Fig. 12. (Colour online) (a) Crystal structure of pristine Bi_2S_3 (*Pbnm* space group), with Bi (S) atoms represented by violet (yellow) spheres and the black line box outlining the unit cell. The S and Bi sites are labelled according to Table 4. (b) Partial density of states of pristine Bi_2S_3 computed by SCAN + rVV10. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

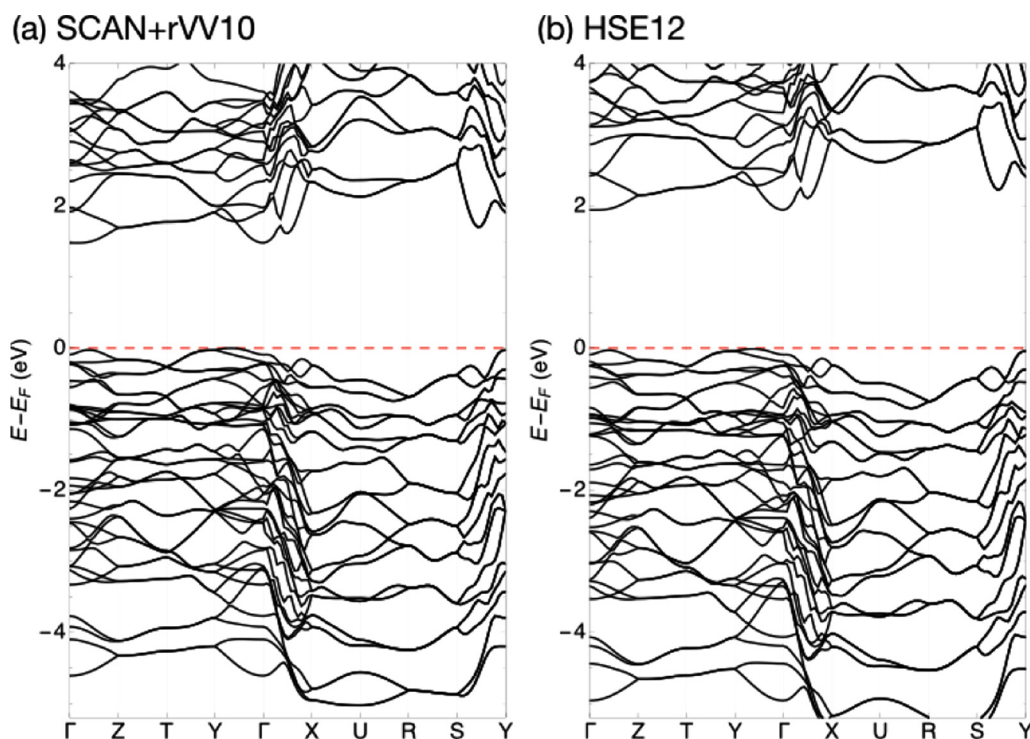


Fig. 13. Band structure of the pristine crystal structure of Bi_2S_3 computed using (a) SCAN + rVV10 (BG = 1.40 eV) and (b) HSE12 (BG = 1.98 eV). The results indicate the presence of an indirect BG.

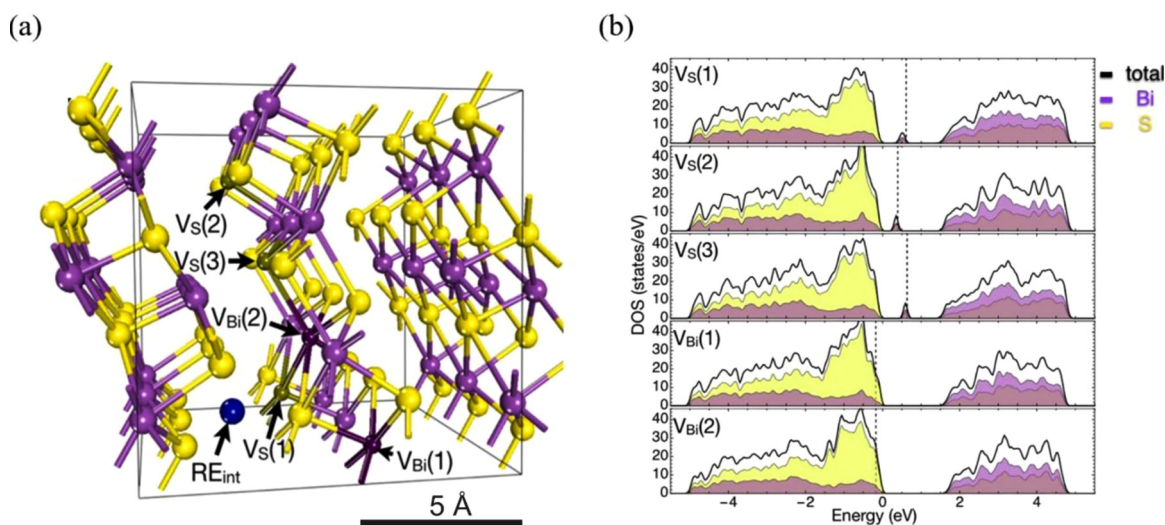


Fig. 14. (a) Bi_2S_3 ($1 \times 3 \times 1$) supercell with the location of defect sites as presented in Table 5, with violet (dark-violet) and yellow (dark-yellow) spheres representing Bi (V_{Bi}) and S (V_{S}) atoms (sites), respectively, and the dark-blue sphere showing the position of the RE interstitial. (b) SCAN + rVV10-computed PDOS for a ($1 \times 3 \times 1$) Bi_2S_3 supercell with V_{S} and V_{Bi} sites. The Fermi level is indicated by a vertical dotted line. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

Table 5

SCAN + rVV10-computed formation energies (E_{for}) and BGs (E_{g}) [both in eV] for neutral defects: S and Bi vacancies (V_{S} and V_{Bi} , respectively). RE doping on S and Bi sites (RE_{S} and RE_{Bi}) and RE interstitials, RE_{int} with RE = Er and Yb. Defect labelling is in accordance with Fig. 14a.

	V_{S}			V_{Bi}		RE_{S}		RE_{Bi}		RE_{int}	
	1	2	3	1	2	Er	Yb	Er	Yb	Er	Yb
E_{for}	4.84	4.78	4.66	7.53	7.36	-1.65	0.79	-6.40	-2.10	-5.73	-3.45
E_{F}	BG	BG	BG	VB	VB	CB	GB	VB	VB	CB	GB
E_{g}	0.8	0.9	0.7	1.4	1.4	0.7	0.4	1.4	1.5	0.7	0.4


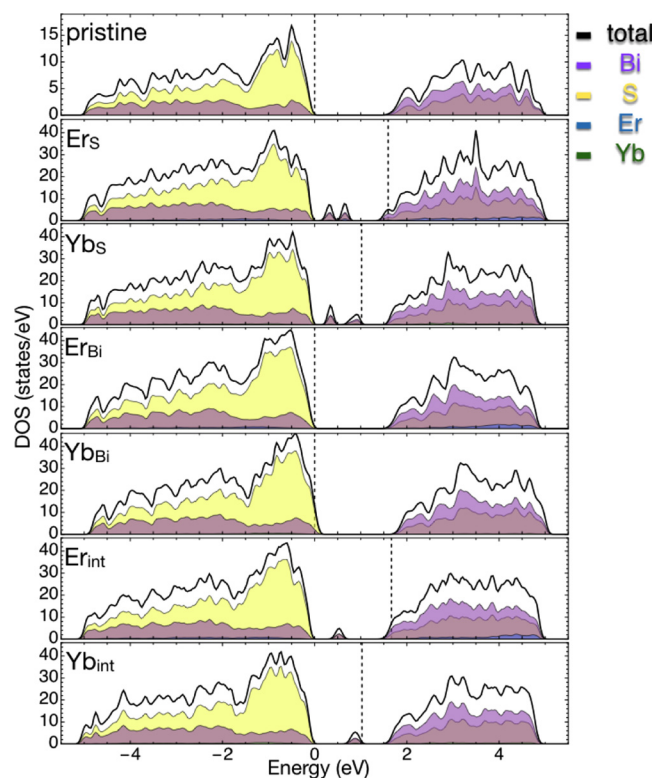





Fig. 15. (Colour online) SCAN + rVV10-computed PDOS for the $(1 \times 3 \times 1)$ Bi_2S_3 supercell with RE_S , RE_Bi , and RE_int defects. The Fermi level is located along the dotted line.

hydrogen generation over the most active photocatalyst, $10\text{Yb}_{10}\text{Bi}_2\text{S}_3/\text{TiO}_2$ (Fig. 17). In line with the results of XPS analysis, which showed the presence of TiO_2 as well as Bi_2O_3 and Bi_2S_3 together with electronic states identifying the presence of Yb, the proposed mechanism involves interactions between the three semiconductors (TiO_2 , Bi_2O_3 , and Bi_2S_3 doped with Yb^{3+}).

As sulphides are known to be unstable during photocatalytic reactions [94,95] because of photocorrosion, Bi_2S_3 was also expected to show instability. Photocatalyst excitation affords electron-hole pairs, with electrons involved in the reduction of water to molecular hydrogen and the remaining holes involved in the oxidation of the sulphur-based photocatalyst (reaction (1)). Similarly to the case of CdS [87], Bi ions can be released into the solution upon the concomitant precipitation of elemental S to rapidly decrease catalyst activity and hydrogen yield.





Sulphide photocorrosion can be inhibited through the use of a suitable sacrificial agent [87,96,97], as described in our investigations. In the case of sulphides, sulphur-based electrolytes containing Na_2S , Na_2SO_3 , and NaOH are most often used [87,97,98]. In these electrolytes, S^{2-} and SO_3^{2-} ions act as electron donors and participate in a series of reactions during the photocatalytic process to afford other sulphur-based ions such as S_2^{2-} , $\text{S}_2\text{O}_3^{2-}$, SO_4^{2-} , and $\text{S}_2\text{O}_6^{2-}$ [87,96]. During exposure to UV-vis light, the photocatalyst (TiO_2 as well as Bi_2O_3 and Bi_2S_3) is excited, which is followed by electron-hole generation in all involved semiconductors, as shown in reaction (2–4).



Electrons from the TiO_2 CB can be transported to the lower-lying CB of Bi_2O_3 , while holes from the TiO_2 VB can be directly involved in the oxidation of water to oxygen.

In turn, holes created in the Bi_2S_3 VB can take part in the oxidation of S^{2-} and SO_3^{2-} anions to $\text{S}_2\text{O}_3^{2-}$ ions (reaction (5)), which are subsequently oxidised to $\text{S}_4\text{O}_6^{2-}$ ions (reaction (6)) or reduced by electrons created in the Bi_2O_3 CB to $\text{S}^{2-} + \text{SO}_3^{2-}$ anions (reaction (7)). Additionally, in an alkaline environment (NaOH), $\text{S}_4\text{O}_6^{2-}$ ions can decompose into SO_3^{2-} and $\text{S}_2\text{O}_3^{2-}$ (reaction (8)), while $\text{S}_2\text{O}_3^{2-}$ ions, under the influence of light and hydroxyl ions, generate SO_3^{2-} and S^{2-} (reaction (9)). These ions (see Fig. 17) can be oxidised by holes originating from the Bi_2S_3 VB to $\text{S}_2\text{O}_3^{2-}$ ions, and the entire reaction cycle is repeated.



In this way, the oxidising effect of holes on the sulphide photocatalyst is blocked, and high-energy electrons arising from the Bi_2S_3 CB can be directly involved in the reduction of water to molecular hydrogen (reaction (10)), considering that Bi_2S_3 has the highest potential to reduce water molecules. Furthermore, the presence of Bi_2S_3 crystal lattice defects in the form of Yb^{3+} ions facilitates photocatalyst excitation with lower-energy irradiation by narrowing the BG of Bi_2S_3 , as also demonstrated by computer simulations (Fig. 16).

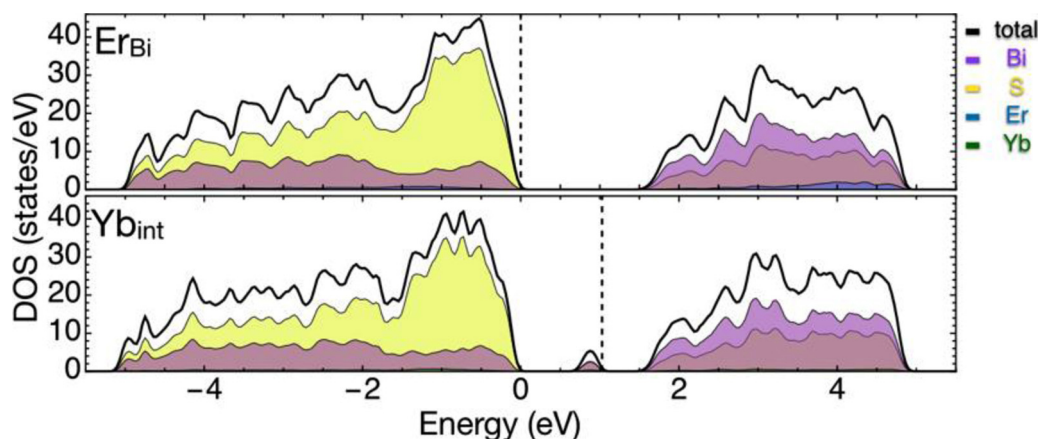


Fig. 16. (Colour online) SCAN + rVV10-computed PDOS for the most stable RE defects: Er_Bi and Yb_int , with dotted line indicating the position of the Fermi level.


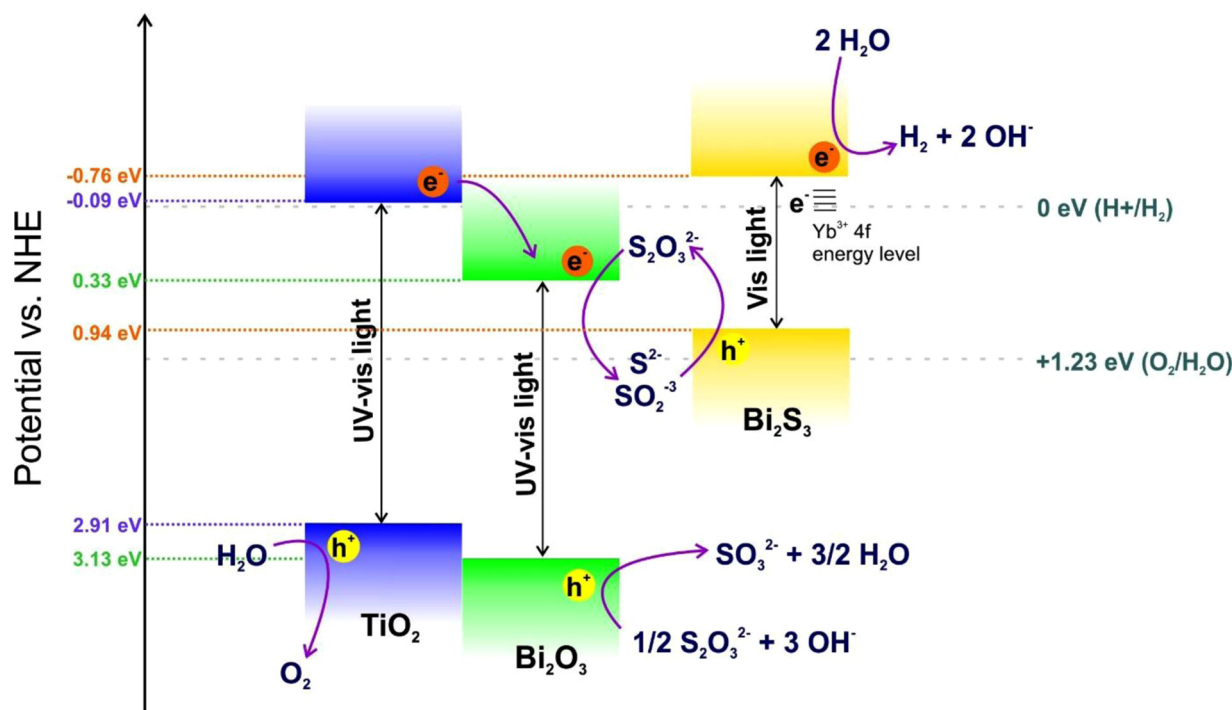


Fig. 17. Proposed mechanism of photocatalytic water splitting under UV–vis light in the presence of TiO_2 decorated by Yb-doped $\text{Bi}_2\text{O}_3/\text{Bi}_2\text{S}_3$ QDs.



The large amount of hydrogen generated during the irradiation of the sulphur-based electrolyte in the absence of any photocatalyst can be explained by reaction (11).



4. Conclusion

Photocatalysts including Bi_2S_3 and Er- or Yb-doped Bi_2S_3 QDs deposited on rutile TiO_2 spheres were prepared and characterised in terms of morphology and structural, surface, and optical properties. SEM and TEM imaging confirmed the presence of Bi_2S_3 and RE- Bi_2S_3 QDs (with diameters of 4–5 nm) evenly distributed on nanorod-comprising TiO_2 spheres with an expanded surface. UV–vis spectra confirmed the increase in the intensity of visible light absorption by TiO_2 after its decoration with pristine or doped Bi_2S_3 QDs. Moreover, photoluminescence spectroscopy revealed that compared to bare TiO_2 , these hybrids featured a lower luminescence intensity. XPS analysis of the photocatalyst surface confirmed the presence of electron states due to Bi_2S_3 doped with Yb^{3+} and Er^{3+} , while XRD spectroscopy indicated the presence of only Bi_2O_3 and TiO_2 phases in composite samples. These findings demonstrated the partial oxidation of Bi_2S_3 and RE-doped Bi_2S_3 QDs on the TiO_2 surface during annealing at 300 °C in the last stage of the synthesis. As a result, the Bi_2O_3 - Bi_2S_3 - TiO_2 system composed of three semiconductors and doped with Yb or Er was constructed, and the action synergy of these components was observed for photocatalytic water decomposition to generate hydrogen under UV–vis and visible light. The highest photocatalytic activity was observed for 10Yb-10 $\text{Bi}_2\text{S}_3/\text{TiO}_2$, both under UV–vis and visible light, with the corresponding rate constant of hydrogen evolution in a sulphur-based electrolyte oscillating at 94.1 and 0.24 $\mu\text{mol g}^{-1} \text{h}^{-1}$, respectively. The $\text{Na}_2\text{S}/\text{Na}_2\text{SO}_3$ electrolyte stabilised the photocatalyst during the photocatalytic process, in contrast to the 10 wt% TEOA electrolyte, which had a destructive effect on Bi_2S_3 QDs. To better understand the photocatalytic reaction mechanism and the structure of doped Bi_2S_3 QDs, a RE- Bi_2S_3 QDs model was constructed, and theoretical calculations were

performed. As a result, it was proven that Er^{3+} and Yb^{3+} ions can be incorporated into the Bi_2S_3 structure, with the former ion preferentially occupying the sites of Bi atoms, and the latter ion preferring to be located in the interstitial space of the cell. This incorporation reduced the BGs of Er- Bi_2S_3 and Yb- Bi_2S_3 semiconductors, improved the transport of photogenerated charges during light exposure, and inhibited the recombination of these charges.

CRediT authorship contribution statement

Magdalena Miodyńska: Investigation, Methodology, Data curation, Writing - original draft, Writing - review & editing, Visualization. **Alicja Mikolajczyk:** Formal analysis, Software. **Beata Bajorowicz:** Project administration. **Julia Zwara:** Investigation. **Tomasz Klimczuk:** Investigation. **Wojciech Lisowski:** Investigation. **Grzegorz Trykowski:** Investigation. **Henry P. Pinto:** Formal analysis, Software. **Adriana Zaleska-Medynska:** Conceptualization, Supervision, Writing - review & editing, Project administration, Funding acquisition.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

This research was financially supported by the National Science Centre of Poland (grant 2016/23/B/ST8/03336: “Mechanism of quantum dot excitation in photocatalytic reactions”) and the Foundation for Polish Science (FNP) (START 001.2019). We also acknowledge Maria Zaleska for graphical abstract design and drawing.

Appendix A. Supplementary data

Supplementary data associated with this article can be found, in the online version, at <https://doi.org/10.1016/j.apcatb.2020.118962>.

References

- [1] P. Zhang, T. Song, T. Wang, H. Zeng, Enhancement of hydrogen production of a Cu-TiO₂ nanocomposite photocatalyst combined with broad spectrum absorption sensitizer Erythrosin B, *RSC Adv.* 7 (2017) 17873–17881, <https://doi.org/10.1039/C6RA27686E>.
- [2] A. Zaleska-Medynska, *Metal Oxide-Based Photocatalysis: Fundamentals and Prospects for Application*, Elsevier, 2018.
- [3] J. Huo, L. Fang, Y. Lei, G. Zeng, H. Zeng, Facile preparation of yttrium and aluminum co-doped ZnO via a sol-gel route for photocatalytic hydrogen production, *J. Mater. Chem. A* 2 (2014) 11040–11044, <https://doi.org/10.1039/C4TA02207F>.
- [4] H. Liu, K. Zhao, T. Wang, J. Deng, H. Zeng, Facile preparation of cerium (Ce) and antimony (Sb) codoped SnO₂ for hydrogen production in lactic acid solution, *Mater. Sci. Semicond. Process.* 40 (2015) 670–675, <https://doi.org/10.1016/j.mssp.2015.07.041>.
- [5] F. Raziq, M. Humayun, A. Ali, T. Wang, A. Khan, Q. Fu, W. Luo, H. Zeng, Z. Zheng, B. Khan, H. Shen, X. Zu, S. Li, L. Qiao, Synthesis of S-Doped porous g-C₃N₄ by using ionic liquids and subsequently coupled with Au-TiO₂ for exceptional cocatalyst-free visible-light catalytic activities, *Appl. Catal. B Environ.* 237 (2018) 1082–1090, <https://doi.org/10.1016/j.apcatb.2018.06.009>.
- [6] T. Song, P. Zhang, T. Wang, A. Ali, H. Zeng, Constructing a novel strategy for controllable synthesis of corrosion resistant Ti₃+ self-doped titanium-silicon materials with efficient hydrogen evolution activity from simulated seawater, *Nanoscale* 10 (2018) 2275–2284, <https://doi.org/10.1039/C7NR07095K>.
- [7] B. Bajorowicz, A. Gołębiewska, J. Nadolna, A. Malankowska, M.P. Kobyłański, A. Zaleska-Medynska, Quantum dot-decorated semiconductor micro- and nanoparticles: a review of their synthesis, characterization and application in photocatalysis, *Adv. Colloid Interface Sci.* 256 (2018) 352–372, <https://doi.org/10.1016/j.cis.2018.02.003>.
- [8] J. Sowiak, M. Miodyńska, B. Bajorowicz, A. Mikolajczyk, W. Lisowski, T. Klimczuk, D. Kaczor, A. Zaleska Medynska, A. Malankowska, Optical and photocatalytic properties of rare earth metal-modified ZnO quantum dots, *Appl. Surf. Sci.* 464 (2019) 651–663, <https://doi.org/10.1016/j.apsusc.2018.09.104>.
- [9] M.C. Beard, A.G. Midgett, M.C. Hanna, J.M. Luther, B.K. Hughes, A.J. Nozik, Comparing multiple exciton generation in quantum dots to impact ionization in bulk semiconductors: implications for enhancement of solar energy conversion, *Nano Lett.* 10 (2010) 3019–3027, <https://doi.org/10.1021/nl101490z>.
- [10] A.H. Reshak, Quantum dots in photocatalytic applications: efficiently enhancing visible light photocatalytic activity by integrating CdO quantum dots as sensitizers, *Phys. Chem. Chem. Phys.* 19 (2017) 24915–24927, <https://doi.org/10.1039/C7CP05312F>.
- [11] L. Ge, F. Zuo, J. Liu, Q. Ma, C. Wang, D. Sun, L. Bartels, P. Feng, Synthesis and efficient visible light photocatalytic hydrogen evolution of polymeric g-C₃N₄ coupled with CdS quantum dots, *J. Phys. Chem. C* 116 (2012) 13708–13714, <https://doi.org/10.1021/jp3041692>.
- [12] C. Wang, R.L. Thompson, P. Ohodnicki, J. Baltrus, C. Matranga, Size-dependent photocatalytic reduction of CO₂ with PbS quantum dot sensitized TiO₂ heterostructured photocatalysts, *J. Mater. Chem.* 21 (2011) 13452–13457, <https://doi.org/10.1039/C1JM12367J>.
- [13] G.-S. Li, D.-Q. Zhang, J.C. Yu, A new visible-light photocatalyst: CdS quantum dots embedded mesoporous TiO₂, *Environ. Sci. Technol.* 43 (2009) 7079–7085, <https://doi.org/10.1021/es9011993>.
- [14] X. Wang, Z. Wang, M. Zhang, X. Jiang, Y. Wang, J. Lv, G. He, Z. Sun, Nanoheterostructure Engineering of CdS/PbS Quantum-Dot Co-Sensitized TiO₂ Nanorod Arrays for Enhanced Photoelectrochemical and Photocatalytic Properties, *J. Electrochem. Soc.* 164 (2017) H707–H713, <https://doi.org/10.1149/2.0291712jes>.
- [15] B. Bajorowicz, J. Nadolna, W. Lisowski, T. Klimczuk, A. Zaleska-Medynska, The effects of bifunctional linker and reflux time on the surface properties and photocatalytic activity of CdTe quantum dots decorated KTaO₃ composite photocatalysts, *Appl. Catal. B Environ.* 203 (2017) 452–464, <https://doi.org/10.1016/j.apcatb.2016.10.027>.
- [16] S. Azimi, A. Nezamzadeh-Ejhieh, Enhanced activity of clinoptilolite-supported hybridized PbS–CdS semiconductors for the photocatalytic degradation of a mixture of tetracycline and cephalixin aqueous solution, *J. Mol. Catal. A Chem.* 408 (2015) 152–160, <https://doi.org/10.1016/j.molcata.2015.07.017>.
- [17] Y. Bessekhouad, D. Robert, J.V. Weber, Bi₂S₃/TiO₂ and CdS/TiO₂ heterojunctions as an available configuration for photocatalytic degradation of organic pollutant, *J. Photochem. Photobiol. A Chem.* 163 (2004) 569–580, <https://doi.org/10.1016/j.jphotochem.2004.02.006>.
- [18] J. Fu, B. Chang, Y. Tian, F. Xi, X. Dong, Novel C₃N₄–CdS composite photocatalysts with organic–inorganic heterojunctions: in situ synthesis, exceptional activity, high stability and photocatalytic mechanism, *J. Mater. Chem. A* 1 (2013) 3083–3090, <https://doi.org/10.1039/C2TA00672C>.
- [19] T. Lv, L. Pan, X. Liu, T. Lu, G. Zhu, Z. Sun, C.Q. Sun, One-step synthesis of CdS–TiO₂–chemically reduced graphene oxide composites via microwave-assisted reaction for visible-light photocatalytic degradation of methyl orange, *Catal. Sci. Technol.* 2 (2012) 754–758, <https://doi.org/10.1039/C2CY00452F>.
- [20] W.-C. OH, M. CHEN, K. CHO, C. KIM, Z. MENG, L. ZHU, Synthesis of Graphene-CdSe composite by a simple hydrothermal method and its photocatalytic degradation of organic dyes, *Chinese J. Catal.* 32 (2011) 1577–1583, [https://doi.org/10.1016/S1872-2067\(10\)60264-1](https://doi.org/10.1016/S1872-2067(10)60264-1).
- [21] S.W. Cao, Y.P. Yuan, J. Fang, M.M. Shahjamali, F.Y.C. Boey, J. Barber, S.C. Joachim Loo, C. Xue, In-situ growth of CdS quantum dots on g-C₃N₄ nanosheets for highly efficient photocatalytic hydrogen generation under visible light irradiation, *Int. J. Hydrogen Energy* 38 (2013) 1258–1266, <https://doi.org/10.1016/j.ijhydene.2012.10.116>.
- [22] R.M. Navarro, F. del Valle, J.L.G. Fierro, Photocatalytic hydrogen evolution from CdS–ZnO–CdO systems under visible light irradiation: Effect of thermal treatment and presence of Pt and Ru cocatalysts, *Int. J. Hydrogen Energy* 33 (2008) 4265–4273, <https://doi.org/10.1016/j.ijhydene.2008.05.048>.
- [23] S.V. Kahane, R. Sasikala, B. Vishwanadh, V. Sudarsan, S. Mahamuni, CdO–CdS nanocomposites with enhanced photocatalytic activity for hydrogen generation from water, *Int. J. Hydrogen Energy* 38 (2013) 15012–15018, <https://doi.org/10.1016/j.ijhydene.2013.09.077>.
- [24] X. Wang, G. Liu, G.Q. Lu, H.-M. Cheng, Stable photocatalytic hydrogen evolution from water over ZnO–CdS core-shell nanorods, *Int. J. Hydrogen Energy* 35 (2010) 8199–8205, <https://doi.org/10.1016/j.ijhydene.2009.12.091>.
- [25] L. Xu, W. Shi, J. Guan, Preparation of crystallized mesoporous CdS/Ta₂O₅ composite assisted by silica reinforcement for visible light photocatalytic hydrogen evolution, *Catal. Commun.* 25 (2012) 54–58, <https://doi.org/10.1016/j.catcom.2012.03.037>.
- [26] W. Cui, S. Ma, L. Liu, Y. Liang, PbS-sensitized K₂Ti₄O₉ composite: preparation and photocatalytic properties for hydrogen evolution under visible light irradiation, *Chem. Eng. J.* 204–206 (2012) 1–7, <https://doi.org/10.1016/j.cej.2012.07.075>.
- [27] M. Wang, J. Wang, S. Feng, P. Meng, Time-dependent toxicity of cadmium telluride quantum dots on liver and kidneys in mice: histopathological changes with elevated free cadmium ions and hydroxyl radicals, *Int. J. Nanomedicine* (2016) 2319–2328.
- [28] R. Hardman, Review A Toxicologic Review of Quantum Dots: Toxicity Depends on Physicochemical and Environmental Factors, *Environ. Health Perspect.* 114 (2012) 165–172, <https://doi.org/10.1289/ehp.8284>.
- [29] H. Zhang, H. Huang, H. Ming, H. Li, L. Zhang, Y. Liu, Z. Kang, Carbon quantum dots/Ag₃PO₄ complex photocatalysts with enhanced photocatalytic activity and stability under visible light, *J. Mater. Chem.* 22 (2012) 10501–10506, <https://doi.org/10.1039/C2JM30703K>.
- [30] H. Yu, Y. Zhao, C. Zhou, L. Shang, Y. Peng, Y. Cao, L.-Z. Wu, C.-H. Tung, T. Zhang, Carbon quantum dots/TiO₂ composites for efficient photocatalytic hydrogen evolution, *J. Mater. Chem. A* 2 (2014) 3344–3351, <https://doi.org/10.1039/C3TA14108J>.
- [31] H. Li, R. Liu, S. Lian, Y. Liu, H. Huang, Z. Kang, Near-infrared light controlled photocatalytic activity of carbon quantum dots for highly selective oxidation reaction, *Nanoscale* 5 (2013) 3289–3297, <https://doi.org/10.1039/C3NR00092C>.
- [32] X. Qian, D. Yue, Z. Tian, M. Reng, Y. Zhu, M. Kan, T. Zhang, Y. Zhao, Carbon quantum dots decorated Bi₂WO₆ nanocomposite with enhanced photocatalytic oxidation activity for VOCs, *Appl. Catal. B Environ.* 193 (2016) 16–21, <https://doi.org/10.1016/j.apcatb.2016.04.009>.
- [33] D. Wang, L. Guo, Y. Zhen, L. Yue, G. Xue, F. Fu, AgBr quantum dots decorated mesoporous Bi₂WO₆ architectures with enhanced photocatalytic activities for methylene blue, *J. Mater. Chem. A* 2 (2014) 11716–11727, <https://doi.org/10.1039/C4TA01444H>.
- [34] Q. Chen, R. Tong, X. Chen, Y. Xue, Z. Xie, Q. Kuang, L. Zheng, Ultrafine ZnO quantum dot-modified TiO₂ composite photocatalysts: the role of the quantum size effect in heterojunction-enhanced photocatalytic hydrogen evolution, *Catal. Sci. Technol.* 8 (2018) 1296–1303, <https://doi.org/10.1039/C7CY02310C>.
- [35] D. Qu, M. Zheng, P. Du, Y. Zhou, L. Zhang, D. Li, H. Tan, Z. Zhao, Z. Xie, Z. Sun, Highly luminescent S, N co-doped graphene quantum dots with broad visible absorption bands for visible light photocatalysts, *Nanoscale* 5 (2013) 12272–12277, <https://doi.org/10.1039/C3NR04402E>.
- [36] Y.-J. Yuan, S. Yang, P. Wang, Y. Yang, Z. Li, D. Chen, Z.-T. Yu, Z.-G. Zou, Bandgap-tunable black phosphorus quantum dots: visible-light-active photocatalysts, *Chem. Commun.* 54 (2018) 960–963, <https://doi.org/10.1039/C7CC08211H>.
- [37] I. Zns, S. Yu, X. Fan, X. Wang, J. Li, Q. Zhang, A. Xia, L. Wu, Y. Zhou, G.R. Patzke, S. Wei, Efficient photocatalytic hydrogen evolution with, *Nat. Commun.* (n.d.) 1–10. doi:10.1038/s41467-018-06294-y.
- [38] J. Sun, L. Duan, Q. Wu, W. Yao, Synthesis of MoS₂ quantum dots cocatalysts and their efficient photocatalytic performance for hydrogen evolution, *Chem. Eng. J.* 332 (2018) 449–455, <https://doi.org/10.1016/j.cej.2017.09.026>.
- [39] Y.-J. Yuan, G. Fang, D. Chen, Y. Huang, L.-X. Yang, D.-P. Cao, J. Wang, Z.-T. Yu, Z.-G. Zou, High light harvesting efficiency CuInS₂ quantum dots/TiO₂/MoS₂ photocatalysts for enhanced visible light photocatalytic H₂ production, *Dalton Trans.* 47 (2018) 5652–5659, <https://doi.org/10.1039/C8DT00356D>.
- [40] T.-L. Li, C.-D. Cai, T.-F. Yeh, H. Teng, Capped CuInS₂ quantum dots for H₂ evolution from water under visible light illumination, *J. Alloys. Compd.* 550 (2013) 326–330, <https://doi.org/10.1016/j.jallcom.2012.10.157>.
- [41] V. Ramasamy, V. Mohana, V. Rajendran, Characterization of Ca doped CeO₂ quantum dots and their applications in photocatalytic degradation, *OpenNano* 3 (2018) 38–47, <https://doi.org/10.1016/j.onano.2018.04.002>.
- [42] R. Sumi, A.R. Warrior, C. Vijayan, Visible-light driven photocatalytic activity of β-indium sulfide (In₂S₃) quantum dots embedded in Nafion matrix, *Physica E: Low-dimensional Systems and Nanostructures* 105103 (n.d.). doi:10.1088/0022-3727/47/10/105103.
- [43] N.L. Reddy, S. Emin, V.D. Kumari, S. Muthukonda Venkatakrishnan, CuO quantum dots decorated TiO₂ nanocomposite photocatalyst for stable hydrogen generation, *Ind. Eng. Chem. Res.* 57 (2018) 568–577, <https://doi.org/10.1021/acs.iecr.7b03785>.
- [44] M. Miodyńska, B. Bajorowicz, P. Mazierski, W. Lisowski, T. Klimczuk, M.J. Wiñariński, A. Zaleska-Medynska, J. Nadolna, Preparation and photocatalytic properties of BaZrO₃ and SrZrO₃ modified with Cu₂O/Bi₂O₃ quantum dots, *Solid State Sci.* 74 (2017) 13–23, <https://doi.org/10.1016/j.solidstatesciences.2017.10.003>.
- [45] X. Lin, X. Guo, W. Shi, F. Guo, H. Zhai, Y. Yan, Q. Wang, Ag₃PO₄ quantum dots

- sensitized AgVO₃ nanowires: A novel Ag₃PO₄/AgVO₃ nanojunction with enhanced visible-light photocatalytic activity, *Catal. Commun.* 66 (2015) 67–72, <https://doi.org/10.1016/j.catcom.2015.03.015>.
- [46] W. Chen, T.-Y. Liu, T. Huang, X.-H. Liu, J.-W. Zhu, G.-R. Duan, X.-J. Yang, In situ fabrication of novel Z-scheme Bi₂WO₆ quantum dots/g-C₃N₄ ultrathin nanosheets heterostructures with improved photocatalytic activity, *Appl. Surf. Sci.* 355 (2015) 379–387, <https://doi.org/10.1016/j.apsusc.2015.07.111>.
- [47] B. Li, Z. Cao, S. Wang, Q. Wei, Z. Shen, BiVO₄ quantum dot-decorated BiPO₄ nanorods 0D/1D heterojunction for enhanced visible-light-driven photocatalysis, *Dalton Trans.* 47 (2018) 10288–10298, <https://doi.org/10.1039/C8DT02402B>.
- [48] A.P. Chowdhury, B.H. Shambharkar, S.G. Ghugal, S.S. Umare, A.G. Shende, Ethylene glycol mediated synthesis of SnS quantum dots and their application towards degradation of eosin yellow and brilliant green dyes under solar irradiation, *RSC Adv.* 6 (2016) 108290–108297, <https://doi.org/10.1039/C6RA10532G>.
- [49] W. Zhao, Z. Wei, L. Ma, J. Liang, X. Zhang, Ag₂S quantum dots based on flower-like SnS₂ as matrix and enhanced photocatalytic degradation, *Materials* (2019) 1–11, <https://doi.org/10.3390/ma12040582>.
- [50] B. Bajorowicz, E. Kowalska, J. Nadolna, Z. Wei, M. Endo, B. Ohtani, A. Zaleska-Medynska, Preparation of CdS and Bi₂S₃ quantum dots co-decorated perovskite-type KNbO₃ ternary heterostructure with improved visible light photocatalytic activity and stability for phenol degradation, *Dalton Trans.* 47 (2018) 15232–15245, <https://doi.org/10.1039/C8DT03094D>.
- [51] S.R. Kadam, R.P. Panmand, R.S. Sonawane, S.W. Gosavi, B.B. Kale, A stable Bi₂S₃ quantum dot–glass nanosystem: size tuneable photocatalytic hydrogen production under solar light, *RSC Adv.* 5 (2015) 58485–58490, <https://doi.org/10.1039/C5RA10244H>.
- [52] M. Bernechea, Y. Cao, G. Konstantatos, Size and bandgap tunability in Bi₂S₃ colloidal nanocrystals and its effect in solution processed solar cells, *J. Mater. Chem. A* 3 (2015) 20642–20648, <https://doi.org/10.1039/C5TA04441C>.
- [53] P. Mazierski, A. Mikołajczyk, B. Bajorowicz, A. Malankowska, A. Zaleska-medynska, J. Nadolna, *Appl. Catal. B Environ.* 233 (2018) 301–317, <https://doi.org/10.1016/j.apcatb.2018.04.019>.
- [54] S. Obregón, A. Kubacka, M. Fernández-García, G. Colón, High-performance Er³⁺–TiO₂ system: dual up-conversion and electronic role of the lanthanide, *J. Catal.* 299 (2013) 298–306, <https://doi.org/10.1016/j.jcat.2012.12.021>.
- [55] W. Yang, X. Li, D. Chi, H. Zhang, Lanthanide-doped upconversion materials: emerging applications for photovoltaics and photocatalysis, *Nanotechnology* 482001 (n.d.). doi:10.1088/0957-4484/25/48/482001.
- [56] J. Reszczyńska, T. Grzyb, J.W. Sobczak, W. Lisowski, M. Gazda, B. Ohtani, A. Zaleska, Lanthanide co-doped TiO₂: the effect of metal type and amount on surface properties and photocatalytic activity, *Appl. Surf. Sci.* 307 (2014) 333–345, <https://doi.org/10.1016/j.apsusc.2014.03.199>.
- [57] J. Reszczyńska, T. Grzyb, J.W. Sobczak, W. Lisowski, M. Gazda, B. Ohtani, A. Zaleska, Visible light activity of rare earth metal doped (Er³⁺, Yb³⁺ or Er³⁺/Yb³⁺) titania photocatalysts, *Appl. Catal. B Environ.* 163 (2015) 40–49, <https://doi.org/10.1016/j.apcatb.2014.07.010>.
- [58] J. Reszczyńska, T. Grzyb, Z. Wei, M. Klein, E. Kowalska, B. Ohtani, A. Zaleska-Medynska, Photocatalytic activity and luminescence properties of RE³⁺–TiO₂ nanocrystals prepared by sol–gel and hydrothermal methods, *Appl. Catal. B Environ.* 181 (2016) 825–837, <https://doi.org/10.1016/j.apcatb.2015.09.001>.
- [59] P. Mazierski, W. Lisowski, T. Grzyb, M.J. Winiarski, T. Klimczuk, A. Mikołajczyk, J. Flisikowski, A. Hirsch, A. Kołakowska, T. Puzyn, A. Zaleska-medynska, J. Nadolna, Enhanced photocatalytic properties of lanthanide-TiO₂ nanotubes: an experimental and theoretical study, *Appl. Catal. B, Environ.* (2016), <https://doi.org/10.1016/j.apcatb.2016.12.044>.
- [60] X. Wang, D. Li, Y. Guo, X. Wang, Y. Du, R. Sun, Preparation of lanthanide doped CdS, ZnS quantum dots in natural polysaccharide template and their optical properties, *Opt. Mater. (Amst)*. 34 (2012) 646–651, <https://doi.org/10.1016/j.optmat.2011.09.013>.
- [61] A. Sarkar, A.B. Ghosh, N. Saha, A.K. Dutta, D.N. Srivastava, P. Paul, B. Adhikary, Enhanced photocatalytic activity of Eu-doped Bi₂S₃ nanoflowers for degradation of organic pollutants under visible light illumination, *Catal. Sci. Technol.* 5 (2015) 4055–4063, <https://doi.org/10.1039/C5CY00473J>.
- [62] Y. Xue, J. Lin, Y. Fan, A. Elsanousi, X. Xu, J. Mi, J. Li, X. Zhang, Y. Lu, T. Zhang, C. Tang, Controllable synthesis of uniformly distributed hollow rutile TiO₂ hierarchical microspheres and their improved photocatalysis, *Mater. Chem. Phys.* 143 (2013) 446–454, <https://doi.org/10.1016/j.matchemphys.2013.09.026>.
- [63] Y. Wang, F. Xin, J. Chen, T. Xiang, X. Yin, Photocatalytic reduction of CO₂ in Isopropanol on exposed 001 facets, *J. Nanosci. Nanotechnol.* 17 (2017) 1863–1869, <https://doi.org/10.1166/jnn.2017.12871>.
- [64] G. Kresse, J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Phys. Rev. B* 54 (1996) 11169–11186, <https://doi.org/10.1103/PhysRevB.54.11169>.
- [65] G. Kresse, J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, *Comput. Mater. Sci.* 6 (1996) 15–50, [https://doi.org/10.1016/0927-0256\(96\)00008-0](https://doi.org/10.1016/0927-0256(96)00008-0).
- [66] G. Kresse, D. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, *Phys. Rev. B* 59 (1999) 1758–1775, <https://doi.org/10.1103/PhysRevB.59.1758>.
- [67] J. Sun, A. Ruzsinszky, J.P. Perdew, Strongly Constrained and Appropriately Normed Semilocal Density Functional, *Phys. Rev. Lett.* 115 (2015) 36402, <https://doi.org/10.1103/PhysRevLett.115.036402>.
- [68] J. Sun, R.C. Remsing, Y. Zhang, Z. Sun, A. Ruzsinszky, H. Peng, Z. Yang, A. Paul, U. Waghmare, X. Wu, M.L. Klein, J.P. Perdew, Accurate first-principles structures and energies of diversely bonded systems from an efficient density functional, *Nat. Chem.* 8 (2016) 831.
- [69] H. Peng, Z.-H. Yang, J.P. Perdew, J. Sun, Versatile van der waals density functional based on a meta-generalized gradient approximation, *Phys. Rev. X* 6 (2016) 41005, <https://doi.org/10.1103/PhysRevX.6.041005>.
- [70] J. Heyd, G.E. Scuseria, M. Ernzerhof, J. Heyd, G.E. Scuseria, M. Ernzerhof, Hybrid functionals based on a screened Coulomb potential Hybrid functionals based on a screened Coulomb potential, *J. Chem. Phys.* 8207 (2003), <https://doi.org/10.1063/1.1564060>.
- [71] S.F. Wang, F. Gu, Z. Sen Yang, M.K. Lu, Facile synthesis of silica-coated Bi₂S₃ nanorods and hollow silica nanotubes, *J. Cryst. Growth* 282 (2005) 79–84, <https://doi.org/10.1016/j.jcrysgro.2005.04.082>.
- [72] M. Klein, J. Nadolna, A. Gołębiewska, P. Mazierski, T. Klimczuk, H. Remita, A. Zaleska-Medynska, The effect of metal cluster deposition route on structure and photocatalytic activity of mono- and bimetallic nanoparticles supported on TiO₂ by radiolytic method, *Appl. Surf. Sci.* 378 (2016) 37–48, <https://doi.org/10.1016/j.apsusc.2016.03.191>.
- [73] P. Mazierski, M. Nischk, M. Golkowska, W. Lisowski, M. Gazda, M.J. Winiarski, T. Klimczuk, A. Zaleska-Medynska, Photocatalytic activity of nitrogen doped TiO₂ nanotubes prepared by anodic oxidation: the effect of applied voltage, anodization time and amount of nitrogen dopant, *Appl. Catal. B Environ.* 196 (2016) 77–88, <https://doi.org/10.1016/j.apcatb.2016.05.006>.
- [74] H. Tang, H. Berger, P.E. Schmid, F. Lévy, Optical properties of anatase (TiO₂), *Solid State Commun.* 92 (1994) 267–271, [https://doi.org/10.1016/0038-1098\(94\)90889-3](https://doi.org/10.1016/0038-1098(94)90889-3).
- [75] F.J. Knorr, C.C. Mercado, J.L. McHale, Trap-State Distributions and Carrier Transport in Pure and Mixed-Phase TiO₂: Influence of Contacting Solvent and Interphasial Electron Transfer, *J. Phys. Chem. C* 112 (2008) 12786–12794, <https://doi.org/10.1021/jp8039934>.
- [76] P.C. A. Naumkin, A. Kraut-Vass, S. Gaarenstroom, NIST X-ray photoelectron spectroscopy database 20, version 4.1, *Natl. Inst. Stand. Technol. Gaithersbg.* (2012), <https://doi.org/10.18434/T4T88K>.
- [77] Y. Wang, Y. Wang, Y. Meng, H. Ding, Y. Shan, X. Zhao, X. Tang, A Highly Efficient Visible-Light-Activated Photocatalyst Based on Bismuth- and Sulfur-Codoped TiO₂, *J. Phys. Chem. C* 112 (2008) 6620–6626, <https://doi.org/10.1021/jp7110007>.
- [78] G.T.K. Swami, F.E. Stageberg, A.M. Goldman, XPS characterization of erbium sesquioxide and erbium hydroxide, *J. Vac. Sci. Technol. A* 2 (1984) 767–770, <https://doi.org/10.1116/1.572568>.
- [79] J. Zhou, L. Jiang, D. Chen, J. Liang, L. Qin, L. Bai, X. Sun, Y. Huang, Facile synthesis of Er-doped BiFeO₃ nanoparticles for enhanced visible light photocatalytic degradation of tetracycline hydrochloride, *J. Solgel Sci. Technol.* 90 (2019) 535–546, <https://doi.org/10.1007/s10971-019-04932-5>.
- [80] R.P. Panmand, M.V. Kulkarni, M. Valant, S.W. Gosavi, B.B. Kale, R.P. Panmand, M.V. Kulkarni, M. Valant, Quantum confinement of Bi₂S₃ in glass with magnetic behavior Quantum confinement of Bi₂S₃ in glass with magnetic behavior, *AIP Adv.* 022123 (2013) 0–11, <https://doi.org/10.1063/1.4794155>.
- [81] A.B. Kathare, Development of Bismuth Sulphide Quantum Dot's in Silicate Glass Matrix, *Int. J. Sci. Res.* 6 (2017) 515–521.
- [82] P.K. Panigrahi, A. Pathak, The growth of bismuth sulfide nanorods from spherical-shaped amorphous precursor particles under hydrothermal condition, *J. Nanoparticles* 2013 (2013) 1–12.
- [83] T.A.F. A.S. Kanishcheva, Y.N. Mikhailov, Refinement of the crystal-structure of synthetic bismuthinite, *Inorg. Mater. Appl. Res.* 17 (1981) 1466–1468.
- [84] The crystal structure of rutile as a function of temperature up to 1600° C, *Zeitschrift für krist. Cryst. Mater.* 194 (1991) 305, <https://doi.org/10.1524/zkri.1991.194.14.305>.
- [85] O. Bi, Z. Jie, X. Ying, Assisted hydrothermal synthesis of Sb₂S₃ and Bi₂S₃ nanocrystals and their elevated-temperature oxidation behavior for conversion into, *J. Phy. Chem. Solids Biomol.* 70 (2009) 1121–1131, <https://doi.org/10.1016/j.jpms.2009.06.010>.
- [86] F. Liu, Y. Yang, J. Liu, W. Huang, Z. Li, Preparation of Bi₂O₃@Bi₂S₃ core–shell nanoparticle assembled thin films and their photoelectrochemical and photoresponsive properties, *J. Electroanal. Chem.* 665 (2012) 58–62, <https://doi.org/10.1016/j.jelechem.2011.11.015>.
- [87] R.K. Chava, J.Y. Do, M. Kang, A. Abdel-wahab, Photocatalytic Hydrogen Production: Role of Sacrificial Reagents on the Activity of Oxide, Carbon, and Sulfide Catalysts, *Catalysts* (n.d.). doi:10.3390/catal9030276.
- [88] Y. Huang, J. Qin, X. Liu, D. Wei, H. Jin, Hydrothermal synthesis of flower-like Nd-doped α-Bi₂O₃ and improved photocatalytic activity via the induced oxygen vacancies, *J. Taiwan Inst. Chem. Eng.* (2018), <https://doi.org/10.1016/j.jtice.2018.11.029>.
- [89] J. Zhang, Y. Wang, RSC Advances A convenient method to prepare a novel alkali metal sodium doped carbon nitride photocatalyst with a tunable band structure, *RSC Adv.* 4 (2014) 62912–62919, <https://doi.org/10.1039/C4RA11377B>.
- [90] L. Zhang, N. Ding, M. Hashimoto, K. Iwasaki, N. Chikamori, K. Nakata, Y. Xu, J. Shi, H. Wu, Y. Luo, D. Li, A. Fujishima, Q. Meng, Sodium-doped carbon nitride nanotubes for efficient visible light-driven hydrogen production, *Nano Res.* 11 (2018) 2295–2309, <https://doi.org/10.1007/s12274-017-1853-3>.
- [91] X. Yu, C. Cao, H. Zhu, Synthesis and photoluminescence properties of Bi₂S₃ nanowires via surfactant micelle-template inducing reaction, *Solid State Commun.* 134 (2005) 239–243, <https://doi.org/10.1016/j.ssc.2005.01.035>.
- [92] F.-A. Liu, Y.-C. Yang, J. Liu, W. Huang, Z.-L. Li, Preparation of Bi₂O₃@Bi₂S₃ core–shell nanoparticle assembled thin films and their photoelectrochemical and photoresponsive properties, *J. Electroanal. Chem.* 665 (2012) 58–62, <https://doi.org/10.1016/j.jelechem.2011.11.015>.
- [93] D.Y.C. Leung, X. Fu, C. Wang, M. Ni, M.K.H. Leung, X. Wang, X. Fu, Hydrogen production over titania-based photocatalysts, *ChemSusChem.* 3 (2010) 681–694, <https://doi.org/10.1002/cssc.201000014>.

- [94] Z. Shi, X. Dong, H. Dang, Facile fabrication of novel red phosphorus-CdS composite photocatalysts for H₂ evolution under visible light irradiation, *Int. J. Hydrogen Energy* 41 (2016) 5908–5915, <https://doi.org/10.1016/j.ijhydene.2016.02.146>.
- [95] C. Wang, L. Wang, J. Jin, J. Liu, Y. Li, M. Wu, L. Chen, B. Wang, X. Yang, B.-L. Su, Probing effective photocorrosion inhibition and highly improved photocatalytic hydrogen production on monodisperse PANI@CdS core-shell nanospheres, *Appl. Catal. B Environ.* 188 (2016) 351–359, <https://doi.org/10.1016/j.apcatb.2016.02.017>.
- [96] M. Wang, S. Shen, Effects of sacrificial reagents on photocatalytic hydrogen evolution over different photocatalysts, *J. Mater. Sci.* (2017), <https://doi.org/10.1007/s10853-017-0752-z>.
- [97] Y.G. Kim, W. Jo, ScienceDirect Photodeposited-metal / CdS / ZnO heterostructures for solar photocatalytic hydrogen production under different conditions, *Int. J. Hydrogen Energy* (2017) 1–8, <https://doi.org/10.1016/j.ijhydene.2017.02.176>.
- [98] N. Bao, L. Shen, T. Takata, K. Domen, Self-templated synthesis of nanoporous CdS nanostructures for highly efficient photocatalytic hydrogen production under visible light, *Chem. Mater.* (2008) 110–117.