




Zagreb, 7th – 8th December

ICWST 2023

32nd International Conference
on Wood Science and Technology



Unleashing The Potential of Wood-based Materials

PROCEEDINGS



S U P P O R T E D B Y :



Vukovar-Srijem County



GALEKOVIĆ
kvaliteta u tradiciji



ORGANISERS

Department of Wood Technology, Faculty of Forestry and Wood
Technology, University of Zagreb, Croatia

Wood Science and Technology Department, Biotechnical Faculty,
University of Ljubljana, Slovenia

Faculty of Forest Industry, University of Forestry, Sofia, Bulgaria

InnovaWood, Bruxelles, Belgium

IN COLLABORATION WITH

Academy of Forestry Sciences, Croatia
Croatian Chamber of Forestry and Wood Technology Engineers, Croatia
The Croatian Chamber of Economy
Drvna industrija scientific journal

SUPPORTED BY

VUKOVAR-SRIJEM COUNTY

Croatian Chamber of Forestry and Wood Technology Engineers, Croatia

SOBOČAN d.o.o.

PPS Galeković d.o.o.

Ravna d.o.o.

Hrvatske šume d.o.o.

CIPRIJANOVIĆ d.o.o.

Drvna industrija Zelina d.d.

Drvodjelac d.o.o.

SPIN VALIS d.d.

Naturalis d.o.o. (CETINA)

Sigma plus d.o.o.

Tvin drvna industrija d.o.o.

Mobilar d.o.o.

DI ČAZMA d.o.o.

ANTE MIJIĆ-QUERCUS d.o.o.

VELINAC d.o.o.

Kronospan CRO d.o.o.

Sinago d.o.o.


Krekić avangard d.o.o.

PRIMA NAMJEŠTAJ d.o.o.

Stolarija-pilana Antun Pečenec d.o.o.







Department of Wood Technology, Faculty of Forestry and Wood Technology, University of Zagreb, Croatia

Wood Science and Technology Department, Biotechnical Faculty, University of Ljubljana, Slovenia

Faculty of Forest Industry, University of Forestry, Sofia, Bulgaria

InnovaWood, Bruxelles, Belgium

32nd International Conference on Wood Science and Technology (ICWST)

UNLEASHING THE POTENTIAL OF WOOD-BASED MATERIALS

PROCEEDINGS

Zagreb, 07th - 08th December 2023

Disclaimer: This book of papers compiles the papers and posters presented at the 32nd International Conference on Wood Science and Technology (ICWST) *Unleashing the potential of wood-based materials* held in Zagreb, Croatia on 07th and 08th December 2023. The opinions expressed within are those of the authors and not necessarily represent those of the host, the editors and or any institution included in organisation of this conference.

Although all reasonable efforts were made by the organising team to ensure the scientific quality of the contents of papers, the final responsibility for the content therein and in the final conference proceeding remains with the respective authors. The editors accept no responsibility for the information contained in the proceedings. The editors are not responsible for the contents of external websites referred to in this publication.

The CIP record for this publication is available in the catalogue of the National and University Library in Zagreb under number: **001206196**.

Publisher:

Faculty of Forestry and Wood Technology, University of Zagreb, Croatia

Organizers:

Department of Wood Technology, Faculty of Forestry and Wood Technology, University of Zagreb, Croatia
Wood Science and Technology Department, Biotechnical Faculty, University of Ljubljana, Slovenia
Faculty of Forest Industry, University of Forestry, Sofia, Bulgaria
InnovaWood, Bruxelles, Belgium

In Collaboration with:

Academy of Forestry Sciences, Croatia
Croatian Chamber of Forestry and Wood Technology Engineers, Croatia
The Croatian Chamber of Economy
Drvna industrija scientific journal

Organizing Committee:

Ružica Beljo Lučić, Ph.D. (Croatia); **Jelena Trajković**, Ph.D. (Croatia); **Vlatka Jirouš-Rajković**, Ph.D. (Croatia); **Silvana Prekrat**, Ph.D. (Croatia); **Anka Ozana Čavlović**, Ph.D. (Croatia); **Maja Moro**, Ph.D. (Croatia); **Andreja Pirc Barčić**, Ph.D. (Croatia); **Danijela Domljan**, Ph.D. (Croatia); **Kristina Klarić**, Ph.D. (Croatia); **Iva Ištok**, Ph.D. (Croatia); **Azra Tafro**, Ph.D. (Croatia); **Ivana Perić**, Ph.D. (Croatia); **Karla Vukman**, M.Eng. (Croatia); **Ivona Josipović**, M.Eng. (Croatia); **Tajana Kruhak**, M.Eng. (Croatia); **Gordana Orešković**, M.Eng. (Croatia); **Silvija Zec**, M.Eng. (Croatia); **Mladen Brezović**, Ph.D. (Croatia); **Vladimir Jambreko**, Ph.D. (Croatia); **Tomislav Sinković**, Ph.D. (Croatia); **Denis Jelačić**, Ph.D. (Croatia); **Darko Motik**, Ph.D. (Croatia); **Hrvoje Turkulin**, Ph.D. (Croatia); **Stjepan Pervan**, Ph.D. (Croatia); **Bogoslav Šefc**, Ph.D. (Croatia); **Josip Ištvančić**, Ph.D. (Croatia); **Maks Merela**, Ph.D. (Slovenia); **Uwe Kies**, Ph.D. (Germany); **Zhivko Gochev**, Ph.D. (Bulgaria); **Neno Trichkov**, Ph.D. (Bulgaria); **Pavlin Vichev**, Ph.D. (Bulgaria); **Jaroslav Kljak**, Ph.D. (Croatia); **Nikola Španić**, Ph.D. (Croatia); **Igor Đukić**, Ph.D. (Croatia); **Krešimir Greger**, Ph.D. (Croatia); **Vjekoslav Živković**, Ph.D. (Croatia); **Zoran Vlaović**, Ph.D. (Croatia); **Ivica Župčić**, Ph.D. (Croatia); **Josip Miklečić**, Ph.D. (Croatia); **Goran Mihulja**, Ph.D. (Croatia); **Marin Hasan**, Ph.D. (Croatia); **Branimir Šafran**, Ph.D. (Croatia); **Kristijan Radmanović**, Ph.D. (Croatia); **Matija Jug**, Ph.D. (Croatia); **Tomislav Sedlar**, Ph.D. (Croatia); **Branimir Jambreko**, Ph.D. (Croatia); **Marko Rastija**, M.Eng. (Croatia); **Juraj Jovanović**, M.Eng. (Croatia); **Tomislav Gržan**, M.Eng. (Croatia); **Alan Antonović**, Ph.D. (Croatia); **Stjepan Posavec**, Ph.D. (Croatia); **Dinko Vusić**, Ph.D. (Croatia); **Andreja Đuka**, Ph.D. (Croatia); **Miljenko Klarić**, Ph.D. (Croatia); **Josip Margaletić**, Ph.D. (Croatia).

Editors:

Miljenko Klarić, Ph.D. (Croatia)
Ružica Beljo Lučić, Ph.D. (Croatia)
Juraj Jovanović, M.Eng. (Croatia)
Nikola Španić, Ph.D. (Croatia)
Kristina Klarić, Ph.D. (Croatia)

Technical editor:

Juraj Jovanović, M.Eng. (Croatia)

Programme Committee and Reviewers:

Nikola Španić, Ph.D. (Croatia)
Miljenko Klarić, Ph.D. (Croatia)
Ružica Beljo Lučić, Ph.D. (Croatia)
Silvija Zec, M.Eng. (Croatia)
Juraj Jovanović, M.Eng. (Croatia)
Mladen Brezović, Ph.D. (Croatia)
Anka Ozana Čavlović, Ph.D. (Croatia)
Silvana Prekrat, Ph.D. (Croatia)
Branimir Jambreković, Ph.D. (Croatia)
Kristina Klarić, Ph.D. (Croatia)
Igor Đukić, Ph.D. (Croatia)
Danijela Domljan, Ph.D. (Croatia)
Németh Róbert, Ph.D. (Hungary)
Miklós Bak, Ph.D. (Hungary)
Vladimir Jambreković, Ph.D. (Croatia)
Andreja Pirc Barčić, Ph.D. (Croatia)
Hrvoje Turkulin, Ph.D. (Croatia)
Zoran Vlaović, Ph.D. (Croatia)
Josip Miklečić, Ph.D. (Croatia)
Andrija Novosel, Ph.D. (Croatia)
Tomislav Gržan, M.Eng. (Croatia)
Josip Margaletić, Ph.D. (Croatia)
Tibor Pentek, Ph.D. (Croatia)
Emilia-Adela Salca, Ph.D. (Romania)
Matija Jug, Ph.D. (Croatia)
Ivica Župčić, Ph.D. (Croatia)
Kristijan Radmanović, Ph.D. (Croatia)
Marin Hasan, Ph.D. (Croatia)
Maks Merela, Ph.D. (Slovenia)
Aleš Straže, Ph.D. (Slovenia)
Matej Jošt, Ph.D. (Slovenia)
Alan Antonović, Ph.D. (Croatia)
Milan Gaff, Ph.D. (Czech Republic)
Luigi Todaro, Ph.D. (Italy)
Marijan Grubešić, Ph.D. (Croatia)
Vanesa Baño, Ph.D. (Spain)
Uwe Kies, Ph.D. (Germany)
Filip Galeković, dipl. oec. (Croatia)
Zhivko Gochev, Ph.D. (Bulgaria)
Neno Trichkov, Ph.D. (Bulgaria)
Pavlin Vichev, Ph.D. (Bulgaria)
Goran Mihulja, Ph.D. (Croatia)

Edition:
200 copies

ISBN: 978-953-292-083-3



FOREWORD

Welcome to the 32nd International Conference on Wood Science and Technology – ICWST 2023, themed "Unleashing the Potential of Wood-Based Materials." As we embark on this annual gathering, it is with great excitement that we delve into a rich tradition that has evolved over the years, connecting experts, researchers, and enthusiasts in the field of wood science and technology.

This year marks a significant juncture for ICWST, as we explore the endless possibilities within wood-based materials. Building upon the success of previous conferences, ICWST 2023 is set to be a catalyst for innovative discussions, collaborations, and breakthroughs in the ever-expanding realm of wood science.

Our conference is honoured to be hosted by esteemed institutions such as the Faculty of Forestry, University of Zagreb; Biotechnical Faculty, University of Ljubljana; Faculty of Forest Industry, University of Forestry - Sofia, and InnovaWood. This collaborative effort reflects the commitment of diverse scientific communities to the advancement of wood science and its applications.

In the spirit of tradition and progress, ICWST 2023 seeks to create a multidisciplinary platform where the exchange of ideas transcends borders. We anticipate the convergence of scientists and researchers from a variety of backgrounds, fostering an environment conducive to scientific novelty, industrial applicability, and comprehensive syntheses of high-impact subjects.

As we reflect on the achievements of the past, present, and future, ICWST 2023 is proud to unveil a program that encapsulates the essence of wood science. Distinguished speakers will explore a wide range of topics. We are honoured to host renowned experts who will share their insights, contributing to the rich tapestry of wood science discourse.

In conclusion, ICWST 2023 extends its gratitude to the institutions and companies whose financial support has made this conference possible. This year's conference aims to go beyond the realms of wood science and technology, touching upon interconnected topics such as materials, technologies, design, and more. We aspire to raise awareness about the vital role of wood as a natural resource in the bioeconomy, advocating for its use as a green building material in the fight against climate change.

We look forward to a conference filled with intellectual exchange, collaboration, and the exploration of the untapped potential within wood-based materials. May ICWST 2023 be a stepping stone towards a future where the sustainable utilization of wood contributes to the betterment of our world.

Editors





CONTENTS

Evaluation of the Irregularities of the Milled Surface of Beech, Maple and Birch Wood using Areal Surface Texture Parameters Adamčík, Lukáš; Kminiak, Richard; Banski, Adrián	1
Wood Research at the University of Sopron – Modifications pt. 2 Bak, Miklós;Németh, Róbert; Báder, Mátyás.....	7
The Influence of Structural Elements on the Measurement of Thermal Conductivity Using the Hot Disc Method of Wood-based panels Balaško, Krešimir.....	12
Modified PUR Adhesive and its Effect on Longitudinal Tensile Strength Under Tensile Stress Bárta, Josef; Sikora, Adam; Holeček, Tomáš; Šedivka, Přemysl	19
Basic Physical and Mechanical Properties of Driftwood Used for Art Installations Bego, Margarita; Lobas Kukavicić, Iris; Martinović, Sandra; Hajdarevic, Seid; Obucina, Murco.....	27
Wood Research at the University of Sopron – Modifications pt. 1 Buga-Kovács, Luca; Fodor, Fanni; Horváth, Norbert; Németh, Róbert; Báder, Mátyás	35
Design Requirements of Upholstered Furniture for Seating and Rest for Smaller Living Spaces Based on the User's Needs Domljan, Danijela; Lamot, Bernard; Vlaović, Zoran; Pirc Barčić, Andreja.....	43
Increasing the Durability of the Exterior Coating System by Surface Sealing Dvořák, Ondřej; Zachara, Tadeáš; Sarvašová Kvietková, Monika; Štěrbová, Irena; Sahula, Lukáš ..	50
Energy Efficiency and Machined Surface Roughness in Machining Solid Oak Wood (<i>Quercus robur</i> L.) on the High Performance Two-Side Thicknessing Planer Đukić, Igor; Jovanović, Juraj; Župčić, Ivica	58
Real Parameters of a Focused CO ₂ Laser Beam and its Determination when Using Lenses with Different Focal Lengths Gochev, Zhivko.....	67
Acoustic Parameters of Birch Wood Compared to Maple Wood and Medium Density Fibreboard Horák, Petr; Borůvka, Vlastimil; Kozel, Jan; Novák, David	75
Mycelium-Based Biocomposites from Recycled Wood: Influence of Fungal Species on Properties of Biocomposites Hýsek, Štěpán; Daňková, Markéta; Jozífek, Miroslav; Němec, Miroslav; Wimmer, Rupert.....	83
The Effect of Wooden Material Type and Additional Adhesive Fortification on the Withdrawal Capacity of the Double-thread Nuts Ibrisevic, Alen; Hajdarevic, Seid; Obucina, Murco; Busuladzic, Ibrahim; Mihulja, Goran;.....	90
Water Resistance of Fiberglass Reinforced Plywood during Prolonged Water Exposure Jakimovska Popovska, Violeta; Iliev, Borche	98
Influence of the Inappropriate School Furniture on the Bodies of Children in Development Jevtoska, Elena; Gruevski, Gjorgi.....	106
The Influence of Drying and Initial Moisture Content of Milled and Solid Oak Wood (<i>Quercus robur</i> L.) Samples on its Solubility in Cold Water Klarić, Miljenko; Matišev, Borno; Španić, Nikola; Barlović, Nikolina	113

The Effect of Thermal Modification on the Quality of the Milled Surface of Beech and Pine Wood Kminiak, Richard; Adamčík, Lukáš; Chuchala, Daniel	121
Rationalization of Furniture Constructions in the Design Phase_Using the CAD Program Inventor Konsa, Petar; Prekrat, Silvana	129
Design-Built Projects from Wood as Training Tool_for Obtaining Complex Skills Kotradyová, Veronika	136
A study on the Environmental Assessment of 3D Printing with Wood-PLA Composites Krapež Tomec, Daša; Oblak, Leon; Kariž, Mirko; Kitek Kuzman, Manja	144
Determination of Thermal Insulation properties of the Developed Material based on Foamed Wood Kubista, Kryštof; Pavelek, Miloš; Zachara, Tadeáš¹; Krotký, Martin; Sahula, Lukáš; Lexa, Martin; Šedivka, Přemysl	149
Characterization of Particleboards Produced with Orange (<i>Citrus sinensis</i> L.) and Turkey Oak (<i>Quercus cerris</i> L.) Wood Species Using Modified Starch as Adhesive Lo Giudice, Valentina; Todaro, Luigi	154
Assessing the Impact of Forest Management in Life Cycle Assessment: Wooden Table Case Study Remic, Katarina; Jošt, Matej	163
Change in Physical Properties at Different Humidity Levels During Laser Wood Processing Sedlecký, Miroslav; Čiháková Veronika; Corleto, Roberto	171
Analysis of Yield and Sawing Methods During Processing Low Value Pedunculate Oak (<i>Quercus robur</i> L.) Logs to Sawmill Products Smajic, Selver; Obucina, Murco; Antonovic, Alan; Istvanic, Josip; Jovanovic, Juraj	180
Comparison of Log Taper in Different Wood Species Stamenkoska, Ana Marija; Rabadziski, Branko; Zlateski Goran	186
Bio-Based Adhesives Made From Liquefied Wood, Tannin and Lignin Šernek, Milan; Žigon, Jure; Saražin, Jaša	194
Maximizing Process Efficiency in the Wood Industry: A Case Study of FMEA in GoSoft ERP Vukman, Karla; Josipović, Ivona; Klarić, Kristina; Perić, Ivana	202
Wood Formation to Evaluate Tree Species Adaptation Capacity and Productivity in Drought-prone Forests Balzano, Angela; Čufar, Katarina; Krže, Luka; Merela, Maks	210
Research needs for European species in a scenario of increasing structural wood demand in a bioeconomy based model Baño, Vanesa; Kies, Uwe; Zaton, Patrycja	211
Captain Vlaho Podic's sea Chest from 1871 Bego, Margarita; Španić, Nikola	212
Influence of the Focal Length Position of the Focusing Lens on the Plywood Discoloration under Different Modes of CO2 Laser Engraving Gochev, Zhivko; Vichev, Pavlin	213
Empowering Advancement of the Wood and Furniture Sector Through Key Digital and Sustainability Competencies Goropečnik, Luka; Makovec Radovan, Danijela; Kropivšek, Jože	214
Frequency Spectrum of Roughness Signal Obtained on Machined Surface of Solid Oak Wood After Sawing on the Circular Saw Jovanović, Juraj; Jug, Matija; Đukić, Igor	215

Determination of Flexible Pipe Pressure Loss in a Chip and Dust Suction System Jug, Matija; Beljo Lučić, Ružica; Dujmović, Marin; Šafran, Branimir; Radmanović, Kristijan; Jovanović, Juraj; Kruljac, Antonio	216
Possibilities for using Artificial Intelligence in Furniture/Woodworking industry. Kariž, Mirko; Kitek Kuzman, Manja; Kropivšek, Jože	217
Analysis of Primary Value Chains in the Slovenian Forest and Wood Bioeconomy Kropivšek, Jože; Straže, Aleš; Gornik Bučar, Dominika	218
Life Cycle Assessment (LCA) Study for Early Design Stages of Wooden Wall Coverings with Enhanced Aesthetics and Functionality Kruhak, Tajana; Pirc Barčič, Andreja; Mamić, Domagoj; Domljan, Danijela; Klarić, Kristina	219
Chemical Characterization of Liquefied Forest Biomass of Common Spruce (<i>Picea abies</i> L.) and Oak (<i>Quercus robur</i> L.) Matin, Božidar; Đurović, Alen; Matin, Ana; Brandić, Ivan; Tomić, Ivana; Ištvančić, Josip; Antonović, Alan	220
Formaldehyde Free Particleboard Bonded with Imidazole Citric Acid Adhesive System Medved, Sergej; Jones, Dennis; Alan Antonović	221
Structural Based Analysis of Moisture Resistance of Different Wood-Based Panels Điporović-Momčilović, Milanka; Medved, Sergej; Popović, Mladan; Španić, Nikola; Jambreković Vladimir	222
Modelling of Peripheral Wood Milling Power Using Design of Experiment Approach Merhar, Miran; Bjelić Aldin; Hodžić, Atif	223
Colouring of Oak Wood Veneers with Water-based Stains Miklečić, Josip; Jirouš-Rajković, Vlatka	224
Market Trend Analysis of Wood Products and Wood Waste in the EU Towards a Better Understanding of Environmental Sustainability and Climate Change Obranković, Jelena; Pirc Barčič, Andreja; Tafro, Azra; Vukman, Karla; Klarić, Kristina	225
Impact of Ultrasonic Waves on the Synthesis of ZnO Nanoparticles for Wood Modification. Paul, Dabosmita; Tesařová, Daniela; Petrič, Marko	226
Acoustic Properties of Certain Types of Wood from Croatia Radmanović, Kristijan; Bojčić, Ivan; Šafran, Branimir; Dujmović, Marin; Balaško, Krešimir; Župčić, Ivica	227
Study on the Natural Aging Process of Old Fir (<i>Abies alba</i> Mill.) Structural Timber Straže, Aleš; Dremelj, Matjaž; Merela, Maks; Balzano, Angela; Žigon, Jure; Krže, Luka	228
Addition of Rotten Wood with the Aim of Improving the Wood Pellet Properties Šafran, Branimir; Dujmović, Marin; Radmanović, Kristijan; Jug Matija; Antonović, Alan; Hasan, Marin; Kruljac, Antonio	229
Impact of Feed Rate on Energy Consumption During Cutting Dry Beech Wood with a Circular Saw Temelkova Anastasija; Trposki Zoran	230
Sustainability Through FSC Recycling: An In-Depth Assessment of European Adoption and Trends Vukman, Karla; Klarić, Kristina; Nikolay Neykov; Perić, Ivana; Obranković, Jelena; Pirc Barčič, Andreja	231

increased surface area, did not significantly differ in extractive solubility compared to solid wood samples when both were in an absolutely dry state. This finding could reshape current perceptions regarding the impact of physical state and moisture content on the extraction efficiency of wood. The application of the cold water extraction method proved effective in quantifying the extractive content, which is essential for industries where wood colour consistency and hydrothermal treatment quality are of utmost importance. The results of this research offer valuable insights that can be applied to improve industrial processes, such as drying, steaming, and boiling of oak wood, ensuring better product quality and reducing financial losses due to colour imperfections. This study not only contributes to the fundamental understanding of oak wood's chemical behaviour in the presence of cold water but also provides practical guidance for enhancing the hydrothermal treatment of wood. The findings underline the critical need to consider the unique properties of wood extractives in industrial applications, paving the way for more efficient and cost-effective wood processing techniques

Acknowledgements: This research paper is a part of Bachelor thesis of student Borno Matišev.

REFERENCES

- ASTM D1110-21 : Standard Test Methods for Water Solubility of Wood
Babiak, M. (2007): Sorption isotherms of wood. In: Fundamentals of Wood Drying. Editor: Patrick Perré. COST E-15, A.R.BO.LOR, France. ISBN 9782907 086127.
Boddy, L. (1992): Microenvironmental Aspects of Xylem Defenses to Wood Decay Fungi. In: Defense Mechanisms of Woody Plants Against Fungi. Editors: Blanchette, R. A.; Biggs, A. R. Springer Series in Wood Science. Springer-Verlag. ISBN: 978-3-662-01642-8 (eBook).
Fengel, D.; Wegener, G. (1989): Wood – Chemistry, Ultrastructure, Reactions. Verlag Kessel, Germany. Reprint 2003 (Edition of 1989). ISBN 3935638-39-6.



The Effect of Thermal Modification on the Quality of the Milled Surface of Beech and Pine Wood

Kminiak, Richard^{a,*}; Adamčík, Lukáš^a; Chuchala, Daniel^b

^aDepartment of Woodworking, Faculty of Wood Sciences and Technology, Technical University in Zvolen, Zvolen, Slovakia

^bInstitute of Manufacturing and Materials Technology, Faculty of Mechanical Engineering and Ship Technology, Gdansk University of Technology, Gdansk, Poland

*Corresponding author: richard.kminiak@tuzvo.sk

ABSTRACT

The article deals with the effect of thermal modification on the quality of the created surface during milling on CNC milling cutters. The quality of the created surface is evaluated based on surface roughness, specifically its roughness parameter Ra. The observed surface is created by a shank cutter with a diameter of 20 mm and three cutting edges in a spiral at a standard speed of 18,000. min⁻¹. The article compares thermally modified pine wood and beech wood of at temperatures of 160, 180, 200 and 220 °C with a reference sample of kiln dried wood of the given wood species. The article also monitors the variability of the quality of the created surface due to the change in the feed speed of 2, 4 and 6 m·min⁻¹ and the thickness of removal of 1, 3 and 5 mm within the given degree of thermal modification. The article points to the fact that the average value of the arithmetic mean height (Ra) is below 10 µm for both types of wood, regardless of the degree of thermal modification. This meets the general requirements for the surface quality of furniture blanks. The mutual comparison of wood species showed that beech wood forms an average of 1.5 µm higher quality surface than wood pine. Thermal modification within both studied wood species improves the quality indicators of the created surface. In terms of the effect of specific temperatures, the highest quality of the created surface is at 180 °C and deteriorates in the range of 180, 200, 160, 220 °C. From the point of view of the influence of the investigated technological factors, no statistically significant influence of either the feed speed or the thickness of removed layer was demonstrated.

Key words: beech wood, pine wood, thermally modified wood, temperature of thermal modification, quality of the created surface, technological parameters of the process

1. INTRODUCTION

The current trend is to reduce the environmental footprint of the production process. One of the aspects is the minimization of the consumption of chemical substances in the production process, especially in the case of products for children. One of the potential ways is to change the color and increase the resistance of the surfaces due to the thermal treatment of the wood.

In general, thermal treatment can be defined as a process in which high temperatures in the range of 150 to 260 °C are applied to wood in an environment with different types of media (steam, nitrogen, oil, etc.) without chemicals (Sandberg and Kutnar, 2016). As noted by Budakci *et al.* (2013), the effect of these modifications depends on the medium used and its temperature. In Europe, the most commercially used technologies include ThermoWood in Finland, Plato Wood in the Netherlands, oil-heat treatment (OHT) in Germany and Les Bois Perdure and the rectification process (Retiwood) in France (Esteves and Pereira, 2011; Reinprecht and Vidholdova, 2008).

The production process of thermally modified wood is associated with several chemical changes in the structure of the material, in simplified terms it is a change in the proportion of lignin and the degradation of higher cellulose to lower cellulose, and these changes

subsequently affect its physical and mechanical properties (Reinprecht and Vidholdová, 2008; Kačíková and Kačík, 2011; ThermoWood Handbook, 2003; Čabalová *et al.*, 2016).

The intensity of the change in physical and mechanical properties consequently limits the use of thermally modified material. For this reason, this article was also created, the aim of which is to assess the effect of thermal modification on the quality of the machined surface. At the same time, the article aims to carry out the given assessment not with the help of classic technologies, as is customary, but with the use of CNC technology.

2. MATERIAL AND METHODS

Experimental samples: In the experiment, native and heat-treated blanks of Scots pine (*Pinus sylvestris*) and European Beech (*Fagus sylvatica* L.) with dimensions of 30 × 55 × 500 mm and moisture content 8 ± 1 % were used.

Heat treatment of wood: Samples for the experiment were heat treated with ThermoWood technology at the FLD Arboretum area (ČZU Prague) in Kostelec nad Černými lesy. Thermal treatment was carried out using the chamber S400/03 (LAC Ltd., Czech Republic). The course of the process was controlled by temperature and humidity sensors directly on the processed samples. The course of thermal modification itself was controlled via a computer, using a program from the company Katres spol. Ltd. The treatment process for individual thermal treatments is shown in *Figure 1*.

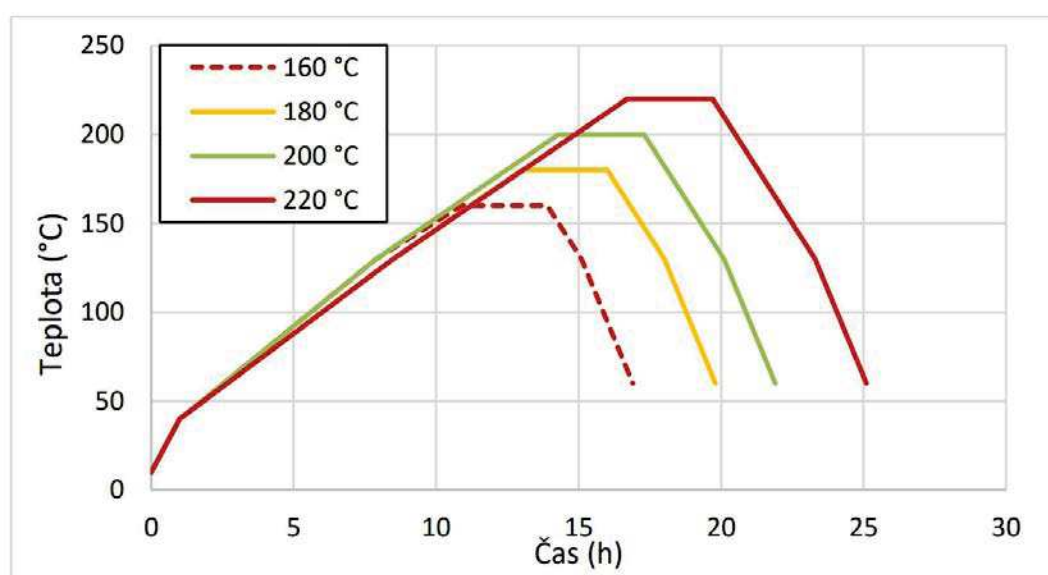


Figure 1. Graphic representation of temperature and time dependence for individual stages of thermal treatment of samples (Korčok *et al.*, 2018).

Machine and tooling: The blanks were milled on a 5-axis CNC machining center SCM Tech Z5 (*Figure 2*) supplied by SCM-group, Rimini, Italy. The basic technical and technological parameters indicated by the manufacturer are listed in *Table 1*. LEUCO VFW 178354 finishers (*Figure 3*) from LEUCO (Beinheim, France) were used for milling. The basic technical and technological parameters indicated by the manufacturer are listed in the *Table. 2*



Figure 2. CNC machining center SCM Tech Z5 (<https://www.scmgroup.com/en>).

Table 1. Technical and technological parameters of the CNC machining center SCM Tech Z5. (<https://www.scmgroup.com/en>)

Technical parameters of CNC machining center SCM Tech Z5	
Useful desktop	x = 3,050mm , y = 1,300mm, z =300mm
Speed X axis	0 ÷ 70 m.min ⁻¹
Speed Y axis	0 ÷ 40 m.min ⁻¹
Speed Z axis	0 ÷ 15 m.min ⁻¹
Vector rate	0 ÷ 83 m.min ⁻¹
Technical parameters of the main spindle - electric spindle with HSK F63	
Rotation axis C	640°
Rotation axis B	320°
Revolutions	600 ÷ 24,000 ot.min ⁻¹
Power	11 kW
Maximum tool diameter	D = 160 mm
	L = 180 mm

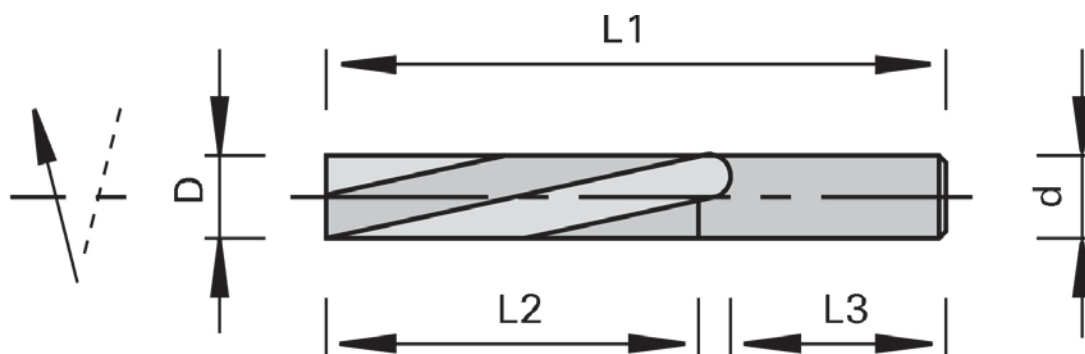


Figure 3. A Finishing cutter LEUCO VFW 178354. (<https://www.leuco.com/EN/US/web/home>).

Table 2. Technical and technological parameters of finishing cutters LEUCO VFW 178354 (<https://www.leuco.com/EN/US/web/home>)

Feature	Value
Ø D = Cutting circle diameter	20 [mm]
L2 = Cutting width	55 [mm]
Ø d = Shank diameter	20 [mm]
L3 = Shank length	50 [mm]
L1 = Total length	115 [mm]
Z = No. of teeth	3
Helical direction = Helical direction	negative
n_{max} = maximum RPM	30,000 [min^{-1}]
L/R = cutting direction	R

Milling process: A LEUCO VFW 178354 milling cutter was fitted to a SOBO 302680291 GM 300 HSK 63F hydraulic chuck from Gühring KG Albstadt. The blanks were placed in the CNC machining center so that the longer side was in the X axis and the shorter side was in the Y axis. clamped with mechanical clamps VCMC-S4 145x145x50 12-80 from J. Schmalz GmbH, Glatten, Germany. The milling process took place at a constant milling speed $n = 20,000 \text{ min}^{-1}$ and varying thickness of the removal layer $a_c = 1, 3$ and 5 mm and varying feed speed $z_{vf} = 2, 4$ and $6 \text{ m} \cdot \text{min}^{-1}$.

Determination of surface roughness: The surface roughness of the samples was measured with a laser profilometer LPM-4 (Figure 4) from the manufacturer Kvant s.r.o. Slovak Republic. The profilometer uses the triangulation principle of laser profilometry. The image of the laser line is captured at an angle by a digital camera. The cross-sectional profile of the object is then evaluated from the scanned image. The obtained data are mathematically filtered and individual indicators of the primary profile, waviness profile and roughness profile are set (Kminiak and Gaff, 2015)

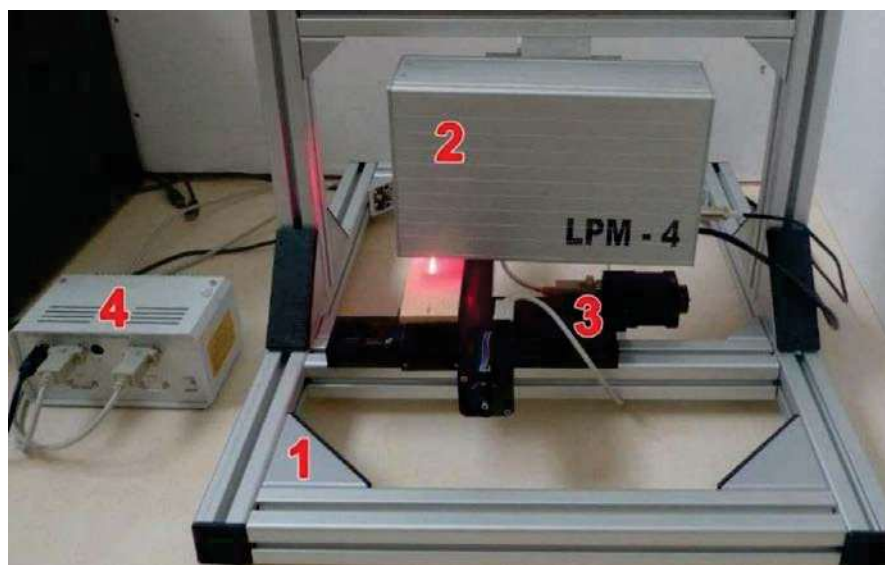


Figure 4. Laser Profilometer LPM - 4 (1 - supporting structure allowing manual setting of working distance and fitting of profilometric head and trolley system, 2 - profilometric head, 3 - feed system of the XZ axis, 4 - control system of working desk shifts) (Kminiak and Gaff 2015).

The methodology of Siklenka and Adamcova (2012) was used to measure the surface roughness, which meets the EN ISO 4287 standard. Within each sample, measurements were made in three traces, located in the center of the sample, evenly distributed over the entire



surface of the sample. sample width (5/10/15 mm from the edge of the sample), the traverse length was 60 mm, and the trace was oriented in the direction of spindle displacement in the milling process. The surface roughness was evaluated using the parameter of the arithmetic mean of the deviation of the roughness profile Ra.

3. RESULTS AND DISCUSSION

Background: Changing the quality of the created surface as a result of the thermal modification of wood is not the goal of the thermal modification, but its side effect. The aim of this article is to assess the risks of thermal modification on quality indicators of the surface, whether it is necessary to choose different technical-technological parameters of the process when processing thermally modified wood than when processing wood without thermal modification.

As an objective criterion for assessing the effect of thermal modification on the quality of the created surface, the roughness of the created surface was chosen, specifically its parameter, the „Ra“ mean arithmetic deviation of the roughness profile. The reason for choosing the roughness parameter as the most representative quality parameter is the premise, surface roughness and waviness are interconnected parameters, surface waviness is primarily dependent on machining kinematics, and surface roughness primarily depends on the tool-workpiece interaction. Based on the following premise, roughness reacts more sensitively to material changes, which was also confirmed in the given experiment.

Analysis of the obtained data: The measured data were subjected to analyses in the statistic software STATISTICA 12.

- the effect of the type of wood, the degree of thermal modification and the thickness of the removal layer was shown to be statistically significant, on the other hand, the effect of the feed speed was shown to be statistically insignificant,
- the order of statistical significance of the factors decreases in the order of type of wood, degree of thermal modification and the thickness of the removal layer, all three investigated factors proved to be highly statistically significant
- the roughness of the surface of beech wood ranges from 4.6 μm to 8.2 μm , the roughness of the surface of pine wood ranges from 5.2 to 9.7 μm , the surface of pine wood is 1.4 μm rougher on average like the surface of beech wood (see *Figure 5*).

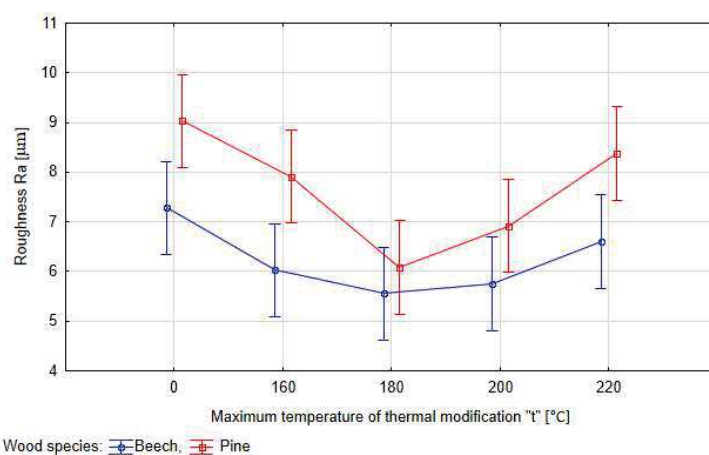


Figure 5. The effect of thermal modification on the quality of the created surface (vertical bars denote 95 % confidence interval for the mean.).

The roughness of the surface of thermally treated beech and pine wood is lower than that of wood without thermal modification, in terms of the influence of specific temperatures, the lowest roughness of the created surface is at 180 °C (on average beech wood 5.6 µm / pine wood 6.1 µm) and deteriorates in the order 180 °C, 200°C (on average beech wood 5.7 µm/ pine wood 6.9 µm), 160 °C (on average beech wood 6.0 µm/ pine wood 7.9 µm), 220 °C (on average beech wood 6.6 µm/ pine wood 8.4 µm) and the reference sample (on average beech wood 7.2 µm/ pine wood 9.0 µm), due to thermal modification there is a decrease in roughness depending on the temperature modifies in the range of 0.7-1.5 µm for beech wood and 0.7-3.0 µm for pine wood.

The statistical significance of the effect of the thickness of the removal layer on the roughness of the created surface was confirmed only within pine wood, in the case of beech wood the given effect is statistically insignificant, in the case of pine wood, as a result of increasing the removal from 1 mm to 3 mm, the roughness of the created surface worsens on average by 1.1 µm, and in the case of an increase in removal from 3 to 5 mm, the roughness will deteriorate by an average of 1.3 µm (see *Figure 6/a*).

The expected influence of the feed speed on the roughness of the created surface was not confirmed, surface roughness differences due to a change in the feed speed by 2 m.min⁻¹, the surface roughness changes on average by 0.3 µm for beech and by 0.7 µm in the case of pine. It is not possible to observe an unequivocal trend of increase or decrease in roughness due to changes in the feed rate (see *Figure 6/b*).

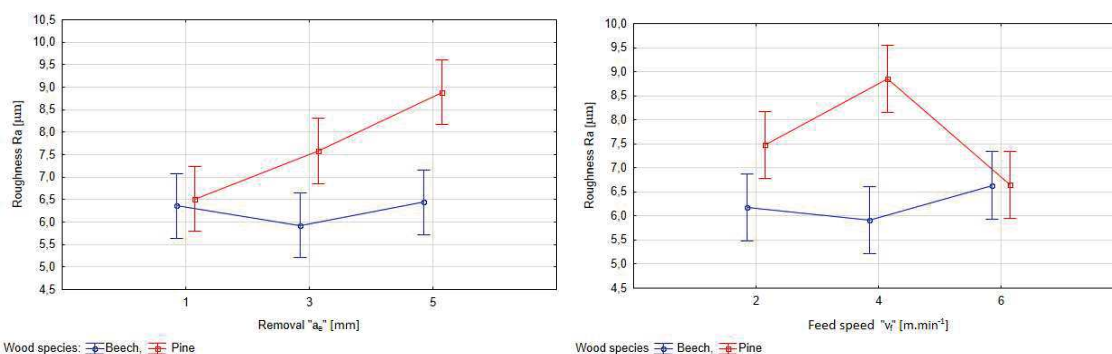


Figure 6. a) The effect of the amount of removal on the quality of the created surface b) the effect of the size of the feed speed on the quality of the created surface (vertical bars denote 95 % confidence interval for the mean.)

Scientific interpretation of the obtained data: For the sake of objectivity, it is necessary to emphasize at the outset the fact that most authors dealing with the given issue use the milling process on the bottom single-spindle cutter and a cutter with a diameter of 120 to 140 mm for surface creation. The experiment carried out by us is carried out on a CNC milling machine with a tool diameter of 20 mm. From a macro point of view, we remove identical layers of material, but from a micro point of view, the chip formation mechanism is not identical. We will use the example of the contact angle, for a tool with a diameter of 120 and a clearance of 1 mm, the contact angle is 10°, and for a tool of 20 mm and a clearance of 1 mm, the contact angle is up to 25°. At the same time, a specific feature of tools for CNC milling machines is the development of the cutting edge into a screw. Both facts significantly influence the vectorization of forces during the creation of new surfaces.

As stated by Škaljič *et al.*, (2009), the physical and mechanical properties and anatomical structure of the wood affect the roughness of the surface. The resistance to blade penetration into wood depends on the size and shape of the cells, as well as the thickness and strength of the cell walls. This creates the hypothesis that the denser and more homogeneous the wood, the better the surface it creates. This statement corresponds to our conclusions as well as the conclusions of Malkoçođlu and Özdemir (2006) and Malkoçođlu (2007) showed in their

research that with the same processing parameters, the surface of conifers is of lower quality than the surface of hardwoods.

The results obtained by us confirm the conclusions of Vančo *et al.*, (2017) that the quality of thermally treated wood is higher than the quality of native wood, at the same time we agree with the trend that when the temperature increases to about 200 °C, the quality improves and above this limit it gradually deteriorates. Thermal modification of wood is a process that changes its chemical structure, making the wood more fragile and easier to protect. As stated by (Ispas *et al.*, 2016), the brittleness of wood is a consequence of the loss of amorphous polysaccharides.

An explanation of the break and the reverse increase in roughness at a temperature of 200-220 °C is offered by Čabalová *et al.*, (2016). A noticeable mass loss (ML) at temperatures above 220 °C suggested there was intensive decomposition of the wood matter. The ML of wood is one of the most important features in heat treatment, and it is commonly referred to as an indicator of quality (Esteves and Pereira, 2009).

Technological interpretation of the results: From a technological point of view, it is necessary to interpret the obtained data regarding the limit value of the surface roughness. Based on our own experience, a milled surface can be considered high-quality if the surface roughness does not exceed the value of $R_a = 20 \mu\text{m}$. Within the setting of technological parameters, thermal modification will not cause changes in material properties that would relate to quality indicators and limit values. From this point of view, there is no need for a differentiated approach when processing thermally modified wood, and it is possible to use the same technical-technological settings of the machining process. From the point of view of the specific values of the technical-technological parameters, it is appropriate to increase them, this is not prevented by other limiting factors (cutting forces F_c , the ability to evacuate classes S_{zm}, \dots).

4. CONCLUSIONS

Thermal modification, in addition to the targeted change for which it is carried out – a change in color, also brings a change in physical-mechanical properties, which subsequently affect the machinability of the material. From the point of view of the quality of the created surface, specifically the surface roughness parameters, it is possible to state that, under the conditions of machining by means of CNC technology, thermally modified wood shows a higher quality of the created surface than natural wood. As the temperature of the thermal modification increases, the quality of the created surface increases approximately up to a temperature of 200 °C, and above this limit the reverse phenomenon occurs, namely that the quality of the surface decreases with further temperature increases. In absolute terms, the values of the surface roughness in the range of recommended values of the technical-technological parameters usual for the given type of CNC machining are below the limit values, and therefore the quality of the surface created in this way can be considered acceptable.

Acknowledgements: This experimental research was prepared within the grant project: APVV- SK-PL-21-0059 “Effect of the application of machining fluids in minimum quantity lubrication (MQL) system on the milling process results of heat-treated wood” and VEGA 1/0324/21 “Analysis of the risks of changes in the material composition and technological background on the quality of the working environment in small and medium-sized wood processing companies”

REFERENCES

- Budakçı, M.; İlçe, A. C.; Gürleyen, T.; Utar, M. (2013): Determination of the surface roughness of heat-treated wood materials planed by the cutters of a horizontal milling machine. *BioResources*, 8(3), pp. 3189-3199. DOI: 10.15376/biores.8.3.3189-3199
- Čabalová, I.; Kačík, F.; Zachar, M.; Dúbravský, R. (2016): Chemical changes of hardwoods at thermal loading by radiant heating. In *Acta Facultatis Xylogologiae*. Zvolen: Technical University in Zvolen, 58(1), 43-50. DOI: 10.17423/afx.2016.58.1.05
- Esteves B.M.; Pereira H.M. (2009): Wood modification by heat treatment. *BioResources*, 2009, 4(1), 370-404. DOI: 10.15376/biores.4.1.370-404
- Ispas, M.; Gurau, L.; Campean, M.; Hacibektasoglu, M.; Racasan, S. (2016): Milling of Heat-Treated Beech Wood (*Fagus sylvatica* L.) and Analysis of Surface Quality. *BioResources*, 11(4), pp. 9095-9111. DOI: 10.15376/biores.11.4.9095-9111
- Kačíková, D.; Kačík, F. (2011): Chemical and mechanical changes during thermal treatment of wood. TU vo Zvolene. ISBN 978-80-228-2249-7, 71.
- Kminiak R.; Gaff M. (2015): Roughness of surface created by transversal sawing of spruce, beech, and oak wood. *BioResources*, 10(2). 2873–2887. DOI: 10.15376/biores.10.2.2873-2887
- Korčok, M.; Koleda, P.; Barcik, Š.; Vančo, M. (2018). Effects of technical and technological parameters on the surface quality when milling thermally modified European oak wood. *BioResources* 13(4), pp. 8569-8577. DOI:10.15376/BIORES.13.4.8569-8577
- Malkoçođlu, A. (2007): Machining properties and surface roughness of various wood species planed in different conditions. *Building and Environment*, 42 (7). 2562-2567. DOI: 10.1016/j.buildenv.2006.08.028
- Malkoçođlu, A.; Özdemir, T. (2006): The machining properties of some hardwoods and softwoods naturally grown in Eastern Black Sea Region of Turkey. *Journal of Materials Processing Technology*, 173 (3), pp. 315-320. DOI: 10.1016/j.jmatprotec.2005.09.031
- Reinprecht, L.; Vidholdová, Z. (2008): *Termodrevo – príprava, vlastnosti a aplikácie*. Zvolen, Technical University in Zvolen, ISBN 978-80-228-1920-6.
- Sandberg, D.; Kutnar, A. (2016): Thermally modified timber: recent developments in Europe and North America. *Wood and fiber Science: journal of the Society of Wood Science and Technology* 48, pp. 28-39
- Škaljić, N., Beljo Lučić, R., Čavlović, A., and Obućina, M. (2009): Effect of feed speed and wood species on roughness of machined surface, *Drvna Industrija* 60(4), pp. 229-234.
- Vančo, M.; Mazán, A.; Barcik, S.; Rajko, L.; Koleda, P.; Vyhňáliková, Z.; Safin, R. R. (2017): Impact of Selected Technological, Technical, and Material Factors on the Quality of Machined Surface at Face Milling of Thermally Modified Pine Wood. *BioResources*, 2017 12(3), pp. 5140-5154. DOI: 10.15376/biores.12.3.5140-5154
- ThermoWood Handbuch [online]. © 2003. URL: https://asiakas.kotisivukone.com/files/en.thermowood_palvelee.fi/downloads/ThermoWood_Handbuch.pdf

