

**A. Zieliński, A. Dziadoń<sup>1</sup>, W. Serbiński, M. Jażdżewska**

Gdańsk University of Technology, Faculty of Mechanical Engineering, Department of Materials Science and Engineering, Gdansk, Poland,

<sup>1</sup>Kielce University of Technology, Faculty of Mechatronics and Machine Building, Department of Materials Science and Engineering, Kielce, Poland

## **SURFACE CRACKING OF LASER MELTED Ti-6Al-4V ALLOY**

### **ABSTRACT**

The characteristic features of surface cracking observed after laser melting with CO<sub>2</sub> and Nd:YAG laser were described. The cracks were always present, their length approaching some part of melted zone and scarcely dependent on laser melting conditions. The appearance of cracks was attributed mainly to martensitic transformation within the surface layer. The possible contribution of developed thermal stresses cannot be also excluded. The existence of cracks may be utilized for the enhancement of bone – implant strength.

*Key words:* cracking, laser treatment, titanium alloys

### **INTRODUCTION**

The modern biomaterials must fulfill a number of requirements. Among them, the extraordinary corrosion resistance in an environment of human body fluids is necessary. Therefore the titanium and its alloys are nowadays the most selected and investigated metallic materials destined for such applications.

There are a number of Ti alloys proposed as biomaterials for endoprostheses cones, with Ti-Al-V alloys being still the most popular. In order to increase the corrosion and wear resistance, a lot of technologies have been proposed. They include among others, an artificial oxidation. The chemical oxidation in acids, like nitric acid, and some concentrated hydroxides, electrochemical oxidation and thermal oxidation in vapour phase followed by heat treatment, have been proposed [1-10].

The laser treatment of Ti and its alloys is not widely accepted. Among others, the lasers have been applied to change the structure of surface layer increasing in such a way its corrosion resistance [11-13]. No appearance of cracks has been reported.

In this paper the previous results and possibilities to use the laser treatment for Ti alloy have been verified at different conditions with aim to especially examine the possible cracking of surface layer.

## EXPERIMENTAL


The Ti6Al4V alloy was melted. The laser treatment was made by two lasers: permanent work CO<sub>2</sub> laser and Nd-YAG pulse laser. For CO<sub>2</sub> laser the power input was ranged between 1.5 and 6 kW, scan rate between 0.25 and 1 m/s, as environment the liquid nitrogen, water and air were imposed, and for the laser treatment in air some specimens were pre-heated between 200 and 550 °C just before laser melting. For Nd-YAG laser the power input was 150 W, scan frequency 50 Hz and scan rate 0.25 to 4 m/min.; the melting was performed only in air.

## RESULTS AND DISCUSSION


The results of performed tests are shown in Figs. 1-4. For every combination of tests parameters the view of the melted surface and cross-section are put together.

The cracks are evident to form at each condition. The depth of the crack is dependent on all variables. Generally, the higher power input and the lower scan rate, the longer cracks. The environment has also an effect: cracks are more significant during laser treatment in air and water. Pre-heating diminishes the cracking. The depth of the crack is always a significant portion of the melted zone and from this point of view, the laser melting in liquid nitrogen seems the most appropriate. The quantitative data are estimated and will be published in future.


Two possible sources of the cracks may be considered. The first is martensitic transformation following fast cooling even in water and air accompanied by an occurrence of high mechanical stresses. On the other hand, the cracking during martensitic transformation has not been reported for this alloy. Another possible source, high shear stresses appearing during solidification of this very hard and brittle alloy may release by formation of cracks.

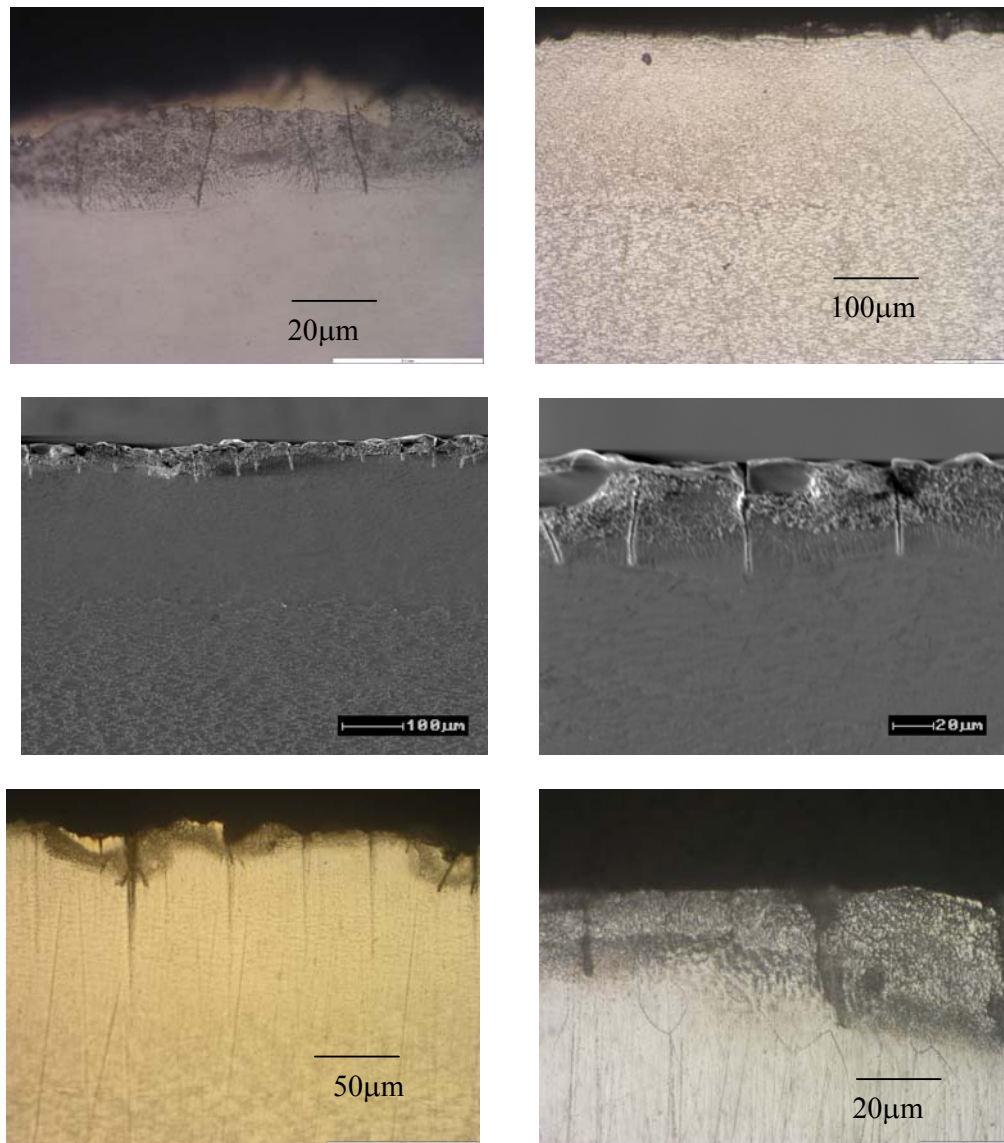


**Fig. 1.** Cracking of surface layers for specimens laser melted with CO<sub>2</sub> laser in liquid nitrogen at scan rate 1 m/min at power input (from top to the bottom): 3 kW, 4 kW, 5 kW and 6 kW

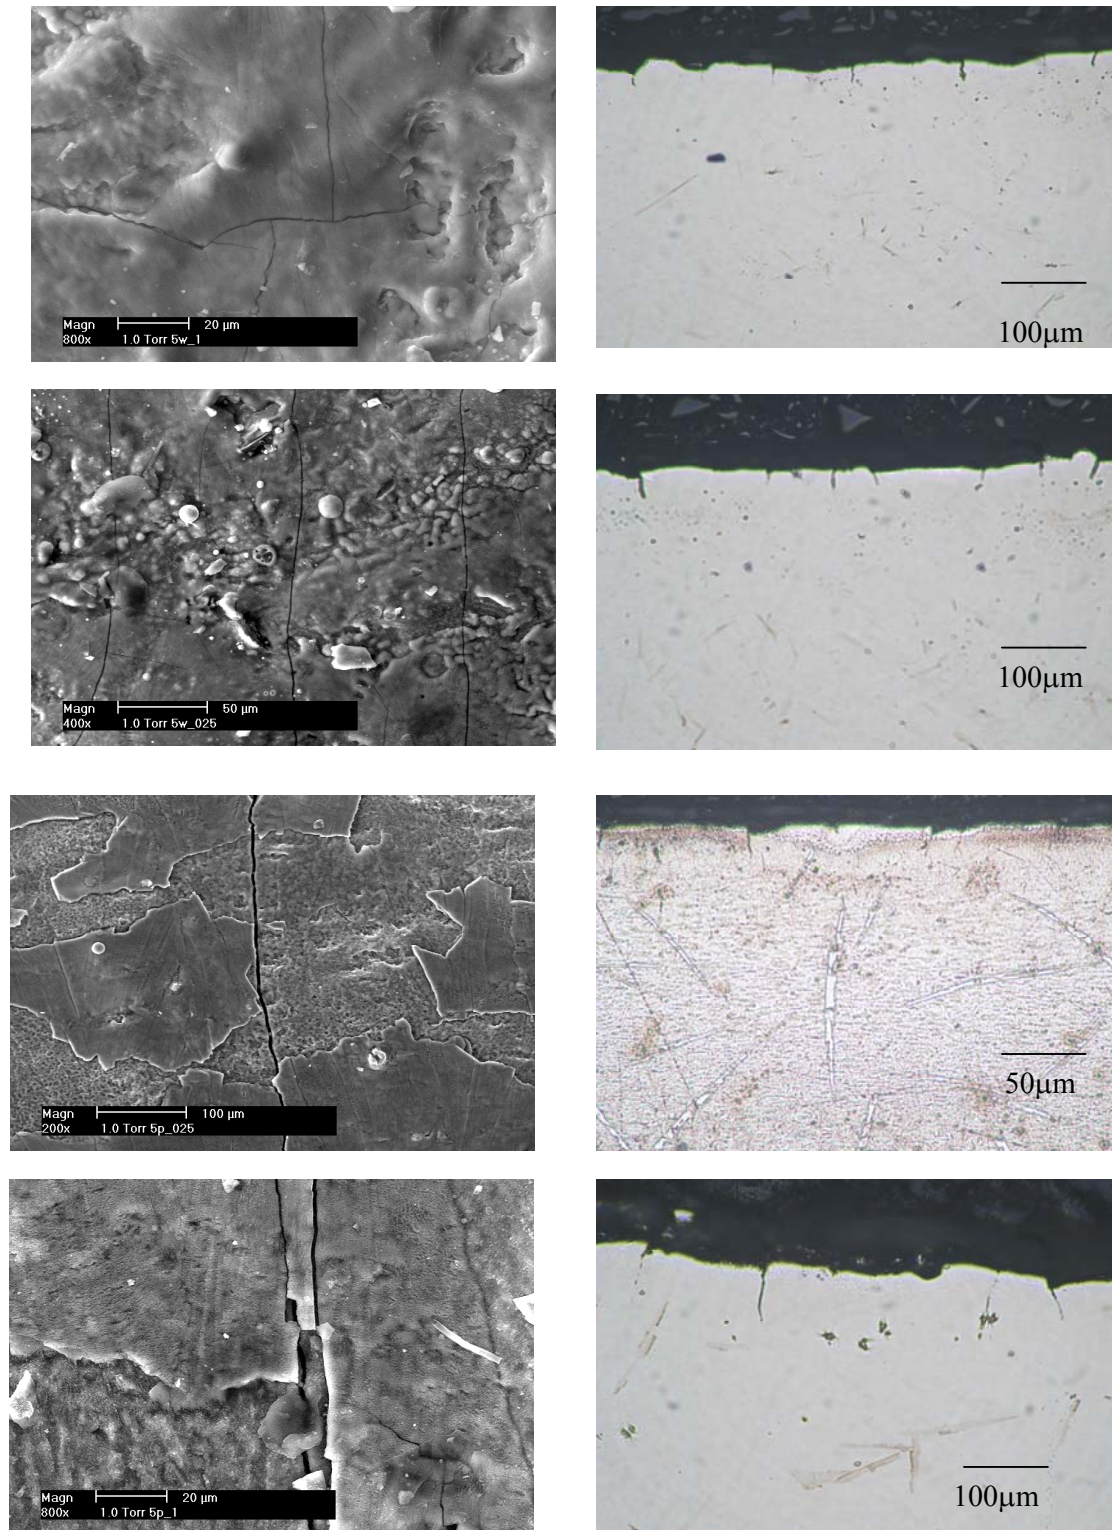


**Fig. 2.** Cracking of surface layers for specimens laser melted with CO<sub>2</sub> laser at 5 kW (from top to the bottom): in water at scan rate 1 m/min.; in water at scan rate 0.25 m/min.; in air at scan rate 1 m/min.; in air at scan rate 0.25 m/min

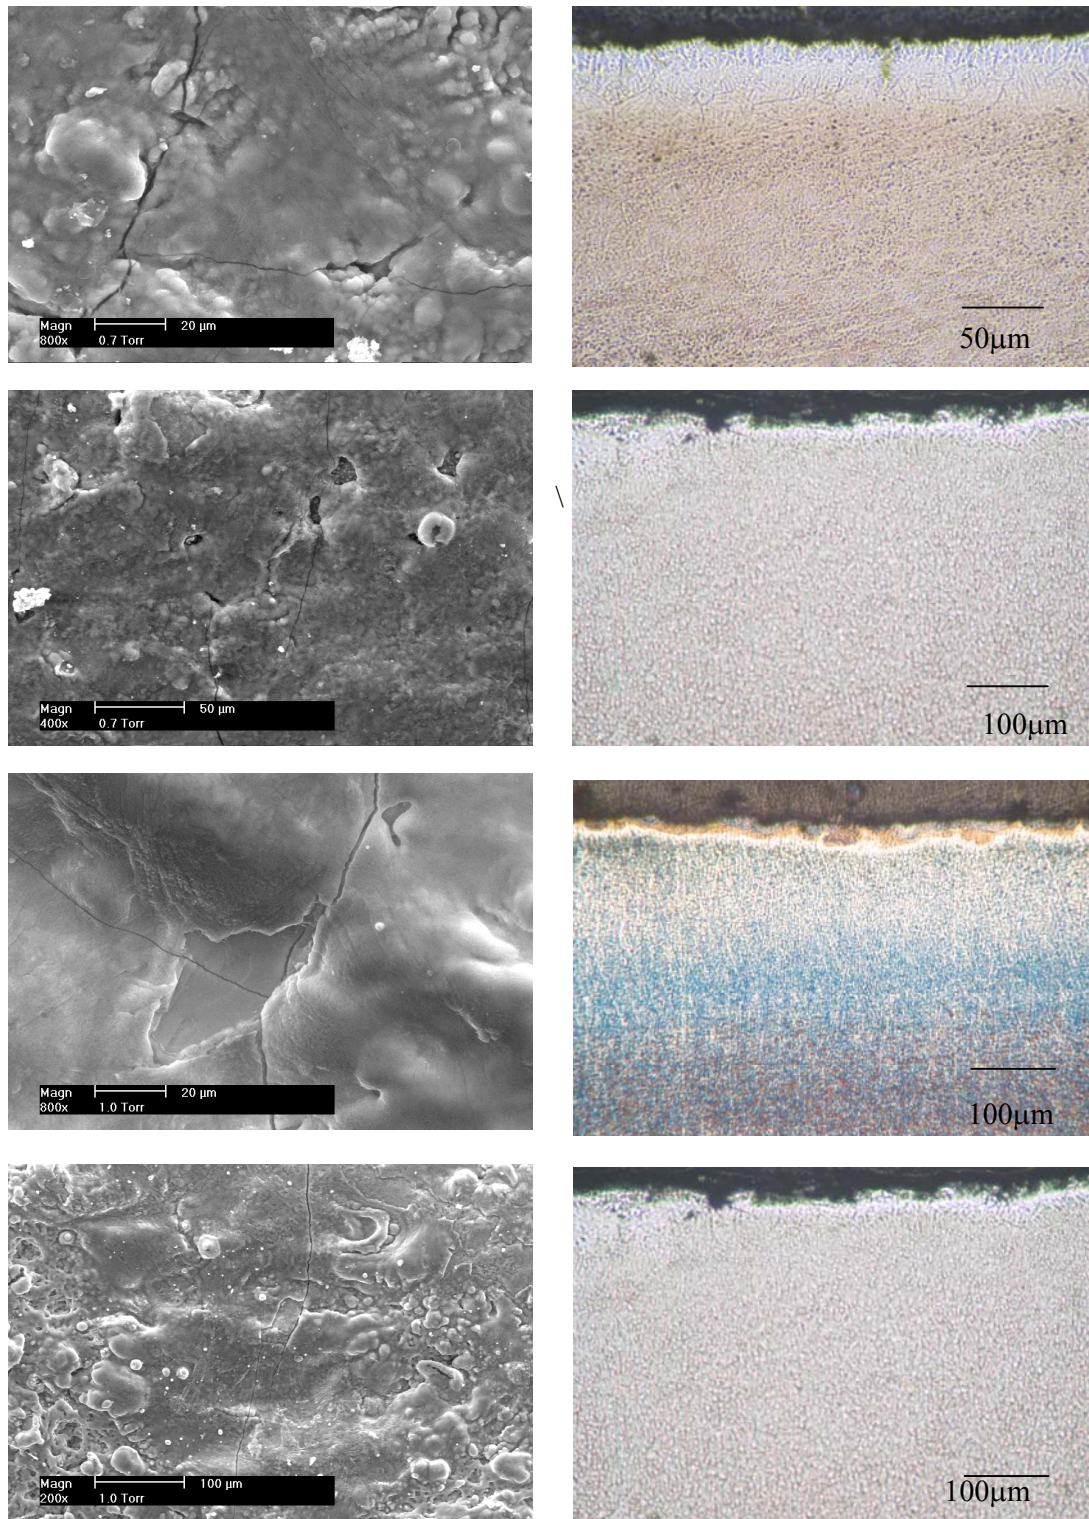

**Fig. 3.** Cracking of surface layers for specimens laser melted with CO<sub>2</sub> laser in air at 5 kW, at 1 m/min. scan rate and after pre-heating at temperature (from top to the bottom): 200, 300, 450 and 550 °C

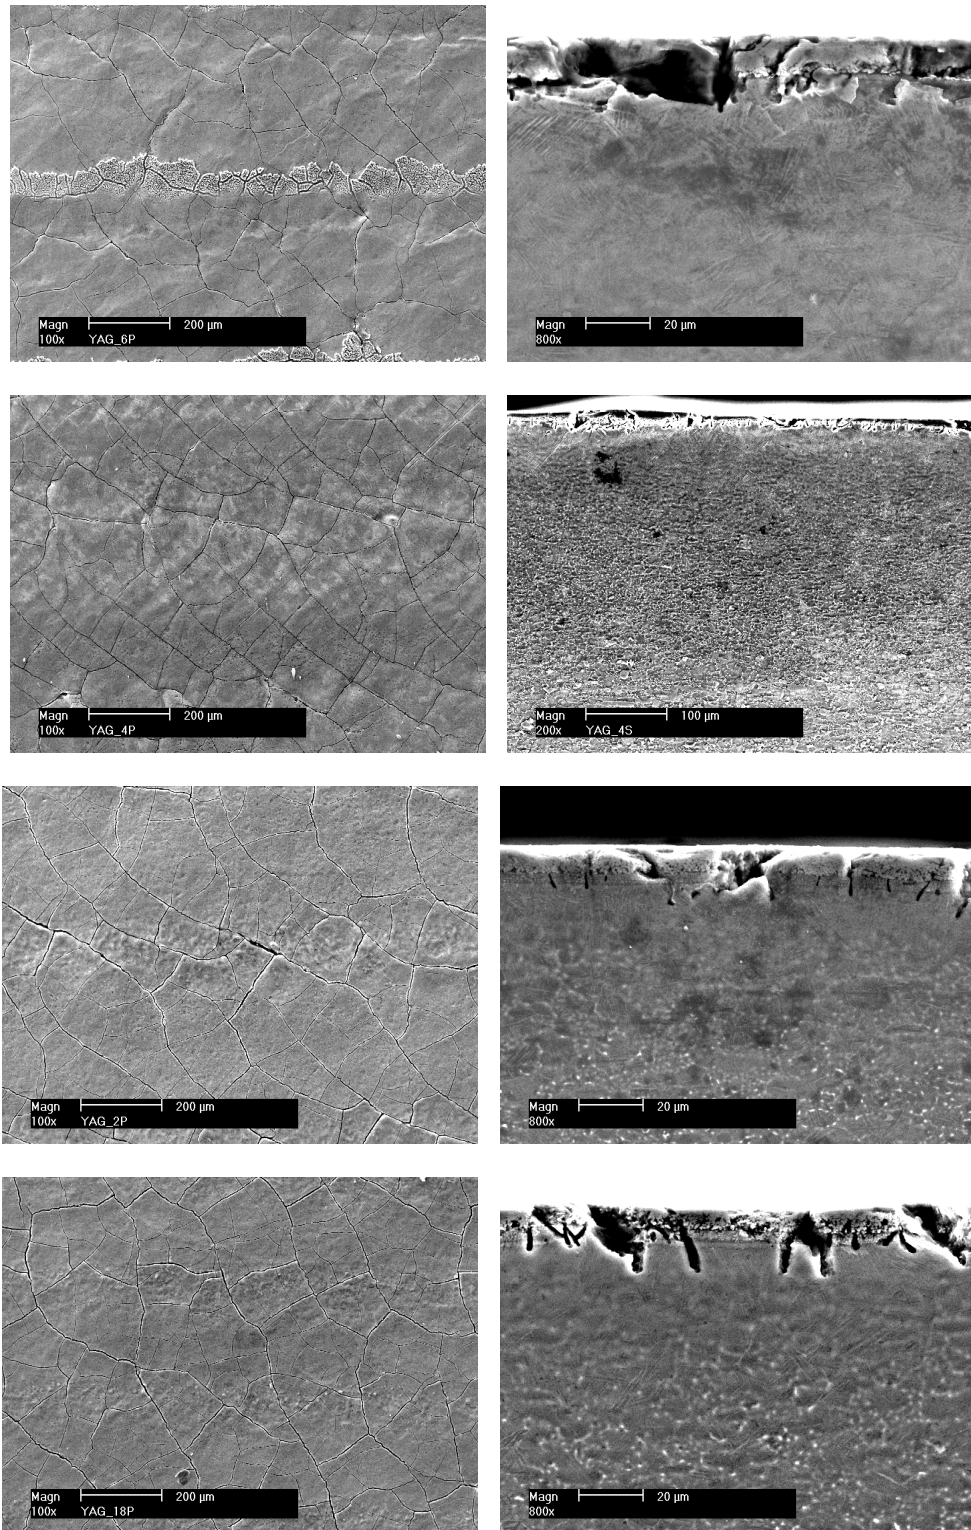

**Fig. 4.** Cracking of surface layers for specimens laser melted with Nd-YAG laser at 150 W and 50 Hz, with overlapping (from top to the bottom): 50%, scan rate 0.25 m/min.; 50%, scan rate 0.45 m/min.; 50%, scan rate 0.65 m/min.; 30%, scan rate 1 m/min

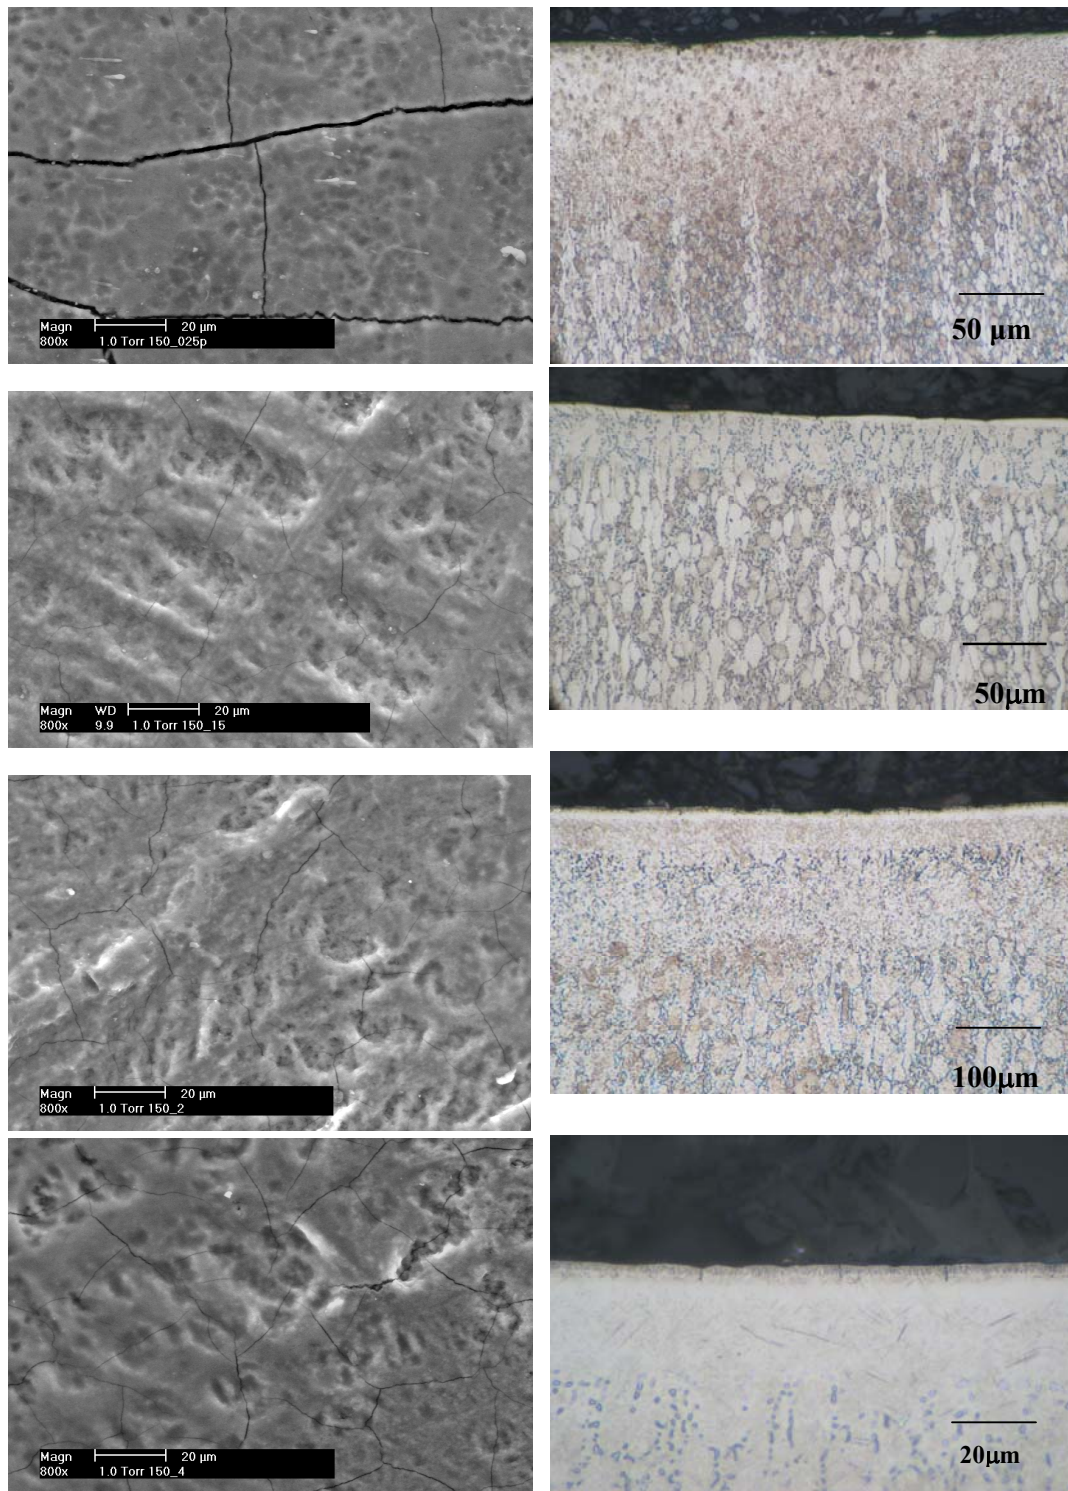

**Fig. 5.** Cracking of surface layers for specimens laser melted with Nd-YAG laser at 150 W and 50 Hz, without overlapping (from top to the bottom) at scan rate: 0.25 m/min., 1.5 m/min., 2 m/min, 4 m/min

## CONCLUSIONS

The laser treatment of the Ti-6Al-4V alloy by both CO<sub>2</sub> laser and Nd:YAG laser causes the melting and fast crystallization of surface layer accompanied by creation of perpendicular cracks from the surface to heat affected zone,  
The appearance of cracks may be attributed to two processes: martensitic transformation and brittle cracking due to high internal stresses.

## ACKNOWLEDGMENTS

The work has been supported by the Polish Ministry of Science and Higher Education as the research project No. 3 T08C 049 29 entitled "Modification of structure and properties of surface layer of the Ti-6Al-4V alloy by surface melting in ultrafast crystallisation conditions".

## REFERENCES

1. MacDonald D.E., Rapuano B.E., Deo N. i in.: Thermal and chemical modification of titanium-aluminum-vanadium implant materials: effects on surface properties, glycoprotein adsorption, and MG63 cell attachment. *Biomaterials* 25 (2004) 3135-314.
2. Nishiguchi S., Kato H., Fujita H. i in.: Titanium metals form direct bonding to bone after alkali and heat treatments. *Biomaterials* 22 (2001) 2525-2533.
3. Yang B., Uchida M., Kim H.-M. i in.: Preparation of bioactive titanium metal via anodic oxidation treatment. *Biomaterials* 25 (2004) 1003-1010.
4. Wang X.-X., Yan W., Hayakawa S. i in.: Apatite deposition on thermally and anodically oxidized titanium surfaces in a simulated body fluid, *Biomaterials*, 24 (2003) 4631-4637.
5. Wang C.X., Wang M. and Zhou X., Nucleation and growth of apatite on chemically treated titanium alloy: an electrochemical impedance spectroscopy study, *Biomaterials*, 24 (2003) 3069-3077.
6. Wang X.-X., Hayakawa S., Tsuru K., Osaka A.: Bioactive titania gel layers formed by chemical treatment of Ti substrate with a H<sub>2</sub>O<sub>2</sub>/HCl solution. *Biomaterials* 23 (2002) 1353-1357.
7. Takeuchi M., Abe Y., Yoshida Y. i in.: Acid pretreatment of titanium implants. *Biomaterials* 24 (2003) 1821-2827.
8. Sul Y.-T., Johansson C.B., Petronis S. i in.: Characteristics of the surface oxides on turned and electrochemically oxidized pure titanium implants up to dielectric





- breakdown: the oxide thickness, micropore configuration, surface roughness, crystal structure and chemical composition. *Biomaterials* 23 (2002) 491-501.
9. Song W.-H., Jun Y.-K., Han Y., Hong S.-H.: Biomimetic apatite coatings on micro-arc oxidized titania. *Biomaterials* 25 (2004) 3341-3349.
  10. Frauchiger V.M., Schlottig F., Gasser B., Textor M.: Anodic plasma-chemical treatment of CP titanium surfaces for biomedical applications. *Biomaterials* 25 (2004) 593-606.
  11. Yue T.M., Cheung T.M., Man H.C.: The effects of laser surface treatment on the corrosion properties of Ti-6Al-4V alloy in Hank's solution. *J. Mater. Sci. Lett.* 19 (2000) 205-208.
  12. Yue T.M., Yu J.K., Mei Z., Man H.C.: Excimer laser surface treatment of Ti-6Al-4V alloy for corrosion resistance enhancement. *Mater. Lett.* 52 (2002) 206-212.
  13. Guillemot F., Prima E. i in.: Ultraviolet laser surface treatment fore biomedical applications of  $\beta$  titanium alloys: morphological and structural characterization. *Appl. Phys. A* 77 (2003) 899-904.

