

WILEY

Online Proofing System


Enabling the Adobe PDF Viewer

In order to proof your article Adobe Reader or Adobe Acrobat needs to be your browser's default PDF viewer. See how to set this up for Internet Explorer, Firefox, and Safari at <https://helpx.adobe.com/acrobat/using/display-pdf-in-browser.html>


Google Chrome and Microsoft Edge do not support Adobe Reader or Adobe Acrobat as a PDF Viewer. We recommend using Internet Explorer, Firefox, or Safari.

1. Mark your corrections, changes, and query responses using the Annotation Tools outlined on the next 2 pages.

2. Save your proof corrections by clicking the “Publish Comments” button in the yellow banner above. Corrections don’t have to be marked in one sitting. You can publish comments and log back in at a later time to add and publish more comments before you click the “Complete Proof Review” button.



3. When your proof review is complete we recommend you download a copy of your annotated proof for reference in any future correspondence concerning the article before publication. You can do this by clicking on the icon to the right of the ‘Publish Comments’ button and selecting ‘Save as Archive Copy...’.

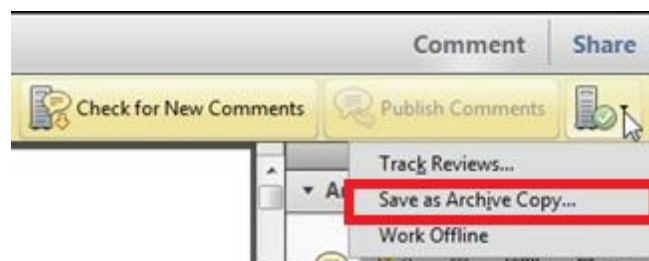

IMPORTANT: Did you reply to all queries listed on the Author Query Form appearing before your proof?

IMPORTANT: Did you click the “Publish Comments” button to save all your corrections? Any unpublished comments will be lost.

IMPORTANT: Once you click “Complete Proof Review” you will not be able to add or publish additional corrections.

4. When your proof review is complete and all corrections have been published to the server by clicking the “Publish Comments” button, please click the “Complete Proof Review” button appearing above the proof in your web browser window.



Author Query Form

Journal: JFBC

Article: 12494









Dear Author,

During the copyediting of your manuscript the following queries arose.

Please refer to the query reference callout numbers in the page proofs and respond to each by marking the necessary comments using the PDF annotation tools.

Please remember illegible or unclear comments and corrections may delay publication.

Many thanks for your assistance.

Query References	Query	Remarks
AQ1	AUTHOR: Please note that all strikethrough text present in the manuscript have been removed. Please check.	
AQ2	AUTHOR: Please check that the hierarchy of ALL section heads and subheads in the manuscript are correct.	
AQ3	AUTHOR: Please note that "Gousterova et al., 2012" has been changed to "Gousterova et al., 2011" in accordance with the reference list. Please check if it is OK as amended.	
AQ4	AUTHOR: Please note that "Maclaren & Mulligans, 1981" has been changed to "Maclaren & Milligan, 1995" in accordance with the reference list. Please check if it is OK as amended.	
AQ5	AUTHOR: Please provide complete details for "de Guzman et al., 2011" in the reference list or delete the citations from the text.	
AQ6	AUTHOR: There is no mention of "Wrześniewska-Tosik et al., 2015" in the text. Please insert a citation in the text or delete the reference as appropriate.	
AQ7	AUTHOR: Please note that "Muhsin et al., 2000" has been changed to "Muhsin & Aubaid, 2001" in accordance with the reference list. Please check if it is OK as amended.	
AQ8	AUTHOR: Please confirm that given names (red) and surnames/family names (green) have been identified correctly.	



Solubilization of keratins and functional properties of their isolates and hydrolysates

Izabela Sinkiewicz  | Hanna Staroszczyk | Agata Śliwińska

Department of Food Chemistry, Technology and Biotechnology, Gdansk University of Technology, G. Narutowicza 11/12, 80-233 Gdańsk, Poland

Correspondence

Department of Food Chemistry, Technology and Biotechnology, Gdansk University of Technology, G. Narutowicza 11/12, 80-233 Gdańsk, Poland.
Email: izabela.sinkiewicz@pg.edu.pl

Abstract

The keratinous wastes of the textile industry and poultry slaughterhouses may be used as sources of soluble keratins or hydrolysates. This review presents methods for processing raw keratin-based materials into bioproducts with functional and bioactive properties suitable for biomedical, cosmetic, food, and agricultural applications. Soluble keratin can be obtained by thermal treatment in some organic solvents, reduction, or oxidation of the disulfide bonds. Recent studies have shown that keratins contain amino acid sequences with high biological activities such as antioxidant, angiotensin I converting enzyme inhibitory, dipeptidyl peptidase IV inhibitory, and antimicrobial. Peptides containing these sequences may find numerous applications as value-added products in the food industry. More research devoted to development of methods for conversion of animal by-products to novel products is needed. Further technological investigations to create large-scale production methods are also necessary.

Practical applications

The keratinous wastes represent a problematic by-product to the wool textile industry and poultry slaughterhouses due to the large volumes and their high pollutant load. They are usually incinerated or used for low value purposes such as fertilizers. This review focuses on the trends of application of keratin recovered from animal by-products. Biomaterials for regenerative medicine, cosmetic formulations, and biodegradable food packaging can be obtained as a result of keratin self-assembly. Several peptide sequences released by hydrolysis as bioactive peptides should be studied further for their in vivo antihypertensive, and antidiabetic effects, as well as functional ingredients in foods.

KEYWORDS

bioactive peptides, functional properties, keratin hydrolysates, keratin isolates

1 | INTRODUCTION

Keratins have biological activity, biocompatibility, biodegradability, and mechanical durability (Cardamone, 2010; Ferraro, Anton, & Santé-Lhoutellier, 2016; Reddy, Chen, & Yang, 2013) and are also capable of facilitating cell adhesion and proliferation (Rouse & Van Dyke, 2010). These properties have led to the development of keratin-based materials which can be suitable for numerous applications: biomedical (wound healing, drug delivery, tissue engineering, and medical devices) (Rouse & Van Dyke, 2010; Vasconcelos, Freddi, & Cavaco-Paulo, 2008), cosmetic materials (Nomura et al., 2005; Vermelho, Villa, De Almeida, de Souza Dias, & Dos Santos, 2008), food products (Goodwin, 1976), and

agricultural uses (Veselá & Friedrich, 2009), as well as for food packaging (Song, Lee, Al Mijan, & Song, 2014).

The industrial applications of keratin-rich materials are limited due to difficulty in dissolving it due to the high level of cross-linking of the protein and tightly packed microfibrils (Reddy, Jiang, et al., 2013). In recent years, bioactive properties related to antioxidant (Ohba et al., 2003), angiotensin I converting enzyme (ACE) inhibitory (Karamać, Flaczyk, Wanasundara, & Amarowicz, 2005), dipeptidyl peptidase IV (DPP IV) inhibitory (Fontoura et al., 2014), antifungal (Gousterova et al., 2011), and antibacterial activity (Sundaram, Legadevi, Banu, Gayathri, & Palanisammy, 2015) have been found in keratin hydrolysates. Production of enzymatic hydrolysates as a source of bioactive peptides can contribute to develop

54 nutritional or pharmaceutical applications (Di Bernardini et al., 2011;
55 Gómez-Guillén, Giménez, López-Caballero, & Montero, 2011).

56 This paper reviews the processing and applications of keratin. The
57 great potential of keratin as a fibrous protein with supramolecular orga-
58 nization in the form of α -helix which is an important factor affecting
59 the characteristic mechanical properties and functionality, is discussed.
60 The potential of keratin as a store house of bioactive peptides is also
61 discussed.

62 2 | STRUCTURE AND OCCURANCE OF 63 KERATINS

64 Keratins (gr. keras—horn) are major structural proteins of vertebrate
65 epithelia. They occur in hair, bristles, wool, feathers, claws, and horns.
66 They perform various functions such as waterproof, excretion of
67 wastes and regulation of temperature, cushion to protect the deeper
68 tissues against mechanical shock and infection (Ferraro et al., 2016).
69 Keratins are very hard, visco-elastic, and resilient (Bonser, 1996). They
70 undergo bundling and have higher Young's modulus than collagen
71 (Eslahi, Dadashian, & Nejad, 2013). They are insoluble in water, weak
72 acids, and alkalis, as well as in organic solvents (Ferraro et al., 2016).
73 Keratins belong to the superfamily of intermediate filament (IF)
74 proteins forming the cytoskeleton (Kornilowicz-Kowalska & Bohacz,
75 2011). Their subunits consist of a central domain with α -helical
76 structure and globular N- and C-terminal domains composed of 15–30
77 amino acid residues, and β -sheet regions (Fraser, MacRae, Parry, &

Suzuki, 1986). The highly conserved central domains contain 310–315
residues arranged in repeating sequences (Bragulla & Homberger,
2009). Keratin subunits associate in a high-order structure forming a
double-stranded superhelix, microfibrils, and macrofibrils embedded in
an amorphous matrix (McKittrick et al., 2012). The right-handed α -helix
of α -keratin is stabilized by hydrogen bonds and numerous disulfide
bridges formed by cysteine residues that cause the insolubility of kera-
tin. Therefore it is not easily degradable by common proteolytic
enzymes such as trypsin, pepsin, and papain. A high cystine content
amounting to 7–20% of the total amino acid residues is characteristic
of keratins. They also contain about 0.5% methionine residues, as well
as large proportion of glycine, serine, leucine, and glutamic acid. The
amino acid sequence of keratin is very similar in different species
(Bragulla & Homberger, 2009).

Keratins are heterogeneous proteins due to variation in amino
acids composition (Table 1) and type of secondary structure. Twenty
isoforms have been identified with molecular weights ranging from 40
to 70 kDa in human epithelial cells (Rodziewicz & Łaba, 2006). Wool,
hair, and skin keratins with cystine content between 10 and 14% are
soft and flexible, but keratins extracted from feathers, beaks, claws,
and horns are hard, rigid, inflexible, and inextensible due to higher cys-
tine content up to 22% (Cardamone, 2010). Keratin polypeptide chains
can curl into two configurations: α -helix and β -sheet. Thus, keratins are
also classified into four groups: α -keratin, β -keratin, feather keratin,
and amorphous keratin (McKittrick et al., 2012). α -Keratins occur in
mammals as the primary constituent of hair (fiber cortex), nails, hooves, 103

TABLE 1 Amino acid composition (% of total amino acid residues) of keratin from different sources

Amino acid	Buffalo horn and hoof (Noda, Imai, Kida, & Otagiri, 1996)	Cow hair (Coward-Kelly, Chang, Agbogbo, & Holtzapple, 2006)	Feathers (Moore, Martelli, Gandolfo, Pires, & Laurindo, 2006)	Wool (Cardamone, 2010)
Alanine	6.3	4.5	3.6	5.8
Arginine	6.8	11.0	5.4	7.8
Aspartic acid	6.7	6.6	4.7	4.1
Cysteine	3.7	nd	7.7	6.1
Glutamic acid	12.6	14.5	7.7	11.4
Glycine	12.3	5.5	6.2	2.9
Histidine	0.6	1.3	-	-
Isoleucine	3.0	4.2	4.3	3.9
Leucine	8.2	9.8	7.0	11.9
Lysine	2.7	5.5	0.6	2.9
Methionine	0.6	0.7	1.3	0.2
Phenylalanine	2.9	3.1	4.2	1.9
Proline	6.8	7.7	8.7	4.1
Serine	10.8	8.9	9.3	8.3
Threonine	5.6	7.5	3.5	5.6
Tyrosine	5.9	2.4	2.0	2.4
Valine	4.1	6.8	6.9	6.1

nd = not determined.

104 horns, quills, and the epidermal layer of the skin. They have α -helical
105 tertiary structure and are rich in cystine residues ranging from 10 to
106 22%. They are divided into two subfamilies, the type I acidic microfibril-
107 lar component of ca. 40–50 kDa and the type II neutral/basic mem-
108 branes of ca. 55–65 kDa (Marchisio, 2000). β -Keratins are found in
109 reptiles and birds in scales, claws, beaks, feathers, and cuticle hair. They
110 are difficult to extract and they do not form useful reconstituted struc-
111 tures such as gels, films, coatings, and fibers suitable for medical appli-
112 cations (wound healing, bone generation, hemostasis, and peripheral
113 nerve repair (Ferraro et al., 2016; Hill, Brantley, & Van Dyke, 2010).
114 They are rich in glycine, alanine, serine, and proline residues, but lack
115 cysteine, thus the structure is stabilized only by hydrogen bonds. In
116 feather keratin β -sheet and α -helix occur in 1/3 and 2/3, respectively
117 (Marchisio, 2000). Feather keratins from various birds are similar with
118 molecular weight of about 10 kDa and cystine content of about 8%
119 which is lower than that in keratin from nail and hair (Akhtar &
120 Edwards, 1997). They are composed of about 20 different types which
121 vary only by few amino acids (Saravanan, 2012). The basic and acid
122 residues are positioned in the N- and C-terminal regions, whereas the
123 hydrophobic residues are located in the central portion. The chemical
124 or enzymatic process of feather keratin degradation is not uniform due
125 to its complex hierarchical structure (Ferraro et al., 2016). Amorphous
126 keratins, so-called γ -keratins are a part of the matrix. These are globu-
127 lar proteins with high cystine content and molecular weight of about
128 15 kDa. γ -Keratins occur in the external layer of the hair cuticle (Hill
129 et al., 2010).

130 The content and structure of various forms of keratin depend on
131 the physiological function and type of organism in which the protein
132 occurs (Wang, Yang, McKittrick, & Meyers, 2016). Structural diversity
133 of keratins also occurs within the same skin appendages. An example
134 of this is the hair in which the external layer of the cuticle contains
135 more cystine than the internal layers which are less resistant to
136 proteolytic enzymes (Kornitowicz-Kowalska & Bohacz, 2011).

137 The physicochemical and biological features of keratins isolated
138 from different sources are reflected in various functionalities of these
139 proteins of which self-assembly is the most important (Dickerson et al.,
140 2013). During thermodynamic equilibrium, the keratin molecules
141 spontaneously arrange forming well-defined networks stabilized by
142 noncovalent interactions. As a result of self-assembly, keratins can
143 provide biomaterials for medicine, bioactive peptides, cosmetic formu-
144 lations, and biodegradable films (Ferraro et al., 2016).

145 3 | SOLUBILIZATION OF KERATINS

146 3.1 | Introduction


147 The method of processing raw keratin-based materials depends on the
148 intended use of the product of keratin solubilization. These include
149 thermal treatment in some organic solvents, reduction or oxidation of
150 the disulfide bonds, alkaline, acid or enzymatic hydrolysis, various
151 hydrothermal methods, and a combination of thermo-chemical and
152 enzymatic treatments (Chojnacka, Górecka, Michalak, & Górecki, 2011;
153 Ferraro et al., 2016; Wolski, 1979).

3.2 | Production of keratin isolates

154

155 Obtaining keratin isolates containing native keratin is difficult in prac-
156 tice due to insolubility of the protein in solutions which do not cause
157 its degradation (Yin, Li, He, Wang, & Wang, 2013). A method of solubi-
158 lization of keratin was developed using organic solvents, for example,
159 N,N-dimethylformamide (DMF) or dimethyl sulfoxide (DMSO). For
160 extraction with DMSO, precipitation of dissolved protein with acetone
161 or benzene is needed. When both solvents are removed, a sediment is
162 dried for dietary purposes as protein preparation (Wolski, 1985). This
163 method requires a long extraction time and high cost caused by the
164 need for solvent recovery (Wolski, 1979). There are no changes in pro-
165 tein structure caused by this procedure and is often used by many
166 researchers on laboratory scale to obtain a substrate for determination
167 of keratinolytic activity (Wawrzkiwicz, Lobarzewski, & Wolski, 1987).


168 Reduction and oxidation of disulfide bonds belong to the common
169 methods for keratin isolation. Reduction of keratin involves use of 2-
170 mercaptoethanol (Balaji et al., 2012; Fujii & Li, 2008; Kakkar, Madhan,
171 & Shanmugam, 2014; Reichl, 2009; Schrooyen, Dijkstra, Oberthür,
172 Bantjes, & Feijen, 2001; Tanabe, Okitsu, & Yamauchi, 2004; Yamauchi,
173 Yamauchi, Kusunoki, Kohda, & Konishi, 1996), dithiothreitol (DTT),
174 dithioerythritol (Vasconcelos et al., 2008; Yang, Zhang, Yuan, & Cui,
175 2009), thioglycolic acid (Hill et al., 2010; Zabashta, Kasprova,
176 Senchurov, & Grabovskii, 2012), glutathione (Schrooyen, Dijkstra,
177 Oberthür, Bantjes, & Feijen, 2000), salts of hydrocyanic acid (Arai,
178 Sakamoto, Naito, & Takahashi, 1989), bisulfites (Tonin et al., 2007), and
179 *m*-bisulphites (Aluigi et al., 2007; Vasconcelos et al., 2008) to solubilize
180 the protein. Many keratins can remain trapped within the protective
181 structure, and usually a hydrogen-bond breaking agent, such as urea,
182 thiourea, transition metal hydroxides, surfactants, and combinations
183 thereof, are included in the extractant to unfold or denature the protein
184 (Torchinsky, 1981). Aqueous solutions of tris(hydroxymethyl)amino-
185 methane in concentrations between 0.1 and 1.0 M, and urea solutions
186 0.1–10 M are used (Schrooyen et al., 2000). The keratin solution is
187 dialyzed to remove the reagents. During dialysis, extensive protein
188 aggregation may occur but is often prevented by addition of sodium
189 dodecylsulfate (SDS) (Schrooyen et al., 2001). Upon reduction, the
190 disulfide bonds are broken to give cysteine thiol (reduced keratin) and
191 cysteine-S-sulphonate (Bunte salt) residues:



192 where keratin-Cys-S- is the reduced keratin and keratin-Cys-SSO₃⁻ is
193 the Bunte salt (Maclaren & Milligan, 1995). If keratins are extracted by
194 reduction, the resulting products are referred to as kerateines which
195 are less polar, less soluble in water, but more stable in acidic and alka-
196 line solutions. They can re-cross-link, and remain in vivo for weeks to
197 months longer than the oxidized derivatives (Hill et al., 2010).

198 When oxidation is applied to extract keratin, strong oxidants are
199 used, such as hydrogen peroxide (Breinl & Baudisch, 1907), potassium
200 permanganate (Lissizin, 1928), ammonium copper hydroxide (Nagai &
201 Nishikawa, 1970), and organic peracids (de Guzman et al., 2011). The
202 disulfide bonds are converted to sulfonic acid groups and cysteic acid
203 derivatives are formed, which are referred to as "keratoses":






203 These keratases are hygroscopic, water soluble, nondisulfide
204 cross-linkable, and degrade relatively quickly in vivo in days to weeks
205 (Hill et al., 2010).

206 3.3 | Chemical hydrolysis


207 During chemical hydrolysis, some amino acids are lost (Zhang, Li, et al.,
208 2013). Keratins can be easily solubilized by hydrolysis in strong acids or
209 alkalis, but they cannot be recovered except as amino acids or peptides,
210 peptones, and proteoses, the properties of which differ significantly
211 from those of the native keratin. The thermo-chemical treatment of
212 keratinous materials with alkali leads to degradation of asparagine,
213 arginine, serine, threonine, and glutamine (Chojnacka et al., 2011). The
214 solubilization of keratin wool at temperatures above 70°C in a pH
215 range of 9–11 for 4–12 hr in the presence of excess alkali can cause
216 conversion of disulfide groups to cystyl residues (CysS⁻):



217 and subsequently the conversion of the cystyl residues into thioether
218 groups, giving lanthionyl residues (Cys-S-Cys) (Cardamone, 2010). Pre-
219 liminary alkaline treatment of wool in the sheep skin unhairing process
220 also leads to the formation of two unnatural amino acids lysinoalanine
221 and ornithinoalanine (Money, 1996). These products are a result of ker-
222 atin hydrolysis under alkaline conditions during unhairing by the lime-
223 sulfide method. Moreover, the treatment of keratins with reducing
224 agents in strong alkaline solutions creates conditions that destroy the
225 cystine and hydroxy amino acid residues (Koleva, Danalev, Ivanova,
226 Vezenkov, & Vassilev, 2009).

227 Keratins can also be solubilized in alkaline solutions of metallic sul-
228 fides. These reagents are generally used in cosmetic depilatories and
229 removal of hair from hides in the tanning industry (Jones & Mechem,
230 1948). Furthermore, alkaline hydrolysis with prolonged exposure at ele-
231 vated temperature produces low molecular weight peptide fragments
232 with poor mechanical properties. This product has limited biomedical
233 application (Smith, Blanchard, & Lankford, 1994).

234 Acidic hydrolysis is highly efficient, but it is not recommended
235 because of the loss of some amino acids, for example, serine, threonine,
236 tyrosine, and cystine, as well as conversion of asparagine, glutamine,
237 and tryptophan to other products. Furthermore, the bonds between
238 valine and isoleucine are gradually disrupted (Chojnacka et al., 2011).
239 Keratin can be solubilized in formic acid (Aluigi et al., 2007), hydrochlo-
240 ric acid (Zhang, Li, et al., 2013), and sulfuric acid (Kurbanoglu &
241 Kurbanoglu, 2007) using appropriately high temperature. During acid
242 hydrolysis of wool keratin, disulfide, and partial peptide bonds are
243 destroyed:




244 The degree of acid hydrolysis of keratin ranges from about 33 to
245 46% (Karamać et al., 2005; Zhang, Li, et al., 2013). Acid-derived keratin
246 hydrolysates have higher glass transition and lower decomposition

temperatures than pristine wool fibers (Katoh, Shibayama, Tanabe, & 247
Yamauchi, 2004; Vasconcelos et al., 2008). They are nontoxic and bio- 248
compatible and therefore can have potential application as biomaterials 249
for wound healing and drug delivery. During acid hydrolysis of wool 250
keratin, most of the hydrogen bonds are broken down which results in 251
the amorphous structure of wool keratin polypeptides (Tung & Daoud, 252
2009). Hence the content of both α -helix and β -sheet structures in 253
wool keratin are decreased as the total crystallinity of wool is the sum 254
of α - and β -crystallinity (Cao & Billows, 1999). The products of acid 255
hydrolysis are more amorphous keratin polypeptides than alkaline- 256
derived keratin hydrolysates (Zhang, Li, et al., 2013). 257

The hydrothermal methods for obtaining soluble keratin are expen- 258
sive and destroy certain amino acids, for example, lysine, methionine, 259
and tryptophan (Grazziotin, Pimentel, De Jong, & Brandelli, 2006). They 260
result in products with poor digestibility and variable nutritional quality 261
(Chojnacka et al., 2011). These processes are performed at 100–150°C 262
and 1.5×10^5 Pa (Grazziotin et al., 2006) and alkali or acid are often 263
added. These hydrolysates have been used in feeding of poultry, rain- 264
bow trout, shrimp, and salmon after supplementation with essential 265
amino acids (Bertsch & Coello, 2005). 266

267 3.4 | Enzymatic hydrolysis

The enzymatic and/or microbiological methods for solubilization of ker- 268
atin waste are cheap and run under mild conditions (Chojnacka et al., 269
2011). These methods are an alternative to environmentally harmful 270
chemical methods used most often in keratin isolation. Keratinases are 271
extracellular serine proteases or metalloproteases produced by bacte- 272
ria, actinomycetes, and fungi (Brandelli, 2008). The characteristics of 273
keratinases produced by some microorganisms are shown in Table 2. 274
These enzymes convert insoluble keratin to feedstuffs, fertilizers, and 275
films, and also materials suitable for cosmetic and pharmaceutical appli- 276
cations (Brandelli, Daroit, & Riffel, 2010). The mechanism of microbial 277
keratinolysis is not completely known. The process of keratin degrada- 278
tion proposed by Kunert (1976) is for dermatophytes and consists of 279
sulfitolysis and proteolysis: 280



In the first stage, disulfide bonds are disrupted by sulfite produced 281
by the fungus which leads to protein denaturation (Kunert, 1976) and 282
proteolysis by endopeptidases. On the other hand, Yamamura, Morita, 283
Hasan, Yokoyama, and Tamiya (2002) proposed a two-stage process of 284
keratin degradation involving disulfide reductase and serine protease 285
produced by *Stenotrophomonas* sp. D-1 from deer fur. Keratin reduced 286
by disulfide reductase is hydrolyzed by protease to amino acids and 287
peptides. Some bacteria, actinomycetes, keratinophilic fungi, and larvae 288
of the common clothes moth (*Tineola bisselliella* Hummel) use native 289
keratin as the sole source of carbon, nitrogen, sulfur, and energy 290
(Kornitowicz-Kowalska & Bohacz, 2011). *Bacillus licheniformis*, *Bacillus* 291
pumilus, *Bacillus cereus*, and *Bacillus subtilis*, and *Stenotrophomonas* sp., 292
Fervidobacterium pannavorans, and *Fervidobacterium islandicum* were 293
isolated from plumage and bird feathers, and fermented feather waste 294

TABLE 2 Characteristic of keratinases from some microorganisms

Source of keratinase	Molecular mass (kDa)	Optimum pH	Optimum temperature (°C)	References
<i>Aspergillus fumigatus</i> TKF1	24	6.0	50	Paul et al. (2014)
<i>Aspergillus parasiticus</i>	36	7.0	50	Anitha and Palanivelu (2013)
<i>Bacillus licheniformis</i> PWD-1	33	7.5	50	Lin, Lee, Casale, and Shih (1992)
<i>Bacillus pumilus</i> A1	–	9.0	55–60	Fakhfakh-Zouari, Haddar, Hmidet, Frikha, and Nasri (2010)
<i>Bacillus subtilis</i> S14	–	8.0	50	Silva, Macedo, and Termignoni (2014)
<i>Brevibacillus</i> sp.	83.2	12.5–13.0	45	Rai and Mukherjee (2011)
<i>Chryseobacterium indologenes</i> A22	–	7.5	45	Bach, Daroit, Corrêa, and Brandelli (2011)
<i>Chryseobacterium</i> sp. kr6	64	8.5	50	Riffel et al. (2007)
<i>Fervidobacterium islandicum</i> AW-1	>200	9.0	100	Nam et al. (2002)
<i>Microsporum canis</i>	33	8.0	35–45	Descamps et al. (2003)
<i>Microsporum gypseum</i>	33	8.0	35	Raju, Neogi, Saumya, and Goud (2007)
<i>Stenotrophomonas</i> sp. D-1	40	7.0	30	Yamamura et al. (2002)
<i>Streptomyces fradiae</i>	24	8.0	50	Galas and Kałużewska (1991)
<i>Streptomyces gulbargensis</i>	46	9.0	45	Syed, Lee, Li, Kim, and Agasar (2009)
<i>Streptomyces thermoviolaceus</i> SD8	40	8.0	55	Chitte, Nalawade, and Dey (1999)
<i>Trichophyton mentagrophytes</i>	38	5.5	55	Muhsin and Aubaid (2001)

AQ7

295 (Burt & Ichida, 1999; Ichida et al., 2001; Williams & Shih, 1989).
 296 Keratinolytic species of actinomycetes, particularly from the genus
 297 *Streptomyces*, and some species from *Thermoactinomyces* occur in
 298 feathers, hairs, nails, and horns. The keratinophilic fungi live in the soil,
 299 birds, mammals, avian nests, bird plumage, mammalian hair, communal
 300 waste water, waste sediments, communal waste, and polluted water.
 301 They are represented by dermatophytes (some species of *Trichophyton*
 302 and *Microsporum*), and two genera: *Chryso sporium* and *Myceliophthora*
 303 (Korniłowicz-Kowalska & Bohacz, 2011).

304 Another method used to dissolve keratins is a combination of
 305 enzymatic and chemical treatment (Mokrejs, Svoboda, Hrcirik,
 306 Janacova, & Vasek, 2011). Reports on application of thermo-chemical
 307 treatment of keratins have appeared recently, however these methods
 308 occur in different experimental layout, aimed in aiding subsequent
 309 enzymatic digestion (Łaba et al., 2015).

310 4 | BIOACTIVE PROPERTIES OF KERATIN 311 PRODUCTS

312 4.1 | Introduction

313 Hydrolyzed proteins from many sources such as milk casein, soybean,
 314 rice bran, quinoa seed protein, canola, egg yolk protein, and muscle
 315 proteins have been reported to be sources of biologically active pep-
 316 tides (Gómez-Guillén et al., 2011) (Table 3). These peptides, sequences
 317 of 2–30 amino acids, are inactive in the parent protein and can be
 318 released during gastrointestinal digestion, enzymatic processing or
 319 microbial fermentation (Di Bernardini et al., 2011; Ferraro et al., 2016;

Gómez-Guillén et al., 2011). After liberation, they display biological
 320 activities, for example, antioxidant, ACE inhibitory, and antimicrobial.
 321 Keratins have also been shown to be a source of bioactive peptides by
 322 Ferraro et al. (2016) and Lasekan, Bakar, and Hashim (2013).
 323

324 4.2 | Antioxidant activity

325 Reports on the antioxidant properties of hydrolysates or peptides from
 326 various proteins are abundant, but only a few from keratin. The antioxi-
 327 dant peptides often contain hydrophobic amino acid residues, proline,
 328 histidine, tyrosine, and tryptophan (Brandelli, Daroit, & Corrêa, 2015).
 329 Ohba et al. (2003) reported high antioxidant activity in the enzymatic
 330 hydrolysate of a mixture of horn and hoof, and chicken feather. They
 331 suggested that the large amounts of cysteine in keratin were responsi-
 332 ble for this activity. Fakhfakh et al. (2011) also found high antioxidant
 333 activity in the hydrolysate obtained after fermentation of chicken
 334 feather with the bacterium *Bacillus pumilus* A1. The keratin wastes
 335 showed stronger antioxidant activity than the collagen wastes using
 336 the DPPH radical scavenging assay. The authors suggested that the use
 337 of feather protein hydrolysate in fish feed formulations could be
 338 suitable for improving the biological properties of the feed. Kumar
 339 et al. (2012) produced feather protein hydrolysate with a high DPPH
 340 free radical-scavenging activity which was similar to that shown by
 341 Fakhfakh et al. (2011) using the strain *Bacillus pumilus* A1. Fontoura
 342 et al. (2014) obtained hydrolysates from raw chicken feathers with the
 343 bacterium *Chryseobacterium* sp. kr6 which displayed in vitro antioxidant
 344 properties. These hydrolysates might be used as a source of bioactive
 345 constituent for feed, food, and drug production. An antioxidative

TABLE 3 Bioactive peptides from different proteins

Source	Antioxidant peptides	Reference	ACE inhibitory peptides	Reference
Bovine casein	Tyr-Phe-Tyr-Pro-Glu-Leu	Suetsuna, Ukeda, and Ochi (2000)	Arg-Tyr-Leu-Gly-Tyr Ala-Tyr-Phe-Tyr-Pro-Glu-Leu Tyr-Gln-Lys-Phe-Pro-Gln-Tyr	Contreras et al. (2009)
Bovine α -lactalbumin	Ile-Asn-Tyr-Trp	Sadat et al. (2011)	Leu-Ala-His-Lys-Ala-Leu Trp-Leu-Ala-His-Lys Val-Gly-Ile-Asn-Tyr-Trp-Leu-Ala-His-Lys	Pihlanto-Leppälä et al. (1998) Pihlanto-Leppälä, Koskinen, Piilola, Tupasela, and Korhonen (2000)
Bovine β -lactoglobulin	Phe-Asn-Pro-Thr-Gln Leu-Gln-Lys-Trp Leu-Asp-Thr-Asp-Tyr-Lys-Lys Val-Ala-Gly-Thr-Trp-Tyr Trp-Tyr-Ser-Leu	Contreras, Hernández-Ledesma, Amigo, Martín-Álvarez, and Recio (2011) Power et al. (2014) Zhang, Wu, Ling, and Lu (2013)	Ile-Ile-Ala-Glu-Lys Ile-Pro-Ala-Val-Phe-Lys Ala-Leu-Pro-Met-His-Ile-Arg	Power, Fernández, Norris, Riera, and FitzGerald (2014) Mullally, Meisel, and FitzGerald (1997)
Bovine skin gelatin	Gly-Pro-Hyp-Gly-Pro-Hyp-Gly-Pro-Hyp-Gly	Kim, Byun, Park, and Shahidi (2001) and Kim, Kim, Byun, Park, and Ito (2001)	Gly-Pro-Val Gly-Pro-Leu	Kim, Byun, et al. (2001) and Kim, Kim, et al. (2001)
Chicken feather keratin	Ser-Asn-Leu-Cys-Arg-Pro-Cys-Gly	Wan et al. (2016)	-	-
Chicken leg collagen	-	-	Gly-Ala-Hyp-Gly-Leu-Hyp-Gly-Pro	Saiga et al. (2008)
Egg yolk protein	Leu-Met-Ser-Tyr-Met-Trp-Ser-Thr-Ser-Met Leu-Glu-Leu-His-Lys-Leu-Arg-Ser-Ser-His-Trp-Phe-Ser-Arg-Arg	Park, Jung, Nam, Shahidi, and Kim (2001)	-	-
Egg white protein	Ala-His Val-His-His Val-His-His-Ala-Asn-Glu-Asn	Tsuge, Eikawa, Nomura, Yamamoto, and Sugisawa (1991)	Arg-Ala-Asp-His-Pro-Phe-Leu Tyr-Ala-Glu-Glu-Arg-Tyr-Pro-Ile-Leu	Miguel, Recio, Gómez-Ruiz, Ramos, and Lopez-Fandino (2004)
Fish skin gelatin (<i>Jonius belengerii</i>)	His-Gly-Pro-Leu-Gly-Pro-Leu	Mendis, Rajapakse, and Kim (2005)	-	-
Pacific codfish gelatin	-	-	Thr-Cys-Ser-Pro Thr-Gly-Gly-Gly-Asn-Val	Ngo et al. (2011)
Porcine actomyosin	Asp-Leu-Tyr-Ala Ser-Leu-Tyr-Ala Val-Trp	Arihara (2006)	-	-
Porcine skin collagen	Gln-Gly-Ala-Arg	Li, Chen, Wang, Ji, and Wu (2007)	-	-
Porcine skin gelatin	-	-	Gly-Phe-Hyp-Gly-Pro	Ichimura, Yamanaka, Otsuka, Yamashita, and Maruyama (2009)

346 peptide had been isolated from chicken feather hydrolysate obtained
347 by bacterial fermentation and identified as Ser-Asn-Leu-Cys-Arg-Pro-
348 Cys-Gly (Wan, Dong, Yang, & Feng, 2016). Polypeptides from bovine
349 hair exhibited significant antioxidant activity and remarkable food
350 protection. These polypeptides could be a new natural antioxidant
351 used in oil and oil-rich food (Zeng, Zhang, Zhang, & Shi, 2013).

352 4.3 | ACE inhibitory activity

353 Antihypertensive peptides can lower blood pressure through inhibition
354 ACE. Many years of research have been devoted to the synthesis of
355 ACE inhibitors used widely for therapeutic purposes to prevent hyper-
356 tension (Gómez-Guillén et al., 2011). However, they have side effects
357 such as coughing, poor taste, skin rashes, and angioneurotic edema
358 (Atkinson & Robertson, 1979). Therefore, research has focused on
359 identifying natural sources of ACE inhibitors with no side effects. Many
360 antihypertensive/ACE inhibitory peptides have been isolated from
361 casein, collagen, lactalbumin, myosin, ovalbumin, and serum albumin
362 (Brandelli et al., 2015; Contreras, Carrón, Montero, Ramos, & Recio,
363 2009; Pihlanto-Leppälä, Rokka, & Korhonen, 1998; Saiga et al., 2008).

364 Keratin has also been shown to be a source of ACE inhibitory pep-
365 tides, although it has not been studied with regard to this activity as
366 much as other proteins. ACE inhibitory activity has been shown in
367 keratin hydrolysates from poultry feathers (Karamać et al., 2005). The
368 activity of acid hydrolysates from keratin waste was lower (49.6% inhi-
369 bition) than that of collagen hydrolysates (72.3% inhibition). Increase in
370 ACE inhibitory activity with increase of the concentration of proline
371 and hydroxyproline had been observed (Gómez-Guillén et al., 2011).
372 Ohba et al. (2003) reported that the enzymatic hydrolysate of a mixture
373 of horn and hoof also exhibited low ACE inhibitory activity. ACE inhi-
374 bitory activity increased with decreasing molecular weight of hydroly-
375 sates. The hydrolysates obtained from raw chicken feathers with the
376 bacterium *Chryseobacterium* sp. kr6 also had ACE inhibitory activity
377 (Fontoura et al., 2014). The keratin hydrolysates were able to inhibit
378 65% ACE activity and was comparable to ACE inhibitory activity of
379 soybean hydrolysates and milk protein hydrolysates. Enzyme specificity
380 influences the biological activity of protein hydrolysates (Gómez-
381 Guillén et al., 2011). High hydrophobic and aromatic amino acid
382 residues content of 50–60% of the total amino acid residues is charac-
383 teristic of keratins (Fontoura et al., 2014). Hydrophobic amino acids at
384 the C-terminal tripeptide sequence contribute to the ACE inhibitory
385 activity of peptides (Haque & Chand, 2008).

386 4.4 | Other activities

387 Keratins have also been shown to be a source of bioactive peptides
388 with other biological activities. Fontoura et al. (2014) showed that the
389 hydrolysates obtained from raw chicken feathers had the ability to
390 inhibit DPP IV activity by 44%. This activity was found only in whey
391 hydrolysates which positively affect blood glucose control and insulino-
392 tropic responses in humans. Bioactive peptides from whey proteins
393 stimulate the secretion gut hormones, and also act as DPP IV inhibitors
394 in vivo (Jakubowicz & Froy, 2013).

Gousterova et al. (2011) found that feather hydrolysate obtained 395
using a mixed culture of *Thermoactinomyces* strains showed good activ- 396
ity against plant pathogenic fungi *Fusarium solani*, *Fusarium oxysporum*, 397
Mucor sp., and *Aspergillus niger*. It was suggested that the feather 398
hydrolysate could be used as an alternative soil amendment for restor- 399
ing contaminated soils, accelerating ryegrass growth, and improving the 400
quality of agricultural soils. 401

Sundaram et al. (2015) observed antibacterial activity of keratin 402
hydrolysate and keratin nanoparticles. The radius of inhibition zone for 403
keratin hydrolysate against *Staphylococcus aureus* and *Escherichia coli* 404
was 7.5 mm and 9 mm, respectively, at 100 µg/mL. They reported that 405
the inhibition zone formulated for keratin nanoparticles was higher 406
than that for keratin hydrolysates. 407

5 | CONCLUSIONS AND PERSPECTIVES 408

Keratin extracted from waste is a source of bioactive compounds for 409
biological, food, and biomaterial applications. There is more information 410
on the nonbiological functions of keratins than bioactive properties. 411
Thus there is a need for further research devoted to selecting enzyme 412
systems that convert keratin waste into bioactive peptides which could 413
be used for formation of useful novel bioproducts. Literature shows an 414
increasing number of reports on the use of various enzymes and 415
conditions to obtain bioactive peptides from keratin. The peptides with 416
antioxidant and antimicrobial activities could possibly be used as addi- 417
tives in functional food products. Similarly, the fragments of keratin 418
with ACE inhibitory and DPP IV inhibitory activity could be suitable for 419
food and pharmaceutical applications. Therefore, advanced research on 420
safety of these future bioproducts, maintenance of their bioactivity in 421
humans mechanism of action, and industrial production are necessary. 422

ORCID 423

Izabela Sinkiewicz  <http://orcid.org/0000-0001-5221-552X> 424

REFERENCES 425

- Akhtar, W., & Edwards, H. G. M. (1997). Fourier-transform Raman 426
spectroscopy of mammalian and avian keratotic biopolymers. *Spectro-* 427
chimica Acta A, 53(1), 81–90. 428
- Aluigi, A., Zoccola, M., Vineis, C., Tonin, C., Ferrero, F., & Canetti, M. 429
(2007). Study on the structure and properties of wool keratin regen- 430
erated from formic acid. *International Journal of Biological Macromole-* 431
cules, 41(3), 266–273. 432
- Anitha, T. S., & Palanivelu, P. (2013). Purification and characterization of 433
an extracellular keratinolytic protease from a new isolate of *Aspergil-* 434
lus parasiticus. *Protein Expression and Purification*, 88(2), 214–220. 435
- Arai, K., Sakamoto, M., Naito, S., & Takahashi, T. (1989). Crosslinking 436
structure of keratin. II. Intermolecular and intramolecular crosslinks in 437
potassium-cyanide-treated wool fibers. *Journal of Applied Polymer* 438
Science, 38(1), 29–44. 439
- Arihara, K. (2006). Strategies for designing novel functional meat 440
products. *Meat Science*, 74(1), 219–229. 441
- Atkinson, A. B., & Robertson, J. I. S. (1979). Captopril in the treatment of 442
clinical hypertension and cardiac failure. *Lancet*, 314(8147), 836–839. 443

- 444 Bach, E., Daroit, D. J., Corrêa, A. P. F., & Brandelli, A. (2011). Production
445 and properties of keratinolytic proteases from three novel Gram-
446 negative feather-degrading bacteria isolated from Brazilian soils.
447 *Biodegradation*, 22(6), 1191.
- 448 Balaji, S., Kumar, R., Sripriya, R., Kakkar, P., Ramesh, D. V., Reddy, P. N.
449 K., & Sehgal, P. K. (2012). Preparation and comparative characteriza-
450 tion of keratin-chitosan and keratin-gelatin composite scaffolds for
451 tissue engineering applications. *Materials Science and Engineering: C*,
452 32(4), 975–982.
- 453 Bertsch, A., & Coello, N. (2005). A biotechnological process for treatment
454 and recycling poultry feathers as a feed ingredient. *Bioresource*
455 *Technology*, 96(15), 1703–1708.
- 456 Bonser, R. H. C. (1996). The mechanical properties of feathers keratin.
457 *Journal of Zoology*, 239(3), 477–484.
- 458 Bragulla, H. H., & Homberger, D. G. (2009). Structure and functions of
459 keratin proteins in simple, stratified, keratinized and cornified
460 epithelia. *Journal of Anatomy*, 214(4), 516–559.
- 461 Brandelli, A. (2008). Bacterial keratinases: Useful enzymes for bioproc-
462 essing agroindustrial wastes and beyond. *Food and Bioprocess*
463 *Technology*, 1(2), 105–116.
- 464 Brandelli, A., Daroit, D. J., & Corrêa, A. P. F. (2015). Whey as a source of
465 peptides with remarkable biological activities. *Food Research*
466 *International*, 73, 149–161.
- 467 Brandelli, A., Daroit, D. J., & Riffel, A. (2010). Biochemical features of
468 microbial keratinases and their production and applications. *Applied*
469 *Microbiology and Biotechnology*, 85(6), 1735–1750.
- 470 Breinl, F., & Baudisch, O. (1907). The oxidative breaking up of keratin
471 through treatment with hydrogen peroxide. *Zeitschrift für Physiologi-*
472 *sche Chemie*, 52(1–2), 158–169.
- 473 Burt, E. H. Jr., & Ichida, J. M. (1999). Occurrence of feather-degrading
474 bacilli in the plumage of birds. *The Auk*, 116(2), 364–372.
- 475 Cao, J., & Billows, C. A. (1999). Crystallinity determination of native and
476 stretched wool by X-ray diffraction. *Polymer International*, 48(10),
477 1027–1033.
- 478 Cardamone, J. M. (2010). Investigating the microstructure of keratin
479 extracted from wool: Peptide sequence (MALDI-TOF/TOF) and
480 protein conformation (FTIR). *Journal of Molecular Structure*, 969(1),
481 97–105.
- 482 Chitte, R. R., Nalawade, V. K., & Dey, S. (1999). Keratinolytic activity
483 from the broth of a feather-degrading thermophilic *Streptomyces*
484 *thermiovulaceus* strain SD8. *Letters in Applied Microbiology*, 28(2),
485 131–136.
- 486 Chojnacka, K., Górecka, H., Michalak, I., & Górecki, H. (2011). A review:
487 Valorization of keratinous materials. *Waste and Biomass Valorization*,
488 2(3), 317–321.
- 489 Contreras, M., Carrón, R., Montero, M. J., Ramos, M., & Recio, I. (2009).
490 Novel casein-derived peptides with antihypertensive activity. *Interna-*
491 *tional Dairy Journal*, 19(10), 566–573.
- 492 Contreras, M., Hernández-Ledesma, B., Amigo, L., Martín-Álvarez, P. J., &
493 Recio, I. (2011). Production of antioxidant hydrolyzates from a whey
494 protein concentrate with thermolysin: Optimization by response sur-
495 face methodology. *LWT-Food Science and Technology*, 44(1), 9–15.
- 496 Coward-Kelly, G. U., Chang, V. S., Agbogbo, F. K., & Holtzapple, M. T.
497 (2006). Lime treatment of keratinous materials for the generation of
498 highly digestible animal feed: 2. Animal hair. *Bioresource Technology*,
499 117(11), 1344–1352.
- 500 Descamps, F., Brouta, F., Vermout, S., Monod, M., Losson, B., & Mignon,
501 B. (2003). Recombinant expression and antigenic properties of a
502 31.5-kDa keratinolytic subtilisin-like serine protease from *Microspo-*
503 *rum canis*. *FEMS Immunology & Medical Microbiology*, 38(1), 29–34.
- Di Bernardini, R., Harnedy, P., Bolton, D., Kerry, J., O'Neill, E., Mullen, A. 504
M., & Hayes, M. (2011). Antioxidant and antimicrobial peptide hydro- 505
lysates from muscle protein sources and by-products. *Food Chemistry*, 506
124(4), 1296–1307. 507
- Dickerson, M. B., Sierra, A. A., Bedford, N. M., Lyon, W. J., Gruner, W. 508
E., Mirau, P. A., & Naik, R. R. (2013). Keratin-based antimicrobial 509
textiles, films, and nanofibers. *Journal of Materials Chemistry B*, 40, 510
5505–5514. 511
- Eslahi, N., Dadashian, F., & Nejad, N. H. (2013). An investigation on kera- 512
tin extraction from wool and feathers waste by enzymatic hydrolysis. 513
Preparative Biochemistry and Biotechnology, 43(7), 624–648. 514
- Fakhfakh, N., Ktari, N., Haddar, A., Mnif, I. H., Dahmen, I., & Nasri, M. 515
(2011). Total solubilisation of the chicken feathers by fermentation 516
with a keratinolytic bacterium, *Bacillus pumilus* A1, and the produc- 517
tion of protein hydrolysate with high antioxidative activity. *Process* 518
Biochemistry, 46(9), 1731–1737. 519
- Fakhfakh-Zouari, N., Haddar, A., Hmidet, N., Frikha, F., & Nasri, M. 520
(2010). Application of statistical experimental design for optimization 521
of keratinases production by *Bacillus pumilus* A1 grown on chicken 522
feather and some biochemical properties. *Process Biochemistry*, 45(5), 523
617–626. 524
- Ferraro, V., Anton, M., & Santé-Lhoutellier, V. (2016). The “sisters” 525
 α -helices of collagen, elastin and keratin recovered from animal by- 526
products: Functionality, bioactivity and trends of application. *Trends* 527
in Food Science & Technology, 51, 65–75. 528
- Fontoura, R., Daroit, D. J., Correa, A. P., Meira, S. M., Mosquera, M., & 529
Brandelli, A. (2014). Production of feather hydrolysates with antioxi- 530
dant, angiotensin-I converting enzyme-and dipeptidyl peptidase-IV- 531
inhibitory activities. *New Biotechnology*, 31(5), 506–513. 532
- Fraser, R. D., MacRae, T. P., Parry, D. A., & Suzuki, E. (1986). Intermedi- 533
ate filaments in alpha-keratins. *Proceedings of the National Academy* 534
of Sciences, 83(5), 1179–1183. 535
- Fujii, T., & Li, D. (2008). Preparation and properties of protein films and 536
particles from chicken feather. *International Journal of Biological* 537
Macromolecules, 8(2), 48–55. 538
- Galas, E., & Kałużewska, M. (1991). Proteinases of *Streptomyces fradiae*. 539
III. Catalytic and some physico-chemical properties of keratinolytic 540
proteinase. *Acta Microbiologica Polonica*, 41(3–4), 169–177. 541
- Gómez-Guillén, M. C., Giménez, B., López-Caballero, M. E., & Montero, 542
M. P. (2011). Functional and bioactive properties of collagen and 543
gelatin from alternative sources: A review. *Food Hydrocolloids*, 25(8), 544
1813–1827. 545
- Goodwin, W. D. (1976). Nutrient protein from keratinaceous material 546
solubilized with N, N-dimethylformamide. *U.S. Patent No. 3,970,614*. 547
Washington, DC: U.S. Patent and Trademark Office. 548
- Gousterova, A., Nustorova, M., Paskaleva, D., Naydenov, M., Neshev, G., 549
& Vasileva-Tonkova, E. (2011). Assessment of feather hydrolysate 550
from thermophilic actinomycetes for soil amendment and biological 551
control application. *International Journal of Environmental Research*, 5
4(4), 1065–1070. 553
- Grazziotin, A., Pimentel, F. A., De Jong, E. V., & Brandelli, A. (2006). 554
Nutritional improvement of feather protein by treatment with micro- 555
bial keratinase. *Animal Feed Science and Technology*, 126(1), 135–144. 556
- Haque, E., & Chand, R. (2008). Antihypertensive and antimicrobial 557
bioactive peptides from milk proteins. *European Food Research and* 558
Technology, 227(1), 7–15. 559
- Hill, P., Brantley, H., & Van Dyke, M. (2010). Some properties of keratin 560
biomaterials: Kerateines. *Biomaterials*, 31(4), 585–593. 561
- Ichida, J. M., Krizova, L., Lefevre, C. A., Keener, H. M., Elwell, D. L., & 562
Burt, E. H. Jr. (2001). Bacterial inoculum enhances keratin 563

- 564 degradation and biofilm formation in poultry compost. *Journal of*
565 *Microbiological Methods*, 47(2), 199–208.
- 566 Ichimura, T., Yamanaka, A., Otsuka, T., Yamashita, E., & Maruyama, S.
567 (2009). Antihypertensive effect of enzymatic hydrolysate of collagen
568 and Gly-Pro in spontaneously hypertensive rats. *Bioscience, Biotech-*
569 *nology, and Biochemistry*, 73(10), 2317–2319.
- 570 Jakubowicz, D., & Froy, O. (2013). Biochemical and metabolic mecha-
571 nisms by which dietary whey protein may combat obesity and type 2
572 diabetes. *The Journal of Nutritional Biochemistry*, 24(1), 1–5.
- 573 Jones, C. B., & Mecham, D. K. (1948). Method of dispersing keratin
574 proteins with amides and the composition resulting therefrom. U.S.
575 Patent No. 2,445,028. Washington, DC: U.S. Patent and Trademark
576 Office.
- 577 Kakkar, P., Madhan, B., & Shanmugam, G. (2014). Extraction and charac-
578 terization of keratin from bovine hoof: A potential material for
579 biomedical applications. *SpringerPlus*, 3(1), 596.
- 580 Karamać, M., Flaczyk, E., Wanasundara, P. K. J. P. D., & Amarowicz, R.
581 (2005). Angiotensin I-converting enzyme (ACE) inhibitory activity of
582 hydrolysates obtained from muscle food industry by-products—a short
583 report. *Polish Journal of Food and Nutrition Sciences*, 14, 133–137.
- 584 Katoh, K., Shibayama, M., Tanabe, T., & Yamauchi, K. (2004). Preparation
585 and physicochemical properties of compression-molded keratin films.
586 *Biomaterials*, 25(12), 2265–2272.
- 587 Kim, S. K., Byun, H. G., Park, P. J., & Shahidi, F. (2001). Angiotensin I
588 converting enzyme inhibitory peptides purified from bovine skin gela-
589 tin hydrolysate. *Journal of Agricultural and Food Chemistry*, 49(6),
590 2992–2997.
- 591 Kim, S. K., Kim, Y. T., Byun, H. G., Park, P. J., & Ito, H. (2001). Purifica-
592 tion and characterization of antioxidative peptides from bovine skin.
593 *BMB Reports*, 34(3), 219–224.
- 594 Koleva, M., Danalev, D., Ivanova, D., Vezenkov, L., & Vassilev, N. (2009).
595 Synthesis of two peptide mimetics as markers for chemical changes
596 of wool's keratin during skin unhairing process and comparison of
597 the wool quality obtained by ecological methods for skins unhairing.
598 *Bulgarian Chemical Communications*, 41, 160–164.
- 599 Kornitowicz-Kowalska, T., & Bohacz, J. (2011). Biodegradation of keratin
600 waste: Theory and practical aspects. *Waste Management*, 31(8),
601 1689–1701.
- 602 Kumar, D. M., Priya, P., Balasundari, S. N., Devi, G. S. D. N., Rebecca, A. I.
603 N., & Kalaichelvan, P. T. (2012). Production and optimization of feather
604 protein hydrolysate from *Bacillus* sp. MPTK6 and its antioxidant poten-
605 tial. *Middle-East Journal of Scientific Research*, 11(7), 900–907.
- 606 Kunert, J. (1976). Keratin decomposition by dermatophytes II. Presence
607 of S-sulfocysteine and cysteic acid in soluble decomposition prod-
608 ucts. *Zeitschrift für Allgemeine Mikrobiologie*, 16(2), 97–105.
- 609 Kurbanoglu, E. B., & Kurbanoglu, N. I. (2007). Ram horn hydrolysate as
610 enhancer of xanthan production in batch culture of *Xanthomonas*
611 *campestris* EBK-4 isolate. *Process Biochemistry*, 42(7), 1146–1149.
- 612 Łaba, W., Kopeć, W., Chorążyk, D., Kancelista, A., Piegza, M., & Malik, K.
613 (2015). Biodegradation of pretreated pig bristles by *Bacillus cereus*
614 B5esz. *International Biodeterioration & Biodegradation*, 100, 116–123.
- 615 Lasekan, A., Bakar, F. A., & Hashim, D. (2013). Potential of chicken by-
616 products as sources of useful biological resources. *Waste Manage-*
617 *ment*, 33(3), 552–565.
- 618 Li, B., Chen, F., Wang, X., Ji, B., & Wu, Y. (2007). Isolation and identifica-
619 tion of antioxidative peptides from porcine collagen hydrolysate by
620 consecutive chromatography and electrospray ionization–mass spec-
621 trometry. *Food Chemistry*, 102(4), 1135–1143.
- 622 Lin, X., Lee, C. G., Casale, E. S., & Shih, J. C. (1992). Purification and char-
623 acterization of a keratinase from a feather-degrading *Bacillus*
licheniformis strain. *Applied and Environmental Microbiology*, 58(10), 624
3271–3275. 625
- Lissizin, T. (1928). The oxidation products of keratin by oxidation with
permanganate II. *Zeitschrift für Physiologische Chemie*, 173(5–6), 626
309–311. 627
- Maclaren, J. A., & Milligan, B. (1995). The chemical reactivity of the wool
628 fiber. *Wool Science*, 3, 45–49. 629
- Marchisio, V. F. (2000). Keratinophilic fungi: Their role in nature and deg- 631
radation of keratinic substrates. In R. K. S. Kushawaha & J. Guarro 632
(Eds.), *Biology of dermatophytes and other keratinophilic fungi* (Vol. 17, 633
pp. 86–92). Bilbao, Spain: Revista Iberoamericana de Micología. 634
- McKittrick, J., Chen, P. Y., Bodde, S. G., Yang, W., Novitskaya, E. E., & 635
Meyers, M. A. (2012). The structure, functions, and mechanical 636
properties of keratin. *JOM*, 64(4), 449–468. 637
- Mendis, E., Rajapakse, N., & Kim, S. K. (2005). Antioxidant properties of 638
a radical-scavenging peptide purified from enzymatically prepared 639
fish skin gelatin hydrolysate. *Journal of Agricultural and Food* 640
Chemistry, 53(3), 581–587. 641
- Miguel, M., Recio, I., Gómez-Ruiz, J. A., Ramos, M., & Lopez-Fandino, R. 642
(2004). Angiotensin I-converting enzyme inhibitory activity of 643
peptides derived from egg white proteins by enzymatic hydrolysis. 644
Journal of Food Protection, 67(9), 1914–1920. 645
- Mokrejs, P., Svoboda, P., Hrcirik, J., Janacova, D., & Vasek, V. (2011). 646
Processing poultry feathers into keratin hydrolysate through 647
alkaline-enzymatic hydrolysis. *Waste Management & Research*, 29(3), 648
260–267. 649
- Money, C. A. (1996). Unhairing and dewooling – Requirements for 650
quality and the environment. *Journal of the Society of Leather Technol-* 651
ogists & Chemists, 80, 175–186. 652
- Moore, G. R., Martelli, S. M., Gandolfo, C. A., Pires, A. T., & Laurindo, J. 653
B. (2006). Queratina de penas de frango: Extração, caracterização e 654
obtenção de filmes. *Ciência e Tecnologia de Alimentos*, 26(2), 421. 655
- Muhsin, T. M., & Aubaid, A. H. (2001). Partial purification and some bio- 656
chemical characteristics of exocellular keratinase from *Trichophyton* 657
mentagrophytes var. *erinacei*. *Mycopathologia*, 150(3), 121–125. 658
- Mullally, M. M., Meisel, H., & FitzGerald, R. J. (1997). Identification of a 659
novel angiotensin-I-converting enzyme inhibitory peptide correspond- 660
ing to a tryptic fragment of bovine β-lactoglobulin. *FEBS Letters*, 402 661
(2–3), 99–101. 662
- Nagai, Y., & Nishikawa, T. (1970). Solubilization of chicken feather 663
keratin by ammonium copper hydroxide (Schweitzer's reagent). 664
Agricultural and Biological Chemistry, 34(4), 575–584. 665
- Nam, G. W., Lee, D. W., Lee, H. S., Lee, N. J., Kim, B. C., Choe, E. A., ... 666
Pyun, Y. R. (2002). Native-feather degradation by *Fervidobacterium* 667
islandicum AW-1, a newly isolated keratinase-producing thermophilic 668
anaerobe. *Archives of Microbiology*, 178(6), 538–547. 669
- Ngo, D. H., Ryu, B., Vo, T. S., Himaya, S. W. A., Wijesekara, I., & Kim, S. K. 670
(2011). Free radical scavenging and angiotensin-I converting enzyme 671
inhibitory peptides from Pacific cod (*Gadus macrocephalus*) skin gelatin. 672
International Journal of Biological Macromolecules, 49(5), 1110–1116. 673
- Noda, J., Imai, T., Kida, K., & Otagiri, M. (1996). The physicochemical and 674
biopharmaceutical properties of fragmented keratin as a new drug 675
carrier. *Biological & Pharmaceutical Bulletin*, 19(3), 466–473. 676
- Nomura, Y., Aihara, M., Nakajima, D., Kenjou, S., Tsukuda, M., & Tsuda, 677
Y. (2005). Process for producing solubilized keratin. U.S. Patent 678
Application No. 10/594,758. 679
- Ohba, R., Deguchi, T., Kishikawa, M., Arsyad, F., Morimura, S., & Kida, K. 680
(2003). Physiological functions of enzymatic hydrolysates of collagen 681
or keratin contained in livestock and fish waste. *Food Science and* 682
Technology Research, 9(1), 91–93. 683

- 684 Park, P. J., Jung, W. K., Nam, K. S., Shahidi, F., & Kim, S. K. (2001). Purifi- 744
 685 cation and characterization of antioxidative peptides from protein 745
 686 hydrolysate of lecithin-free egg yolk. *Journal of the American Oil 746*
 687 *Chemists' Society*, 78(6), 651–656.
- 688 Paul, T., Das, A., Mandal, A., Halder, S. K., DasMohapatra, P. K., Pati, B. 747
 689 R., & Mondal, K. C. (2014). Production and purification of keratinase 748
 690 using chicken feather bioconversion by a newly isolated *Aspergillus 749*
 691 *fumigatus* TKF1: Detection of valuable metabolites. *Biomass Conver- 750*
 692 *sion and Biorefinery*, 4(2), 137–148. 751
- 693 Pihlanto-Leppälä, A., Koskinen, P., Piilola, K., Tupasela, T., & Korhonen, 752
 694 H. (2000). Angiotensin I-converting enzyme inhibitory properties of 753
 695 whey protein digests: Concentration and characterization of active 754
 696 peptides. *Journal of Dairy Research*, 67(1), 53–64. 755
- 697 Pihlanto-Leppälä, A., Rokka, T., & Korhonen, H. (1998). Angiotensin I 756
 698 converting enzyme inhibitory peptides derived from bovine milk pro- 757
 699 teins. *International Dairy Journal*, 8(4), 325–331. 758
- 700 Power, O., Fernández, A., Norris, R., Riera, F. A., & FitzGerald, R. J. (2014). 759
 701 Selective enrichment of bioactive properties during ultrafiltration of a 760
 702 tryptic digest of β -lactoglobulin. *Journal of Functional Foods*, 9, 38–47. 761
- 703 Rai, S. K., & Mukherjee, A. K. (2011). Optimization of production of an 762
 704 oxidant and detergent-stable alkaline β -keratinase from *Brevibacillus 763*
 705 sp. strain AS-S10-II: Application of enzyme in laundry detergent for- 764
 706 mulations and in leather industry. *Biochemical Engineering Journal*, 54 765
 707 (1), 47–56. 766
- 708 Raju, K. C., Neogi, U., Saumya, R., & Goud, N. R. (2007). Studies on extra 767
 709 cellular enzyme keratinase from dermatophyte *Microsporum gypseum*. 768
 710 *International Journal of Biological Chemistry*, 1(3), 174–178. 769
- 711 Reddy, N., Chen, L., & Yang, Y. (2013). Biothermoplastics from hydro- 770
 712 lyzed and citric acid crosslinked chicken feathers. *Materials Science & 771*
 713 *Engineering: C, Materials for Biological Applications*, 33(3), 1203–1208. 772
- 714 Reddy, N., Jiang, Q., Jin, E., Shi, Z., Hou, X., & Yang, Y. (2013). Bio-ther- 773
 715 moplastics from grafted chicken feathers for potential biomedical 774
 716 applications. *Colloids and Surfaces B: Biointerfaces*, 110, 51–58. 775
- 717 Reichl, S. (2009). Films based on human hair keratin as substrates for cell 776
 718 culture and tissue engineering. *Biomaterials*, 30(36), 6854–6866. 777
- 719 Riffel, A., Brandelli, A., Bellato, C. D. M., Souza, G. H., Eberlin, M. N., & 778
 720 Tavares, F. C. (2007). Purification and characterization of a keratino- 779
 721 lytic metalloprotease from *Chryseobacterium* sp. kr6. *Journal of 780*
 722 *Biotechnology*, 128(3), 693–703. 781
- 723 Rodziewicz, A., & Łaba, W. (2006). Keratins and their biodegradation. 782
 724 *Biotechnology*, 2(73), 130–147. 783
- 725 Rouse, J. G., & Van Dyke, M. E. (2010). A review of keratin-based bioma- 784
 726 terials for biomedical applications. *Materials*, 3(2), 999–1014. 785
- 727 Sadat, L., Cakir-Kiefer, C., N'Negue, M. A., Gaillard, J. L., Girardet, J. M., & 786
 728 Miclo, L. (2011). Isolation and identification of antioxidative peptides 787
 729 from bovine α -lactalbumin. *International Dairy Journal*, 21(4), 214–221. 788
- 730 Saiga, A. I., Iwai, K., Hayakawa, T., Takahata, Y., Kitamura, S., Nishimura, 789
 731 T., & Morimatsu, F. (2008). Angiotensin I-converting enzyme-inhibi- 790
 732 tory peptides obtained from chicken collagen hydrolysate. *Journal of 791*
 733 *Agricultural and Food Chemistry*, 56(20), 9586–9591. 792
- 734 Saravanan, K. (2012). Exploration of amino acids content and morpholog- 793
 735 ical structure in chicken feather fiber. *Journal of Textile and Apparel, 794*
 736 *Technology and Management*, 7(3), 1–6. 795
- 737 Schrooyen, P. M., Dijkstra, P. J., Oberthür, R. C., Bantjes, A., & Feijen, J. 796
 738 (2001). Stabilization of solutions of feather keratins by sodium dodecyl 797
 739 sulfate. *Journal of Colloid and Interface Science*, 240(1), 30–39. 798
- 740 Schrooyen, P. M., Dijkstra, P. J., Oberthür, R. C., Bantjes, A., & Feijen, J. 799
 741 (2000). Partially carboxymethylated feather keratins. 1. Properties in 800
 742 aqueous systems. *Journal of Agricultural and Food Chemistry*, 48(9), 801
 743 4326–4334. 802
- Silva, L. A. D., Macedo, A. J., & Termignoni, C. (2014). Production of 803
 keratinase by *Bacillus subtilis* S14. *Annals of Microbiology*, 64(4), 804
 1725–1733. 805
- Smith, R. A., Blanchard, C. R., & Lankford, J. Jr. (1994). Nonantigenic 806
 keratinous protein material. *U.S. Patent No. 5,358,935*. Washington, 807
 DC: U.S. Patent and Trademark Office. 808
- Song, N. B., Lee, J. H., Al Mijan, M., & Song, K. B. (2014). Development 809
 of a chicken feather protein film containing clove oil and its applica- 810
 tion in smoked salmon packaging. *LWT-Food Science and Technology*, 811
 57(2), 453–460. 812
- Suetsuna, K., Ukeda, H., & Ochi, H. (2000). Isolation and characterization 813
 of free radical scavenging activities peptides derived from casein. *The 814*
Journal of Nutritional Biochemistry, 11(3), 128–131. 815
- Sundaram, M., Legadevi, R., Banu, N. A., Gayathri, V., & Palanisammy, A. 816
 (2015). A study on anti bacterial activity of keratin nanoparticles 817
 from chicken feather waste against *Staphylococcus aureus* (Bovine 818
 mastitis bacteria) and its anti oxidant activity. *European Journal of 819*
Biotechnology and Bioscience, 6, 1–5. 820
- Syed, D. G., Lee, J. C., Li, W. J., Kim, C. J., & Agasar, D. (2009). Produc- 821
 tion, characterization and application of keratinase from *Streptomyces 822*
gulbargensis. *Bioresource Technology*, 100(5), 1868–1871. 823
- Tanabe, T., Okitsu, N., & Yamauchi, K. (2004). Fabrication and characteri- 824
 zation of chemically crosslinked keratin films. *Materials Science and 825*
Engineering: C, 24(3), 441–446. 826
- Tonin, C., Aluigi, A., Vineis, C., Varesano, A., Montarsolo, A., & Ferrero, F. 827
 (2007). Thermal and structural characterization of poly (ethylene- 828
 oxide)/keratin blend films. *Journal of Thermal Analysis and Calorimetry*, 829
 89(2), 601–608. 830
- Torchinsky, Y. M. (1981). *Sulfur in proteins*. Oxford: Pergamon Press. 831
- Tsuge, N., Eikawa, Y., Nomura, Y., Yamamoto, M., & Sugisawa, K. (1991). 832
 Antioxidative activity of peptides prepared by enzymatic hydrolysis 833
 of egg-white albumin. *Nippon Nogeikagaku Kuishi*, 65(11), 1635–1641. 834
- Tung, W. S., & Daoud, W. A. (2009). Photocatalytic self-cleaning keratins: 835
 A feasibility study. *Acta Biomaterialia*, 5(1), 50–56. 836
- Vasconcelos, A., Freddi, G., & Cavaco-Paulo, A. (2008). Biodegradable 837
 materials based on silk fibroin and keratin. *Biomacromolecules*, 9(4), 838
 1299–1305. 839
- Vermelho, A. B., Villa, A. L. V., De Almeida, A. M. M., de Souza Dias, E. 840
 P., & Dos Santos, E. P. (2008). Keratin hydrolysates, process for their 841
 production and cosmetic composition containing the same. *U.S. 842*
Patent Application No. 12/666,409. 843
- Veselá, M., & Friedrich, J. (2009). Amino acid and soluble protein cocktail 844
 from waste keratin hydrolysed by a fungal keratinase of *Paecilomyces 845*
marquandii. *Biotechnology and Bioprocess Engineering*, 14(1), 84–90. 846
- Wan, M. Y., Dong, G., Yang, B. Q., & Feng, H. (2016). Identification and 847
 characterization of a novel antioxidant peptide from feather keratin 848
 hydrolysate. *Biotechnology Letters*, 38(4), 643–649. 849
- Wang, B., Yang, W., McKittrick, J., & Meyers, M. A. (2016). Keratin: 850
 Structure, mechanical properties, occurrence in biological organisms, 851
 and efforts at bioinspiration. *Progress in Materials Science*, 76, 852
 229–318. 853
- Wawrzkiwicz, K., Lobarzewski, J., & Wolski, T. (1987). Intracellular kera- 854
 tinase of *Trichophyton gallinae*. *Journal of Medical and Veterinary 855*
Mycology: Bi-Monthly Publication of the International Society for Human 856
and Animal Mycology, 25(4), 261–268. 857
- Williams, C. M., & Shih, J. C. H. (1989). Enumeration of some microbial 858
 groups in termophilic poultry waste digestors and enrichment of a 859
 feather-degrading culture. *Journal of Applied Bacteriology*, 67(1), 25–35. 860
- Wolski, T. (1979). Urea granulates obtained from feathers for use in 861
 feeds. *Food Industry*, 33, 302–303. 862

- 804 Wolski, T. (1985). *Modified keratin proteins, their physicochemical proper-*
805 *ties, analysis and application* (DSc Dissertation). Medical Academy,
806 Lublin, Poland.
- 807 Wrześniewska-Tosik, K., Zajchowski, S., Ryszkowska, J., Tomaszewska,
808 J., Mirowski, J., & Szota, K. (2015). Influence of preparation
809 method of keratin fibers from poultry feathers on the properties of
810 composites from recycled high density polyethylene. *Polimery*, 60(2),
AQ6 811 109–117.
- 812 Yamamura, S., Morita, Y., Hasan, Q., Yokoyama, K., & Tamiya, E. (2002).
813 Keratin degradation: A cooperative action of two enzymes from
814 *Stenotrophomonas* sp. *Biochemical and Biophysical Research Communi-*
815 *cations*, 294(5), 1138–1143.
- 816 Yamauchi, K., Yamauchi, A., Kusunoki, T., Kohda, A., & Konishi, Y. (1996).
817 Preparation of stable aqueous solution of keratins, and physiochemi-
818 cal and biodegradational properties of films. *Journal of Biomedical*
819 *Materials Research Part Research*, 31(4), 439–444.
- 820 Yang, X., Zhang, H., Yuan, X., & Cui, S. (2009). Wool keratin: A novel
821 building block for layer-by-layer self-assembly. *Journal of Colloid and*
822 *Interface Science*, 336(2), 756–760.
- 823 Yin, X. C., Li, F. Y., He, Y. F., Wang, Y., & Wang, R. M. (2013). Study on
824 effective extraction of chicken feather keratins and their films for
825 controlling drug release. *Biomaterials Science*, 1(5), 528–536.
- Zabashta, Y. F., Kasprova, A. V., Senchurov, S. P., & Grabovskii, Y. E. 826
(2012). The location of the thioglycolic acid molecules in intrafibrillar 827
unordered areas of the human hair keratin structure. *International* 828
Journal of Cosmetic Science, 34(3), 223–225. 829
- Zeng, W. C., Zhang, W. C., Zhang, W. H., & Shi, B. (2013). Antioxidant 830
activity and characterization of bioactive polypeptides from bovine 831
hair. *Reactive and Functional Polymers*, 73(3), 573–578. 832
- Zhang, J., Li, Y., Li, J., Zhao, Z., Liu, X., Li, Z., . . . Chen, A. (2013). Isolation 833
and characterization of biofunctional keratin particles extracted from 834
wool wastes. *Powder Technology*, 246, 356–362. 835
- Zhang, Q. X., Wu, H., Ling, Y. F., & Lu, R. R. (2013). Isolation and identifi- 836
cation of antioxidant peptides derived from whey protein enzymatic 837
hydrolysate by consecutive chromatography and Q-TOF MS. *Journal* 838
of Dairy Research, 80(3), 367–373. 839

How to cite this article: Sinkiewicz I, Staroszczyk H, Śliwińska 841
A. Solubilization of keratins and functional properties of their 842
isolates and hydrolysates. *J Food Biochem.* 2017;e12494. 843
<https://doi.org/10.1111/jfbc.12494> 844

AQ1

845

WILEY
Author Proof

