

Article

Pilot-Scale Studies of WO₃/S-Doped g-C₃N₄ Heterojunction toward Photocatalytic NO_x Removal

Marta Kowalkińska ¹, Agnieszka Fiszka Borzyszkowska ^{1,2}, Anna Grzegórska ¹, Jakub Karczewski ³, Paweł Głuchowski ⁴, Marcin Łapiński ³, Mirosław Sawczak ⁵ and Anna Zielińska-Jurek ^{1,2,*}

¹ Department of Processing Engineering and Chemical Technology, Gdansk University of Technology, Gabriela Narutowicza 11/12, 80-233 Gdansk, Poland; marta.kowalkinska@pg.edu.pl (M.K.); agnieszka.borzyszkowska@pg.edu.pl (A.F.B.); anna.grzegorska@pg.edu.pl (A.G.)

² EcoTech Center, Gdańsk University of Technology, G. Narutowicza 11/12, 80-233 Gdansk, Poland

³ Institute of Nanotechnology and Materials Engineering, Faculty of Applied Physics and Mathematics, Gdańsk University of Technology, Gabriela Narutowicza 11/12, 80-233 Gdansk, Poland; jakub.karczewski@pg.edu.pl (J.K.); marcin.lapinski@pg.edu.pl (M.Ł.)

⁴ Institute of Low Temperature and Structural Research, Polish Academy of Sciences, 50-422 Wrocław, Poland; p.gluchowski@intibs.pl

⁵ Centre for Plasma and Laser Engineering, The Szewalski Institute of Fluid-Flow Machinery Polish Academy of Sciences, Fiszera 14, 80-231 Gdansk, Poland; mireks@imp.gda.pl

* Correspondence: annjurek@pg.edu.pl

Abstract: Due to the rising concentration of toxic nitrogen oxides (NO_x) in the air, effective methods of NO_x removal have been extensively studied recently. In the present study, the first developed WO₃/S-doped g-C₃N₄ nanocomposite was synthesized using a facile method to remove NO_x in air efficiently. The photocatalytic tests performed in a newly designed continuous-flow photoreactor with an LED array and online monitored NO₂ and NO system allowed the investigation of photocatalyst layers at the pilot scale. The WO₃/S-doped-g-C₃N₄ nanocomposite, as well as single components, were characterized by X-ray diffraction (XRD), scanning electron microscopy (SEM), Brunauer–Emmett–Teller surface area analysis (BET), X-ray fluorescence spectroscopy (XRF), X-ray photoemission spectroscopy method (XPS), UV–vis diffuse reflectance spectroscopy (DR/UV–vis), and photoluminescence spectroscopy with charge carriers' lifetime measurements. All materials exhibited high efficiency in photocatalytic NO₂ conversion, and 100% was reached in less than 5 min of illumination under simulated solar light. The effect of process parameters in the experimental setup together with WO₃/S-doped g-C₃N₄ photocatalysts was studied in detail. Finally, the stability of the composite was tested in five subsequent cycles of photocatalytic degradation. The WO₃/S-doped g-C₃N₄ was stable in time and did not undergo deactivation due to the blocking of active sites on the photocatalyst's surface.

Keywords: photocatalysis; NO_x removal; S-doped g-C₃N₄; WO₃; scaling-up



Citation: Kowalkińska, M.; Fiszka Borzyszkowska, A.; Grzegórska, A.; Karczewski, J.; Głuchowski, P.; Łapiński, M.; Sawczak, M.; Zielińska-Jurek, A. Pilot-Scale Studies of WO₃/S-Doped g-C₃N₄ Heterojunction toward Photocatalytic NO_x Removal. *Materials* **2022**, *15*, 633. <https://doi.org/10.3390/ma15020633>

Academic Editor: Aymen Amine Assadi

Received: 8 December 2021

Accepted: 11 January 2022

Published: 14 January 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

The development of industry and intensified agricultural activities, energy production, and transport has led to increased NO_x concentration in the air and contributed to environmental degradation resulting in acid rain or fog formation. The presence of NO_x in the air can give rise to various toxicological responses in humans and animals, including respiratory system damage, weakening the immune system, and genetic mutation [1–3]. Due to harmful effects on human health, research attention is focused on controlling and decreasing the NO_x concentration in the air. One of the promising methods of nitrogen oxides removal is heterogeneous photocatalysis, in which the combination of semiconductor materials and light allows the generation of reactive oxygen species (ROS) to degrade emerging contaminants [4,5]. Among various methods of NO_x decomposition, the main

advantage of photocatalytic processes is the possibility of initiating the reaction at nearly ambient temperature [2].

Over the past years, photocatalytic nitrogen oxides removal has been extensively investigated. The most described photocatalysts are based on titanium, carbon, tungsten, or bismuth compounds as a single material or a composite [1]. An example of feasible photocatalysts is graphitic carbon nitride (g-C₃N₄), a graphite analog and the most stable allotrope of carbon nitride at ambient conditions [6]. Graphitic carbon nitride has unique physicochemical properties such as a suitable bandgap energy (~2.7 eV), corresponding to visible-light absorption [7]. Therefore, g-C₃N₄ can be applied as a visible-light-driven photocatalyst toward NO_x removal in the gas phase, which was confirmed in the previous studies [8,9]. From the technological point of view, the synthesis of g-C₃N₄ is simple (typical calcination of N-containing organic precursor, e.g., urea, melamine) and low-price. However, the significant restriction of practical use of graphitic carbon nitride is a fast recombination rate of photoexcited electron-hole pairs, which lowers the photocatalytic efficiency [10]. Therefore, various modifications of g-C₃N₄ have been investigated, including doping to generate electron trapping centers or heterojunction in composites to enhance the charge carriers' separation and limit the recombination process [10,11].

An effective way of improving the photocatalytic performance of g-C₃N₄-based material is by introducing dopants. Considering non-metal doping, incorporating sulfur with an extra electron to the crystal lattice is especially worthy of attention. According to first-principle calculations performed by Ling et al. [12], S-doping can extend the light response range by narrowing the bandgap and creating gap states. These predictions were confirmed by Kadam et al. [13], who have shown enhanced photocatalytic degradation of rhodamine B and tetracycline hydrochloride under visible light compared with an unmodified photocatalyst. Another approach to increase the photocatalytic activity is creating a heterojunction with a metal oxide such as tungsten(VI) oxide (WO₃), an n-type semiconductor that can be activated under visible light irradiation (2.4–2.8 eV) [14].

The WO₃/g-C₃N₄ composite photocatalysts in a Z-scheme heterojunction were examined towards antibiotics removal [15], dye degradation [16], and hydrogen generation [17]. Considering the promising properties of S-doped g-C₃N₄ compared with un-doped g-C₃N₄, for the first time, we propose WO₃/S-doped g-C₃N₄ nanocomposite for solar-driven photodegradation of NO_x.

Considering the technological point of view, we have focused on synthesizing the unsophisticated and efficient composite material. However, most of the scale-up studies and practical applications of photocatalysts considered only titania-based materials [18–21]. However, titanium(IV) oxide is efficient only under ultraviolet light [22], which is in the minority in the solar light spectrum. Therefore, more investigations in the application of visible-light-driven photocatalysts are needed. In this regard, the main goal of the present work is the pilot-scale studies of WO₃/S-g-C₃N₄ toward photocatalytic NO_x removal in the design of a continuous-flow system. The experimental setup of a continuous-flow photoreactor is schematically presented in Figure 1. The experimental setup consists of bottles with gas mixtures of air and NO_x, a set of reducers and mass flow controllers enabling the generation of a stream of polluted air, the photocatalytic chamber, LEDs panels 300 × 300 mm as irradiation sources, and electro-mechanical control system coupled to the computer which also secures automatic recording of measurement data and process parameters. The main element of the stand is a research chamber made of 2 mm thick stainless steel. The entire chamber consists of three modules (1) where the photocatalysts immobilized on glass plates in a dimension of 305 × 305 mm are placed. There is a free space of 5 mm above the sample for the contaminated air to flow.

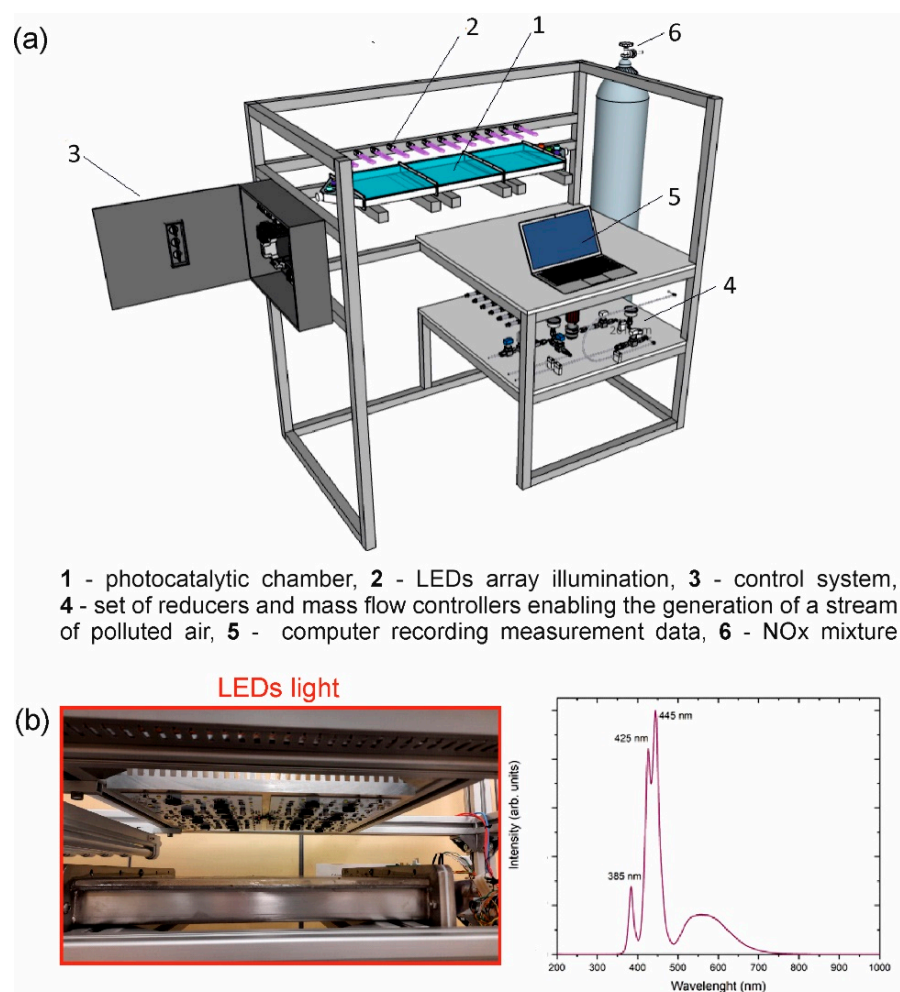


Figure 1. (a) Schematic presentation of the experimental setup of a continuous-flow photoreactor; (b) equipped with LED panels as irradiation source with an emission spectrum of UV–vis light.

At the top, the chamber is closed with a plate of quartz glass, which enables exposure of the samples to the full spectrum of simulated solar light. The light spectrum of the light source is presented in Figure 1b. The light flux in the range of 310–380 nm was $5 \text{ mW} \cdot \text{cm}^{-2}$. The air is supplied to the chamber using mass flow controllers (Bronkhorst F-201CV-10K-RGD-00-V), enabling digital flow control in the range of 0.2–10 nL/min (with an accuracy of $\pm 0.5\%$ of reading plus $\pm 0.1\%$ range). The connected chambers on both sides end with diffusers (2), ensuring even gas distribution. Gas chemical sensors (3) are installed in the diffusers, enabling the measurement of the following parameters: the 4-electrode electrochemical sensor for nitrogen oxide concentration measurement, the 4-electrode electrochemical sensor for nitrogen dioxide concentration measurement, temperature, humidity, and pressure sensors.

The degradation mechanism and effect of process parameters (humidity, gas flow rate, NO₂ concentration, and amount of photocatalyst) on NO_x removal efficiency were studied in detail.

2. Materials and Methods

2.1. Materials

Melamine (ACS reagent, 99.0–100.5%) and thiourea (ACS reagent, $\geq 99\%$) for the synthesis of S-doped-g-C₃N₄, sodium tungstate dihydrate (ACS reagent, $\geq 99\%$), and oxalic acid (98%) for the synthesis of WO₃ were purchased from Sigma-Aldrich (Poznan, Poland). Ethanol (96%) for WO₃/S-doped-g-C₃N₄ synthesis was purchased from POCh.

All reagents were used as received without further purification. Deionized water (DI) was used in all experiments.

2.2. Synthesis of Photocatalysts

2.2.1. Synthesis of WO₃

Firstly, 7.34 g of Na₂WO₄ · 2H₂O was dissolved in 90 cm³ of DI water and 2M HCl with the volume ratio of 1:1 and marked as solution A. Next, 0.35 g of oxalic acid was dissolved in 90 cm³ of DI water and marked as solution B. Solution A was added to solution B and mixed for 15 min. The mixture was transferred to a 200 cm³ Teflon-lined stainless steel reactor, and solvothermal synthesis was performed at 90 °C for 3 h. The obtained material was rinsed three times with DI water, once with methanol, and then dried at 80 °C for 2 h. Finally, the powder was calcined at 500 °C for 1 h with a heating rate of 5 °C/min.

2.2.2. Synthesis of S-Doped-g-C₃N₄

In the first step, 7.5 g of melamine and 7.5 g of thiourea were ground together in a mortar. Then, the material was calcined at 580 °C for 3 h with a heating rate of 10 °C/min.

2.2.3. Synthesis of WO₃/S-Doped-g-C₃N₄ Composite

Typically, 3 g of S-doped-g-C₃N₄ was dispersed in a 100 cm³ mixture of DI water and ethanol with the volume ratio of 1:1 and ultrasonicated for 1 h. Then, 3 g of WO₃ was added and ultrasonicated for another 1 h. The resulting suspension was transferred to a 200 cm³ Teflon-lined stainless steel reactor, and solvothermal synthesis was performed at 150 °C for 6 h with a heating rate of 5 °C/min. The obtained material was rinsed a few times with DI water and dried at 80 °C for 3 h.

2.3. Material Characterization

The structure and phase composition of synthesized photocatalysts were investigated using X-ray powder diffraction (XRD). X-ray diffraction patterns were recorded on the Rigaku MiniFlex 600 X-ray diffractometer (Tokyo, Japan) with Cu K α radiation ($\lambda \sim 1.54 \text{ \AA}$) in the $2\theta = 10\text{--}80^\circ$ range. Moreover, the chemical structure and bond identification in samples was determined by Fourier-transform infrared spectroscopy (FTIR) in the transmittance mode. The FTIR Nicolet iS10 (Thermo Fisher Scientific, Waltham, MA, USA) spectrometer was used at room temperature in the wavenumber range from 4000 to 400 cm⁻¹. The pellets containing 95% of potassium bromide and 5% (wt.) of a photocatalyst were analyzed in each measurement.

The morphologies of prepared powders were characterized by scanning electron microscope (SEM) with field emission gun, model Quanta FEG 250 (FEI, Hillsboro, OR, USA). The content of sulfur and WO₃ in the composite were measured using a WDXRF S8 TIGER analyzer (Bruker, S8 TIGER, Bruker, Karlsruhe, Germany) using X-ray fluorescence spectroscopy (XRF). The analyses were performed according to the standard PN-EN 15309:2010. To determine the parameters of the porous structure of the single components and the composite, including Brunauer–Emmett–Teller (BET) surface area and pore volume using low-temperature nitrogen sorption, a Micromeritics Gemini V apparatus (model 2365; Norcross, GA, USA) was used. Before each measurement, the analyzed photocatalysts were degassed at 200 °C for 2 h. The specific surface areas were determined by the multipoint BET method in the p/p_0 range from 0.05 to 0.30. Total pore volumes were estimated from the nitrogen adsorbed at $p/p_0 = 0.995$.

The detailed chemical composition of the samples and nitrates identification were analyzed by the X-ray photoemission spectroscopy method (XPS). XPS measurements were carried out at room temperature under ultrahigh vacuum conditions with pressures below 1.1×10^{-6} Pa using Omicron NanoScience equipment with an Argus hemispherical analyzer (ScientaOmicron, Uppsala, Sweden). Spectra deconvolution was performed with the CASA XPS software (Casa Software Ltd., ver. 2.3.23., Devon, UK) package using the Shirley background subtraction and Gauss–Lorentz curve fitting algorithm by the least-

squares method—GL (30). The XPS spectra were calibrated to obtain binding energy of 285.00 eV for the C 1 s peak.

The optical properties, including absorbance and Kubelka–Munk functions, were studied by a UV–vis spectrophotometer (Thermo Fisher Scientific Evolution 220, Waltham, MA, USA) to measure diffuse reflectance (DRS). During measurements, barium sulfate was used as a standard. Based on the obtained spectra, the bandgap energy calculations were performed by Tauc's method.

The photoluminescence spectra were recorded using an FLS980 fluorescence spectrophotometer from Edinburg Instruments (Livingston, Wielka Brytania) equipped with a 450 W xenon lamp as an excitation source and a Hamamatsu 928 PMT detector. Measured PL spectra were corrected for the sensitivity and wavelength of the experimental setup. The slit width was 2 μm (excitation spectra) or 0.3 μm (emission spectra). The same equipment was used for decay measurements to calculate the charge carrier lifetime, and the lamp was changed to a 150 W pulse xenon lamp. All measurements were recorded at room temperature. The average experimental lifetimes of obtained photocatalysts were calculated according to Hu et al. [23].

2.4. Coating Methodology

Firstly, 2 g of the photocatalyst was mixed with deionized water (30 cm^3) in Falcon tubes (50 cm^3) using the vortex mixer. The homogenous sample was transferred onto glass (30.5 $\text{cm} \times 30.5 \text{ cm}$) and evenly distributed on the whole surface. Finally, the coatings were dried at room temperature for 24 h.

2.5. Photocatalytic Setup

The photocatalytic experiments were carried out in a flat quartz glass photoreactor in a volume of 1.5 dm^3 with continuous NO_2 flow. The photoreactor was used for NO_2 photocatalytic conversion over WO_3 , S-doped g- C_3N_4 , and WO_3 /S-doped g- C_3N_4 , as depicted in Figure 1a. The plate with the photocatalyst is parallel to an air-tight optical window for photoirradiation. The gas with pollution passes only through the space between the test plate and the window. The flow rates of the reactant gases (100 ppm NO_2 in synthetic air, Linde Gas) and the pretreatment gas (synthetic air, Linde Gas) were adjusted with gas flow meters. The relative humidity (RH) level of the NO_2 flow was controlled at 40% by passing the zero air stream through a humidification chamber. The air stream, NO_2 , and humidity flow rates were controlled at 0.9 dm^3/min , 0.1 dm^3/min , and 0.3 dm^3/min . The concentration of NO_2 was detected continuously by employing a NO_x analyzer (AlphaSense, NO-B4 4-electrode nitric oxide sensor, Alphasense 000-0NO2-B43F nitric dioxide sensor). A LED panel light was used in the photocatalytic reaction as a light source. The light flux in the range of 310–380 nm was on average 5 $\text{mW}\cdot\text{cm}^{-2}$.

Before each measurement, the test gas was allowed to flow into the photoreactor without photoirradiation to reach adsorption-desorption equilibrium. After 30 min, the lamp was turned on to start the photocatalytic process. Finally, the photocatalytic performance of obtained photocatalysts NO_2 was demonstrated in terms of NO_2 conversion rate (Equation (1)):

$$\text{NO}_2 \text{ conversion} = \left(\frac{[\text{NO}_2 \text{ inlet}] - [\text{NO}_2 \text{ outlet}]}{[\text{NO}_2 \text{ inlet}]} \right) \times 100\%. \quad (1)$$

3. Results and Discussion

3.1. Characterization of Photocatalysts

The structural parameters and phase compositions of photocatalysts were examined using X-ray diffraction. XRD patterns are presented in Figure 2. The XRD patterns of the single-phase components monoclinic WO_3 and S-g- C_3N_4 are in good agreement between the recorded and calculated patterns. No signals originating from impurities were detected. The diffractogram of WO_3 /S-g- C_3N_4 was similar to pure tungsten(VI) oxide patterns.



However, a significant difference is noted in the range of $2\theta = 25^\circ\text{--}30^\circ$ (inset in Figure 2). In the presented composite, the peaks (120) and (112) originating from monoclinic WO_3 and the main peak (002) from S-g- C_3N_4 can be distinguished. This analysis confirmed the presence of a hybrid photocatalyst of graphitic carbon nitride and WO_3 .

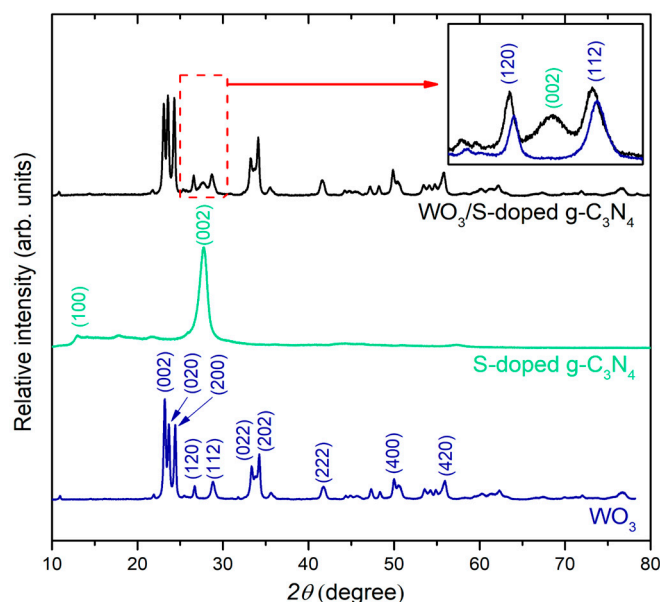


Figure 2. XRD patterns of $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ and single components. The inset shows the zoom at diffractograms of WO_3 and $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ in the range $2\theta = 25^\circ\text{--}30^\circ$.

The chemical bonding identification of obtained samples was investigated by infrared spectroscopy. The presence of characteristic bands in single components of WO_3 and S-g- C_3N_4 confirmed the previous phase identification of $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ (see Figure 3). In the case of pure WO_3 , a broad absorption band in the wavenumber range of $420\text{--}1000\text{ cm}^{-1}$ attributed to the vibration modes of the W–O bond verifies the formation of tungsten(VI) oxide. The strong bands in 745 cm^{-1} and 818 cm^{-1} are assigned to the stretching mode of W–O–W [24]. These peaks probably overlap with a band located at 946 cm^{-1} , attributed to W=O stretching vibration [25,26]. In the case of S-doped graphitic carbon nitride, a narrow band at 808 cm^{-1} can be attributed to the triazine ring mode, which corresponds to condensed CN heterocycles [27,28]. The distinct absorption bands at 1572 and 1639 cm^{-1} are attributed to C=N stretching, while the four bands at 1231 , 1314 , 1396 , and 1453 cm^{-1} to aromatic C–N stretching [29]. In the composite, FTIR spectra are similar to the doped carbon nitride. The difference can be noticed below 1000 cm^{-1} , in which triazine ring modes from S-g- C_3N_4 overlap with bands assigned to the stretching mode of W–O–W. Therefore, FTIR spectra confirmed the presence of two phases in the $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ composite.

The morphology of the $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ composite and single components was determined by scanning electron microscopy. SEM images of the photocatalysts are presented in Figure 4. WO_3 possessed a polydisperse nature in which small nanoparticles and disc-shaped nanostructures can be distinguished (Figure 4a). In the case of S-g- C_3N_4 (Figure 4b), a flake-like morphology was observed, which is in agreement with previous reports [6,7,13]. Comparing SEM images of the composite (Figure 4c) with the morphology of single components, features of two phases can be indicated. The two-dimensional flakes of S-g- C_3N_4 are covered with nanoparticles of WO_3 . Therefore, each phase is connected with the other, which results in creating a heterojunction.

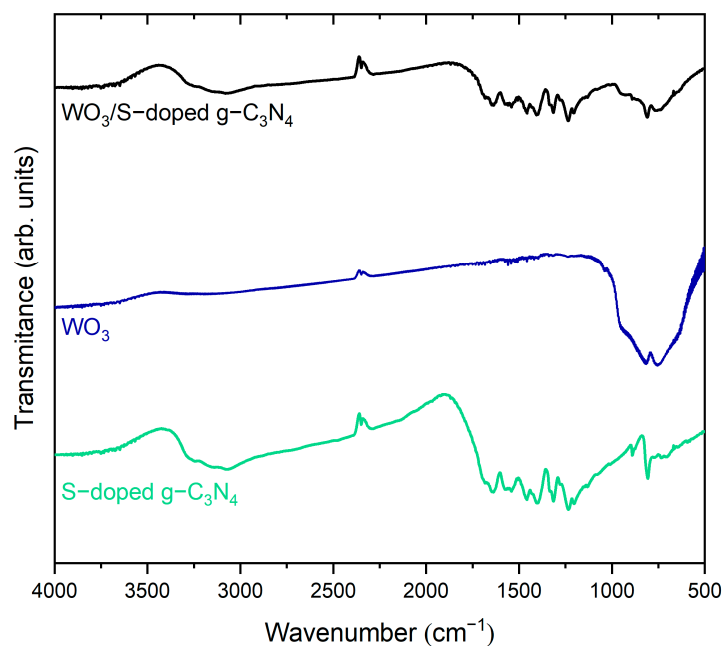


Figure 3. FTIR spectra of $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ and single components.

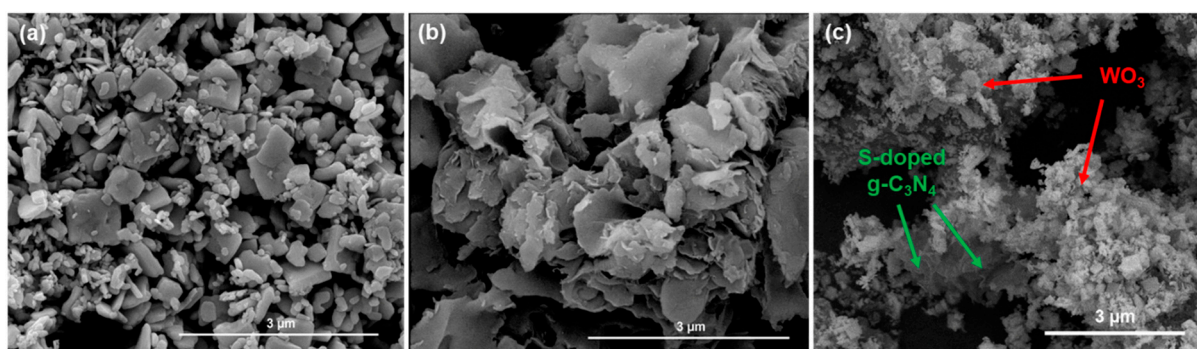


Figure 4. SEM images of (a) WO_3 ; (b) $\text{S-g-C}_3\text{N}_4$; and (c) $\text{WO}_3/\text{S-g-C}_3\text{N}_4$.

Moreover, the surface area of obtained samples was calculated using the BET method. The values of specific surface areas and pore volumes are presented in Table 1. All materials possessed surface area in the range of 11.5–14.5 m^2/g . Moreover, to confirm the presence of sulfur in the $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ composite, X-ray fluorescence spectroscopy (XRF) was performed. The content of S in the binary $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ (1:1) photocatalyst was about 0.03–0.05% (m/m). Lin et al. [30] have shown that the high dopant concentration can hinder photocatalytic activity. In the case of Fe-doped TiO_2 , it was demonstrated that the extent of photodegradation diminishes with increasing dopant concentration, and only the 0.01 mol% Fe- TiO_2 film showed enhanced photoactivity. It resulted from the presence of lattice distortions at high dopant amounts, which increased the number of recombination centers, hindering photocatalytic activity [25].

Table 1. Morphological and optical properties of obtained samples.

Sample	BET Surface Area (m^2/g)	Pore Volume (cm^3/g)	Bandgap (eV)	Average Carrier Lifetime (ns)	
				300 nm	415 nm
WO_3	14.0	0.0069	2.48	-	-
S-doped $\text{g-C}_3\text{N}_4$	14.5	0.0073	2.55	15.3	16.1
$\text{WO}_3/\text{S-doped g-C}_3\text{N}_4$	11.5	0.0058	2.51	17.6	14.2

To study the chemical composition of the surface WO_3 and WO_3/S -doped $\text{g-C}_3\text{N}_4$ photocatalysts after the photocatalytic NO_x conversion, high-resolution X-ray photoelectron spectroscopy (XPS) analyses were performed. Further analysis of the final composite material confirmed the presence of sulfur (Figure 5a). The peaks at 165.5 eV and 168.5 eV originate from N-S groups and H-SO₃ groups present in the S-doped carbon nitride [31]. On the basis of survey spectra, it can be concluded that the sulfur content is relatively low compared with other elements, which is in agreement with XRF results. In the case of XPS spectra of the C1s regions (Figure 5b), the experimental curve can be deconvoluted into two peaks with binding energies at 285 eV and 288.5 eV, which could be ascribed to C-C and/or graphite C=C surface coordination of carbon, and sp²-bonded carbon (C=N), respectively, which are typical groups for $\text{g-C}_3\text{N}_4$ [32,33]. The doublet peaks in Figure 5c, located at a binding energy of 35.5 eV and 37.6 eV, are attributed to $\text{W}4f_{7/2}$ (W^{+5}) and $\text{W}4f_{5/2}$ (W^{+6}), respectively [14]. No sub-stoichiometry of tungsten(VI) oxide and the $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ was observed. The N1s signal (Figure 5d) may be deconvoluted to two peaks at 399 eV and 401 eV, which corresponds to triazine rings (C=N-C) and C-N-H, respectively [32,34,35]. For pure WO_3 N1s region weak broad peak about 400 eV may be assigned to the unreacted NO adsorbed on the surface [36].

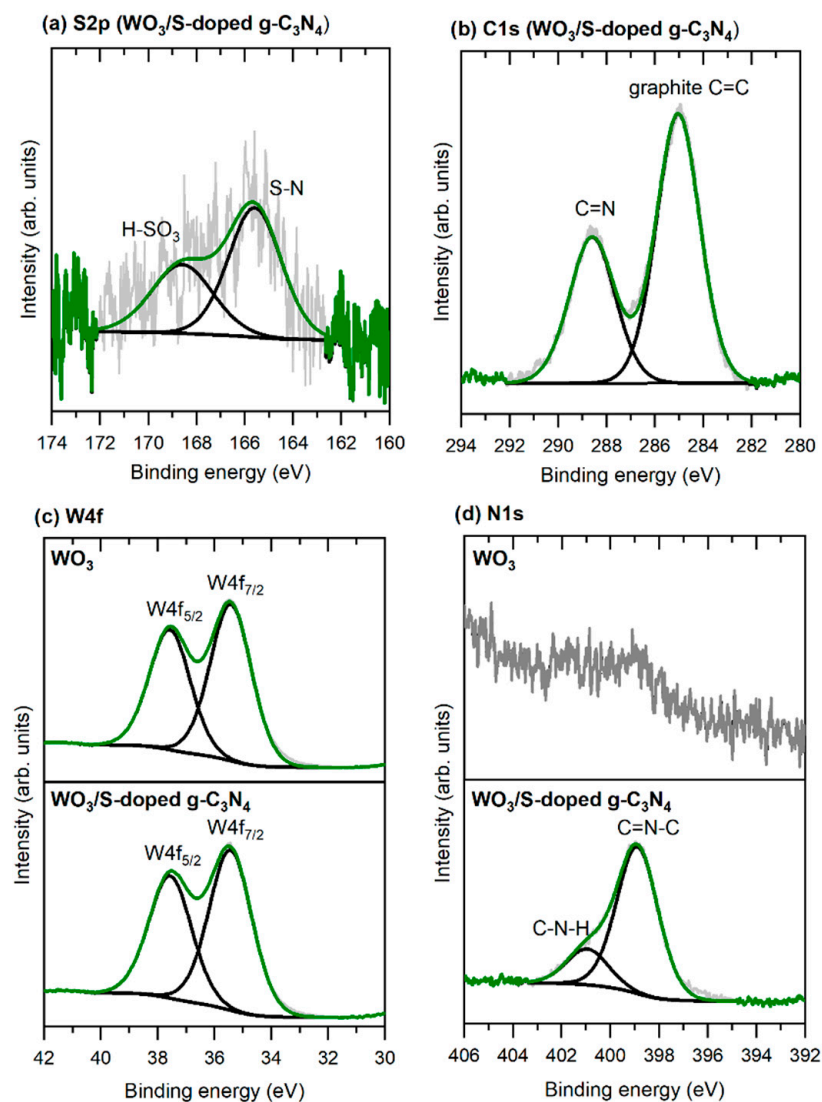


Figure 5. XPS spectra of (a) S2p, (b) C1s, (c) W4f, and (d) N1s signals for WO_3 and WO_3/S -doped $\text{g-C}_3\text{N}_4$.

The DR/UV-vis spectra of WO_3 , S-doped $\text{g-C}_3\text{N}_4$, and $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ are presented in Figure 6. All materials revealed the highest absorbance in the range from 200–450 nm. These photocatalysts are also capable of absorbing visible light at higher wavelengths, which is consistent with the fact that all samples are colorful (WO_3 is lime-green, whereas S-doped $\text{g-C}_3\text{N}_4$ is yellow, which corresponds to light absorption in the 530–590 nm range). Based on this observation and the calculated bandgap values, it was assumed that all samples could efficiently utilize visible light, which is in the majority of the solar light spectrum.

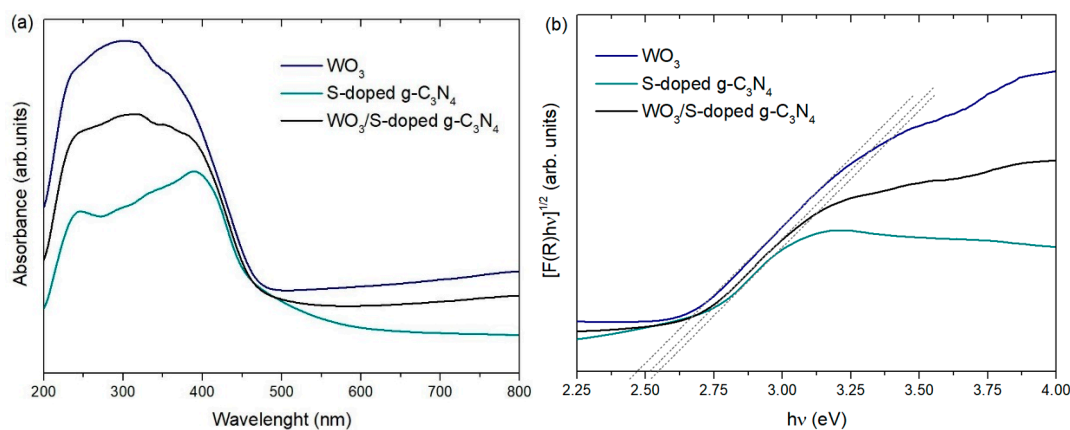


Figure 6. (a) DR/UV-vis spectra and (b) the Kubelka–Munk transformation of obtained samples.

Moreover, photoluminescence spectra and luminescence decay curves were determined, as presented in Figure 7. The highest PL emission was observed for S-doped $\text{g-C}_3\text{N}_4$ with the maximum at ~ 455 nm (blue light) under UV-light excitation (Figure 7a). Similar observations were noticed when the sample was excited in visible light (Figure 7b). According to Zhang et al. [7], carbon nitride can be characterized by enhanced photoresponse and an extremely high quantum yield up to 19.6%. Although these properties are attractive in many potential applications, e.g., bioimaging, in the case of photocatalysis, the high PL emission may hinder the photocatalytic activity. The emission is connected with radiative recombination, which is not desirable because this process lowers the charge carriers' concentration [4]. Therefore, the photocatalytic processes with $\text{g-C}_3\text{N}_4$ as a single compound are insufficient and require further photocatalyst modification [37]. The lower PL intensity for $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ in comparison with pure S-doped carbon nitride was noticed. The most visible differences are especially in Figure 6a under $\lambda_{exc} = 300$ nm conditions. These results confirm the limited recombination rate due to efficient charge carriers' separation in the heterojunction [38]. Furthermore, charge carriers' lifetimes were calculated based on luminescence decay curves (Figure 7c,d). The average carrier lifetimes $\langle \tau \rangle$ are presented in Table 1. All photocatalysts possessed the $\langle \tau \rangle$ value of 14–16 ns. It is worth highlighting that the charge carrier lifetimes do not decrease when the light excitation wavelength is changed from 300 nm (UV) to 415 nm (visible). This is another confirmation that these materials are photoactive under solar irradiation. Moreover, there is no significant decline in the $\langle \tau \rangle$ value when S-doped carbon nitride is introduced into the composite with WO_3 . Under 300 nm excitation conditions, the carrier lifetime is prolonged in comparison with single S-g- C_3N_4 , which can be explained by efficient charge carriers' separation. This process resulted in enhanced photocatalytic performance.

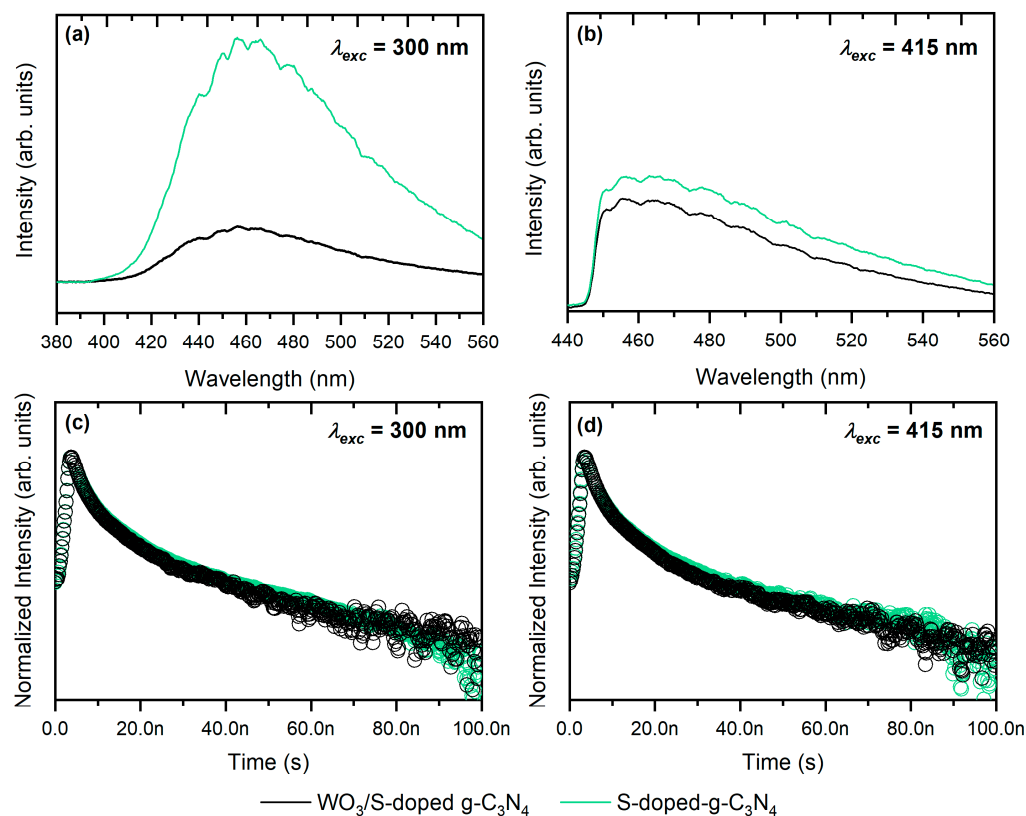


Figure 7. (a,b) Photoluminescence spectra and (c,d) luminescence decay curves of S-doped $\text{g-C}_3\text{N}_4$ and $\text{WO}_3/\text{S-doped g-C}_3\text{N}_4$ composite under different excitation wavelengths.

3.2. Photocatalytic Activity and Degradation Mechanism

The photocatalytic activity of the $\text{WO}_3/\text{S-g-C}_3\text{N}_4$ composite, as well as single-phase photocatalysts, were demonstrated towards NO_2 conversion in a continuous-flow system under simulated solar light irradiation. The initial concentration of NO_2 was about 5 ppm. As shown in Figure 8a, $\text{WO}_3/\text{S-doped g-C}_3\text{N}_4$ composite exhibited near 100% NO_2 removal within 5 min of the process. The high efficiency of this composite is almost constant within time. In the case of pure WO_3 and S-doped $\text{g-C}_3\text{N}_4$, rapid removal of NO_2 concentration was also observed; however, photocatalytic activity decreased within the time, which was particularly noticeable for S-doped $\text{g-C}_3\text{N}_4$. S-doped $\text{g-C}_3\text{N}_4$ was supposed to transform NO_2 to forms, which caused blocking of the active sites on the photocatalyst's surface [39]. These results were compared with NO production (Figure 8b). Noticeably, the $\text{NO}_2 \rightarrow \text{NO}$ conversion is favorable for the WO_3 single compound. Che-Chin Yu et al. [40] reported the phototransformation of NO_2 into NO in the N_2 presence over WO_3 photocatalyst regarding the following reaction: $\text{NO}_2 + \text{N}_2 \rightarrow 2\text{NO}$. It is consistent with the probable presence of unreacted NO adsorbed on the surface, indicated by XPS spectra. Therefore, reduction processes are predominant in the case of tungsten(VI) oxide.

Considering the overall degradation of NO_x species, only the composite $\text{WO}_3/\text{S-doped g-C}_3\text{N}_4$ allowed the complete degradation of NO_2 and did not cause the production of NO. According to the available literature reports, two possible explanations of this observation for the composite are possible. First, the surface of the binary composite is more reactive than for single components because of the more efficient charge carriers' separation. A similar effect was described by Méndez-Román and Cardona-Martínez [41], who investigated $\text{SiO}_2\text{-TiO}_2$ photocatalysts towards oxidation of toluene. The composite exhibited better photocatalytic performance and lower deactivation than TiO_2 due to higher toluene adsorption capacity and changes in Brønsted acidity of intermediates. Therefore, new surface sites would be responsible for the enhanced photocatalytic performance. The second possibility is a change of photocatalytic mechanism when WO_3 and S-doped $\text{g-C}_3\text{N}_4$

C_3N_4 are present in the heterojunction. However, changes in charge carriers' transport in the composite caused the promotion of NO_2 reduction to gaseous NO and N_2 . In this case, less NO_3^- was adsorbed on the photocatalyst surface than from NO_2 oxidation [42]. Therefore, according to Dalton et al. [36], XPS spectroscopy is needed as a technique suitable for surface analysis. However, the accurate indication of the NO_2 conversion pathway is difficult for WO_3/S -doped $g-C_3N_4$ using XPS spectroscopy because of the predominant C-N signals in N1s spectra. This inconvenience was described precisely by Li et al. [43], who modified graphitic carbon nitride using nitric acid or ammonia gas atmosphere. Remarkably, there were no differences in XPS spectra of N1s signals, although the adsorption of nitrates or ammonia was certain. In this study, the negligible NO production during the photocatalytic process in the presence of composite photocatalyst may result from advanced photodecomposition without NO as a main intermediate product. The second possibility is photooxidation to nitrates. However, in this case, blocking active sites and a further decrease in activity should be observed, whereas the performed subsequent degradation cycles showed the long-term stability of the WO_3/S -doped $g-C_3N_4$ composite material [44,45].

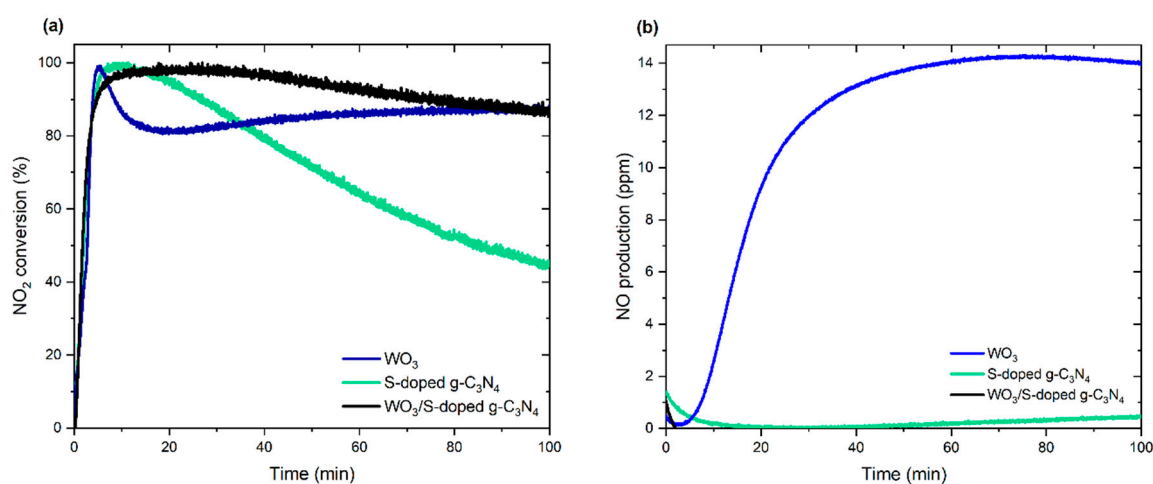


Figure 8. (a) Photocatalytic NO_2 conversion and (b) NO production using obtained photocatalysts.

3.2.1. Effect of Process Parameters

The photocatalytic process, including NO_2 removal, depends on different factors, including temperature, relative humidity, pollutant concentration, and the amount of photocatalyst [31,32]. Therefore, in this study, the effect of these parameters on photocatalytic activity was evaluated. Three relative humidity values were set as 25%, 40%, and 55%, respectively. As shown in Figure 9a for the WO_3/S -doped $g-C_3N_4$ composite, relative humidity had no significant effect on the NO_2 conversion. Other observations were reported by Maggos et al. [46] during photocatalytic NO_x removal in the presence of TiO_2 . In their study, humidity plays a crucial role in the photooxidation process since water contributes to reactive oxygen species (ROS) formation. From the technological point of view, eliminating the humidity effect can allow photocatalysis without the dependence on external weather conditions.

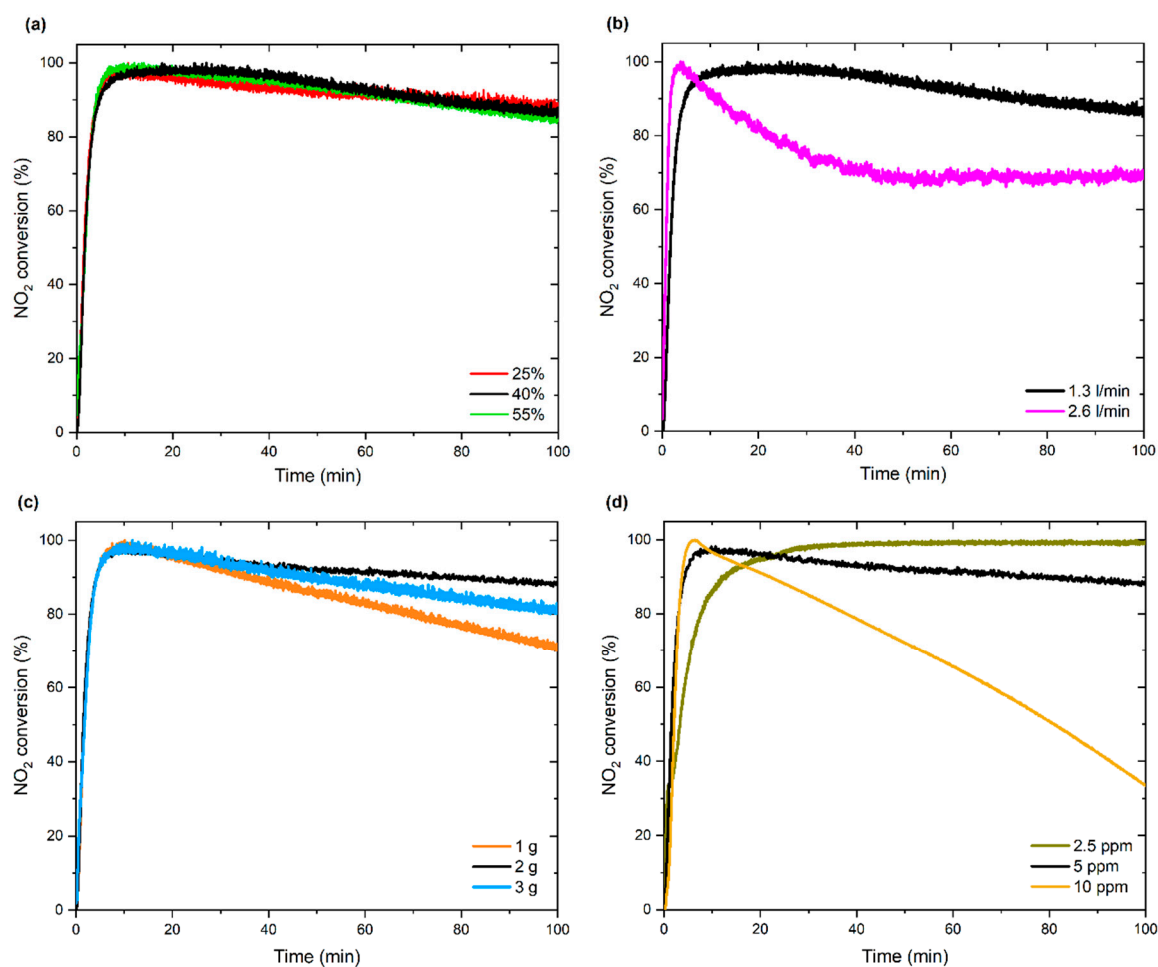


Figure 9. Effect of: (a) humidity, (b) gas flow, (c) photocatalyst amount, and (d) NO_2 initial concentration on NO_2 conversion using WO_3/S -doped $\text{g-C}_3\text{N}_4$.

Afterward, the effect of gas flow rate was evaluated and fixed on $1.3 \text{ dm}^3/\text{min}$ and $2.6 \text{ dm}^3/\text{min}$. In contrast to observations from the influence of humidity, the gas flow rate was a significant parameter affecting the photocatalytic efficiency, as shown in Figure 9b. A two-fold increase in gas flow rate caused a remarkable decrease in NO_2 conversion. This may be related to the short contact time between pollutant and photocatalyst surface during the passage of higher gas flow rate [47]. A similar effect was observed by Li et al. [48] in photocatalytic depolymerization of the oxidized $\beta\text{-O-4}$ molecule in the continuous-flow reactor. The authors noticed that too fast flow rate reduced photocatalytic efficiency due to the short contact time between the reactant and photocatalyst, while when the flow rate was too slow, performance was limited due to the possible mass transfer resistance.

Subsequently, the effect of photocatalyst dose was investigated (Figure 9c). Firstly, the chosen amount of photocatalyst—2 g for the glass plate in the size $30.5 \text{ cm} \times 30.5 \text{ cm}$ —allowed for the highest conversion of NO_2 . Other investigated doses: 1 g and 3 g caused the depletion of NO_2 removal within the experimental time. The observed reduction of NO_2 conversion during the process with the smaller amount of the photocatalyst could be explained by the smaller presence of available active sites. On the other hand, the rise of the catalyst dose could cause the covering of some photocatalysts particles, thereby cutting off the radiation access.

Finally, the NO_2 initial concentration effect on NO_2 conversion was examined. The selected initial concentrations of NO_2 were as follows: 2.5 ppm, 5.0 ppm, and 10.0 ppm. As shown in Figure 9d, 100% of NO_2 conversion was maintained after 5 min and 30 min, respectively, for 5 ppm and 2.5 ppm. On the contrary, during the process with the initial

concentration of 10 ppm, the effectiveness of NO₂ removal decreased over time from 100% after 5 min up to 37% after 100 min.

3.2.2. Stability Tests

The stability of the WO₃/S-doped g-C₃N₄ composite was evaluated in five subsequent cycles, as presented in Figure 10. The decline of NO₂ conversion to ca. 80% was observed. This is consistent with the fact that adsorption of the NO_x and water molecules are necessary to initiate the photocatalytic process, which can block the active sites. However, the second and fifth cycles with increased photocatalytic efficiency confirmed that the WO₃/S-doped g-C₃N₄ material is capable of desorbing the adsorbed species and unblocking the active species for better NO₂ conversion. This observation confirms that the obtained composite showed long-term stability.

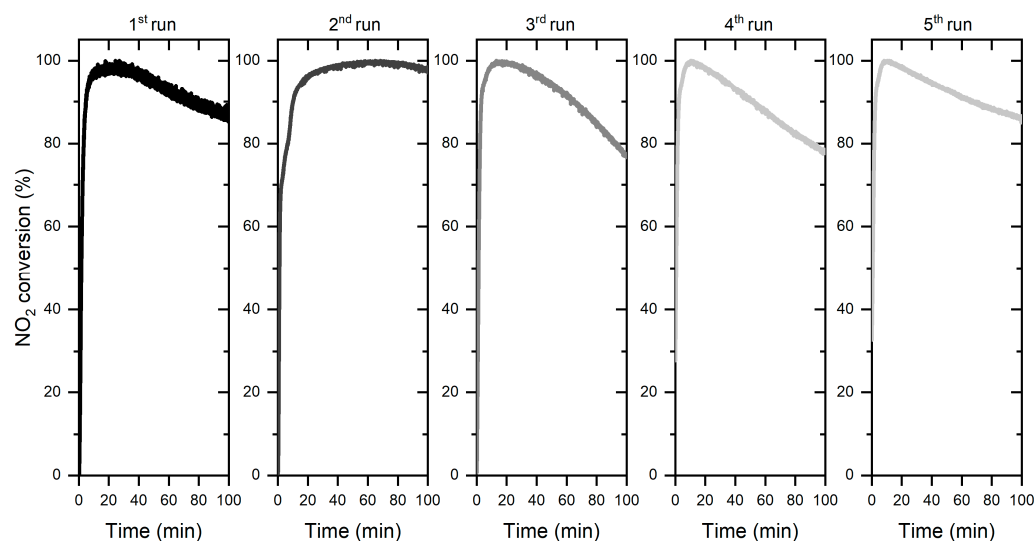


Figure 10. Cycling test of the photocatalytic NO₂ removal using WO₃/S-doped g-C₃N₄.

In addition, XRD analysis and FTIR spectra after the photocatalytic process were performed. As presented in Figure 11a, no signals on XRD patterns, which can originate from the presence of an additional phase, were noticed. Similar conclusions can be noted from FTIR spectra in Figure 11b; no additional bands were detected after the photocatalytic process.

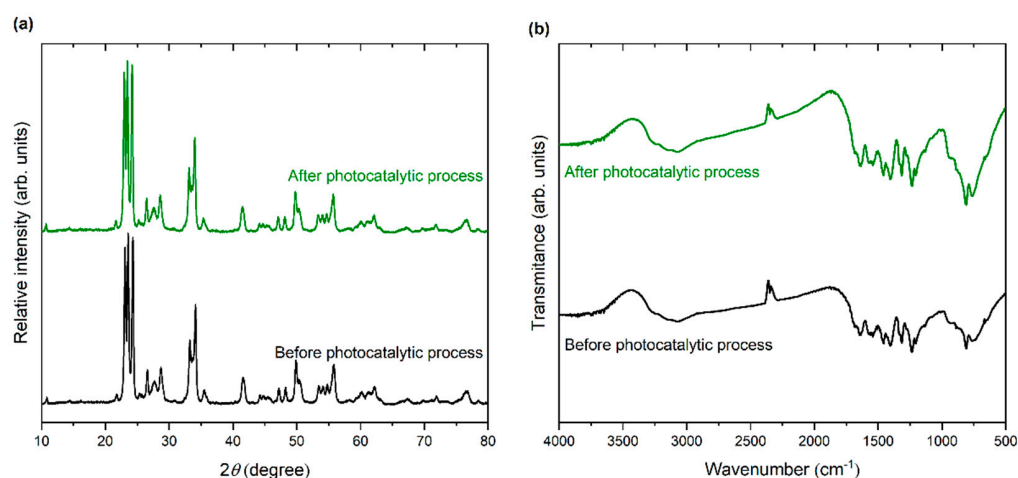


Figure 11. (a) XRD patterns and (b) FTIR spectra of WO₃/S-doped g-C₃N₄ before and after the photocatalytic process.

4. Conclusions

In this study, the photocatalytic performance of WO₃/S-doped g-C₃N₄ nanocomposite towards NO_x removal was studied for the first time. The experiment was performed in a continuous-flow photoreactor on the pilot scale. Simulated solar light emitted by a newly designed LED array was used as a light source. The highly efficient composites were successfully obtained without additional phases, confirmed by X-ray diffraction. SEM images of the nanomaterials showed the nanocomposite morphology as two-dimensional. S-doped g-C₃N₄ nanosheets were covered by WO₃ nanoparticles. XPS and XRF spectroscopy confirmed the presence of sulfur in the final photocatalyst. High absorbance and suitable bandgap value proved that the obtained photocatalysts utilize solar light efficiently. The photoluminescence spectra and carriers' lifetime calculations showed better separation of charge carriers in the composite than in a single component. Finally, WO₃, S-doped g-C₃N₄, and WO₃/S-doped g-C₃N₄ were characterized by fast photocatalytic NO₂ removal. Almost 100% of NO₂ was degraded in less than 5 min of the process. For S-doped g-C₃N₄ nanosheets and WO₃ nanoparticles, active sites were further blocked, which caused a decrease in NO₂ removal. This effect was not observed for the WO₃/S-doped g-C₃N₄ composite. Additionally, the newly developed composite efficiently degraded NO₂ without the simultaneous production of NO. Remarkably, the composite photocatalyst was tested in the subsequent degradation cycles, which confirmed the long-term stability of the composite. No structural changes were noticed after the photocatalytic processes.

To summarize, the pilot-scale studies of the photocatalysts towards NO_x conversion under simulated solar light were demonstrated. The high photocatalytic activity of WO₃/S-doped g-C₃N₄ and simple photocatalyst synthesis encourages the industrial application of the obtained nanocomposites in air purification processes.

Author Contributions: Conceptualization, methodology, formal analysis, A.Z.-J.; investigation, M.K., A.G., A.F.B., P.G.; SEM analysis, J.K.; XPS spectra analysis, M.L.; PL photoluminescence spectroscopy with charge carriers' lifetime measurements, P.G.; irradiation source spectrum analysis, M.S.; writing—original draft preparation, M.K., A.G. and A.F.B.; writing—review and editing, M.K., A.G., A.F.B. and A.Z.-J.; supervision, A.Z.-J.; project administration, funding acquisition, A.Z.-J. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by The National Centre for Research and Development, grant number POIR.01.01.01-00-0071/20-00.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: The authors confirm that the data supporting the findings of this study are available within the article. Derived data supporting the findings of this study are available from the corresponding author [A.Z.-J.] on request.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Nguyen, V.H.; Nguyen, B.S.; Huang, C.W.; Le, T.T.; Nguyen, C.C.; Nhi Le, T.T.; Heo, D.; Ly, Q.V.; Trinh, Q.T.; Shokouhimehr, M.; et al. Photocatalytic NO_x abatement: Recent advances and emerging trends in the development of photocatalysts. *J. Clean. Prod.* **2020**, *270*, 121912. [[CrossRef](#)]
2. Xu, M.; Wang, Y.; Geng, J.; Jing, D. Photodecomposition of NO_x on Ag/TiO₂ composite catalysts in a gas phase reactor. *Chem. Eng. J.* **2017**, *307*, 181–188. [[CrossRef](#)]
3. Rao, X.; Zhong, J.; Brook, R.D.; Rajagopalan, S. Effect of Particulate Matter Air Pollution on Cardiovascular Oxidative Stress Pathways. *Antioxidants Redox Signal.* **2018**, *28*, 797–818. [[CrossRef](#)]
4. Carp, O.; Huisman, C.L.; Reller, A. Photoinduced reactivity of titanium dioxide. *Prog. Solid State Chem.* **2004**, *32*, 33–177. [[CrossRef](#)]
5. Rauf, M.A.; Ashraf, S.S. Fundamental principles and application of heterogeneous photocatalytic degradation of dyes in solution. *Chem. Eng. J.* **2009**, *151*, 10–18. [[CrossRef](#)]
6. Zhu, J.; Xiao, P.; Li, H.; Carabineiro, S.A.C. Graphitic carbon nitride: Synthesis, properties, and applications in catalysis. *ACS Appl. Mater. Interfaces* **2014**, *6*, 16449–16465. [[CrossRef](#)]

7. Zhang, X.; Xie, X.; Wang, H.; Zhang, J.; Pan, B.; Xie, Y. Enhanced photoresponsive ultrathin graphitic-phase C_3N_4 nanosheets for bioimaging. *J. Am. Chem. Soc.* **2013**, *135*, 18–21. [[CrossRef](#)]
8. Wu, X.; Cheng, J.; Li, X.; Li, Y.; Lv, K. Enhanced visible photocatalytic oxidation of NO by repeated calcination of g- C_3N_4 . *Appl. Surf. Sci.* **2019**, *465*, 1037–1046. [[CrossRef](#)]
9. Todorova, N.; Papailias, I.; Giannakopoulou, T.; Ioannidis, N.; Boukos, N.; Dallas, P.; Edelmannová, M.; Reli, M.; Koci, K.; Trapalis, C. Photocatalytic H₂ Evolution, CO₂ Reduction, and NO_x Oxidation by Highly Exfoliated g- C_3N_4 . *Catalysts* **2020**, *10*, 1147. [[CrossRef](#)]
10. Zhu, Y.; Cui, Y.; Xiao, B.; Ou-yang, J.; Li, H.; Chen, Z. Z-scheme 2D/2D g- C_3N_4 /Sn₃O₄ heterojunction for enhanced visible-light photocatalytic H₂ evolution and degradation of ciprofloxacin. *Mater. Sci. Semicond. Process.* **2021**, *129*, 105767. [[CrossRef](#)]
11. Cai, Z.; Huang, Y.; Ji, H.; Liu, W.; Fu, J.; Sun, X. Type-II surface heterojunction of bismuth-rich Bi₄O₅Br₂ on nitrogen-rich g- C_3N_4 nanosheets for efficient photocatalytic degradation of antibiotics. *Sep. Purif. Technol.* **2022**, *280*, 119772. [[CrossRef](#)]
12. Ling, F.; Li, W.; Ye, L. The synergistic effect of non-metal doping or defect engineering and interface coupling on the photocatalytic property of g- C_3N_4 : First-principle investigations. *Appl. Surf. Sci.* **2019**, *473*, 386–392. [[CrossRef](#)]
13. Kadam, A.N.; Kim, H.; Lee, S.W. Low-temperature in situ fabrication of porous S-doped g- C_3N_4 nanosheets using gaseous-bubble template for enhanced visible-light photocatalysis. *Ceram. Int.* **2020**, *46*, 28481–28489. [[CrossRef](#)]
14. Yadav, A.A.; Hunge, Y.M.; Kang, S.W. Porous nanoplate-like tungsten trioxide/reduced graphene oxide catalyst for sonocatalytic degradation and photocatalytic hydrogen production. *Surf. Interfaces* **2021**, *24*, 101075. [[CrossRef](#)]
15. Xiao, T.; Tang, Z.; Yang, Y.; Tang, L.; Zhou, Y.; Zou, Z. In situ construction of hierarchical WO₃/g- C_3N_4 composite hollow microspheres as a Z-scheme photocatalyst for the degradation of antibiotics. *Appl. Catal. B Environ.* **2018**, *220*, 417–428. [[CrossRef](#)]
16. Singh, J.; Arora, A.; Basu, S. Synthesis of coral like WO₃/g- C_3N_4 nanocomposites for the removal of hazardous dyes under visible light. *J. Alloys Compd.* **2019**, *808*, 151734. [[CrossRef](#)]
17. Katsumata, H.; Tachi, Y.; Suzuki, T.; Kaneco, S. Z-scheme photocatalytic hydrogen production over WO₃/g- C_3N_4 composite photocatalysts. *RSC Adv.* **2014**, *4*, 21405–21409. [[CrossRef](#)]
18. Huang, M.; Wen, X. Experimental study on photocatalytic effect of nano TiO₂ epoxy emulsified asphalt mixture. *Appl. Sci.* **2019**, *9*, 2464. [[CrossRef](#)]
19. Segundo, I.R.; Freitas, E.; Landi, S.; Costa, M.F.M.; Carneiro, J.O. Smart, photocatalytic and self-cleaning asphalt mixtures: A literature review. *Coatings* **2019**, *9*, 696. [[CrossRef](#)]
20. Liu, W.; Wang, S.; Zhang, J.; Fan, J. Photocatalytic degradation of vehicle exhausts on asphalt pavement by TiO₂/rubber composite structure. *Constr. Build. Mater.* **2015**, *81*, 224–232. [[CrossRef](#)]
21. Nevshupa, R.; Jimenez-Relinque, E.; Grande, M.; Martinez, E.; Castellote, M. Assessment of urban air pollution related to potential nanoparticle emission from photocatalytic pavements. *J. Environ. Manag.* **2020**, *272*, 111059. [[CrossRef](#)]
22. Maurer, D.L.; Koziel, J.A. On-farm pilot-scale testing of black ultraviolet light and photocatalytic coating for mitigation of odor, odorous VOCs, and greenhouse gases. *Chemosphere* **2019**, *221*, 778–784. [[CrossRef](#)]
23. Hu, J.; Xia, H.; Hu, H.; Zhang, Y.; Jiang, H.; Chen, B. Synthesis and efficient near-infrared quantum cutting of Pr³⁺/Yb³⁺ co-doped LiYF₄ single crystals. *J. Appl. Phys.* **2012**, *112*, 073518. [[CrossRef](#)]
24. Liu, Y.; Li, J.; Li, W.; Liu, Q.; Yang, Y.; Li, Y.; Chen, Q. Enhanced photoelectrochemical performance of WO₃ film with HfO₂ passivation layer. *Int. J. Hydrogen Energy* **2015**, *40*, 8856–8863. [[CrossRef](#)]
25. Najafi-Ashtiani, H.; Bahari, A.; Gholipour, S.; Hoseinzadeh, S. Structural, optical and electrical properties of WO₃-Ag nanocomposites for the electro-optical devices. *Appl. Phys. A Mater. Sci. Process.* **2018**, *124*, 1–9. [[CrossRef](#)]
26. Kim, D.; Kim, G.; Bae, H.; Kim, E.; Moon, B.; Cheon, D.; Tarte, N.H. An external energy independent WO₃/MoCl₅ nano-sized catalyst for the superior degradation of crystal violet and rhodamine B dye. *Catalysts* **2019**, *9*, 642. [[CrossRef](#)]
27. Fahimirad, B.; Asghari, A.; Rajabi, M. Magnetic graphitic carbon nitride nanoparticles covalently modified with an ethylenediamine for dispersive solid-phase extraction of lead(II) and cadmium(II) prior to their quantitation by FAAS. *Microchim. Acta* **2017**, *184*, 3027–3035. [[CrossRef](#)]
28. Kim, M.; Hwang, S.; Yu, J.S. Novel ordered nanoporous graphitic C₃N₄ as a support for Pt-Ru anode catalyst in direct methanol fuel cell. *J. Mater. Chem.* **2007**, *17*, 1656–1659. [[CrossRef](#)]
29. Wang, Z.T.; Xu, J.L.; Zhou, H.; Zhang, X. Facile synthesis of Zn(II)-doped g- C_3N_4 and their enhanced photocatalytic activity under visible light irradiation. *Rare Met.* **2019**, *38*, 459–467. [[CrossRef](#)]
30. Lin, M.Z.; Chen, H.; Chen, W.F.; Nakaruk, A.; Koshy, P.; Sorrell, C.C. Effect of single-cation doping and codoping with Mn and Fe on the photocatalytic performance of TiO₂ thin films. *Int. J. Hydrogen Energy* **2014**, *39*, 21500–21511. [[CrossRef](#)]
31. Chhabra, T.; Bahuguna, A.; Dhankhar, S.S.; Nagaraja, C.M.; Krishnan, V. Sulfonated graphitic carbon nitride as a highly selective and efficient heterogeneous catalyst for the conversion of biomass-derived saccharides to 5-hydroxymethylfurfural in green solvents. *Green Chem.* **2019**, *21*, 6012–6026. [[CrossRef](#)]
32. Gao, D.; Liu, Y.; Liu, P.; Si, M.; Xue, D. Atomically Thin B doped g- C_3N_4 Nanosheets: High-Temperature Ferromagnetism and calculated Half-Metallicity. *Sci. Rep.* **2016**, *6*, 35768. [[CrossRef](#)]
33. Alman, V.; Singh, K.; Bhat, T.; Sheikh, A.; Gokhale, S. Sunlight Assisted improved photocatalytic degradation of rhodamine B using Pd-loaded g- C_3N_4 /WO₃ nanocomposite. *Appl. Phys. A Mater. Sci. Process.* **2020**, *126*, 724. [[CrossRef](#)]
34. Gong, S.; Jiang, Z.; Zhu, S. Heterojunctions With Enhanced Visible-Light Photocatalytic Activities. *J. Nanopart Res.* **2018**, *20*, 310–323. [[CrossRef](#)]

35. Wang, P.; Guan, Z.; Li, Q.; Yang, J. Efficient visible-light-driven photocatalytic hydrogen production from water by using Eosin Y-sensitized novel g-C₃N₄/Pt/GO composites. *J. Mater. Sci.* **2018**, *53*, 774–786. [[CrossRef](#)]
36. Dalton, J.S.; Janes, P.; Jones, N.; Hallam, K.R.; Nicholson, J.A.; Allen, G.C. Photocatalytic oxidation of NO_x gases using TiO₂: A spectroscopic approach. *Environ. Pollut.* **2002**, *45120*, 415–422. [[CrossRef](#)]
37. Hao, Q.; Song, Y.; Ji, H.; Mo, Z.; She, X.; Deng, J.; Muhmood, T.; Wu, X.; Yuan, S.; Xu, H.; et al. Surface N modified 2D g-C₃N₄ nanosheets derived from DMF for photocatalytic H₂ evolution. *Appl. Surf. Sci.* **2018**, *459*, 845–852. [[CrossRef](#)]
38. Wang, C.; Fu, M.; Cao, J.; Wu, X.; Hu, X.; Dong, F. BaWO₄/g-C₃N₄ heterostructure with excellent bifunctional photocatalytic performance. *Chem. Eng. J.* **2020**, *385*, 123833. [[CrossRef](#)]
39. Wu, Z.; Sheng, Z.; Liu, Y.; Wang, H.; Mo, J. Deactivation mechanism of PtOx/TiO₂ photocatalyst towards the oxidation of NO in gas phase. *J. Hazard. Mater.* **2011**, *185*, 1053–1058. [[CrossRef](#)]
40. Yu, J.C.C.; Lasek, J.; Nguyen, V.H.; Yu, Y.H.; Wu, J.C.S. Visualizing reaction pathway for the photo-transformation of NO₂ and N₂ into NO over WO₃ photocatalyst. *Res. Chem. Intermed.* **2017**, *43*, 7159–7169. [[CrossRef](#)]
41. Méndez-Román, R.; Cardona-Martínez, N. Relationship between the formation of surface species and catalyst deactivation during the gas-phase photocatalytic oxidation of toluene. *Catal. Today* **1998**, *40*, 353–365. [[CrossRef](#)]
42. Nguyen, N.H.; Wu, H.Y.; Bai, H. Photocatalytic reduction of NO₂ and CO₂ using molybdenum-doped titania nanotubes. *Chem. Eng. J.* **2015**, *269*, 60–66. [[CrossRef](#)]
43. Li, Z.; Wu, S.; Zhang, J.; Yuan, Y.; Wang, Z.; Zhu, Z. Improving Photovoltaic Performance Using Perovskite/Surface-Modified Graphitic Carbon Nitride Heterojunction. *Sol. RRL* **2020**, *4*, 1–8. [[CrossRef](#)]
44. Yang, L.; Hakki, A.; Zheng, L.; Jones, M.R.; Wang, F.; Macphree, D.E. Photocatalytic concrete for NO_x abatement: Supported TiO₂ efficiencies and impacts. *Cem. Concr. Res.* **2019**, *116*, 57–64. [[CrossRef](#)]
45. Lasek, J.; Yu, Y.H.; Wu, J.C.S. Removal of NO_x by photocatalytic processes. *J. Photochem. Photobiol. C Photochem. Rev.* **2013**, *14*, 29–52. [[CrossRef](#)]
46. Maggos, T.; Bartzis, J.G.; Leva, P.; Kotzias, D. Application of photocatalytic technology for NO_x removal. *Appl. Phys. A Mater. Sci. Process.* **2007**, *89*, 81–84. [[CrossRef](#)]
47. Casagrande, C.A.; Repette, W.L.; Hotza, D. Effect of environmental conditions on degradation of NO_x gases by photocatalytic nanotitania-based cement mortars after long-term hydration. *J. Clean. Prod.* **2020**, *274*, 123067. [[CrossRef](#)]
48. Li, S.; Hao, Z.; Wang, K.; Tong, M.; Yang, Y.; Jiang, H.; Xiao, Y.; Zhang, F. Visible light-enabled selective depolymerization of oxidized lignin by an organic photocatalyst. *Chem. Commun.* **2020**, *56*, 11243–11246. [[CrossRef](#)] [[PubMed](#)]

