

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24

# **A review on electrospun membranes for potential air filtration application**

Francesca Russo<sup>1</sup>, Roberto Castro-Muñoz<sup>2,3\*</sup>, Sergio Santoro<sup>4</sup>, Francesco Galiano<sup>1</sup>,  
Alberto Figoli<sup>1\*</sup>

<sup>1</sup> Institute on Membrane Technology (CNR-ITM), Via P. Bucci 17/c, 87036 Rende (CS), Italy

---

<sup>2</sup> Gdansk University of Technology, Faculty of Chemistry, Department of Process Engineering and Chemical Technology, 80 – 233 Gdansk, G. Narutowicza St. 11/12, Poland

<sup>2</sup> Gdansk University of Technology, Faculty of Civil and Environmental Engineering, Department of Sanitary Engineering, 80 – 233 Gdansk, G. Narutowicza St. 11/12, Poland

<sup>3</sup> Tecnologico de Monterrey, Campus Toluca. Av. Eduardo Monroy Cárdenas 2000 San Antonio Buenavista, 50110 Toluca de Lerdo, México

<sup>4</sup> Department of Environmental Engineering (DIAM), University of Calabria, Via P. Bucci 45/a 87036 Rende (CS), Italy

25 **Abstract**

26 Air pollution is one of the major environmental concerns in most highly populated cities,  
27 which is typically caused by particulate ( $PM_{2.5}$  and  $PM_{0.1}$ ) or gaseous pollutants. In this  
28 framework, membranes produced by the electrospinning technique are attracting more and  
29 more interest thanks to their peculiar properties such as interconnected pore structure,  
30 tunable porosity and fiber dimension, high surface area to volume ratio and controllable  
31 morphology. This review aims to provide an exhaustive overview on the electrospun  
32 membranes applied in air filtration introducing the key principles and fundamentals of the  
33 separation mechanisms and discussing the influence of membrane properties (e.g.,  
34 morphology and charge) on their filtration efficiency. The materials generally employed  
35 for the fabrication of electrospun membranes (polymers, solvents) and their combination  
36 with additives with defined properties are reviewed also in light of the new environmentally  
37 friendly approaches which are increasingly adopted in membrane fabrication. Finally, the  
38 practical use of electrospun membranes in several application fields such as individual  
39 protection devices, environmental remediation, recovery of volatile organic compounds  
40 (VOCs), and ventilation and climate control aspects is widely discussed providing also an  
41 outlook on the upscaling potential of electrospun membranes and future directions.

42

43 **Key Words:** Electrospinning; electrospun nanofiber membranes; air filtration; aerosols;  
44 air pollution.

45

46

47

48


49 **1. Introduction**

50 The World Health Organization (WHO) has estimated and declared that around seven  
51 million people die per year due to air pollution. Atmospheric pollution is a serious matter,  
52 which can be classified into indoor and outdoor pollution. The first one, also named  
53 household air pollution, is caused by burning, in inefficient stoves or open hearths, solid  
54 fuel sources, including firewood and crop wastes, for cooking and heating. Among these  
55 non-controlled human activities, a number of compounds are extensively produced such as  
56 methane, carbon monoxide, particulate matter (PM), and volatile organic compounds,  
57 resulting in a negative impact on human health. The exposure to these compounds becomes  
58 relevant for low- and middle-income countries that often do not have access to clean fuels.  
59 On the other hand, outdoor air pollution, or ambient air pollution, is primarily caused by  
60 elemental necessities and activities in combustion processes from industries, motor  
61 vehicles, power generation, agriculture/waste incineration, among others. This later type  
62 of pollution is responsible for 4.2 million deaths per year due to heart disease, lung cancer,  
63 stroke, and respiratory diseases [1]. Apart from the inherent pollution of human activities,  
64 other natural sources of pollution are also produced such as pollen, spores, fungi, bacteria,  
65 and virus carrying-aerosols that can be responsible for various health effects, including  
66 asthma, allergy reactions, and infectious illnesses, such as influenza and chronic pulmonary  
67 diseases [2].

68 The hazardousness and toxicity of inhaled particles strongly depends on their dimensions.  
69 For instance, if thoracic particles with a diameter lower than 10  $\mu\text{m}$  ( $\text{PM}_{10}$ ) are partially  
70 blocked by nasal cavities [3,4], fine (diameter lower than 2.5  $\mu\text{m}$  ( $\text{PM}_{2.5}$ )) and ultrafine  
71 particles (diameter lower than 0.1  $\mu\text{m}$  ( $\text{PM}_{0.1}$ )) can be deeply inhaled into the lungs and be  
72 accumulated on the alveoli causing a series of harmful effects [5] by crossing into the

73 pulmonary and systemic circulations and directly affecting the heart and blood vessels [6].  
74 Therefore, there is a need of implementing devices with ability to sequestrate both natural  
75 and anthropogenic **pollutants** from the air. In this sense, various air filtration materials have  
76 been intentionally studied over the last years to protect human health against particle  
77 pollution [7]. Potentially, membrane filtration can act as a physical barrier and thus remove,  
78 depending on the membrane pore size, various types of particles, molecules, contaminants,  
79 and microorganisms. Ideally, a membrane aimed for air purification must display the  
80 ability to retain exclusively the pollutant particles while facilitating the transport of air [8].  
81 In addition to this, membranes should also meet other requirements in terms of high  
82 lifetime, low-pressure drop, easy to handle and installation, and low-production cost [9,10].  
83 Regarding the particle's separation efficiency, current conventional air filtration  
84 membranes are based on micro-sized fibers, which in fact are not efficient enough to  
85 remove smaller contaminants than the range of 0.1-2.5 microns (i.e., PM<sub>0.1</sub> and PM<sub>2.5</sub>)  
86 due to their larger pore size [11]. At this point, electrospun membranes are becoming more  
87 and more attractive as a key tool to satisfy such efficient air filtration performance due to  
88 their interconnected pore structure, tuneable porosity, and fiber dimension (from 40 to 2000  
89 nm in diameter), high surface area to volume ratio and controllable morphology [12,13].  
90 Graphically, **Figure 1** describes a typical electrospun membrane that present a membrane  
91 support.



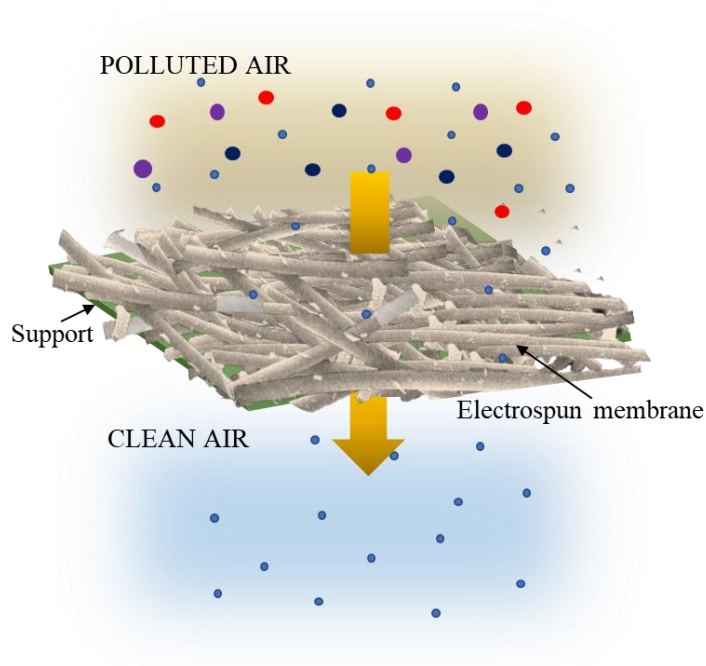

92


93 **Figure 1.** Graphical depiction of a typical electrospun membrane used for air filtration.

94

95 Electrospun nanofiber membranes are mostly fabricated by means of electrospinning  
 96 technique, which is a very versatile technique allowing the tailoring of fibers with a very  
 97 narrow diameter, a large specific surface area, a tuneable pore size, and more importantly,  
 98 it gives the possibility to blend different types of nanoparticles (e.g. catalysts,  
 99 antimicrobial agents) into the nanofibers and thus enhance their properties and purification  
 100 efficiency [14,15]. Importantly, nanofibers can also be directly electrospun from a polymer  
 101 dope solution as self-supporting membranes, but generally, the nanofibers are deposited  
 102 onto a substrate made of polyethylene terephthalate (PET) or polypropylene (PP), which  
 103 acts as a supporting layer conferring mechanical stability to the nanofiber.

104 **Figure 2.a** shows the publications during the last ten years. It is clear that the academic  
 105 interest in this research area has continuously increased and by 2019 over 50 papers per  
 106 year were published. **Figure 2.b** provides a general overview of the publications by type.

107 About 80 % of the publications used are articles published in academic journals. The other  
108 20 % is divided by reviews, conference papers, book chapters, conferences and review  
109 conference.

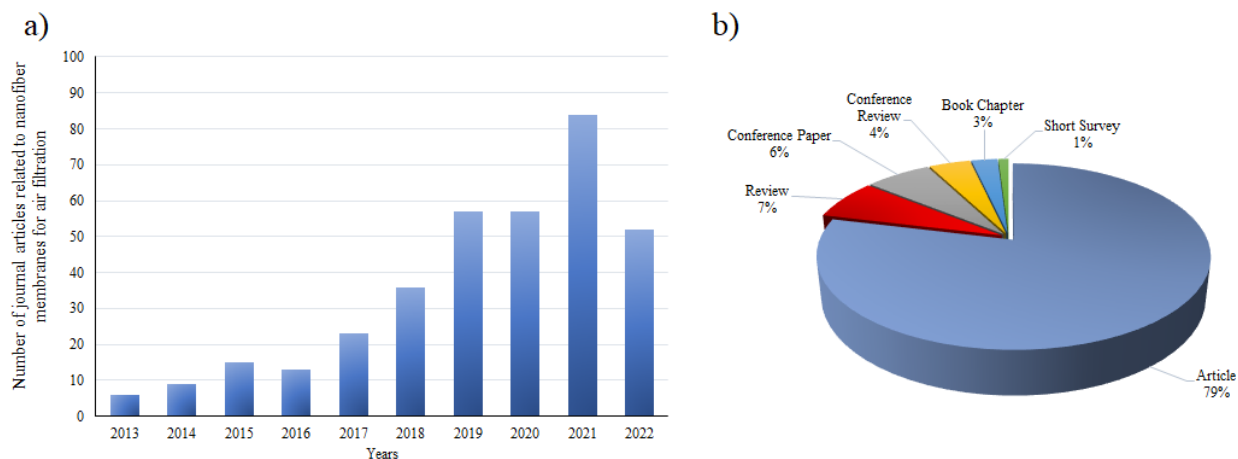

110

111 **Figure 2.** a) Journal articles and b) document types related to nanofibers for air filtration  
112 over the past 10 years (updated until July 2022). Search engine: Scopus using the keywords  
113 “nanofiber membranes” and “air filtration”.

114

115 Reviews on various aspects of electrospun membranes for air filtration have been published

116 in the last two years (2021-2022). Most of them focused on nanofiber materials for that

117 specific application. The research of Zhou Y. et al. [16], for example, based their approach

118 on the characteristics, advantages and disadvantages of single-polymer, composite or

119 hybrid nanofibers. Deng Y. et al. [17] proposed to assess the performance of nanofibers

120 prepared from bio-based polymers and novel bio-matrix such as cyclodextrin, lignin and

121 konjac glucomannan (KGM). Another interesting work was also proposed by the group of

122 Lu T. et al. [18]. They summarized the performance of electrospun air filtration membranes

123 (EAFMs) with different structures such as nanoprotrusion, wrinkled, porous, branched,

124 hollow, core-shell, ribbon, beaded, net structures. Ji et al. [19] introduced some basic

125 concepts involved in particulate matter (PM) filtration, such as classification and source of

126 PM, classic filtration mechanism, and the key evaluation parameters of PM filtration.  
127 Moreover, Schneider R. et al. [20] described recent advances on the post-modification  
128 strategies of spun micro/nanofibers surfaces using 0D, 1D, 2D, and 3D inorganic structures  
129 while the group of Valecia-Osorio L.M. et al. [21] studied the electrospinning process for  
130 air filtration nanofibers through three moments: solution preparation, fabrication  
131 parameters and post-treatment techniques. In this review, we have provided a  
132 comprehensive overview of the different aspects of electrospun membranes for air  
133 filtration. We initially introduced the key principles and fundamentals of the filtration  
134 mechanisms involved in electrospun nanofibers for air filtration, along with the influence  
135 of membrane properties (e.g., morphology and charge) on their separation filtration  
136 efficiency. Lately, we reviewed the preparation procedures employed for their fabrication  
137 overlooking the membrane materials, solvents, additives, electrospun configurations. ~~and~~  
138 ~~finally~~ Finally, we presented the practical applications of nanofibers in air filtration such  
139 as individual protection devices, ventilation and climate control, recovery of volatile  
140 organic compounds (VOCs) and environmental remediation. We also focused the attention  
141 on the upscaling potential of nanofiber air filters, the current companies for electrospun  
142 membranes production and the future challenges.

143

## 144 **2. Filtration mechanism in electrospun membranes**

### 145 *2.1. Theory*


146 ~~Even if~~ Air filtration has a long history ~~and~~ consolidated over time and is closely linked to  
147 industrial and technological developments. However, until the last century ~~that~~ it was not  
148 possible to find theoretical studies elucidating the various filtration mechanisms [22]. More



149 importantly, the lack of steady-state during filtration, which is characterized by the  
150 variation of process efficiency over time together with airflow resistance because of  
151 particles deposition, makes it challenging and limits a comprehensive description of the  
152 phenomena [23].

153 Considering a moderate concentration of particles in the air, the particle accumulation on  
154 the filter is minimal and does not alter the effective diameter of the nanofibers. Thanks to  
155 this, the air filtration performance of an electrospun fibrous membrane is usually  
156 considered stable (i.e. steady-state) [2]. Then, according to the widely known theory,  
157 filtration occurs due to the following trapping mechanisms: interception, inertial impaction,  
158 Brownian diffusion, electrostatic effect, and gravity effect, as represented in **Figure 32**.

159

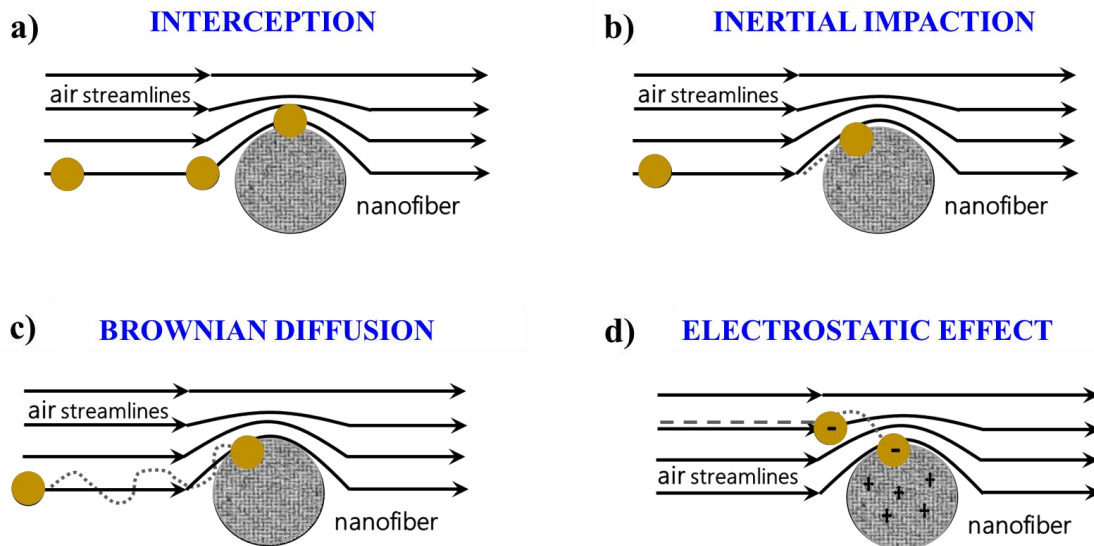

160

161

162 **Figure 32.** Graphical depiction of the air filtration mechanisms through electrospun  
163 nanofibers: a) interception, b) inertial impaction, c) Brownian diffusion, d) electrostatic  
164 effect.

165



166 Typically, the particles tend to flow together with the air streamlines and are intercepted  
167 while contacting nanofiber surface due to the van der Waals forces (see **Figure 3.2a**). This  
168 latter phenomenon, so-called interception, is recognized as the primary filtration  
169 mechanism. The interception is indeed independent of the flow velocity but still efficient  
170 for capturing particles with size ranged from 0.1 to 1  $\mu\text{m}$  [24].


171 Since the electrospun membranes own randomly oriented nanofibers, the pathway of the  
172 streamlines is commonly tortuous through air filtration. Particles often deviate from the  
173 airflow line due to the effect of inertia force, impact subsequently against the nanofibers,  
174 provoking an effective filtration thanks to the inertial impaction [25]. Of course, smaller  
175 particles can succumb to the drag effect and be transported with the streamlines, while the  
176 inertial momentum increases with the particle size and may overcome the drag force in the  
177 case of larger nanoparticles, which causes a perceptible deviation from the streamlines and,  
178 as a consequence, the impact against the nanofibers [26], as illustrated in **Figure**  
179 **3.2b**. Herein, the efficiency of inertial impaction increases as a function of the particle size  
180 and it is affected by the air velocity.

181 In addition to this, particles could slightly and arbitrarily deviate from their original flow  
182 line thanks to the Brownian motion (see **Figure 3.2c**), and pronounced divergences  
183 guarantying the diffusion of the particles towards nanofiber and then a consequent  
184 interception [27]. This latter phenomenon typically occurs for particles smaller than 1  $\mu\text{m}$ .

185 Besides the previous mechanisms, Coulombic attraction between charged particles and  
186 unipolar or bipolar charged nanofibers substantially improves the filtering efficiency, as  
187 represented in **Figure 3.2d**. It is worth mentioning that neutral particles can be also  
188 polarized by unipolar or bipolar charged nanofibers or dielectrophoretic forces originated

189 by an external field [28]. Ultimately, the contribution of the gravity effect tends to be  
190 negligible for particles smaller than 0.5  $\mu\text{m}$ .

191 **Definitively, the sum of the contributions of each mechanism of filtration- which are**  
192 **significantly affected by the particle size- determines the overall air filtration efficiency of**  
193 **electrospun membrane (Figure 4).**

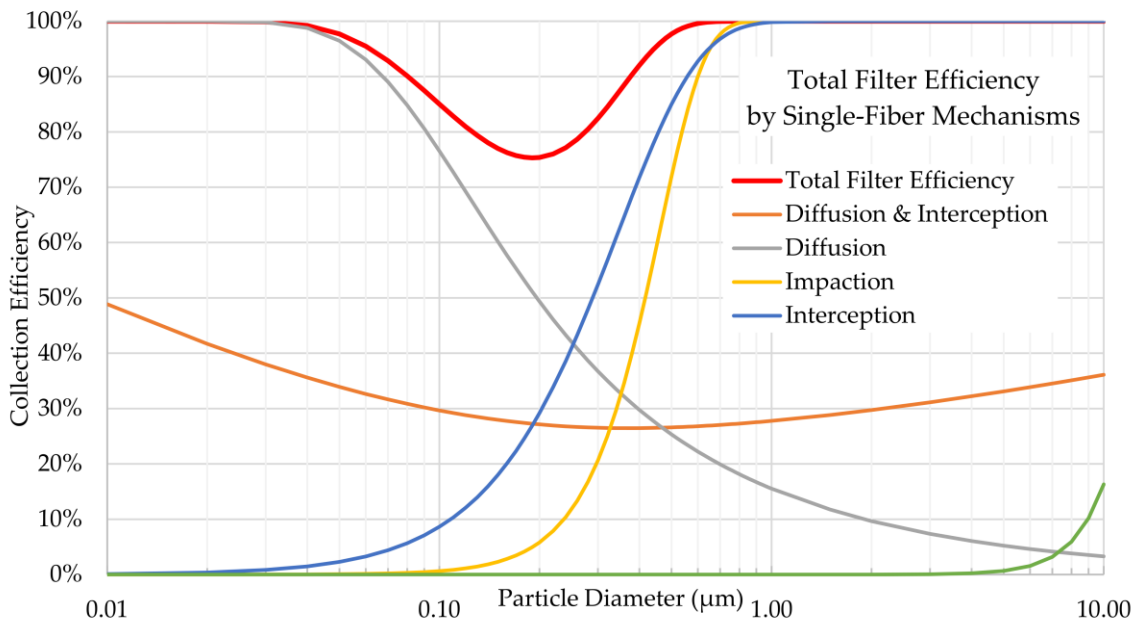

194 **Figure 4.** Filtration efficiency of a single nanofiber and contribution of the different  
195 **mechanism of air filtration modelled with a Digital Twin [29]. This work is licensed under**  
196 **a Creative Commons Attribution 4.0 International License.**  
197  
198

## 199 2.2. Effect of membrane structure

200 As it is well known electrospinning is a versatile technique for the fabrication of efficient  
201 air filters possessing high level of control on membrane morphology. Handling the  
202 operative parameters of the electrospinning, as well as the chemical-physical properties of  
203 the polymeric dope solution, is feasible to tailor different features of the nanofibers such  
204 as their diameter, pore size, porosity and the packing density. These morphological and  
205 structural features of the air filters meaningfully affect their performance. In general, the

206 filtration efficiency, represented as  $\eta$ , is usually described by the Kuwabara model, as  
207 follows (1):

$$\eta = 1 - \exp \left[ \frac{-4\eta_s \alpha L}{\pi d_f (1 - \alpha)} \right] \quad (1)$$

208


209 where  $\eta_s$  represents the filtration efficiency of a single fiber,  $\alpha$  corresponds the fiber volume  
210 fraction (i.e., packaging density),  $d_f$  represents the average fiber diameter, and  $L$  is the filter  
211 thickness [30]. For instance, Eq. 1 spells out the robust dependence of the filter efficacy on  
212 its structural and morphological properties, which is inversely proportional to the  
213 nanofiber' diameter. Such description has been proven by experimental results as with  
214 **polyacrylonitrile (PAN)** transparent electrospun nanofibers demonstrating a decrease of the  
215 filtration efficiency (PM<sub>2.5</sub>) from 98.11±1.41% to 48.21 ± 4.19%, as a result of their  
216 diameter increase from ~0.2 to approximately 1 μm [31].

217 Surprisingly, nanofibers with a tiny diameter display minor pressure drop due to the slip  
218 effect induced by unique aerodynamic conditions [32] (**Figure 5a**). Actually, the diameters  
219 of electrospun nanofibers ( $d_f$ ) and the mean free path of air molecules ( $\lambda$ ) are comparable,  
220 while the Knudsen number (Kn), expressed as  $Kn = 2\lambda/d_f$ , achieves values ranged from 0.1  
221 to 10, which correspond to transition flow regime (**Figure 5b**). Here, the drag force is  
222 substantially reduced and the air velocity on the nanofiber's surface is non-zero. This  
223 means that the slip flow reduces the friction effect, the air molecules bypass the nanofibers  
224 with the maximum probability of alleviating the pressure drop [31,33], as systematically  
225 proved by a study on 122 nanofibers [34].

226 Of course, the high porosity is fundamental in reducing the pressure drop in combination  
227 with “through” open pores, while “blind” closed pores remain as undesirable. Importantly,

228 pore size becomes also crucial for meeting a good performance in terms of filtration  
 229 efficiency and permeability: small pore sizes gives an effective filtration but limit the  
 230 permeability by promoting the pressure drop [35].

231

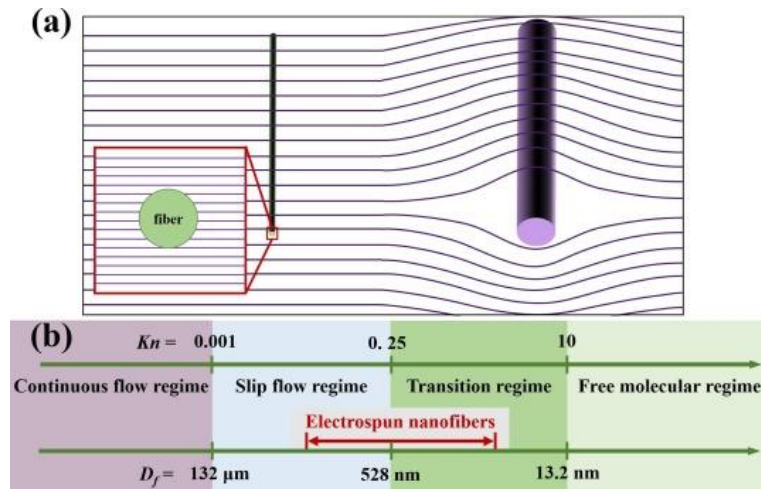

232

233 **Figure 5.** (a) The air flow field around two single fibers with different diameters according  
 234 to the Kuwabara Model and (b) Knudsen numbers and fluid flow regimes of the electrospun  
 235 fibers. Reprinted from [36] with the permission of Elsevier.

236

237

### 238 2.3. Effect of membrane and particle charge

239 As explained previously, **Brownian** motion is the random motion of particles suspended in  
 240 the air, which is a result from their collision with the fast-moving of particles. However,  
 241 this phenomenon is identified at a specific range of particle size. Particles with size smaller  
 242 than  $\approx 1 \mu\text{m}$  exhibit a significant Brownian motion [37], causing diffusion and deposition  
 243 on the membrane surface, particularly in fibers [38]. Notably, Brownian motion becomes  
 244 relevant with the decrement of particle size. Apart from described phenomena, if both  
 245 particles/molecules or fibers are charged, the electrostatic effect is another parameter that  
 246 interferes [39]. Theoretically, there are two ways to induce electrostatic forces in a

247 membrane air filter; the first one is directly related by charging the airborne particles, while  
248 the second one can be a results of producing an electric field in the membrane [28]. In  
249 recent times, this latter scenario has been investigated by embedding inorganic nanofillers  
250 in membranes independently if the electrospun fibers already **displayed** any charge. It is  
251 worth mentioning that within the electrospinning process, the used high positive voltage  
252 may potentially confer a charge into the polymer solution, which certainly contributes to  
253 the formation of volume charges and surface charges [7].

254 A charged particle (i.e. airborne particle) polarizes the fiber releasing a force that is equal  
255 to the Coulombic force among the charge and the particle, but it is opposite to the charge  
256 located inside the fiber at a position related to the optical image of the particle. Usually,  
257 the image force is not highly crucial unless the particles own extremely high charges. The  
258 electrostatic interactions, along with Coulombic interactions and polarization forces [40],  
259 can indeed shift the pattern flow of particles in comparison with the initial air stream, this  
260 may promote particles to deposit onto the membrane surfaces. Potentially, the electrostatic  
261 effect will also promote the particle adhesion onto the fiber surfaces. This latter **effect** has  
262 been commonly utilized in various aerosol filtration devices during the separation of sub-  
263 micrometer particles [41], which in fact can enhance the particles' collection efficiency  
264 [28]. As an example, nanofibrous mats containing boehmite nanoparticles, proposed as  
265 electret filter, have shown exceptional separation performance by using the  
266 nanomaterials, which played **as** an electrostatic charging agent [42]. In such research,  
267 PA6 nanofibers were fabricated via electrospinning, obtaining **an average fiber diameter**  
268 **between 73-90 nm**. Here, boehmite nanoparticles were smartly incorporated to induce  
269 higher electrostatic charging characteristics of the unfilled PA6 nanofiber. It was concluded



270 that the filtration properties of PA6 nanofibers were mainly ascribed to the electrospinning  
271 and the corona charging device [42]. Alternatively, the electrically charged nanoparticles  
272 contained in polymer fibers may also provide another perspective when dealing with air  
273 disinfection, since electrostatic interactions between microorganisms and charged particles  
274 can lead to cell wall rupture, and thus the death of the possible bacteria, fungi, and viruses  
275 [43,44]. This has been evidenced by Selvam and Nallathambi [45], who observed a 99%  
276 bacterial filtration efficiency when using 10-12.4 wt.% of Ag nanoparticles into PAN  
277 composite membranes. Ag nanoparticles have been also merged into electrospun fibers. In  
278 this case, Zhang et al. [46] have utilized  $-C(NH_2)=N-OH$  groups, coming from the reaction  
279 of hydroxylamine and acrylic on PAN substrate, to smartly coordinate  $Ag^+$  ions [46]. As  
280 expected, the electrospun **nanofibers** displayed efficient antimicrobial properties, and no  
281 substantial morphological changes were observed in the resulting fibers while maintaining  
282 the filtration efficiency.

283 It is important to point out that electrically charged fibers tend to create in its vicinity an  
284 electric field, which displays a force provoking the movement of a charged particle.  
285 Apparently, the field produced by a charged fiber could polarize a particle as well,  
286 unfortunately, such force on a polarized particle is considered negligible for small particles  
287 [47]. In particular fibers, such as electret fibers, ~~they can display~~ a permanent line dipole  
288 charge **can be observed which results** in a non-uniform field. Notably, the field may also  
289 provoke a dipole charge in a particle but it does not represent a relevant **issue fact** for small  
290 particles.

291 It is worth mentioning that the implementation of aerosol filtration via electrostatic forces  
292 is likely to be challenging, but it has been already investigated. As an example, the Hansen



293 filter represents the first pioneering development and application of electrostatic forces in  
294 aerosol filtration. Hansen discovered that the collection efficiency can be notably improved  
295 when a wool filter was charged with colophony resin particles. Such an improvement  
296 induces a better action of electrostatic forces [28]. Resin particles of approximately 1 mm  
297 in diameter can be ~~be~~ negatively charged by contact (triboelectric charging). The charge  
298 was maintained on the resin particle for a long time due to the fact that the resin owns good  
299 electrical isolate agent. Electret filters have been initially based on dielectric fibers with a  
300 quasi-permanent electrical charge. Unfortunately, membrane filter devices charged  
301 electrostatically were fabricated using polymeric fibers including PP, PET, and nylon-6  
302 (PA6). All fibers show relatively high electrical resistivity allowing them to be electrified  
303 via corona charging, triboelectrification and induction. The applications of such  
304 electrostatically charged filters can be extended to other relevant approaches, such as face  
305 masks, building air conditioning systems [48], automobiles, air purifiers, to mention just a  
306 few [42,49,50].

307 In current times, researchers are endeavouring on the design and development of innovative  
308 electrically charged membrane materials to fabricate more efficient filtration systems. Al-  
309 Attabi et al. [51], for instance, developed silica doped electrospun nanofiber membranes  
310 with tuned surface roughness for potential aerosol air filtration, which revealed filtration  
311 efficiencies as high as 95%. The research also pointed out that both surface charge and  
312 electrostatic attraction of aerosol particles could also foster the air filtration performance  
313 improvement of tetraethyl orthosilicate (TEOS)/PAN electrospun nanofibers.  
314 Simultaneously, the filtration efficiency of polyvinylidene fluoride (PVDF) electret  
315 nanofiber filters was also evidenced by Sun et al. [52], who studied the dielectrophoretic



316 effect toward neutrally charged nano- and sub-micron aerosols. Their size was ranged from  
317 50 to 500 nm. Theoretically, the dielectrophoretic effect involves the induction of dipole  
318 charges on neutrally charged aerosols as long as they are close to the charged nanofibers;  
319 afterward, the polarized aerosols can be electrostatically caught by the charged fibers [53].  
320 Apart from the stability for 24 h operation, the PVDF fiber filters displayed high filtration  
321 efficiency and low-pressure drops. Punctually, the long-time operating effectiveness of the  
322 electret multi-layer membrane filter was credited to the superhydrophobic properties and  
323 exceptional electrical resistant properties of PVDF, leading to suitable electrostatic charge  
324 stability and thus stable filtration performance [54,55].

325

326

327

### 328 **3. Electrospun nanofiber materials for air filtration**

329 Most of the research ~~has been focused~~ ~~emphasized~~ on the exploration of different classes  
330 of polymers ~~with the view of~~ for tailoring nanofibers properties to be used in different ~~for~~  
331 ~~various~~ applications, but particularly for air filtration at room and high temperatures. The  
332 choice of utilizing ~~several relative~~ materials either polymeric or ~~biopolymeric~~, organic or  
333 inorganic additives, and appropriate solvents, for the fabrication of fibers ~~aimed for air~~  
334 ~~filters~~ becomes relevant from the fluid dynamics point of view, since the properties of a  
335 polymeric solution in terms of viscosity, surface tension, and conductivity may ~~have~~  
336 ~~display~~ a great impact on electrospinning process parameters [35]. Initially, polymers, as  
337 organic materials, have been primarily explored for the fabrication of electrospun  
338 nanofibers with ~~an~~ application in the air filtration. Polyimide (PA) [56,57],





339 ~~polyacrylonitrile (PAN)~~ [58], polyurethane (PU) [11], polysulfone (PS) [59], polyamide-  
 340 56 [60] and polyamide-66 (PA 6,6) [61] are, for example, among the most utilized  
 341 polymers in nanofibers preparation ~~as enlisted in Table 1. enlists some of these polymers~~  
 342 ~~successfully used in nanofibers prepared by electrospinning aimed for air filtration~~  
 343 ~~applications.~~ However, according to the current necessities in finding better materials, the  
 344 merging of inorganic materials into polymer phases has conducted to the fabrication of  
 345 mixed matrix nanofibers or composites. Today, the preparation of this latter type of  
 346 membranes stands out as compelling strategy at enhancing the filtration efficiency of  
 347 nanofibers while improving their chemical, mechanical and thermal stability together with  
 348 enhanced antimicrobial properties [55,62]. Various nanomaterials, such as TiO<sub>2</sub> [63], SiO<sub>2</sub>  
 349 [64], ZnO [65], and Ag nanoparticles [63], have been successfully imbedded into polymer  
 350 nanofibers.

351

352 **Table 1.** Polymer electrospun nanofibers fabricated via electrospinning. Adapted from  
 353 [35].

354

Polymers	Polymer conc. (wt%)	Solvent	Electrospinning parameters			Reference
			Voltage (kV)	Flow rate (ml/min)	Distance (cm)	
PVA	10	Boric acid (BA)	15	0.5	15	[66]
	35.5	N,N-dimethylformamide (DMF)/acetic acid (AA)	24	0.5	16	[15]
PVA/ TiO <sub>2</sub>	-	Water	14	-	15	[67]
PA 6/6	9-14	Formic acid (FA)	20-50	0.25	11-16	[15]
PA 6	12	2,2,2-tri-fluoro ethanol (TFE)	8-20	0.3	15	[68]
PAN	15	DMF	19	0.8	20	[15]
	-	DMF	12.5-22.5	2	10-16	[69]
PAN/ SiO <sub>2</sub>	-	DMF	30	1.5	15	[62]
PU	-	DMF	10-30	0.6-1.2	20	[70]

355



356 The following subsections give an overview of the different materials applied in  
357 electrospun nanofiber fabrication via electrospinning **technique**.

358

### 359 *3.1. Polymers*

360 **Polyamide (PA)**, PAN, and fluoropolymers such as PVDF and polytetrafluoroethylene  
361 (PTFE), are among the most **used preferred** polymers by the research community due to  
362 their inherent high chemical and thermal stability [71,72]. They also offer the advantage of  
363 excellent processability for spinning and versatility to be adapted in various membrane  
364 preparation protocols. For instance, PA is a widely investigated polymer for tailoring  
365 filters thanks to its ability to be dissolved by different solvents, such as formic or acetic  
366 acid, or dimethylformamide (DMF), to mention just a few. It also displays resistance to  
367 water and thus humidity. It is biocompatible and presents a good mechanical resistance.  
368 Promisingly, several researches documented the preparation of fibers from two types of  
369 PA, named PA 6 (Nylon 6) and PA 6,6 (Nylon 6,6) [73,74]. These membranes were able  
370 to perform ~~for~~ air filtration due to interesting features including their small diameter,  
371 narrow diameter distribution, large surface area, and electrostatic charge [75]. A  
372 comparative analysis among PA 6 and PA 6,6 fibers has been done by Matulevicius et al.  
373 [76], who concluded that PA 6,6 fibers were likely to be the most performing ones. **In**  
374 **particular, electrospun** fibers formulated with 8 wt.% of polymer concentration exhibited **a**  
375 **filtration** efficiency **ranging** from 84% to 90% with a quality factor (QF) from 0.0486 to  
376 0.0749 1/Pa.

377 PAN is yet another synthetic polymer with exceptional thermal resistance (degradation  
378 above 300°C). The polymer is inert to plenty of organic solvents and acids and certainly



379 displays good processability. PAN fibers also represent a **valid** choice in producing carbon  
380 membranes, e.g., they **can** be used as precursors for high-quality carbon fibers [77]. It has  
381 been reported that PAN nanofibers have demonstrated high mechanical and thermal  
382 stability, together with good efficiency for gaseous pollutants filtration in respect to other  
383 polymer fibers [15]. Additionally, they can be operated in a wide and extreme hazardous  
384 air-quality conditions (**PM<sub>2.5</sub>** index >300, exhibiting an efficiency of 95-100% ascribed to  
385 the surface capture ability and higher dipole moments [31].

386 Fluorine polymers on their own present also advantages **due to, such as** presence of the C-  
387 F bond, which is stronger with respect to the C-H bond. The use of F instead of H in the  
388 C-H bond fosters the bond strength that passes from 99.5 kcal/mol for the C-H bond to 116  
389 kcal/mol for the C-F bond, resulting in a higher thermal and chemical stability of PTFE,  
390 ~~this is because more~~ **because of the high energy is** needed to break the C-F bond [78]  
391 **considering** that the fluorine atom is larger than hydrogen and it has unshared electron pairs  
392 with higher electron density. Polymers presenting more fluorine atoms (such as PTFE) own  
393 a high melting point, low coefficient of friction (e.g., PVDF: 0.3 Dynamic and PTFE: 0.04  
394 Dynamic), and low surface tension (e.g., PVDF: 25 dyne/cm and PTFE: 18 dyne/cm).  
395 Interestingly, the C-F bond is mainly responsible for the insolubility of the polymer in  
396 common solvents; PTFE, for instance, is fully overlaid with fluorine atoms and frequently  
397 demands high temperatures to be solubilized; while, PVDF, presenting the C-F bond and  
398 the C-H bond in the structure, **shows** greater flexibility to be solubilized in different  
399 solvents. Fiber filters based on fluoropolymers tend to show high filtration efficiency with  
400 low-pressure drops and good filtration stability over time. On the other hand, PVDF filters  
401 present high hydrophobic nature and a suitable electrical conductivity, allowing them to



402 display good charge stability and stable filtration performance [54,79]. PVDF filters were  
403 combined with the typical air conditioning filters meshes based on polyester, PA, and nylon  
404 for the air filtration of ~~PM<sub>2.52.5</sub>~~ (PM with aerodynamic diameter  $\leq 2.5 \mu\text{m}$ ) [80]. Also,  
405 polyvinylpyrrolidone (PVP) and silver nitrate crystals were incorporated into the dope  
406 solution to reduce defects or beads ~~while benefiting also of the for~~ antibacterial properties.  
407 The scope of this study was devoted to outline the importance of the materials, such as  
408 polymers, meshes, and the operating preparation parameters (such as voltage: 40, 45, 50,  
409 55, 60 kV) on the final nanofiber's features and thus performance. By using polyester 80  
410 mesh material, the QF turned to be the largest at 40 kV (QF:  $23 \cdot 10^{-3}$ ), the smallest at 45 kV  
411 (QF:  $21 \cdot 10^{-3}$ ), ~~with~~ a filtration efficiency of 90%. Thanks to the properties of PVDF, the  
412 recent development works rely on the production of novel electret fiber filters with high  
413 strength, low air resistance, and outperforming for long-term aerosol filtration [52,81].  
414 Similar to PVDF, PTFE fibers stand out as alternative candidates for air filtration thanks  
415 to their high-temperature resistance, low-pressure drops, and high efficiency. The filtration  
416 operation presenting PTFE filters take places at the surface of the fibers, which make them  
417 suitable for a number of applications in high-efficiency particulate arresting (HEPA) and  
418 ultralow penetration air (ULPA) in class cleanrooms. Very recently, Xu et al. [66]  
419 fabricated and then tested PTFE nanofiber membranes for fine particulate filtration. In this  
420 study, the filtration performance against aerosol particles was as high as 98% with a  
421 relatively low-pressure drop (ca. 90 Pa). At this point, the area of the filter acted as the  
422 contact surface, and due to its microporous structure, expressed as millions of pores per  
423 square centimetre, the submicron particles were successfully separated. It is important to  
424 mention that the layer below played merely as a support and its contribution to the filtration

425 process was considered as negligible. Strictly, the evaluation performance of these fibers  
426 must be suitable for the filtration of particle sizes comparable with dust particles, which  
427 are much larger than the pore size of the fibers, permitting only gas molecules to go  
428 through. Its main disadvantage deals with the fouling phenomenon that can occur at the  
429 surface. In other words, the particles can potentially form a cake layer on the surface of the  
430 material, which will definitely compromise its separation performance [82]. Aiming to  
431 address this latter point, several cleaning strategies have been investigated to restore the  
432 functionality of the membranes including the passive cleaning with carbon particles [66]  
433 or synergic effects based on adsorption photochemical catalysis, non-thermal plasma  
434 photocatalysis, among others [22].

435

### 436 *3.2. Biopolymers*

437 In recent times, there is a strong necessity to produce and apply biopolymers [83,84],  
438 produced from raw materials, for manufacturing nanofibers aimed for different membrane  
439 separation techniques, but specially for air filtration. As an example, polyurethane (PU) is  
440 a polyester that can be found in soft and rigid forms. It has a hydrophilic nature and ~~it is of~~  
441 ~~course~~ derived from renewable sources [85,86]. PU fibers have shown fast absorption of  
442 volatile organic compounds (VOCs) at both surface and the polymeric matrix, revealing a  
443 competitive uptake capacity compared with traditional adsorbents such as activated carbon  
444 [70].

445 PVA is yet another biopolymer that owns a semi-crystalline structure presenting hydroxyl  
446 groups and hydrogen bonds. Interestingly, it is a water-soluble polymer with exceptional  
447 hydrophilicity and good adhesive and barrier properties [87]. It is worth mentioning that



448 has been investigated in producing membranes for selective gas and solvent separations  
449 [71,88,89]. When dealing with air filtration applications, Lv et al. [90] blended PVA with  
450 a high molecular weight polysaccharide, like konjac glucomannan (KGM), ~~to obtain~~  
451 displaying an efficiency of 99.9% in air filtration testing. A mixture of DEHS and neutral  
452 monodispersed NaCl were employed as model aerosol particles with diameter ranging from  
453 300 nm to 10  $\mu\text{m}$ .

454 Poly(lactic acid) (PLA), made up of elements similar to lactic acid, is characterized by  
455 excellent processability and high melting point temperature between 170-180  $^{\circ}\text{C}$ , and  $T_g$   
456 values in the range of 50 - 65 $^{\circ}\text{C}$  [83,91]. An important environmental aspect behind PLA  
457 regards its a low carbon footprint , making it as a good candidate for the production of  
458 fibers for air filtration [35,86,92]. Finally, poly(acrylic acid) (PAA) [93] polyethylene  
459 oxide (PEO), polyvinyl acetate (PVAc) [15], keratin, chitosan [94], and aliphatic  
460 polyhydroxy-butyrates (PHB) [95–97] are among other biopolymers to be potentially used  
461 for nanofibers production and implemented in air filtration.

462

463


### 464 3.3. Nanomaterials and other additives

465 The application of additives, such as inorganic materials or salts, within the fabrication of  
466 nanofibers for air filtration applications, are frequently needed to improve not only the  
467 filtration efficiency but also the pressure drop and QF. Presently, it is a common practice  
468 the blending of additives in the electrospinning technique in order to favour the formation  
469 of nanofibers. For instance, the incorporation of additives results in a viscosity increase of  
470 the solution and, in some particular cases, in the reduction of the fibers diameter of the



471 ~~fibers~~. Common salts are generally LiCl [79,98], tetraethylammonium bromide (TEAB)  
472 [99], NaNO<sub>3</sub>, NaCl, CaCl<sub>2</sub> [100]. ~~In the case of~~ LiCl has an electrical conductivity  
473 estimated about 394 μS cm<sup>-1</sup> and it can be employed for changing the conductivity of the  
474 solution and thus improving the charge density on the surface of the charged jet. This latter  
475 fact becomes relevant in producing nanofibers with a more uniform morphology. TEAB,  
476 for example, exhibits similar conductivity than LiCl in water. In general, salts dissolve in  
477 the aprotic solvents in which the solvation can depend on the dielectric constant of the  
478 solvent (known as general solvation), or the chemical structure of both solute and solvent  
479 (known as specific solvation) [99,101]. Metal oxides, including Al<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, SiO<sub>2</sub>, β-  
480 cyclodextrins (β-CDs) [55,67,102,103], and ZnO [90], are other additive agents that can  
481 increase the surface roughness of the membranes, and particularly TiO<sub>2</sub> exhibits  
482 antimicrobial and photocatalytic activities [104]. TiO<sub>2</sub> particles have been involved in  
483 nanofiber production reducing the diameter of PS [59] and PVA nanofibers [105]. Another  
484 important material is graphene oxide (GO), which has received considerable attention  
485 lately [106–108]. GO has improved the filtration efficiency of PM<sub>2.5</sub> (~ 99%) - **thanks to**  
486 **its ability to effectively absorb PM<sub>2.5</sub> particles (Figure 6.a)** - demonstrating an excellent  
487 air filtration system in combination with PAN nanofibers [107].  
488 Silver nanoparticles (Ag NPs), which are also known by their inhibitory activity towards  
489 various bacteria [109], are typical dispersing inorganic phases in biocomposite nanofiber  
490 fabrication. Zinc oxide nanoparticles (ZnO NPs) can improve the surface roughness  
491 **resulting into** ~~translated to~~ a uniform narrow pore size distribution with an almost complete  
492 air filtration efficiency (approximately 99.99%). β-CDs, which are cyclic oligosaccharide  
493 presenting seven glucose units, are commercially available, low-cost, non-toxic,

494 biodegradable items derived from starch digestion. Such compounds have been recently  
495 investigated in air filtration applications according to their particular cone-shaped cavity  
496 structure.  $\beta$ -CDs have been involved for composite nanofibers preparation based on classic  
497 polymers, such as PAN, where it has improved the adsorption capacity against VOCs.  
498 Additionally, the combination of  $\beta$ -CDs with biopolymers, such as gelatin, allows the  
499 production of bio-nanofibers ~~as a green solution and~~ as a green alternative solution to ~~the~~  
500 ~~use of~~ fossil-based materials. As an example, composite gelatin/ $\beta$ -cyclodextrin nanofibers  
501 displayed the ability to separate aerosol particles (0.3–5  $\mu\text{m}$ ) with <95% filtration  
502 efficiency at 0.029/Pa [110]. Such biodegradable nanofibers owned a uniform morphology  
503 with a second “web” structure, characterized by superimposed and interconnected fibers  
504 which presented a much smaller dimension than the main nanofibers, as showed in **Figure**  
505 **6.b.**  
506

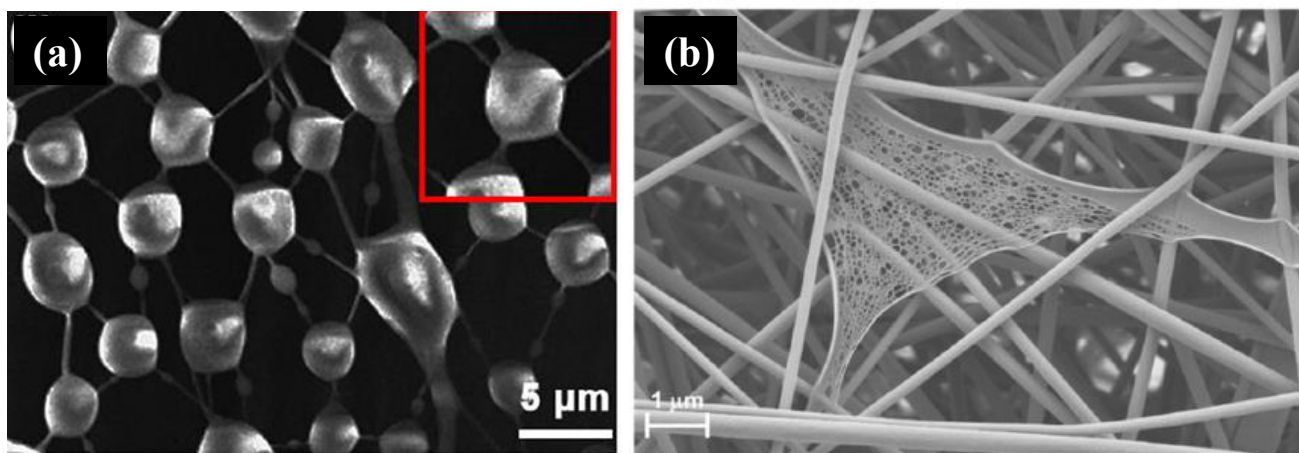

507 **Figure 6.** (a) Absorbed PM<sub>2.5</sub> particles on the PAN/GO. Reprinted (adapted) with  
508 permission from [107]. Copyright 2019 American Chemical Society. (b) SEM images of  
509 composite gelatin/ $\beta$ -cyclodextrin nanofibers with “web” structure. Reprinted from [110]  
510 with the permission of Elsevier.

511  
512  
513

#### 3.4. 4. Solvents for electrospun membranes





514 ~~The~~ Solvent is an important component ~~dealing with the crucial items needed~~ necessary  
515 for the fabrication of most polymeric membranes ~~in membrane fabrication~~. This becomes  
516 ~~relevant since it~~ In electrospinning processes, the solvent favours the formation of various  
517 interactions between materials ~~in the electrospinning process~~. Also, the physicochemical  
518 properties of the solvent can influence the morphology and more importantly the pore size  
519 diameters of the resulting fibers. The solvent influences drastically the dope solution  
520 properties such as viscosity and conductivity. To date, chloroform, DMF, and  
521 dimethylacetamide (DMA) were found to be the best solvents for fabricating nanofibers.  
522 Herein, solubility parameters are **essentially** pivotal to estimate solvent-polymer ~~the~~  
523 affinity [111]. In theory, very close solvent-polymer parameters reveal a good solubility  
524 and also the possibility to electrospin the solution at room or mild temperatures. With the  
525 aim of tailoring defect-free nanofiber membranes, a second volatile solvent, such as  
526 acetone or alcohols, are usually utilized in combination with the main solvent. The usage  
527 of this **co-solvent** increases the time of solvent evaporation during the fibers formation  
528 thanks to the high vapour pressure, ~~this promotes~~ **promoting** the production of uniform 3D  
529 **nanofiber networks** ~~in nanofibers~~ [112]. National and international regulations limit the use  
530 of dangerous chemicals and **encourage** ~~promote~~ the transition to more sustainable and less  
531 toxic alternatives [113]. A series of other green solvents derived from biomass have been  
532 recently proposed for the fabrication of polymeric membranes (in flat-sheet and hollow  
533 fiber configuration) including dimethyl isosorbide (DMI) [114],  $\gamma$ -valerolactone (GVL)  
534 [115], dihydrolevoglucosenone (Cyrene™) [116] ionic liquids [117] and/or deep eutectic  
535 solvents (DESs) [118,119]. Recently, Russo et al. [79] produced PVDF electrospun  
536 membranes using dimethyl sulfoxide (DMSO) as a low toxicity solvent in a mixture with



537 acetone. The results obtained have opened new perspectives for more sustainable  
 538 production of electrospun membranes. The research in this direction remains open and  
 539 attractive for the next future.

540

541

542

543

544

545

546

547

548

549 **4. 5. Characterizations and performance evaluation**

550 It is widely known that the design and development of a new membrane concepts implies  
 551 the characterization and performance when implemented in a specific membrane process.  
 552 For instance, **Table 2** lists main **characterization** techniques used for the characterization  
 553 of electrospun nanofiber membranes.

554 **Table 2.** Typical characterization methods and techniques used for electrospun nanofiber  
 555 membranes. Adapted from [120].

Characterization	Method
Pore size	Bubble point method
Pore size distribution	Permporometry
Pore size distribution	Gas and liquid displacement methods (GLDP-LLDP)
Pore size distribution	Mercury porosimetry (MP)
Morphology, thickness	Scanning Electron Microscopy (SEM), Transmission Electron Microscopy (TEM)
Surface porosity, roughness	Atomic force microscopy (AFM)



Studies of chemical group	Infrared Spectroscopy (FT-IR, ATR, Photoacoustic)
Surface studies, chemical analysis	Energy Dispersive X-rays Spectroscopy (EDX or EDS), wavelength dispersive X-ray spectroscopy (WDS)
Thermal analysis	Differential Scanning Calorimetry (DSC)
Wettability	Contact angle measurement
Mechanical properties	Mechanical resistance, Stress-Strain measurements
Chemical stability	Swelling and contact angle

556

557 In general, the characterizations methods reveal important information about the  
558 morphology, structural, physical, chemical and thermal properties. ~~While~~ ~~When~~ dealing  
559 with air filtration, a dust filtration set-up is usually employed to evaluate the typical  
560 filtration parameters including filtration efficiency and pressure drop. In this experimental  
561 testing, particles, with size ranged from 0.6 to 180  $\mu\text{m}$ , are commonly used and fed at a  
562 given air velocity [121]. The filtration efficiency of each fiber membrane ~~for air filtration,~~  
563 which results in overall filter efficiency, is ~~expressed denoted~~ as follows (2) (3) [39]:

564

$$\eta_s = \frac{\text{particles collected by fiber}}{\text{particles in a volume of air geometrically swept out by fiber}} \quad (2)$$

565

566

$$\eta = 1 - \exp(-\eta_s S) \quad (3)$$

567

568 where  $\eta_s$  refers to the filtration efficiency of a single fiber,  $S$  refers to the filter area factor,  
569 which is the projected area of fiber per unit of filter area, and  $\eta$  denotes the overall filter  
570 efficiency.

571 In addition to the high filtration efficiencies, electrospun membranes also display  
572 antibacterial properties during the filtration of air, which not only presents submicron


573 aerosol particles but also specific microorganisms (e.g., bacteria). Recently, Vanangamudi  
574 et al. [55] engineered new composite nanofibrous based on PVDF and Ag–Al<sub>2</sub>O<sub>3</sub>, with  
575 excellent antibacterial efficiency as high as 99.5%. Additionally, detoxifying properties  
576 higher than 35% against paraoxon were observed. In aerosol filtration containing particles  
577 (diameter of 0.36 μm), the filtration efficiency rate increased proportionally to the Al<sub>2</sub>O<sub>3</sub>  
578 content, ranging from 2 to 8 wt.%. The filtration efficiency depended on the nanoparticle  
579 loading, achieving ca. 99% filtration efficiency (at 8 wt.% Al<sub>2</sub>O<sub>3</sub> loading). Furthermore,  
580 the composite nanofibrous membranes revealed apparently stable antibacterial properties  
581 over 99% towards *E. coli* [55]. In a different investigation, Ding et al. also evidenced  
582 competitive filtration efficiency ranging from 80 to 90% of electrospun PVDF/SiO<sub>2</sub>  
583 nanofibrous membranes [122]. This latter development confirms the effect of nanoparticles  
584 into pristine polymer nanofiber ~~with an~~ in enhancing the filtration rate. Concurrently,  
585 Cannalli et al. [63], for instance, evaluated various inorganic particles into PAN nanofibers,  
586 including TiO<sub>2</sub>, ZnO, and Ag. Basically, all membranes performed with an average  
587 filtration efficiency, but interestingly TiO<sub>2</sub>-containing membranes owned the smallest fiber  
588 diameter along with a complete filtration efficiency (ca.100%).

589 Shao et al. [123] have intentionally designed self-powered electrospun nanofiber  
590 membranes for highly efficient air filtration. In this approach, the proposed electrospun  
591 membranes were fabricated based on polyvinyl chloride (PVC) nanofibers and polyamide-  
592 6 (PA6) nanofibers. By inducing air vibration, the triboelectric effect between both  
593 adjacent nanofibers resulted in electrostatic charges, which contributed to observe  
594 electrostatic adsorption capacity. Experimentally, the removal efficiency of the designed  
595 nanofibers was as high as 98%, while the pressure drop was estimated as 67.5 Pa, this

596 proved a higher quality factor compared with the membrane lacking of electrostatic  
597 charges. This development works proposed by Shao et al. [123] opens a new window **in**  
598 **the fabrication of** outperforming membranes by exploiting the polymer features and the  
599 electrospinning technique.

600 Zhu et al. [12] utilized silica nanoparticles with superhydrophobic nature which were  
601 subsequently filled into a chitosan/poly (vinyl alcohol) (PVA) air filtration membrane via  
602 green electrospinning and UV-cured nanofibers [12]. The inorganic hydrophobic fillers  
603 were favourably added to form a rough surface and thus increase filtration efficiency. As  
604 for filtration of fine particles (between 300 and 500 nm), the filtration efficiency and  
605 pressure drop were noted to increase by increasing the basis weights, in other words, the  
606 increase of the basis weight in membranes from 1.48 to 6.2 g/m<sup>2</sup> resulted in an  
607 enhancement of the filtration efficiency from 42.97 % (with a pressure drop of 33.6) to  
608 96.60 % (with a pressure drop of 305.6) for NaCl particles (**Figure 7.a**). Additionally, these  
609 membranes showed a filtration separation towards di-ethyl-hexyl-sebacate (DEHS)  
610 particles from 51% (with a pressure drop of 33) to 99 % (with a pressure drop of 296)  
611 (**Figure 7.b**). Based on authors' conclusions, this phenomenon was credited to the high  
612 basis weight, which **allowed confer** to the membranes to display more contact points while  
613 increasing tortuous airflow channels [12].



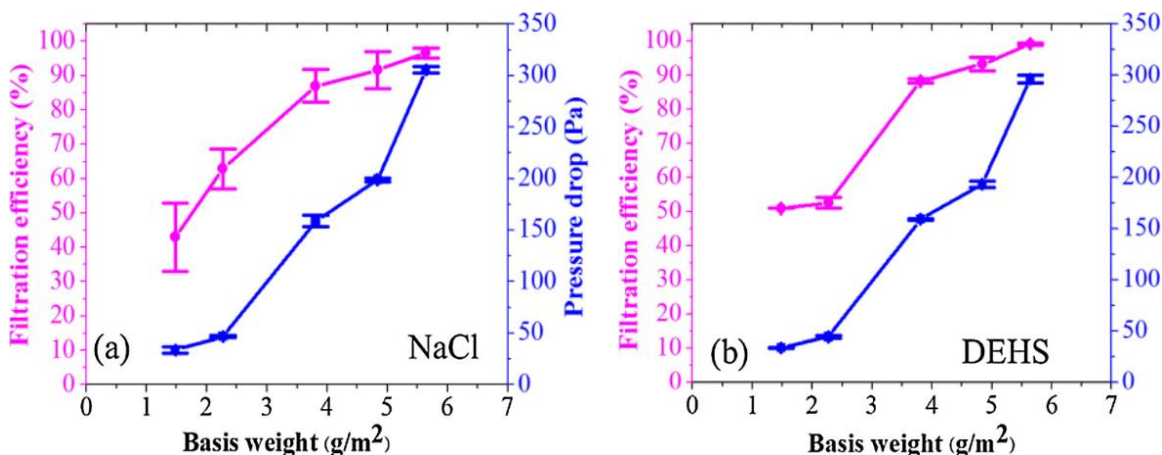

614

615 **Figure 76.** Filtration performance of silica nanoparticles filled into a chitosan/poly (vinyl  
 616 alcohol) (PVA) nanofibrous membranes with different basis weight investigated by using  
 617 NaCl and DEHS particles. Reprint from [12] with the permission of Elsevier.

618

619 **Table 3** enlists a few examples of nanofiber membranes aimed at separating different  
 620 pollutants from air. In general, it can be seen that most of the nanofibers display a good  
 621 performance towards environmental remediation and mask filtration which is  
 622 currently an area of research related to coronavirus disease.

623

624 **Table 3.** Performance of various nanofiber membranes for air filtration.

Pollutants	Materials	Efficiency	Pressure drop	Quality Factor (QF)	Notes	Ref.
		(%)	(Pa)	(Pa <sup>-1</sup> )		
PM <sub>0.3</sub>	CNFs/PVP	86.4	17	0.117	For environmental remediation	[124]
	HNTs@CS/PVA/NWF	96.8	143.9	0.0239	For environmental remediation	[125]
	PP	87.28	40	0.052	For environmental remediation	[126]
	PVA (nanofibers deposited on PP nonwoven)	99.1	78	-	For ideal surgical mask and dust mask	[127]
	PLA	82.156	-	-	For ideal mask filtration	[128]
PM <sub>2.5</sub>	PLA/ artificially cultured diatom frustules (DFs)	99.99	-	-	For ideal mask filtration	[128]
	PVDF	98.16	30	0.120	For environmental remediation	[129]
	TPP/N6	99.06	253	0.018	For environmental remediation	[130]

	PAA@ZIF-8	99.6	146.3	0.034	For environmental remediation	[131]
	PVA (nanofibers deposited on PP nonwoven)	99.9	56		For ideal surgical mask and dust mask	[127]
	PU/SiO <sub>2</sub>	95.37	126	0.001	For multilayer face masks (0.5 wt% of SiO <sub>2</sub> )	[132]
	PTFE/PP@PTFE	94.96	8	0.0348	for applications in nanogenerators, wearable electronics, medical products and other fields	[133]
NaCl aerosol particles	PMIA/PAN	99	-	-	For air pollution	[134]
	PTFE/PVA/ boric acid (BA)	98	30	-	For air pollution	[66]
	PVDF	99.2	-	-	For ideal mask filtration for SARS - COVID virus	[135]
	PVA/sodium lignosulfonate (LS)	99.44	24.5	0.212	For ideal mask filtration for SARS - COVID virus	[126]
Murine hepatitis virus A59 (MHV-A59)	PVDF	97.1	-	-	For ideal mask filtration for SARS - COVID virus	[135]
Diocetyl phthalate(DOP) aerosolparticles (0.3 μm) (TSI 3160 test)	PES/PAN	99.54	133.9	-	For ideal mask filtration for SARS - COVID virus	[136]
Diethylhexyl sebacate (DEHS) aerosols	PTFE/PP@PTFE	95.39	-	0.0358	For applications in nanogenerators, wearable electronics, medical products and other fields ( DEHS size 0.200–4.595 μm)	[133]

625

626

627 **5. 6. Electrospun nanofibers configurations**

628 The material properties and the operating parameters of the electrospinning technique

629 greatly determines the configuration of nanofibers. **The configuration** influences ~~in~~ the

630 construction of two-dimensional (2D) and three-dimensional (3D) networks of nanofibers

631 [137]. Experimentally, the features of these networks are systematically analysed with the

632 aid of different characterization techniques, such as porosimetry, which determines the


633 pore size, while scanning electron microscopy (SEM), transmission electron microscopy

634 (TEM), and atomic force microscopy (AFM) are used to investigate the morphology and

635 surface roughness. In the case of SEM, this technique is primarily applied for the  
636 morphology study and thickness measurement of the nanofibers, while TEM tends to be  
637 more convenient for the nanofibers having a diameter less than 300nm. The AFM is  
638 commonly applied to characterize the total surface topography [138].

639 As for the pore size, polymeric nanofibers may present a pore size distribution ranged from  
640 tens of nanometers to several micrometres; favourably, the submicron range is suggested  
641 for better filtering efficiency. Eventually, A uniform and interconnected pore structure with  
642 high surface area per unit volume is preferred as well [139].

643 The morphology of different polymer electrospun nanofibers based on PVDF, PAA, PAN,  
644 PLA, CA is shown in Figure 8.

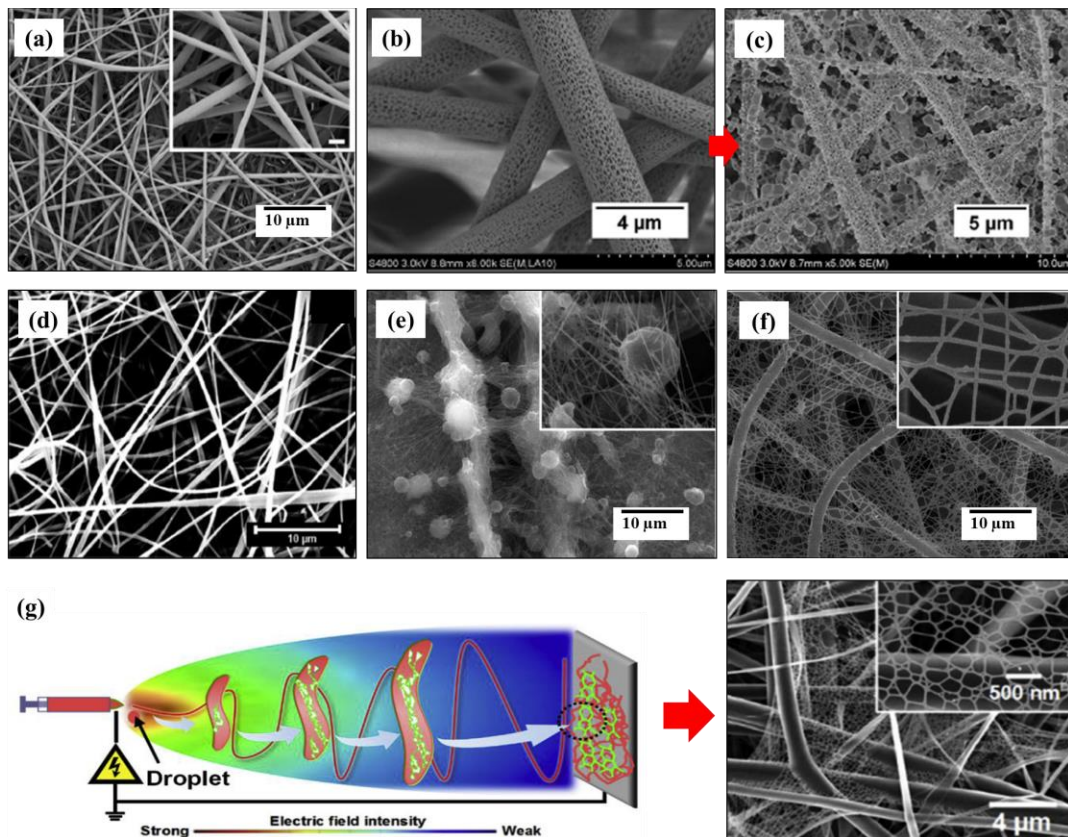

645

646



647 **Figure 8.** Morphology of different electrospun filtration membranes based on various  
 648 polymers. (a) PLA, reprinted from [140] with permission of Elsevier; (b and c) Hierarchical  
 649 structured nano-sized/porous poly(lactic acid) (PLA-N/PLA-P) composite nanofibers  
 650 prepared at 45% RH of humidity before and after filtration test, reprinted from [141] with  
 651 permission of Elsevier; (d) CA nanofibers with cationic surfactant cetylpyridinium  
 652 bromide (CPB), reprinted from [142] with permission of Elsevier; (e) PVDF, reprinted  
 653 from [143] open access; (f) PAN reprinted from [143] open access; (g) hypothetical  
 654 situation simulation of electrospinning/netting and (h) nanofiber/nets structure of poly  
 655 (acrylic acid) (PAA) with 0.03 wt% of NaCl, reprinted from [144] with permission of  
 656 Elsevier.

657

658

659

660

661

662

## 663 **6.7. Electrospun membrane applications for air filtration**

### 664 *6.7.1. Individual protection devices*

665 The current importance of electrospun membranes relies on the new perspectives for  
 666 individual protection devices for air pollution or emerging infectious diseases (EIDs)  
 667 including Coronavirus 2019 (COVID-19). A typical protector device for air filtration is  
 668 characterized by fibrous (nonwoven filter) membranes composed by fine fibers. The  
 669 mechanism of particles separation deals with an aerosol stream and entrapped between the  
 670 fibers inside the filter [42]. **Table 5.3** provides a summary of regulations and/or tests used  
 671 to certify masks elaborated by Das et al. [145].

672

673 **Table 5.3.** Regulations/test used to certify facemasks. Reprint from [145] with the  
 674 permission of Elsevier.

Regulation/test	Scope	Limitation	Note
-----------------	-------	------------	------



Swedish Standard SS-EN 149 + A1:2009	Respiratory protective devices – Filtering half masks to protect against particles	At least 92% of the tested elements cannot leak N5% particles	Value taken for FFP3 device class.
NIOSH 42 CFR 84 US (NIOSH 1995)	Filtering capacity	At least 95% of the influent particles should be filtered	NaCl particles are used as surrogate particles. Typical values for N95 respirator masks.
T4D bacteriophage virus filtration, by [146]	Test the filtration property of different filter layers	1 h filtration time resulted on “infinite” T4D virus capture, while 2 h gave $1.1 \times 10^8$	Based on a FFP2 mask
Relative survivability (RS) of MS2 viruses on filters, by [147]	Test the ratio of virus survival on treated filters relative to untreated filters	1. PF PP filter (DuPont™ 01361 N): RS = $1 \pm 0.1$ . 2. CCF coarse pore cellulose filter paper (Whatman™ Grade 54): RS = $1 \pm 0.2$ . 3. FCF fine pore cellulose filter paper (Whatman™ Grade 50): RS = $1 \pm 0.15$	
ASTM F2100 – 19e1	Standard specification for performance of materials used in medical facemasks	Medical facemask materials are required to: 1. Bacterial filtration N95% 2. Sub-micron particle filtration efficiency (0.1 $\mu\text{m}$ ) N 95. 3. Resistance to penetration of blood N80%. 4. Flame spread Class 1	Values based on a Level 1 barrier. 1. Bacterial filtration efficiency based on Test Method F2101. 2. Sub-micron Particle Filtration based on Test Method F2299 3. Resistance to Penetration by Synthetic Blood based on Test Method F1862. 4. Flammability based on 16 CFR Part 1610

675

676 The use of polymeric nanofibers is considered ~~recognized~~ as a new generation of filter  
677 devices for enhancing the overall filtration performance in terms of efficiency and lifetime  
678 compared with conventional systems. As previously mentioned, aerosol particles can  
679 potentially be separated by different mechanisms including interception, inertial impaction,  
680 gravitational settling, electrostatic attraction, and Brownian diffusion (dominant respect  
681 others) [42]. The efficiency is dictated by the synergy of these mechanisms and it is  
682 dependent on the particles size [148]. Certainly, other factors can also affect influence the

683 facemask efficiency including the facial fit of individual wearers and different mask types  
 684 commercially available [149]. As for HEPA masks, i.e., without the presence of  
 685 electrostatic attraction from the polymer fibers, an efficiency as high as 99.97% was  
 686 demonstrated at 0.3 microns [42]. It is well known that PP, PA, PAN, PVDF, and PTFE  
 687 are among the common polymers used for the production of facemasks. In a very recent  
 688 study, Shen et al. [150] developed PVDF/PTFE fiber layers and implemented them in the  
 689 facemasks, which were later evaluated for the removal efficiency of PM with different sizes  
 690 (from 0.3  $\mu\text{m}$  to  $>10 \mu\text{m}$ ). The outcomes demonstrated that for facemask wearers, the  
 691 exposure to ~~PM<sub>2.5-2.5</sub>~~ concentrations in the air could be reduced by less than 20%. To  
 692 improve the electret performance and the uniformity of fiber structures, the perspectives  
 693 are oriented toward the design of novel network of nanofibers containing nanoparticles  
 694 [151], i.e., hybrid polymeric fibers [152]. However, the usage of nanoparticles may bring  
 695 another structural issues, for example, depending on the nanoparticles properties, a  
 696 potential agglomeration issue can be originated which can be translated to a non-efficient  
 697 separation performance [153].

698 Regarding the electric properties, these can be estimated by the electric intensity ( $\bar{E}$ ) of the  
 699 fibers from surface potential ( $\bar{U}$ ) analysis. The intensity can be calculated as follows (4):

700

$$\bar{E} = \frac{\lambda}{2 \pi \xi_0 L} \frac{\bar{U}}{\pi \phi (1-p) (\sqrt{R^2 + H^2} - R)L} \quad (4)$$

701

702 where  $\lambda$  corresponds to the charge density of a single fiber,  $\xi_0$  refers to the dielectric  
 703 constant, L is the distance,  $\phi$  and p correspond to the thickness and porosity of fibrous

704 membranes. R and H regard the radius of tested samples and distance, respectively  
705 [152,154].


706 The  $\bar{E}$  parameter varies in an hybrid PS/PVDF nanofibers, and such a variation has been  
707 investigated by Li et al. [152]. In general, such variation of  $\bar{E}$  parameter in the hybrid  
708 PS/PVDF fibers was highlighted in a colour map for single PS and PVDF fibers. The  
709 different surface potential of the materials was considered. As for PS, the red zone proved  
710 the high electret effect on dielectric property ascribed to a positive surface potential ( $\bar{E}$   
711 positive); on the contrary, the graph for PVDF was characterized by negative  $\bar{E}$  values  
712 credited to its negative surface potential, presumably for its polar nature.

713 During the development of anti-bacterial/antiviral materials for personal protective  
714 equipment (PPE), photoactive chemicals were examined as effective for producing  
715 antimicrobial electrospun membranes due to the possibility to produce oxidative biocidal  
716 reactive oxygen species (ROS).  $\text{TiO}_2$ , ZnO and Ag are considered as photoactive  
717 nanoparticles used in the preparation of polymeric nanofibers that inactivate both Gram-  
718 positive and Gram-negative bacteria [155,156]. Salam et al. [155] added the viroblock  
719 (combination of silver and lipid vesicles) agent into a PAN/ZnO electrospun hybrid  
720 membrane for a novel antiviral personal protective equipment (PPE). This viroblock is a  
721 white viscous liquid that acts as an antiviral as well as an antibacterial agent. The  
722 antibacterial efficiency for PAN/ZnO nanofibers loaded with 5% VB was 92.59% and  
723 88.64% in the case of *Staphylococcus Aureus* and *Pseudomonas Aeruginosa*, respectively.  
724 In a recent work, Zhang et al. [157] blended the Vitamin Ks (VKs) for producing antiviral  
725 electrospun PAN membranes (VNFMs). The prepared VNFMs exhibited robust  
726 photoactivity in generating reactive oxygen species (ROS) under both daylight (D65,



727 300–800 nm) and ultraviolet A (UVA,365 nm) irradiation, resulting in high antimicrobial  
728 and antiviral efficiency (>99.9%) within an exposure time of 90 min (**Figure 9.a**).

729 Wang et al. deeply described the benefits of the embodiment of SiO<sub>2</sub>–TiO<sub>2</sub> porous  
730 nanofibrous membrane (STPNM) with Ag [158]. Interestingly, the inorganic nanofibers  
731 were prepared by electrospinning the precursors of SiO<sub>2</sub> and TiO<sub>2</sub> followed by a step of  
732 calcination, whereas Ag nanoparticles were embedded into the electrospun STPNM porous  
733 nanofibers through an impregnation process (**Figure 9.b**). The Ag@ STPNM electrospun  
734 membrane showed an efficiency of 98.84% in PM<sub>2.5</sub> removal with a pressure drop of 59  
735 Pa coupled with an inhibition of the growth of *E. coli* of 95.8% (**Figure 9.c**).

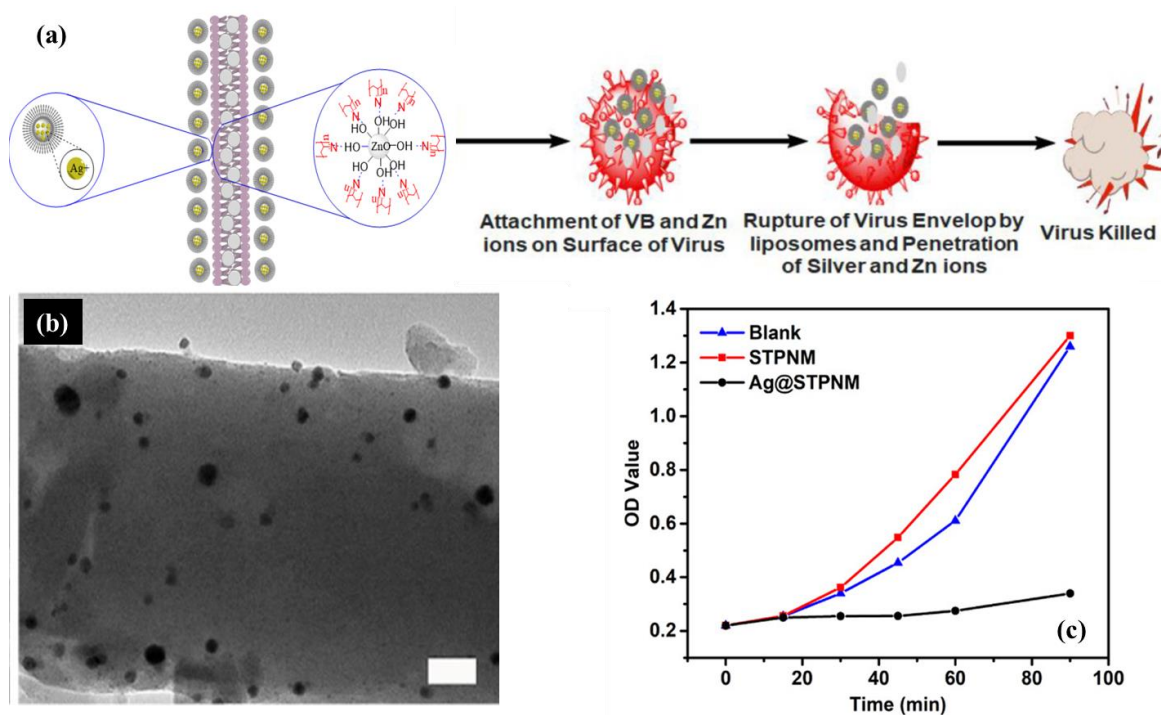


736

737 **Figure 9.** a) Suggested mechanism of working of antiviral activity of VB-loaded PAN/ZnO  
738 electrospun nanofibers [155]. This work is licensed under a Creative Commons Attribution  
739 4.0 International License. b) TEM image and c) antibacterial performance of Ag@STPNM.  
740 Reprinted (adapted) with permission from [158]. Copyright 2019 American Chemical  
741 Society.

742

743 Wang et al. [62] produced high-performance filtration membranes with structural  
 744 alternatives by using different concentration of silica nanoparticles (SNP) into the  
 745 electrospinning PAN solution. The presence of SNP on the filtration performance  
 746 contributed to a high probability of particle capture due to the extended specific surface  
 747 area and ~~can~~ acted as stagnant zones for airstream, generating low air resistance. The  
 748 compromise between filtration efficiency and pressure drop was monitored by modifying  
 749 the SNP content using the NaCl aerosol particles as reported in **Figure 10**.

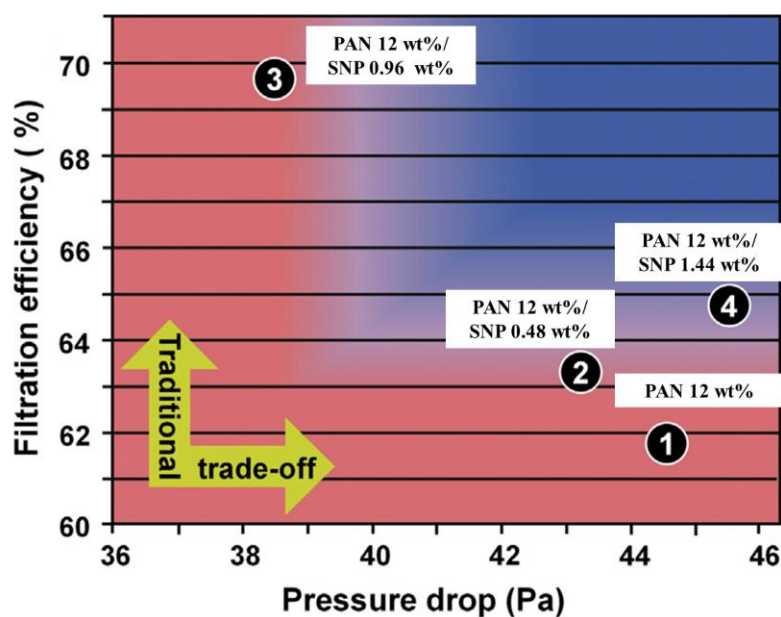

750

751 **Figure 10.** Trade-off between filtration efficiency and pressure drop of relevant PAN/SNP  
 752 electrospun membranes. Reprint from [62] with the permission of Elsevier.

753

754

755

756 *67.2. The role of electrospun nanofibers in environmental remediation*

757 The air pollution increment in highly populated cities **necessitates** the development and  
 758 implementation of **new** efficient air **filtering systems**. Electrospun membranes, due to their  
 759 outstanding properties, represent an **effective** alternative to be applied in these types of  
 760 separation. Patanaik et al. [121], for instance, evaluated various types of PEO for the

761 synthesis of electrospun membranes, followed by their testing in air filtration applications.  
762 Particularly, it was observed that by increasing the polymer concentration, from 3 to 6 w/v,  
763 the diameter of the fibers increased from 85 to 125 nm, while improving their uniformity.  
764 In air filtration testing, dust particles with size between 0.6-180 nm and fed at the constant  
765 air velocity of 4 m/s, the membranes presenting the highest PEO concentration  
766 demonstrated better performance in terms of dust particles retention of approximately 88%.  
767 This latter outcome was ascribed to the fact that the polymer concentration increase  
768 conducted to a reduction of membrane mean pore size (17  $\mu\text{m}$  at 6 w/v of PEO) enabling  
769 the membrane to retain more. Additionally, the membranes prepared at higher PEO  
770 concentrations, resulting in a larger diameter, showed a lower pressure drop (17 Pa at 6  
771 w/v of PEO) compared with the membranes having smaller diameter (28 Pa at 3 w/v of  
772 PEO). In a different work, Canalli Bortolossi et al. [159] interestingly fabricated PAN  
773 electrospun fibers containing particles at different concentrations (from 0 to 50 wt.%), and  
774 deposited on a non-woven substrate. The main purpose was to design ~~a~~-nanofibers with the  
775 ability to remove particles from the air. The final electrospun nanofibers owned a diameter  
776 of approximately 250 nm except for the ones containing 10 wt.% of silver, displaying a  
777 larger diameter (about 400 nm). This latter fact was basically ascribed to the change in  
778 conductivity and solution viscosity ~~caused-provoked~~ by the ~~embodiment~~ of the silver  
779 nanoparticles. Concerning to the air filtration test, the efficiency was initially analysed in  
780 terms of pressure drop. The use of silver nanoparticles (up to 10 wt.%) resulted in an  
781 increase in pressure drop (about 225 Pa) and consequently a decrease in the void space  
782 which hindered the air permeation. Unfortunately, higher content of silver nanoparticles  
783 (50 wt.%) resulted in a lower pressure drop (68 Pa). Such an explanation was justified




784 considering that the membranes containing the highest concentration of silver, thanks to  
785 the higher solution viscosity, ~~were revealed a~~ **resulted in a** lower nanofibers deposition rate  
786 on the collector. When the membrane yield was determined to separate nanoparticles  
787 ranging from 9 to 300 nm, a complete removal, ca. 100%, was obtained for the samples  
788 doped with a silver concentration up to 10 wt.% but, as mentioned previously, with a high-  
789 pressure drop; however, a slight decrease in removal efficiency (approximately 98.6%) was  
790 **observed seen** for the sample containing ~~with~~ the highest silver concentration (50 wt.%)  
791 but with a much lower pressure drop as said above. Considering the obtained outcomes and  
792 regulation established by the European Union Standard for EN 18222 filters, the membrane  
793 lacking in silver loading could be categorized as H13, denominated as High-Efficiency  
794 Particulate Air Filters - HEPA>99.95% collection efficiency. On the other hand, membrane  
795 presenting 1 and 10 wt.% of silver, display the same performance as E12 (Efficiency  
796 Particulate Air Filters – EPA > 99.5% collection efficiency), while membranes with 50  
797 wt.% of silver meet the requirements for E11 filters (EPA > 95% collection efficiency).  
798 Promisingly, credited to the presence of silver, the resulting silver/PAN nanofibers proved  
799 also compelling antibacterial activity towards various *E. coli* bacterial strains.

800 The fabrication and subsequent implementation of polycarbonate (PC) electrospun  
801 nanofibers for the removal of PM from the air was investigated by Li et al. [160]. In this  
802 study, it is relevant mentioning that researchers conducted the air filtration experiments  
803 using real polluted air (full of PM) collected from the outdoor campus of Zhengzhou  
804 University (China). Unlike most investigations reported in literature where the air filtration  
805 performance is determined using air models containing aerogel NaCl particles, which are  
806 far to mimic, in terms of complex chemical composition, the PM dispersed in the polluted





807 air, in Li's study [160], researchers selected three levels of pollution varying in PM  
 808 concentration: 50, 110, and 220 mg/m<sup>3</sup>. The filtration experiments notified how PC  
 809 membranes were capable to separate and ~~this~~ retain the PM with an almost complete  
 810 efficiency (approximately 100%), as reported in **Figure 11**. In addition to this, a good air  
 811 permeability ( $78.36 \pm 11.48$  L/cm<sup>2</sup>h) was observed in such membranes. Taking into  
 812 account that most of the PM owned a dimension lower than 0.3 μm, the membranes  
 813 successfully operated in an outperforming way.

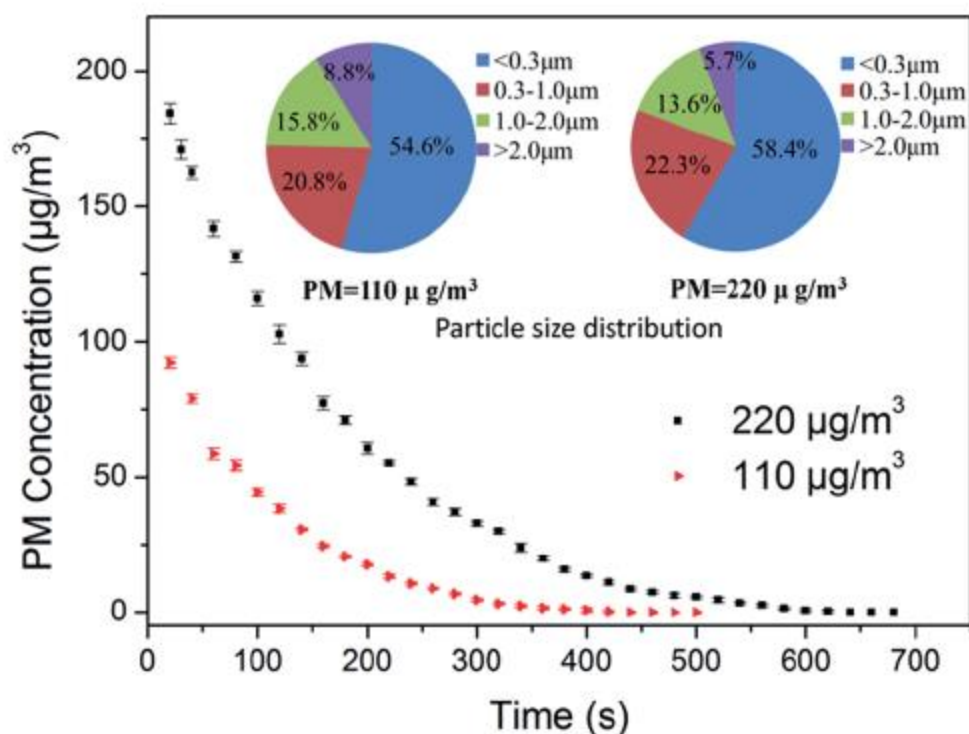

814

815 **Figure 11.** Filtration performance of PC membranes at different PM concentration and as  
 816 a function of time. The particle size distribution is reported in the inserted pie charts.  
 817 Reprinted from [160] with permission of Elsevier.

818

819

820

821 By comparing the filtration performance of PC membranes with PVA and polystyrene

822 membranes, it was concluded that the first ones were the most efficient to remove PM from

823 the air [160]. Favourably, it was found that the removal efficiency increased when the  
824 polarity of polymers repeating units increased as well. Herein, it is quite possible that the  
825 high dipole moment of PC membranes could have improved the binding of PM with  
826 polymer nanofiber surface by means of dipole-dipole or induced-dipole interactions.

827 In a recent work, Cao et al. [161] prepared bead-free ~~polyacrylonitrile (PAN)~~-nanofibers  
828 with diameter ~~lower than of~~ <100 nm to filter ~~PM<sub>2.5-2.5</sub>~~-emissions from burning cigarettes  
829 and ~~from~~ fused deposition modeling (FDM) three-dimensional (3D) printing. The  
830 experiments ~~were~~ carried out by using two-chamber filtering devices. In the case of  
831 filtration of cigarette smoke particles, the device consisted of two chambers as reported in  
832 **Figure 12.a**. The dimension of smoke particles was in the range of 0.3-10 μm and the rate  
833 of number emission was 3.9 x 10<sup>11</sup> particles/min and the ~~PM<sub>2.5-2.5</sub>~~-emission rate was 2690  
834 μg/min. In the case of particles filtration from FDM 3D printing, the device was prepared  
835 by using an interior chamber with a hole covered by the layer of PAN nanofibers membrane  
836 and an exterior chamber as reported in **Figure 12.b**. The emission rate of this type of  
837 particles was fixed to 1-61 x 10<sup>10</sup> particles/min. In these experiments, the efficiency was  
838 calculated by using the equation (5):

$$\text{Filtration efficiency} = (1 - C/ C_0) \times 100\% \quad (5)$$


839

840 where C<sub>0</sub> is the PM concentration from Detection 1 (**Figure 12.a and 12.b**) and C is the  
841 PM concentration from Detection 2 (**Figure 12.a and 12.b**).

842 The results confirmed a ~~an~~ ~~PM<sub>2.5-2.5</sub>~~-removal efficiency of 99.26% in the cigarette smoke  
843 particles filtration experiment and 81.16% in the case of particles sequestration experiment  
844 from FDM 3D printing.



845

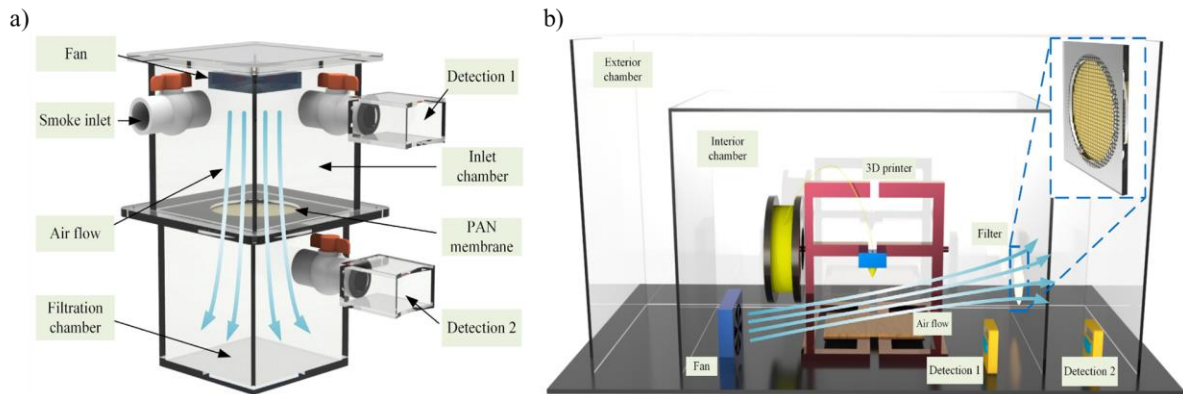

846

847 **Figure 12.** Set-up for a) cigarette smoke particles filtration experiment and b) particles  
848 filtration experiment during 3D printing. Reprinted from [161] with the permission of  
849 Elsevier.

850

851

852

### 853 67.3. Electrospun nanofiber in recovering volatile organic compounds (VOCs)

854 The emissions of VOCs into the environment requires to be strictly regulated by legal limits

855 ~~since~~ due to their ~~negative~~ contribution to the production of polluted waste gas flows, and

856 to their harmful effects on plants, human beings and animals' health. Thereby, the control

857 and regulation of their emissions is a major worldwide concern. VOCs, methane, ethane,

858 tetrachloroethane, BTX, formaldehyde, acetaldehyde and acetone are among the most

859 common atmospheric pollutants, which are ~~the resulting emission of~~ various chemical and

860 petrochemical industries [162]. ~~Towards~~ For the recovery of VOCs, the techniques are

861 primarily categorized in two macro areas: process equipment modifications and add-on-

862 control techniques [162]. Within the second category, ~~we can find~~ it is possible to find

863 membrane ~~processes engineering~~ that represents an interesting alternative to separate

864 VOCs from gaseous streams. This is because membranes ~~processes~~ own several

865 advantages in terms of ~~the high chemical stability of specifically designed membranes~~ in

866 the presence of chlorinated compounds, together with the possibility to be operated at mild  
867 temperatures, thus reducing the overall energy consumption [163]. The main property of  
868 polymer membranes implemented used in membrane contactors for VOCs recovery deal  
869 with is their high permeable-properties-permeation to VOCs while-substantially-hindering  
870 the and low permeation to air [164]. Polydimethylsiloxane (PDMS) and polyimide (PI)  
871 are typical membrane materials for the removal of VOCs, including acetone, toluene, and  
872 xylene, from air or N<sub>2</sub>. As-for PDMS, for instance, displays-a selectivity values ranging  
873 from 11 to 25 in separating acetone [163,165], a selectivity of approximately 84 for toluene  
874 removal and an CO<sub>2</sub>/N<sub>2</sub> ideal selectivity of 21 [166]. Rebollar-Perez et al. [167]; for  
875 instance, investigated the application of PDMS/ $\alpha$ -alumina membranes for vapor  
876 permeation, constructing a device to remove VOCs from air currents (at feed pressure: 3  
877 bar and temperature: 21°C). The preliminary outcomes proved that the membrane was able  
878 to reduce the VOC content as high as 95%.

879 Scholten et al. [70] in their study fabricated and assayed electrospun polyurethane-based  
880 fibers for the separation of VOCs from air, in which particularly was observed a complete  
881 reversible VOCs absorption and desorption using a purge with N<sub>2</sub> at room temperature.  
882 The final fibers exhibited a sorption capacity comparable to active carbon, which is  
883 commonly used for vapor adsorption.

884

#### 885 *67.4. Electrospun nanofiber in ventilation and climate control aspects*

886 Over the last two decades, membrane technology has attracted the attention in the field of  
887 Heating, Ventilation and Air Conditioning (HVAC). From the environmental point of  
888 view, the energy requirements of chillers and air conditioners are responsible for around



889 40–50% of the world's greenhouse gas emissions. Since the World Health Organization  
890 declared the coronavirus disease 2019 (COVID-19) as a Public Health Emergency of  
891 International Concern [168], it is highly needed to develop and implement new and highly  
892 efficient filtration systems for air purification in closed spaces.

893 Vacuum membrane dehumidification, and membrane evaporative cooling and  
894 humidification represent some of the HVAC membrane-aided processes, in which each  
895 process operates differently in terms of inlets and outlets, together with different types of  
896 membranes [169].

897 In the light of membrane-based air dehumidification process, the required membranes must  
898 be dense with hydrophilic nature; requiring a driving force as the vapor pressure gradient  
899 between the feed and permeate sides. In the case of membrane-based evaporative cooling  
900 and membrane-based evaporative humidification process, they are categorized as low-cost  
901 and energy-efficient technologies for the control of the evaporative cooling and the  
902 humidity within the rooms, respectively [169].

903 Nanofibers based filters aimed for the filtration of small aerosols are usually produced by  
904 electrospinning. Presently, Ju et al. [170] explored polyamide-6 polymer for the fabrication  
905 of electrospun nanofibers containing silver nanoparticles. It is a common practice to  
906 evaluate different operating parameters during the electrospinning. In this study, the  
907 investigated parameters were the distance between needle and sample collector (18 cm),  
908 processing temperature (40 °C), the voltage (18 kV), and the average flow rate (0.5 mL/h).

909 The aim of the research was also to evaluate their effect on the antibacterial and antiviral  
910 properties of resulting air filter membranes for a high-efficiency PM removal. The  
911 membranes displayed  $PM_{2.5-2.5}$ -filtration efficiency as high as 99.99%, concurrently with



912 the removal of multiple aerosol pollutants and bacteria, such as *Escherichia Coli* and  
913 *Staphylococcus Aureus*.

914 Photosensitized electrospun nanofibrous membranes were tailored by Shen et al. [135],  
915 who aimed to capture and inactivate coronavirus aerosols. In this case, the rose bengal dye  
916 was employed as a photosensitizer thanks to its exceptional reactivity in virucidal  
917 generation. The electrospun membranes presented a pore size of ca.1.5  $\mu\text{m}$  and a diameter  
918 of approximately 200 nm. Finally, the filtration tests were performed using different virus  
919 types, such as murine hepatitis virus MHV-A59, a coronavirus surrogate for SARS-CoV-  
920 2. The findings evidenced a rapid inactivation of 98.9% after 15 min irradiation of  
921 simulated reading light.

## 922 **8. Upscaling potential of nanofiber air filters and current companies for nanofiber** 923 **production**

924 Over the course of this review, we have reviewed one of the many applications of  
925 electrospun nanofibers. To date, most of the research in electrospun membranes has been  
926 done at a lab scale. Thanks to the outperforming separation of nanofibers for air filtration,  
927 there is a current need of producing nanofibers on a large scale. However, the key  
928 challenges in developing large-scale production of nanofiber rely on establishing accuracy  
929 and reproductivity of the fabrication processing while satisfying the large volume  
930 processing. Additionally, such processes must also meet important safety and eco-friendly  
931 aspects of electrospinning. In this regard, centrifugal electrospinning [171], for instance,  
932 owns the characteristics for large scale production at industrial level, along with high speed  
933 and low cost [172]. It has been reported that such technique is able to tailor fibres with  
934 diameters down to 100 nm [173]. Towards reaching scaling processes, higher flexibility



935 towards the materials and processing with multifunctional properties can be potentially  
936 reached via co-axial and multi-axial technologies. Additionally, it has been documented  
937 that ambient conditions drastically influence on the properties of electrified jets and  
938 consequently on the resultant electrospun materials; to some extent, even small  
939 environmental changes have demonstrated to have an effect on fiber features. Therefore,  
940 several suppliers of commercial electrospinning devices have developed climate-controlled  
941 electrospinning systems, assuring temperature and humidity control. For instance, IME  
942 Technologies, recently named as Vivolta, <https://www.vivolta.com/>) fabricates laboratory-  
943 scale systems for medical purposes, presenting electrospinning chambers and control of air  
944 conditions, water filtration and automatization system.

945 In terms of industrial-scale equipment market of electrospinning devices, several  
946 companies and suppliers have emerged satisfying this field, such as Elmarco  
947 ([www.elmarco.com](http://www.elmarco.com)), NaBond ([www.electro-spinning.com](http://www.electro-spinning.com)), Holmarc Opto-Mechatronics  
948 ([www.holmarc.com](http://www.holmarc.com)), E-SpinNanotech ([www.espinnanotech.com](http://www.espinnanotech.com)), Linari Engineering  
949 ([www.linaribiomedical.com](http://www.linaribiomedical.com)), Kato Tech ([www.keskato.co.jp](http://www.keskato.co.jp)), Mecc Co.  
950 ([www.mecc.co.jp](http://www.mecc.co.jp)), Toptec ([www.toptec.co.kr](http://www.toptec.co.kr)), Electrospinz ([www.electrospinz.co.nz](http://www.electrospinz.co.nz)),  
951 Electrospunra ([www.electrospunra.com](http://www.electrospunra.com)), Vivolta Technologies  
952 (<https://www.vivolta.com/>), Yflow ([www.yflow.com](http://www.yflow.com)), and Ino-venso  
953 ([www.inovenso.com](http://www.inovenso.com)). Importantly, electrospinning at industrial scale majorly implied a  
954 rotating drum or on substrates using winding-unwinding systems, while laboratory set-ups  
955 are based on needle-type electrospinning.

956 According to the experts in the field, to reach a fully implementation of electrospinning  
957 systems at industrial scale, several aspects should be satisfied [173], as follows:

- 958       • As in most of emerging technologies, a substantial reduction in cost is highly  
959       needed. This can be achieved as soon as potential stakeholder may be interested at  
960       implemented electrospun nanofibers in commercial air filters.
- 961       • Multi-functional set-up should be fabricated, which is a current challenge since it  
962       is difficult to offer “all-in-one” set-ups to reach different requirements from the  
963       customer.
- 964       • Compactness in the devices is required since they need to be installed in limited  
965       space.
- 966       • Productivity demand is also a current matter for large-scale electrospinning since the  
967       nanofiber volume may be required by in many sectors.

968       When dealing with the industrialization and availability, various companies have released  
969       electrospun products, such as Donaldson ([www.donaldson.com](http://www.donaldson.com)), DuPont  
970       ([www.dupont.com](http://www.dupont.com)), Ahlstrom Corporation ([www.ahlstrom.com](http://www.ahlstrom.com)), Espin Technologies  
971       ([www.espintechnologies.com](http://www.espintechnologies.com)), Esfil Tehno AS ([www.esfiltehno.ee](http://www.esfiltehno.ee)), Finetex Technology  
972       ([www.finetextech.com](http://www.finetextech.com)), Hemcon Medical Technologies, Inc ([www.hemcon.com](http://www.hemcon.com)),  
973       Hollingsworth ([www.hollingsworthvise.com](http://www.hollingsworthvise.com)), to mention just a few, in which the  
974       nanofiber air-filter market has grown drastically [173].

975       To some extent, electrospinning devices should be also developed according to the needs  
976       in terms of desired nanofiber properties, feedstock and items and, more importantly,  
977       materials used for the fabrication of the nanofibers. In this latter aspect, new functional  
978       materials are currently being developed to overcome the limitations of existing materials.  
979       In this sense, bio-functional nanomaterials based on biomolecules, copolymers, and  
980       polymer blends have been synthesized, such as fibroin in water-soluble polymers,



981 PCL/gelatin, poly(L-lactide acid)/gelatin blends, protein-based and chitosan-  
982 poly(ethylene oxide)(PEO) blend [174–177], among others. Importantly, such materials  
983 produced from natural sources have been proposed to face the eco-friendly weaknesses of  
984 chemically synthesized polymers. Especially, natural protein nanofibers have shown high  
985 efficiency filtration towards particulates, pollutants and toxic gases from polluted air [177].  
986 However, typical polymers produced via chemical synthesized are still the preferred ones  
987 for fabrication of electrospun mats for air filtration, as evidenced by Inovenso Ltd. Co.  
988 [178]. It is worth mentioning that air filters presenting electrospun nanofibers are usually  
989 applied in several applications, such as pulse-clean cartridges for Dust Collection.,  
990 nanofiber filter media in Cabin Air Filtration of Mining Vehicles, and specialized face  
991 mask fabrication, among many others [179]. All these applications will eminently foster  
992 the establishment of electrospinning technology at industrial scale in near future.

993

#### 994 **9. Grand challenges for electrospun membranes for air filtration**

995 The bottleneck of electrospun nanofibers is the technology transfer from the lab scale to  
996 the mass production. In fact, the limited production rate of traditional electrospinning  
997 equipped with a single needle has hindered the practical implementation of nanofiber for  
998 air filtering at large scale (typically the flow rate of the polymeric solution is in the range  
999 of  $1\text{--}5\text{ mL}\cdot\text{h}^{-1}$  with a production rate of the nanofibers lower than  $1\text{ g}\cdot\text{h}^{-1}$ ) [180].

1000 The employment of an auxiliary electrode could enable the ejection of up to 12 nanofibers  
1001 from a single needle [181], but safety issues have limited the feasibility of this route to  
1002 intensify the electrospinning process. As a matter of fact, the productivity of the  
1003 electrospinning process increases as a function of Taylor cones. This has stimulated the

1004 development of multi-spinnerets where numerous needles are arranged in linear or two-  
1005 dimensional arrays (es. circular, elliptic, hexagonal or triangular)[182] expanding the jet  
1006 number up to 38,880 [183]. Moreover, an interesting advantages of multi-needle  
1007 configurations is the opportunity to produce multi-component mat made of polymers not  
1008 soluble in the same solvent [184].


1009 Unfortunately, heterogeneous mat are often obtained with multi-needle spinnerets because  
1010 of: i) the high density of needles which compromises the uniformity of the external field  
1011 and ii) the Coulombic repulsions among the nascent fibers [185]. Several studies have been  
1012 focused on the optimization of the multi-needle electrospinning focusing on the design  
1013 (geometry, needle-to-needle distance, number of needles) of the spinnerets to: i) uniform  
1014 the electric field, ii) minimize the interactions between the nascent fibers and iii) avoid  
1015 their fusion during the flight from the needle to the support [186,187]. These critical issues  
1016 have been also minimized by using polypropylene (PP) as dielectric material on the tip of  
1017 the nozzles [188]. Another emerging and promising practice to mitigate the reciprocal  
1018 interferences among the jets is the employment of a sheath gas in laminar regime (**Figure**  
1019 **13.a**) which secured an improvement of the productivity of ca. 30-50 folds with respect to  
1020 single needle configuration [184].

1021 Just to give an example about the scalability of the electrospinning of nanofiber with multi-  
1022 needle spinneret, Inovenso Inc. has commercialized an industrial electrospinning system  
1023 equipped with 110 needles able to produce up to 5 kg of nanofibers per day [189].

1024 Unfortunately, the improvement of the number of needles drastically increases the risk of  
1025 clogging of the nozzles. A possible solution is to provide the polymeric solution to the  
1026 outside surface of the needle. According to this strategy , thermoplastic polyurethane

1027 (TPU) has been electrospun with production rate of ca.  $50 \text{ g}\cdot\text{h}^{-1}$  obtaining a network of  
 1028 nanofibers with a diameter of 145 nm and a  $\text{PM}_{2.5}$  filtration efficiency of 99.9% [182].  
 1029 Recently, needless spinnerets able to eject nanofibers directly from the surface of the  
 1030 polymer solutions have been purposed (**Figure 13.b**). The mechanism of working of  
 1031 needless electrospinning-which is not influenced by the capillary effect- is based on the  
 1032 self-organization of the liquid solution at mesoscopic scale induced by electromagnetic  
 1033 field able to induce the expulsion of the nanofibers [190]. This strategy has the potential to  
 1034 ensure the industrialization of nanofibrous membranes for air filtering as demonstrated by  
 1035 technology developed by Elmarco Inc. using a wire electrode to eject multiple nanofibers  
 1036 which guaranteed an annual productivity of  $20,000,000 \text{ m}^2$  ( $0,03 \text{ g}\cdot\text{m}^{-2}$  of fibers of 150 nm  
 1037 of PA6)[191].

1038

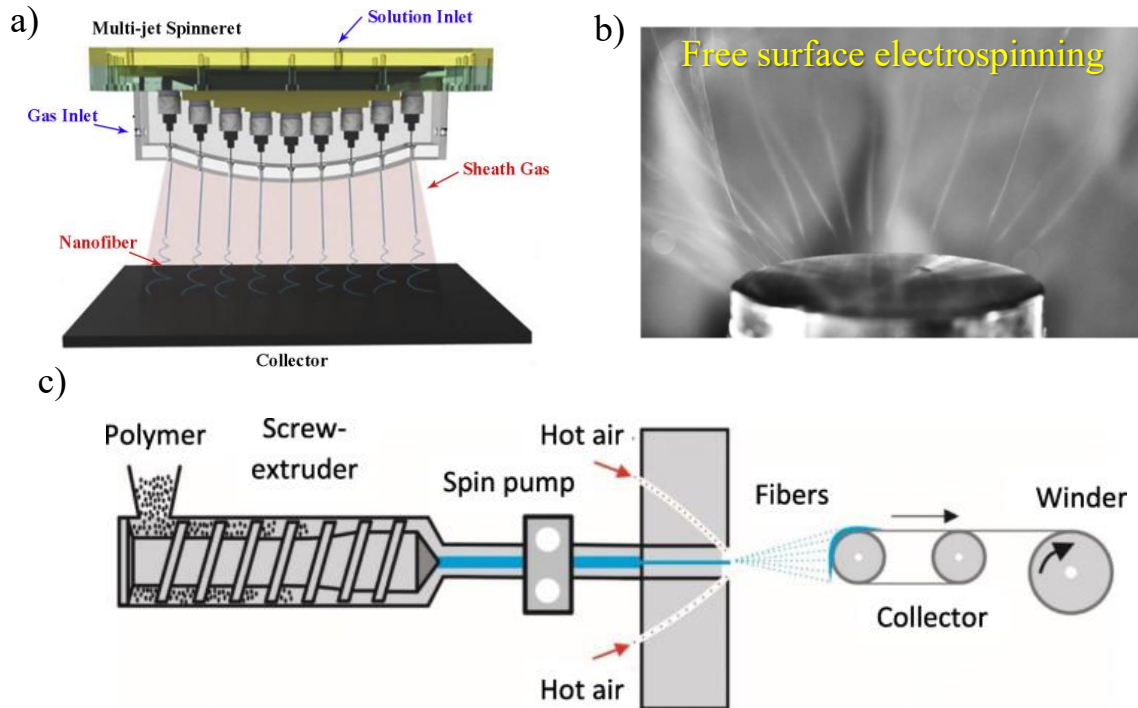

1039

1040 **Figure 13.** a) Multi-jet electrospinning with sheath gas for the intensification of the  
 1041 nanofiber production. Reprinted from [192]. This work is licensed under a Creative

1042 Commons Attribution 4.0 International License. b) PAN nanofibers ejected from a self-  
1043 made free surface electrospinning with a spherical section. Reprint from [193] with the  
1044 permission of Elsevier. c) Scheme of a melt-electrospinning system. Reprinted from [194].  
1045 This work is licensed under a Creative Commons Attribution 4.0 International License.  
1046

1047 Another significant Achilles heel in the industrialization of nanofibers is the environmental  
1048 impact. Tendentially, nanofibers are ejected from diluted polymeric solutions with a  
1049 viscosity below than 20 poise (solvent content >70wt %) [138,195] and they are obtained  
1050 upon the evaporation of the solvent during the flight from the needle to the support. Thus,  
1051 mass production of electrospun nanofibers implies the use of enormous volumes of solvent  
1052 raising serious concerns about the environmental footprint of nanofibers. Thus, it is  
1053 necessary to introduce circular economy strategy to collect and recycle the solvent during  
1054 the production of membranes via electrospinning. Noteworthy, common solvents used for  
1055 electrospinning process are restricted by the Chemical Control Regulation in the European  
1056 Union (REACH), such as halogenated (e.g. chloroform, trifluoroethanol) and toxic  
1057 solvents (e.g. dimethylformamide) [196]. Beyond the employment of green solvent for the  
1058 environmental-friendly production of nanofibers (see Section 3.4) , melt electrospinning  
1059 (**Figure 13c**)- the process of spinning polymers from their melts- guarantees the solvent-  
1060 free preparation of nanofibrous air filters [197]. Interestingly, melt electrospinning secure  
1061 the preparation of i) nanofibers without residual of solvents [198] and ii) air filters of non-  
1062 soluble polymers, such as polypropylene (PP) and polyethylene (PE) [199]. For instance,  
1063 PP nanofibers with a diameter ranging from 7  $\mu\text{m}$  to 14  $\mu\text{m}$  were deposited on PP  
1064 nonwoven support via melt-electrospinning. After post-treatment (i.e. hot-pressing), a mat  
1065 of 0.42 mm of thickness showed a filtration efficiency above of 95% filtration for oil  
1066 particles (size of 2.0  $\mu\text{m}$ ) and an air permeability of 54.69  $\text{mm}\cdot\text{s}^{-1}$ [200].

1067

1068 **7-10. Conclusions and future perspectives**

1069 ~~The growth of the human population, the increase of urbanization, and industrialization~~  
1070 ~~have brought the decrement of air quality over the last few decades. Air pollution starts to~~  
1071 ~~be a major issue that can result in serious risks for human health. In addition to this,~~  
1072 ~~microorganisms and natural contaminants suspended in the air can potentially provoke a~~  
1073 ~~great damage to human life. Looking for~~ Being considered efficient and reliable  
1074 technologies, electrospun membranes are gaining a lot of interest in a plethora of  
1075 applications in air filtration sectors ~~represent a viable tool and have been pointed out~~ for  
1076 their ~~potential at enhancing~~ capacity to effectively improve the air quality ~~by~~ through a  
1077 relatively simple filtration mechanism. Electrospun membranes ~~on their own~~ display  
1078 ~~possess, in fact,~~ a number of advantages in terms of small **nanofibers** diameters, high active  
1079 surface area, tuneable morphology, and interconnected pore structure. This review has  
1080 provided an overview and discussed the potential trapping mechanisms which can occur in  
1081 electrospun membrane filtration, as well as their effect on membrane separation  
1082 performance. ~~We also reviewed~~ A number of applications reporting the successful  
1083 ~~application use~~ of electrospun membranes for air filtration, and their comparison with  
1084 commercial **filters**, was also reported ~~for such a purpose~~. The **removal** performance of  
1085 electrospun membranes in removing different types of contaminants has been evidenced  
1086 as high as 100% with a low-pressure drop up to 68 Pa.

1087 Although many developments and advances have been done in this field, many challenges  
1088 still remain open and are waiting for potential solutions. Unfortunately, some of the  
1089 bottlenecks of electrospun membranes comprise their poor mechanical stability which

1090 frequently demands their deposition on a suitable support, along with their compromised  
1091 application under harsh conditions. An interesting finding in this review reveals that the  
1092 reduction of fibers diameter certainly improves the filtration efficiency, but compromising  
1093 unfavourably the mechanical properties.

1094 For wide exploitation of electrospun fiber, there is a need to ~~turn develop~~ the spinning  
1095 technique into ~~an easy and affordable technology as easy as possible~~ with an applicability  
1096 on a large scale [7]. Within the preparation processes, there is also an interest to replace  
1097 traditional toxic solvents, that are typically used for the fabrication of electrospun  
1098 membranes, ~~herein, the latent~~ with more benign alternatives, ~~are~~ the so-called green  
1099 solvents [111,201]. This aspect becomes relevant when dealing with environmental  
1100 protection and human safety. Some research groups ~~have already started~~ to explore new  
1101 solvents to make the electrospinning process more sustainable and eco-friendly [79,202]  
1102 outlining the importance of this aspect in developing the next generation of membranes  
1103 aimed for environmental remediation.

1104 ~~As a recommendation for the new researchers in the field: great important~~ advances in  
1105 nanofibers synthesis, either polymeric or composite, have been ~~done~~ over the last years;  
1106 however, ~~they were limited to model tests on small lab scales. this review timely finds the~~  
1107 ~~need to initiate the~~ The testing of electrospun membranes ~~for~~ with real air samples, as  
1108 evidenced by Li et al. [160], ~~is, therefore, crucial. Most researches tend to use Air~~ model  
1109 samples for performance evaluation ~~can reveal, in fact,~~ a good approximation but ~~a-~~more  
1110 realistic outcomes, ~~on real case studies, will be determine the feasibility of new concepts~~  
1111 ~~of nanofibers, fundamental to prove the efficiency of nanofiber-based membranes in air~~  
1112 ~~filtration processes.~~

1113

1114 **Acknowledgments**

1115 Financial support from Polish National Agency for Academic Exchange (NAWA) under  
1116 Ulam Programme (Agreement No. PPN/ULM/2020/1/00005/U/00001) is gratefully  
1117 acknowledged. R. Castro-Muñoz also acknowledges the School of Engineering and  
1118 Science and the FEMSA-Biotechnology Center at Tecnológico de Monterrey for their  
1119 support through the Bioprocess (0020209I13) Focus Group.

1120

1121 **References**

- 1122 [1] WHO, World Health Organization Regional Office for Europe SELECTED  
1123 POLLUTANTS, 2010. [www.euro.who.int](http://www.euro.who.int) (accessed December 19, 2021).
- 1124 [2] M. Zhu, J. Han, F. Wang, W. Shao, R. Xiong, Q. Zhang, H. Pan, Y. Yang, S.K.  
1125 Samal, F. Zhang, C. Huang, Electrospun Nanofibers Membranes for Effective Air  
1126 Filtration, *Macromol. Mater. Eng.* 302 (2017) 1–27.  
1127 doi:10.1002/mame.201600353.
- 1128 [3] R.D. Brook, S. Rajagopalan, C.A. Pope, J.R. Brook, A. Bhatnagar, A. V. Diez-  
1129 Roux, F. Holguin, Y. Hong, R. V. Luepker, M.A. Mittleman, A. Peters, D.  
1130 Siscovick, S.C. Smith, L. Whitsel, J.D. Kaufman, Particulate Matter Air Pollution  
1131 and Cardiovascular Disease, *Circulation*. 121 (2010) 2331–2378.  
1132 doi:10.1161/CIR.0b013e3181d8e1.
- 1133 [4] M.C. Lazzaro, S. Romanò, S. Santoro, C. Camuto, A. Carbone, R. Casamassima,  
1134 S. Abate, F. De-Giorgio, A potential cause of asbestos-related granulomatosis due  
1135 to adulterant contamination in a drug abuser, *Virchows Arch.* 478 (2021) 361–366.  
1136 doi:10.1007/s00428-020-02863-z.
- 1137 [5] T.D. Nelin, A.M. Joseph, M.W. Gorr, L.E. Wold, Direct and indirect effects of  
1138 particulate matter on the cardiovascular system, *Toxicol. Lett.* 208 (2012) 293–  
1139 299. doi:10.1016/j.toxlet.2011.11.008.
- 1140 [6] L.E. Wold, B.Z. Simkhovich, M.T. Kleinman, M.A. Nordlie, J.S. Dow, C. Sioutas,

- 1141 R.A. Kloner, In Vivo and In Vitro Models to Test the Hypothesis of Particle-  
 1142 Induced Effects on Cardiac Function and Arrhythmias, *Cardiovasc. Toxicol.* 6  
 1143 (2006) 69–78. doi:10.1385/CT:6:1:69.
- 1144 [7] Y. Li, X. Yin, J. Yu, B. Ding, Electrospun nanofibers for high-performance air  
 1145 filtration, *Compos. Commun.* 15 (2019) 6–19. doi:10.1016/j.coco.2019.06.003.
- 1146 [8] D. Cho, A. Naydich, M.W. Frey, Y.L. Joo, Further improvement of air filtration  
 1147 efficiency of cellulose filters coated with nanofibers via inclusion of  
 1148 electrostatically active nanoparticles, *Polymer (Guildf).* 54 (2013) 2364–2372.  
 1149 doi:10.1016/j.polymer.2013.02.034.
- 1150 [9] N. Vinh, H.-M. Kim, Electrospinning Fabrication and Performance Evaluation of  
 1151 Polyacrylonitrile Nanofiber for Air Filter Applications, *Appl. Sci.* 6 (2016) 235.  
 1152 doi:10.3390/app6090235.
- 1153 [10] M.E. Findley, Vaporization through porous membranes, *Ind. Eng. Chem. Process*  
 1154 *Des. Dev.* 6 (1967) 226–230. doi:10.1021/i260022a013.
- 1155 [11] N. Wang, Z. Zhu, J. Sheng, S.S. Al-Deyab, J. Yu, B. Ding, Superamphiphobic  
 1156 nanofibrous membranes for effective filtration of fine particles, *J. Colloid Interface*  
 1157 *Sci.* 428 (2014) 41–48. doi:10.1016/j.jcis.2014.04.026.
- 1158 [12] M. Zhu, R. Xiong, C. Huang, Bio-based and photocrosslinked electrospun  
 1159 antibacterial nanofibrous membranes for air filtration, *Carbohydr. Polym.* 205  
 1160 (2019) 55–62. doi:10.1016/j.carbpol.2018.09.075.
- 1161 [13] Y. Ding, H. Hou, Y. Zhao, Z. Zhu, H. Fong, Electrospun polyimide nanofibers and  
 1162 their applications, *Prog. Polym. Sci.* 61 (2016) 67–103.  
 1163 doi:10.1016/j.progpolymsci.2016.06.006.
- 1164 [14] R. Al-Attabi, L.F. Dumée, J.A. Schütz, Y. Morsi, Pore engineering towards highly  
 1165 efficient electrospun nanofibrous membranes for aerosol particle removal, *Sci.*  
 1166 *Total Environ.* 625 (2018) 706–715. doi:10.1016/J.SCITOTENV.2017.12.342.
- 1167 [15] J. Matulevicius, L. Kliucininkas, T. Prasauskas, D. Buivydiene, D. Martuzevicius,  
 1168 The comparative study of aerosol filtration by electrospun polyamide, polyvinyl  
 1169 acetate, polyacrylonitrile and cellulose acetate nanofiber media, *J. Aerosol Sci.* 92  
 1170 (2016) 27–37. doi:10.1016/j.jaerosci.2015.10.006.
- 1171 [16] Y.; Zhou, Y.; Liu, M.; Zhang, Z.; Feng, D.-G.; Yu, K. Wang, J.L. Arias, U. Scherf,



- 1172 M.M. El-Hammadi, Y. Zhou, Y. Liu, M. Zhang, Z. Feng, D.-G. Yu, K. Wang,  
1173 Electrospun Nanofiber Membranes for Air Filtration: A Review, *Nanomater.* 2022,  
1174 Vol. 12, Page 1077. 12 (2022) 1077. doi:10.3390/NANO12071077.
- 1175 [17] Y. Deng, T. Lu, J. Cui, S. Keshari Samal, R. Xiong, C. Huang, Bio-based  
1176 electrospun nanofiber as building blocks for a novel eco-friendly air filtration  
1177 membrane: A review, *Sep. Purif. Technol.* 277 (2021) 119623.  
1178 doi:10.1016/J.SEPPUR.2021.119623.
- 1179 [18] T. Lu, J. Cui, Q. Qu, Y. Wang, J. Zhang, R. Xiong, W. Ma, C. Huang,  
1180 Multistructured Electrospun Nanofibers for Air Filtration: A Review, *ACS Appl.*  
1181 *Mater. Interfaces.* 13 (2021) 23293–23313.  
1182 doi:10.1021/ACSAMI.1C06520/ASSET/IMAGES/LARGE/AM1C06520\_0018.JP  
1183 EG.
- 1184 [19] X. Ji, J. Huang, L. Teng, S. Li, X. Li, W. Cai, Z. Chen, Y. Lai, Advances in  
1185 particulate matter filtration: Materials, performance, and application, *Green*  
1186 *Energy Environ.* (2022). doi:10.1016/J.GEE.2022.03.012.
- 1187 [20] R. Schneider, M.H.M. Facure, P.A.M. Chagas, R.S. Andre, D.M. dos Santos, D.S.  
1188 Correa, Tailoring the Surface Properties of Micro/Nanofibers Using 0D, 1D, 2D,  
1189 and 3D Nanostructures: A Review on Post-Modification Methods, *Adv. Mater.*  
1190 *Interfaces.* 8 (2021) 2100430. doi:10.1002/ADMI.202100430.
- 1191 [21] L.M. Valencia-Osorio, M.L. Álvarez-Láinez, Global View and Trends in  
1192 Electrospun Nanofiber Membranes for Particulate Matter Filtration: A Review,  
1193 *Macromol. Mater. Eng.* 306 (2021). doi:10.1002/MAME.202100278.
- 1194 [22] G. Liu, M. Xiao, X. Zhang, C. Gal, X. Chen, L. Liu, S. Pan, J. Wu, L. Tang, D.  
1195 Clements-Croome, A review of air filtration technologies for sustainable and  
1196 healthy building ventilation, *Sustain. Cities Soc.* 32 (2017) 375–396.  
1197 doi:https://doi.org/10.1016/j.scs.2017.04.011.
- 1198 [23] X.-H. Qin, S.-Y. Wang, Filtration properties of electrospinning nanofibers, *J.*  
1199 *Appl. Polym. Sci.* 102 (2006) 1285–1290. doi:doi:10.1002/app.24361.
- 1200 [24] C. YANG, Aerosol Filtration Application Using Fibrous Media—An Industrial  
1201 Perspective, *Chinese J. Chem. Eng.* 20 (2012) 1–9.  
1202 doi:https://doi.org/10.1016/S1004-9541(12)60356-5.

- 1203 [25] B.G. Miller, 8 - Particulate Formation and Control Technologies, in: B.G. Miller  
1204 (Ed.), *Clean Coal Eng. Technol. (Second Ed., Second Edi*, Butterworth-  
1205 Heinemann, 2017: pp. 419–465. doi:[https://doi.org/10.1016/B978-0-12-811365-](https://doi.org/10.1016/B978-0-12-811365-3.00008-9)  
1206 [3.00008-9](https://doi.org/10.1016/B978-0-12-811365-3.00008-9).
- 1207 [26] D. Zhang, 6 - Ash fouling, deposition and slagging in ultra-supercritical coal  
1208 power plants, in: D. Zhang (Ed.), *Ultra-Supercritical Coal Power Plants*,  
1209 Woodhead Publishing, 2013: pp. 133–183.  
1210 doi:<https://doi.org/10.1533/9780857097514.2.133>.
- 1211 [27] S. Marre, J. Palmeri, Theoretical Study of Aerosol Filtration by Nucleopore  
1212 Filters: The Intermediate Crossover Regime of Brownian Diffusion and Direct  
1213 Interception, *J. Colloid Interface Sci.* 237 (2001) 230–238.  
1214 doi:<https://doi.org/10.1006/jcis.2001.7458>.
- 1215 [28] C.-S. Wang, Electrostatic forces in fibrous filters—a review, *Powder Technol.* 118  
1216 (2001) 166–170. doi:[https://doi.org/10.1016/S0032-5910\(01\)00307-2](https://doi.org/10.1016/S0032-5910(01)00307-2).
- 1217 [29] I.P. Beckman, G. Berry, H. Cho, G. Riveros, Digital Twin Geometry for Fibrous  
1218 Air Filtration Media, *Fibers.* 9 (2021). doi:10.3390/fib9120084.
- 1219 [30] S.A. Hosseini, H.V. Tafreshi, 3-D simulation of particle filtration in electrospun  
1220 nanofibrous filters, *Powder Technol.* 201 (2010) 153–160.  
1221 doi:<https://doi.org/10.1016/j.powtec.2010.03.020>.
- 1222 [31] C. Liu, P.-C. Hsu, H.-W. Lee, M. Ye, G. Zheng, N. Liu, W. Li, Y. Cui,  
1223 Transparent air filter for high-efficiency PM2.5 capture, *Nat. Commun.* 6 (2015)  
1224 6205. doi:10.1038/ncomms7205.
- 1225 [32] Y. Bian, S. Wang, L. Zhang, C. Chen, Influence of fiber diameter, filter thickness,  
1226 and packing density on PM2.5 removal efficiency of electrospun nanofiber air  
1227 filters for indoor applications, *Build. Environ.* 170 (2020) 106628.  
1228 doi:<https://doi.org/10.1016/j.buildenv.2019.106628>.
- 1229 [33] Y. Bian, L. Zhang, C. Chen, Experimental and modeling study of pressure drop  
1230 across electrospun nanofiber air filters, *Build. Environ.* 142 (2018) 244–251.  
1231 doi:<https://doi.org/10.1016/j.buildenv.2018.06.021>.
- 1232 [34] T. Xia, Y. Bian, L. Zhang, C. Chen, Relationship between pressure drop and face  
1233 velocity for electrospun nanofiber filters, *Energy Build.* 158 (2018) 987–999.

- 1234 doi:10.1016/j.enbuild.2017.10.073.
- 1235 [35] V. V. Kadam, L. Wang, R. Padhye, Electrospun nanofibre materials to filter air  
1236 pollutants – A review, *J. Ind. Text.* 47 (2018) 2253–2280.  
1237 doi:10.1177/1528083716676812.
- 1238 [36] Z. Quan, Y. Zu, Y. Wang, M. Zhou, X. Qin, J. Yu, Slip effect based bimodal  
1239 nanofibrous membrane for high-efficiency and low-resistance air purification, *Sep.*  
1240 *Purif. Technol.* 275 (2021) 119258.  
1241 doi:https://doi.org/10.1016/j.seppur.2021.119258.
- 1242 [37] B. V. Ramarao, C. Tien, S. Mohan, Calculation of single fiber efficiencies for  
1243 interception and impaction with superposed brownian motion, *J. Aerosol Sci.* 25  
1244 (1994) 295–313. doi:10.1016/0021-8502(94)90081-7.
- 1245 [38] S.K. Friedlander, *Theory of Aerosol Filtration*, *Ind. Eng. Chem.* 50 (1958) 1161–  
1246 1164. doi:10.1021/ie50584a036.
- 1247 [39] C. Yang, Aerosol filtration application using fibrous media - An industrial  
1248 perspective, *Chinese J. Chem. Eng.* 20 (2012) 1–9. doi:10.1016/S1004-  
1249 9541(12)60356-5.
- 1250 [40] J. Wei, C. Chun-Shun, C. Cheong-Ki, Z. Chao, The aerosol penetration through an  
1251 electret fibrous filter, *Chinese Phys.* 15 (2006) 1864–1870. doi:10.1088/1009-  
1252 1963/15/8/039.
- 1253 [41] R. Sahay, P.S. Kumar, R. Sridhar, J. Sundaramurthy, J. Venugopal, S.G.  
1254 Mhaisalkar, S. Ramakrishna, Electrospun composite nanofibers and their  
1255 multifaceted applications, *J. Mater. Chem.* 22 (2012) 12953–12971.  
1256 doi:10.1039/c2jm30966a.
- 1257 [42] B.Y. Yeom, E. Shim, B. Pourdeyhimi, Boehmite nanoparticles incorporated  
1258 electrospun nylon-6 nanofiber web for new electret filter media, *Macromol. Res.*  
1259 18 (2010) 884–890. doi:10.1007/s13233-010-0910-5.
- 1260 [43] R. Castro-Muñoz, The role of new inorganic materials in composite membranes  
1261 for water disinfection, *Membranes (Basel)*. 10 (2020) 101.  
1262 doi:10.3390/membranes10050101.
- 1263 [44] P.K. Stoimenov, R.L. Klinger, G.L. Marchin, K.J. Klabunde, Metal oxide  
1264 nanoparticles as bactericidal agents, *Langmuir*. 18 (2002) 6679–6686.

- 1265 doi:10.1021/la0202374.
- 1266 [45] A.K. Selvam, G. Nallathambi, Polyacrylonitrile / Silver Nanoparticle Electrospun  
1267 Nanocomposite Matrix for Bacterial Filtration, 16 (2015) 1327–1335.  
1268 doi:10.1007/s12221-015-1327-8.
- 1269 [46] L. Zhang, J. Luo, T.J. Menkhous, H. Varadaraju, Y. Sun, H. Fong, Antimicrobial  
1270 nano-fibrous membranes developed from electrospun polyacrylonitrile nanofibers,  
1271 J. Memb. Sci. 369 (2011) 499–505. doi:10.1016/j.memsci.2010.12.032.
- 1272 [47] J. Van Turnhout, J.W.C. Adamse, W.J. Hoeneveld, Electret filters for high-  
1273 efficiency air cleaning, J. Electrostat. 8 (1980) 369–379. doi:10.1016/0304-  
1274 3886(80)90057-1.
- 1275 [48] H.C. Duong, F.I. Hai, A. Al-Jubainawi, Z. Ma, T. He, L.D. Nghiem, Liquid  
1276 desiccant lithium chloride regeneration by membrane distillation for air  
1277 conditioning, Sep. Purif. Technol. 177 (2017) 121–128.  
1278 doi:10.1016/J.SEPPUR.2016.12.031.
- 1279 [49] L. Zhao, L. Jiang, H. Li, C. Hu, J. Sun, L. Li, F. Meng, Z. Dong, C. Zhou,  
1280 Synthesis and characterization of silver-incorporated calcium phosphate  
1281 antibacterial nanocomposites for mask filtration material, Compos. Part B Eng.  
1282 153 (2018) 387–392. doi:10.1016/j.compositesb.2018.09.004.
- 1283 [50] Lee, S.J. Owonubi, S.C. Agwuncha, V.O. Fasiku, E. Mukwevho, B.A. Aderibigbe,  
1284 E.R. Sadiku, D. Bezuidenhout, Biomedical applications of polyolefins, Polyolefin  
1285 Fibres Struct. Prop. Ind. Appl. Second Ed. 221 (2001) 517–538.  
1286 doi:10.1016/B978-0-08-101132-4.00017-5.
- 1287 [51] R. Al-attabi, Y. Morsi, W. Kujawski, L. Kong, J.A. Schütz, Wrinkled silica doped  
1288 electrospun nano- fiber membranes with engineered roughness for advanced  
1289 aerosol air filtration, Sep. Purif. Technol. 215 (2019) 500–507.  
1290 doi:10.1016/j.seppur.2019.01.049.
- 1291 [52] Q. Sun, W.W.F. Leung, Charged PVDF multi-layer filters with enhanced filtration  
1292 performance for filtering nano-aerosols, Sep. Purif. Technol. 212 (2019) 854–876.  
1293 doi:10.1016/j.seppur.2018.11.063.
- 1294 [53] R.J. Han, O.R. Moss, B.A. Wong, Airborne fiber separation by electrophoresis and  
1295 dielectrophoresis: Theory and design considerations, Aerosol Sci. Technol. 21

- 1296 (1994) 241–258. doi:10.1080/02786829408959713.
- 1297 [54] F. Yang, Y. Li, X. Yu, G. Wu, X. Yin, J. Yu, B. Ding, Hydrophobic  
1298 polyvinylidene fluoride fibrous membranes with simultaneously water/windproof  
1299 and breathable performance, *RSC Adv.* 6 (2016) 87820–87827.  
1300 doi:10.1039/c6ra17565a.
- 1301 [55] A. Vanangamudi, S. Hamzah, G. Singh, Synthesis of hybrid hydrophobic  
1302 composite air filtration membranes for antibacterial activity and chemical  
1303 detoxification with high particulate filtration efficiency (PFE), *Chem. Eng. J.* 260  
1304 (2015) 801–808. doi:10.1016/j.cej.2014.08.062.
- 1305 [56] S.X. Wang, C.C. Yap, J. He, C. Chen, S.Y. Wong, X. Li, Electrospinning: A facile  
1306 technique for fabricating functional nanofibers for environmental applications,  
1307 *Nanotechnol. Rev.* 5 (2016) 51–73. doi:10.1515/ntrev-2015-0065.
- 1308 [57] W. Gu, G. Wang, M. Zhou, T. Zhang, G. Ji, Polyimide-Based Foams: Fabrication  
1309 and Multifunctional Applications, *ACS Appl. Mater. Interfaces.* 12 (2020) 48246–  
1310 48258.  
1311 doi:10.1021/ACSAMI.0C15771/ASSET/IMAGES/ACSAMI.0C15771.SOCIAL.J  
1312 PEG\_V03.
- 1313 [58] J. Xu, C. Liu, P.-C. Hsu, K. Liu, R. Zhang, Y. Liu, Y. Cui, Roll-to-Roll Transfer of  
1314 Electrospun Nanofiber Film for High-Efficiency Transparent Air Filter, *Nano Lett.*  
1315 16 (2016) 1270–1275. doi:10.1021/acs.nanolett.5b04596.
- 1316 [59] H. Wan, N. Wang, J. Yang, Y. Si, K. Chen, B. Ding, G. Sun, M. El-Newehy, S.S.  
1317 Al-Deyab, J. Yu, Hierarchically structured polysulfone/titania fibrous membranes  
1318 with enhanced air filtration performance, *J. Colloid Interface Sci.* 417 (2014) 18–  
1319 26. doi:10.1016/j.jcis.2013.11.009.
- 1320 [60] B. Liu, S. Zhang, X. Wang, J. Yu, B. Ding, Efficient and reusable polyamide-56  
1321 nanofiber/nets membrane with bimodal structures for air filtration, *J. Colloid  
1322 Interface Sci.* 457 (2015) 203–211. doi:10.1016/j.jcis.2015.07.019.
- 1323 [61] Y. Yang, S. Zhang, X. Zhao, J. Yu, B. Ding, Sandwich structured polyamide-  
1324 6/polyacrylonitrile nanonets/bead-on-string composite membrane for effective air  
1325 filtration, *Sep. Purif. Technol.* 152 (2015) 14–22.  
1326 doi:10.1016/j.seppur.2015.08.005.

- 1327 [62] N. Wang, Y. Si, N. Wang, G. Sun, M. El-Newehy, S.S. Al-Deyab, B. Ding,  
1328 Multilevel structured polyacrylonitrile/silica nanofibrous membranes for high-  
1329 performance air filtration, *Sep. Purif. Technol.* 126 (2014) 44–51.  
1330 doi:10.1016/j.seppur.2014.02.017.
- 1331 [63] A.C. Canalli Bortolassi, V.G. Guerra, M.L. Aguiar, L. Soussan, D. Cornu, P.  
1332 Miele, M. Bechelany, Composites Based on Nanoparticle and Pan Electrospun  
1333 Nanofiber Membranes for Air Filtration and Bacterial Removal, *Nanomaterials*. 9  
1334 (2019) 1740. doi:10.3390/nano9121740.
- 1335 [64] X. Ding, Y. Li, Y. Si, X. Yin, J. Yu, B. Ding, Electrospun polyvinylidene  
1336 fluoride/SiO<sub>2</sub> nanofibrous membranes with enhanced electret property for efficient  
1337 air filtration, *Compos. Commun.* 13 (2019) 57–62.  
1338 doi:10.1016/j.coco.2019.02.008.
- 1339 [65] T. Blachowicz, A. Ehrmann, Recent developments in electrospun ZnO nanofibers:  
1340 A short review, *J. Eng. Fiber. Fabr.* 15 (2020) 155892501989968.  
1341 doi:10.1177/1558925019899682.
- 1342 [66] H. Xu, W. Jin, F. Wang, G. Liu, C. Li, J. Wang, H. Zhu, Y. Guo, Formation and  
1343 characterization of polytetrafluoroethylene nanofiber membranes for high-  
1344 efficiency fine particulate filtration, *RSC Adv.* 9 (2019) 13631–13645.  
1345 doi:10.1039/C9RA01643K.
- 1346 [67] Y.-H. Chuang, G.-B. Hong, C.-T. Chang, Study on particulates and volatile  
1347 organic compounds removal with TiO<sub>2</sub> nonwoven filter prepared by  
1348 electrospinning, *J. Air Waste Manage. Assoc.* 64 (2014) 738–742.  
1349 doi:10.1080/10962247.2014.889614.
- 1350 [68] N. Vitchuli, Q. Shi, J. Nowak, M. McCord, M. Bourham, X. Zhang, Electrospun  
1351 ultrathin nylon fibers for protective applications, *J. Appl. Polym. Sci.* 116 (2010)  
1352 2181–2187. doi:10.1002/APP.31825.
- 1353 [69] R.S. Barhate, C.K. Loong, S. Ramakrishna, Preparation and characterization of  
1354 nanofibrous filtering media, *J. Memb. Sci.* 283 (2006) 209–218.  
1355 doi:10.1016/J.MEMSCI.2006.06.030.
- 1356 [70] E. Scholten, L. Bromberg, G.C. Rutledge, T.A. Hatton, Electrospun Polyurethane  
1357 Fibers for Absorption of Volatile Organic Compounds from Air, *ACS Appl.*

- 1358 Mater. Interfaces. 3 (2011) 3902–3909. doi:10.1021/am200748y.
- 1359 [71] R. Castro-Muñoz, J. Buera-Gonzalez, O. de la Iglesia, F. Galiano, V. Fíla, M.  
1360 Malankowska, C. Rubio, A. Figoli, C. Tellez, J. Coronas, Towards the dehydration  
1361 of ethanol using pervaporation cross-linked poly(vinyl alcohol)/graphene oxide  
1362 membranes, *J. Memb. Sci.* 582 (2019) 423–434.  
1363 doi:<https://doi.org/10.1016/j.memsci.2019.03.076>.
- 1364 [72] E. Gontarek-Castro, M.K. Rybarczyk, R. Castro-Muñoz, M. Morales-Jiménez, B.  
1365 Barragán-Huerta, M. Lieder, Characterization of PVDF/Graphene Nanocomposite  
1366 Membranes for Water Desalination with Enhanced Antifungal Activity, *Water*. 13  
1367 (2021) 1279. doi:10.3390/w13091279.
- 1368 [73] P. Heikkilä, A. Taipale, M. Lehtimäki, A. Harlin, Electrospinning of polyamides  
1369 with different chain compositions for filtration application, *Polym. Eng. Sci.* 48  
1370 (2008) 1168–1176. doi:10.1002/pen.21070.
- 1371 [74] H.S. Park, Y.O. Park, Filtration properties of electrospun ultrafine fiber webs,  
1372 *Korean J. Chem. Eng.* 22 (2005) 165–172. doi:10.1007/BF02701480.
- 1373 [75] G. Yin, Q. Zhao, Y. Zhao, Y. Yuan, Y. Yang, The electrospun polyamide 6  
1374 nanofiber membranes used as high efficiency filter materials: Filtration potential,  
1375 thermal treatment, and their continuous production, *J. Appl. Polym. Sci.* 128  
1376 (2013) 1061–1069. doi:10.1002/app.38211.
- 1377 [76] J. Matulevicius, L. Kliucininkas, D. Martuzevicius, E. Krugly, M. Tichonovas, J.  
1378 Baltrusaitis, Design and characterization of electrospun polyamide nanofiber  
1379 media for air filtration applications, *J. Nanomater.* 2014 (2014) 1–13.  
1380 doi:10.1155/2014/859656.
- 1381 [77] Y. Qin, A brief description of textile fibers, in: *Med. Text. Mater.*, Elsevier, 2016:  
1382 pp. 23–42. doi:10.1016/b978-0-08-100618-4.00003-0.
- 1383 [78] H. Fan, Y. Peng, Z. Li, P. Chen, Q. Jiang, S. Wang, Preparation and  
1384 characterization of hydrophobic PVDF membranes by vapor-induced phase  
1385 separation and application in vacuum membrane distillation, *J. Polym. Res.* 20  
1386 (2013) 134. doi:10.1007/s10965-013-0134-4.
- 1387 [79] F. Russo, C. Ursino, E. Avruscio, G. Desiderio, A. Perrone, S. Santoro, F. Galiano,  
1388 A. Figoli, Innovative poly (Vinylidene fluoride) (PVDF) electrospun nanofiber

- 1389 membrane preparation using DMSO as a low toxicity solvent, *Membranes* (Basel).  
1390 10 (2020) 36. doi:10.3390/membranes10030036.
- 1391 [80] R. Zhang, H. Wang, Z. Zhu, R. Chen, X. Chen, J. Zeng, G. Xu, C. Wei, Q. Zhang,  
1392 J. Bai, L. Huang, Fabrication of nanofiber filters for electret air conditioning filter  
1393 via a multi-needle electrospinning, *AIP Adv.* 10 (2020) 105217.  
1394 doi:10.1063/5.0009170.
- 1395 [81] Q. Sun, W.W.F. Leung, Enhanced nano-aerosol loading performance of multilayer  
1396 PVDF nanofiber electret filters, *Sep. Purif. Technol.* 240 (2020) 116606.  
1397 doi:10.1016/j.seppur.2020.116606.
- 1398 [82] D. Pichardo-Romero, Z.P. Garcia-Arce, A. Zavala-Ramirez, R. Castro-Muñoz,  
1399 Current Advances in Biofouling Mitigation in Membranes for Water Treatment :  
1400 An Overview, *Processes.* 8 (2020) 182.
- 1401 [83] F. Galiano, K. Briceño, T. Marino, A. Molino, K.V. Christensen, A. Figoli,  
1402 Advances in biopolymer-based membrane preparation and applications, *J. Memb.*  
1403 *Sci.* 564 (2018) 562–586. doi:10.1016/J.MEMSCI.2018.07.059.
- 1404 [84] R. Castro-Muñoz, J. González-Valdez, New trends in biopolymer-based  
1405 membranes for pervaporation, *Molecules.* 24 (2019).  
1406 doi:10.3390/molecules24193584.
- 1407 [85] I. Singh, S.K. Samal, S. Mohanty, S.K. Nayak, Recent Advancement in Plant Oil  
1408 Derived Polyol-Based Polyurethane Foam for Future Perspective: A Review, *Eur.*  
1409 *J. Lipid Sci. Technol.* 122 (2020) 1900225. doi:10.1002/ejlt.201900225.
- 1410 [86] F. Russo, F. Galiano, A. Iulianelli, A. Basile, A. Figoli, Biopolymers for  
1411 sustainable membranes in CO<sub>2</sub> separation: a review, *Fuel Process. Technol.* 213  
1412 (2021) 106643. doi:10.1016/j.fuproc.2020.106643.
- 1413 [87] C.-L. Lai, J.-T. Chen, Y.-J. Fu, W.-R. Liu, Y.-R. Zhong, S.-H. Huang, W.-S.  
1414 Hung, S.J. Lue, C.-C. Hu, K.-R. Lee, Bio-inspired cross-linking with borate for  
1415 enhancing gas-barrier properties of poly(vinyl alcohol)/graphene oxide composite  
1416 films, *Carbon N. Y.* 82 (2015) 513–522. doi:10.1016/j.carbon.2014.11.003.
- 1417 [88] Y. Zhang, N. Wang, S. Ji, R. Zhang, C. Zhao, J. Li, Metal – organic framework /  
1418 poly ( vinyl alcohol ) nanohybrid membrane for the pervaporation of toluene / n -  
1419 heptane mixtures, *J. Memb. Sci.* 489 (2015) 144–152.



- 1420 doi:10.1016/j.memsci.2015.04.012.
- 1421 [89] N. Wang, S. Ji, J. Li, R. Zhang, G. Zhang, Poly(vinyl alcohol)-graphene oxide  
1422 nanohybrid “pore-filling” membrane for pervaporation of toluene/n-heptane  
1423 mixtures, *J. Memb. Sci.* 455 (2014) 113–120. doi:10.1016/j.memsci.2013.12.023.
- 1424 [90] D. Lv, R. Wang, G. Tang, Z. Mou, J. Lei, J. Han, S. De Smedt, R. Xiong, C.  
1425 Huang, Ecofriendly Electrospun Membranes Loaded with Visible-Light-  
1426 Responding Nanoparticles for Multifunctional Usages: Highly Efficient Air  
1427 Filtration, Dye Scavenging, and Bactericidal Activity, *ACS Appl. Mater.*  
1428 *Interfaces.* 11 (2019) 12880–12889. doi:10.1021/acsami.9b01508.
- 1429 [91] A. Iulianelli, F. Russo, F. Galiano, G. Desiderio, A. Basile, A. Figoli, PLA Easy  
1430 Fil – White-based membranes for CO<sub>2</sub> separation, *Greenh. Gases Sci. Technol.* 9  
1431 (2019) 360–369. doi:10.1002/ghg.1853.
- 1432 [92] A. Iulianelli, F. Russo, F. Galiano, M. Manisco, A. Figoli, Novel bio-polymer  
1433 based membranes for CO<sub>2</sub>/CH<sub>4</sub> separation, *Int. J. Greenh. Gas Control.* 117  
1434 (2022) 103657. doi:10.1016/J.IJGGC.2022.103657.
- 1435 [93] M. Zhu, D. Hua, H. Pan, F. Wang, B. Manshian, S.J. Soenen, R. Xiong, C. Huang,  
1436 Green electrospun and crosslinked poly(vinyl alcohol)/poly(acrylic acid)  
1437 composite membranes for antibacterial effective air filtration, *J. Colloid Interface*  
1438 *Sci.* 511 (2018) 411–423. doi:10.1016/j.jcis.2017.09.101.
- 1439 [94] A. Aluigi, C. Vineis, C. Tonin, C. Tonetti, A. Varesano, G. Mazzuchetti, Wool  
1440 keratin-based nanofibres for active filtration of air and water, *J. Biobased Mater.*  
1441 *Bioenergy.* 3 (2009) 311–319. doi:10.1166/jbmb.2009.1039.
- 1442 [95] R. Fryczkowski, M. Gorczowska, B. Fryczkowska, J. Janicki, The effect of solvent  
1443 on the properties of nanofibres obtained by electrospinning from a mixture of  
1444 poly(3-hydroxybutyrate) and polyaniline, *Synth. Met.* 166 (2013) 14–21.  
1445 doi:10.1016/j.synthmet.2013.01.011.
- 1446 [96] P. Tomietto, P. Loulergue, L. Paugam, J.L. Audic, Biobased polyhydroxyalkanoate  
1447 (PHA) membranes: Structure/performances relationship, *Sep. Purif. Technol.* 252  
1448 (2020) 117419. doi:10.1016/J.SEPPUR.2020.117419.
- 1449 [97] S. Santoro, A.J. Moro, C.A.M. Portugal, J.G. Crespo, I.M. Coelho, J.C. Lima,  
1450 Development of oxygen and temperature sensitive membranes using molecular

- 1451 probes as ratiometric sensor, *J. Memb. Sci.* 514 (2016) 467–475.  
1452 doi:10.1016/j.memsci.2016.05.019.
- 1453 [98] S. Santoro, I.M. Vidorreta, V. Sebastian, A. Moro, I.M. Coelho, J.C. Lima, G.  
1454 Desiderio, G. Lombardo, E. Drioli, R. Mallada, J.G. Crespo, A. Criscuoli, A.  
1455 Figoli, A non-invasive optical method for mapping temperature polarization in  
1456 direct contact membrane distillation, *J. Memb. Sci.* 536 (2017) 156–166.  
1457 doi:10.1016/j.memsci.2017.05.001.
- 1458 [99] F. Yalcinkaya, B. Yalcinkaya, O. Jirsak, Influence of salts on electrospinning of  
1459 aqueous and nonaqueous polymer solutions, *J. Nanomater.* 2015 (2015) 1–12.  
1460 doi:10.1155/2015/134251.
- 1461 [100] X.-H. Qin, E.-L. Yang, N. Li, S.-Y. Wang, Effect of different salts on  
1462 electrospinning of polyacrylonitrile (PAN) polymer solution, *J. Appl. Polym. Sci.*  
1463 103 (2007) 3865–3870. doi:10.1002/app.25498.
- 1464 [101] A.J. Fry, Tetraalkylammonium ions are surrounded by an inner solvation shell in  
1465 strong electron pair donor solvents, *Electrochem. Commun.* 11 (2009) 309–312.  
1466 doi:10.1016/j.elecom.2008.11.039.
- 1467 [102] R. Castro-Muñoz, M.Z. Ahmad, V. Fíla, Tuning of Nano-Based Materials for  
1468 Embedding Into Low-Permeability Polyimides for a Featured Gas Separation,  
1469 *Front. Chem.* 7 (2020) 1–14. doi:10.3389/fchem.2019.00897.
- 1470 [103] Z. Li, L. Jia, Y. Li, T. He, X.M. Li, Ammonia-free preparation of Ag@SiO<sub>2</sub>  
1471 core/shell nanoparticles, *Appl. Surf. Sci.* 345 (2015) 122–126.  
1472 doi:10.1016/J.APSUSC.2015.03.159.
- 1473 [104] O.V. Otieno, E. Csáki, O. Kéri, L. Simon, I.E. Lukács, K.M. Szécsényi, I.M.  
1474 Szilágyi, Synthesis of TiO<sub>2</sub> nanofibers by electrospinning using water-soluble Ti-  
1475 precursor, *J. Therm. Anal. Calorim.* 139 (2020) 57–66. doi:10.1007/s10973-019-  
1476 08398-z.
- 1477 [105] Nasikhudin, E.P. Ismaya, M. Diantoro, A. Kusumaatmaja, K. Triyana, Preparation  
1478 of PVA/TiO<sub>2</sub> Composites Nanofibers by using Electrospinning Method for  
1479 Photocatalytic Degradation, in: *IOP Conf. Ser. Mater. Sci. Eng.*, 2017: p. 012011.  
1480 doi:10.1088/1757-899X/202/1/012011.
- 1481 [106] M. Nováček, N. Nová, N. Nováček, O.O. Jankovsk'ý, J. Jankovsk'ý, J. Luxa, D.

- 1482 Sedmidubsk'ý, S. Sedmidubsk'ý, M. Pumera, V. Fila, M. Lhotka, C. Katě, R. Kí  
1483 Imováimov' ímová, S. Matějková, M. Matějkov, M. Matějková, Z. Ek Sofer,  
1484 Tuning of graphene oxide composition by multiple oxidations for carbon dioxide  
1485 storage and capture of toxic metals, *J. Mater. Chem. A*. 5 (2017) 2739–2748.  
1486 doi:10.1039/C6TA03631G.
- 1487 [107] C. Zhang, L. Yao, Z. Yang, E.S.W. Kong, X. Zhu, Y. Zhang, Graphene Oxide-  
1488 Modified Polyacrylonitrile Nanofibrous Membranes for Efficient Air Filtration,  
1489 *ACS Appl. Nano Mater.* 2 (2019) 3916–3924.  
1490 doi:10.1021/ACSANM.9B00806/SUPPL\_FILE/AN9B00806\_SI\_001.PDF.
- 1491 [108] V. Levdansky, O. Šolcová, K. Friess, P. Izák, Mass Transfer Through Graphene-  
1492 Based Membranes, *Appl. Sci.* 10 (2020) 455. doi:10.3390/app10020455.
- 1493 [109] G. Sandri, D. Miele, A. Faccendini, M.C. Bonferoni, S. Rossi, P. Grisoli, A.  
1494 Taglietti, M. Ruggeri, G. Bruni, B. Vigani, F. Ferrari, Chitosan/glycosaminoglycan  
1495 scaffolds: The role of silver nanoparticles to control microbial infections in wound  
1496 healing, *Polymers (Basel)*. 11 (2019) 1207. doi:10.3390/polym11071207.
- 1497 [110] V. Kadam, Y.B. Truong, J. Schutz, I.L. Kyratzis, R. Padhye, L. Wang, Gelatin/β-  
1498 Cyclodextrin Bio-Nanofibers as respiratory filter media for filtration of aerosols  
1499 and volatile organic compounds at low air resistance, *J. Hazard. Mater.* 403 (2021)  
1500 123841. doi:10.1016/j.jhazmat.2020.123841.
- 1501 [111] F. Russo, R. Castro-Muñoz, F. Galiano, A. Figoli, Unprecedented preparation of  
1502 porous Matrimid® 5218 membranes, *J. Memb. Sci.* (2019).  
1503 doi:10.1016/j.memsci.2019.05.036.
- 1504 [112] Y. Liao, R. Wang, M. Tian, C. Qiu, A.G. Fane, Fabrication of polyvinylidene  
1505 fluoride (PVDF) nanofiber membranes by electro-spinning for direct contact  
1506 membrane distillation, *J. Memb. Sci.* 425–426 (2013) 30–39.  
1507 doi:10.1016/j.memsci.2012.09.023.
- 1508 [113] R.A. Sheldon, Green solvents for sustainable organic synthesis: state of the art,  
1509 *Green Chem.* 7 (2005) 267. doi:10.1039/b418069k.
- 1510 [114] F. Russo, F. Galiano, F. Pedace, F. Aricò, A. Figoli, Dimethyl Isosorbide As a  
1511 Green Solvent for Sustainable Ultrafiltration and Microfiltration Membrane  
1512 Preparation, *ACS Sustain. Chem. Eng.* 8 (2020) 659–668.

- 1513 doi:10.1021/acssuschemeng.9b06496.
- 1514 [115] M.A. Rasool, I.F.J. Vankelecom, Use of  $\gamma$ -valerolactone and glycerol derivatives  
1515 as bio-based renewable solvents for membrane preparation, *Green Chem.* 21  
1516 (2019) 1054–1064. doi:10.1039/C8GC03652G.
- 1517 [116] T. Marino, F. Galiano, A. Molino, A. Figoli, New frontiers in sustainable  
1518 membrane preparation: Cyrene<sup>TM</sup> as green bioderived solvent, *J. Memb. Sci.* 580  
1519 (2019) 224–234. doi:10.1016/j.memsci.2019.03.034.
- 1520 [117] A. Merenda, A.C.C. Bortolassi, J. Rodriguez-Andres, R. Al-Attabi, J.A. Schütz,  
1521 W. Kujawski, H.K. Shon, L.F. Dumée, Hybrid polymer/ionic liquid electrospun  
1522 membranes with tunable surface charge for virus capture in aqueous environments,  
1523 *J. Water Process Eng.* 43 (2021) 102278. doi:10.1016/J.JWPE.2021.102278.
- 1524 [118] F. Russo, M. Tiecco, F. Galiano, R. Mancuso, B. Gabriele, A. Figoli, Launching  
1525 deep eutectic solvents (DESs) and natural deep eutectic solvents (NADESs), in  
1526 combination with different harmless co-solvents, for the preparation of more  
1527 sustainable membranes, *J. Memb. Sci.* 649 (2022) 120387.  
1528 doi:10.1016/J.MEMSCI.2022.120387.
- 1529 [119] R. Castro-Muñoz, F. Galiano, A. Figoli, G. Boczkaj, Deep eutectic solvents – A  
1530 new platform in membrane fabrication and membrane-assisted technologies, *J.*  
1531 *Environ. Chem. Eng.* (2021) 106414. doi:10.1016/j.jece.2021.106414.
- 1532 [120] B. Tylkowski, I. Tsibranska, Overview of main techniques used for membrane  
1533 characterization, *J. Chem. Technol. Metall.* 50 (2015) 3–12.
- 1534 [121] A. Patanaik, V. Jacobs, R.D. Anandjiwala, Performance evaluation of electrospun  
1535 nanofibrous membrane, *J. Memb. Sci.* 352 (2010) 136–142.  
1536 doi:10.1016/j.memsci.2010.02.009.
- 1537 [122] X. Ding, Y. Li, Y. Si, X. Yin, J. Yu, B. Ding, Electrospun polyvinylidene  
1538 fluoride/SiO<sub>2</sub> nanofibrous membranes with enhanced electret property for  
1539 efficient air filtration, *Compos. Commun.* 13 (2019) 57–62.  
1540 doi:10.1016/j.coco.2019.02.008.
- 1541 [123] Z. Shao, J. Jiang, X. Wang, W. Li, L. Fang, G. Zheng, Self-Powered Electrospun  
1542 Composite Nanofiber Membrane for Highly Efficient Air Filtration,  
1543 *Nanomaterials.* 10 (2020) 1706. doi:10.3390/nano10091706.

- 1544 [124] E. Goli, S.R. Peterson, P.H. Geubelle, Instabilities driven by frontal  
1545 polymerization in thermosetting polymers and composites, *Compos. Part B Eng.*  
1546 199 (2020) 108306. doi:10.1016/J.COMPOSITESB.2020.108306.
- 1547 [125] H. Liu, Z. Wang, Z. Wu, S. Zhang, S. Ge, P. Guo, M. Hua, X. Lu, S. Wang, J.  
1548 Zhang, Direct tuning of meso-/micro-porous structure of carbon nanofibers  
1549 confining Sb nanocrystals for advanced sodium and potassium storage, *J. Alloys*  
1550 *Compd.* 833 (2020) 155127. doi:10.1016/J.JALLCOM.2020.155127.
- 1551 [126] J. Cui, T. Lu, F. Li, Y. Wang, J. Lei, W. Ma, Y. Zou, C. Huang, Flexible and  
1552 transparent composite nanofibre membrane that was fabricated via a “green”  
1553 electrospinning method for efficient particulate matter 2.5 capture, *J. Colloid*  
1554 *Interface Sci.* 582 (2021) 506–514. doi:10.1016/J.JCIS.2020.08.075.
- 1555 [127] Z. Yang, X. Zhang, Z. Qin, H. Li, J. Wang, G. Zeng, C. Liu, J. Long, Y. Zhao, Y.  
1556 Li, G. Yan, Airflow Synergistic Needleless Electrospinning of Instant Noodle-like  
1557 Curly Nanofibrous Membranes for High-Efficiency Air Filtration, *Small.* 18  
1558 (2022) 2107250. doi:10.1002/SMLL.202107250.
- 1559 [128] C. Zhang, J. Sun, S. Lyu, Z. Lu, T. Li, Y. Yang, B. Li, H. Han, B. Wu, H. Sun, D.  
1560 Li, J. Huang, D. Sun, Poly(lactic acid)/artificially cultured diatom frustules  
1561 nanofibrous membranes with fast and controllable degradation rates for air  
1562 filtration, *Adv. Compos. Hybrid Mater.* 1 (2022) 1–12. doi:10.1007/S42114-022-  
1563 00474-7/FIGURES/8.
- 1564 [129] Q. Fan, W. Liang, T.T. Fan, X. Li, S.Y. Yan, M. Yu, X. Ning, Y.Z. Long,  
1565 Polyvinylidene fluoride composite nanofibrous filter for high-efficiency PM2.5  
1566 capture, *Compos. Commun.* 22 (2020) 100533.  
1567 doi:10.1016/J.COCO.2020.100533.
- 1568 [130] H.C. Woo, D.K. Yoo, S.H. Jung, Highly Improved Performance of Cotton Air  
1569 Filters in Particulate Matter Removal by the Incorporation of Metal-Organic  
1570 Frameworks with Functional Groups Capable of Large Charge Separation, *ACS*  
1571 *Appl. Mater. Interfaces.* 12 (2020) 28885–28893.  
1572 doi:10.1021/ACSAMI.0C07123/ASSET/IMAGES/LARGE/AM0C07123\_0008.JP  
1573 EG.
- 1574 [131] J. Guo, A. Hanif, J. Shang, B.J. Deka, N. Zhi, A.K. An, PAA@ZIF-8 incorporated

- 1575 nanofibrous membrane for high-efficiency PM2.5 capture, *Chem. Eng. J.* 405  
1576 (2021) 126584. doi:10.1016/J.CEJ.2020.126584.
- 1577 [132] P. Bansal, A. Gangwar, A. Verma, R. Purwar, Novel composite multilayer face  
1578 masks for protection against airborne microorganisms, *Indian J. Fibre Text. Res.*  
1579 47 (2022) 13–19.
- 1580 [133] Y. Fan, T. Li, W. Ge, C. Lou, J. Lin, Flexible <sc>micro–nano</sc> composite  
1581 membranes based on a <sc>two-step</sc> strategy: charge recovery and  
1582 efficient gradient air filtration, *Polym. Int.* (2022). doi:10.1002/pi.6410.
- 1583 [134] H. Zhang, Y. Xie, Y. Song, X. Qin, Preparation of high-temperature resistant poly  
1584 (m-phenylene isophthalamide)/polyacrylonitrile composite nanofibers membrane  
1585 for air filtration, *Colloids Surfaces A Physicochem. Eng. Asp.* 624 (2021) 126831.  
1586 doi:10.1016/J.COLSURFA.2021.126831.
- 1587 [135] H. Shen, Z. Zhou, H. Wang, M. Zhang, M. Han, Y. Shen, D. Shuai,  
1588 Photosensitized Electrospun Nanofibrous Filters for Capturing and Killing  
1589 Airborne Coronaviruses under Visible Light Irradiation, *BioRxiv.* 7 (2021)  
1590 454404. doi:10.1101/2021.07.29.454404.
- 1591 [136] Y. Lou, S. Ding, B. Wang, J. Wang, Q. Sun, X. Jin, X. Li, Controllable  
1592 morphology of electrospun nanofiber membranes with tunable groove structure  
1593 and the enhanced filtration performance for ultrafine particulates, *Nanotechnology.*  
1594 32 (2021) 315708. doi:10.1088/1361-6528/ABF8DA.
- 1595 [137] Y. Chen, M. Shafiq, M. Liu, Y. Morsi, X. Mo, Advanced fabrication for  
1596 electrospun three-dimensional nanofiber aerogels and scaffolds, *Bioact. Mater.* 5  
1597 (2020) 963–979. doi:10.1016/j.bioactmat.2020.06.023.
- 1598 [138] N. Bhardwaj, S.C. Kundu, Electrospinning: A fascinating fiber fabrication  
1599 technique, *Biotechnol. Adv.* 28 (2010) 325–347.  
1600 doi:10.1016/j.biotechadv.2010.01.004.
- 1601 [139] N. Wang, X. Mao, S. Zhang, J. Yu, B. Ding, Electrospun Nanofibers for Air  
1602 Filtration, in: *Electrospinning Nanofabrication Appl.*, 2014: pp. 299–323.  
1603 doi:10.1007/978-3-642-54160-5\_12.
- 1604 [140] W. Zhang, C. Huang, O. Kusmartseva, N.L. Thomas, E. Mele, Electrospinning of  
1605 polylactic acid fibres containing tea tree and manuka oil, *React. Funct. Polym.* 117

- 1606 (2017) 106–111. doi:10.1016/J.REACTFUNCTPOLYM.2017.06.013.
- 1607 [141] Z. Wang, Z. Pan, Preparation of hierarchical structured nano-sized/porous  
1608 poly(lactic acid) composite fibrous membranes for air filtration, *ApSS*. 356 (2015)  
1609 1168–1179. doi:10.1016/J.APSUSC.2015.08.211.
- 1610 [142] D.S. de Almeida, L.D. Martins, E.C. Muniz, A.P. Rudke, R. Squizzato, A. Beal,  
1611 P.R. de Souza, D.P.F. Bonfim, M.L. Aguiar, M.L. Gimenes, Biodegradable  
1612 CA/CPB electrospun nanofibers for efficient retention of airborne nanoparticles,  
1613 *Process Saf. Environ. Prot.* 144 (2020) 177–185. doi:10.1016/J.PSEP.2020.07.024.
- 1614 [143] S. Zhang, H. Liu, N. Tang, J. Ge, J. Yu, B. Ding, Direct electrospinning of high-  
1615 performance membranes based on self-assembled 2D nanoarchitected networks,  
1616 *Nat. Commun.* 2019 101. 10 (2019) 1–11. doi:10.1038/s41467-019-09444-y.
- 1617 [144] S. Zhang, K. Chen, J. Yu, B. Ding, Model derivation and validation for 2D  
1618 polymeric nanonets: Origin, evolution, and regulation, *Polymer (Guildf)*. 74  
1619 (2015) 182–192. doi:https://doi.org/10.1016/j.polymer.2015.08.002.
- 1620 [145] O. Das, R.E. Neisiany, A.J. Capezza, M.S. Hedenqvist, M. Försth, Q. Xu, L. Jiang,  
1621 D. Ji, S. Ramakrishna, The need for fully bio-based facemasks to counter  
1622 coronavirus outbreaks: A perspective, *Sci. Total Environ.* 736 (2020).  
1623 doi:10.1016/J.SCITOTENV.2020.139611.
- 1624 [146] G. Tiliket, D. Le Sage, V. Moules, M. Rosa-Calatrava, B. Lina, J.M. Valleton,  
1625 Q.T. Nguyen, L. Lebrun, A new material for airborne virus filtration, *Chem. Eng.*  
1626 *J.* 173 (2011) 341–351. doi:10.1016/J.CEJ.2011.07.059.
- 1627 [147] G.A. Junter, L. Lebrun, Cellulose-based virus-retentive filters: a review, *Rev.*  
1628 *Environ. Sci. Bio/Technology* 2017 163. 16 (2017) 455–489. doi:10.1007/S11157-  
1629 017-9434-1.
- 1630 [148] J.W. Cherrie, A. Apsley, H. Cowie, S. Steinle, W. Mueller, C. Lin, C.J. Horwell,  
1631 A. Sleuwenhoek, M. Loh, Effectiveness of face masks used to protect Beijing  
1632 residents against particulate air pollution, *Occup. Environ. Med.* 75 (2018) 446–  
1633 452. doi:10.1136/oemed-2017-104765.
- 1634 [149] K.M. Shakya, A. Noyes, R. Kallin, R.E. Peltier, Evaluating the efficacy of cloth  
1635 facemasks in reducing particulate matter exposure, *J. Expo. Sci. Environ.*  
1636 *Epidemiol.* 27 (2017) 352–357. doi:10.1038/jes.2016.42.

- 1637 [150] H. Shen, B. Liu, Y. Chen, X. Zhu, X. Yun, W. Meng, C. Lu, G. Shen, Y. Hu, A.G.  
1638 Russell, K.R. Smith, S. Tao, Individual and population level protection from  
1639 particulate matter exposure by wearing facemasks, *Environ. Int.* 146 (2021)  
1640 106026. doi:10.1016/j.envint.2020.106026.
- 1641 [151] S. Wang, X. Zhao, X. Yin, J. Yu, B. Ding, Electret Polyvinylidene Fluoride  
1642 Nanofibers Hybridized by Polytetrafluoroethylene Nanoparticles for High-  
1643 Efficiency Air Filtration, *ACS Appl. Mater. Interfaces.* 8 (2016) 23985–23994.  
1644 doi:10.1021/acsami.6b08262.
- 1645 [152] Y. Li, X. Yin, Y. Si, J. Yu, B. Ding, All-polymer hybrid electret fibers for high-  
1646 efficiency and low-resistance filter media, *Chem. Eng. J.* 398 (2020) 125626.  
1647 doi:10.1016/j.cej.2020.125626.
- 1648 [153] R. Castro-Muñoz, M.Z. Ahmad, V. Fíla, Tuning of Nano-Based Materials for  
1649 Embedding Into Low-Permeability Polyimides for a Featured Gas Separation,  
1650 *Front. Chem.* 7 (2020) 1–14. doi:10.3389/fchem.2019.00897.
- 1651 [154] L. Nanis, W. Kesselman, Engineering Applications of Current and Potential  
1652 Distributions in Disk Electrode Systems, *J. Electrochem. Soc.* 118 (1971) 454.  
1653 doi:10.1149/1.2408080.
- 1654 [155] A. Salam, T. Hassan, T. Jabri, S. Riaz, A. Khan, K.M. Iqbal, S.U. Khan, M.  
1655 Wasim, M.R. Shah, M.Q. Khan, I.S. Kim, Electrospun Nanofiber-Based  
1656 Viroblock/ZnO/PAN Hybrid Antiviral Nanocomposite for Personal Protective  
1657 Applications, *Nanomaterials.* 11 (2021). doi:10.3390/NANO11092208.
- 1658 [156] S. Karagoz, N. Burak Kiremitler, G. Sarp, S. Pekdemir, S. Salem, A.G. Goksu, M.  
1659 Serdar Onses, I. Sozdutmaz, E. Sahmetlioglu, E.S. Ozkara, A. Ceylan, E. Yilmaz,  
1660 Antibacterial, antiviral, and self-cleaning mats with sensing capabilities based on  
1661 electrospun nanofibers decorated with ZnO nanorods and Ag nanoparticles for  
1662 protective clothing applications, *ACS Appl. Mater. Interfaces.* 13 (2021) 5678–  
1663 5690. doi:10.1021/ACSAMI.0C15606/SUPPL\_FILE/AM0C15606\_SI\_001.PDF.
- 1664 [157] G. Sun, Z. Zhang, A.Y. El-Moghazy, N. Wisuthiphaet, N. Nitin, D. Castillo, B.G.  
1665 Murphy, Daylight-induced antibacterial and antiviral nanofibrous membranes  
1666 containing Vitamin K derivatives for personal protective equipment, *ACS Appl.*  
1667 *Mater. Interfaces.* (2020).



- 1668 doi:10.1021/ACSAMI.0C14883/SUPPL\_FILE/AM0C14883\_SI\_001.PDF.
- 1669 [158] B. Wang, Q. Wang, Y. Wang, J. Di, S. Miao, J. Yu, Flexible Multifunctional  
1670 Porous Nanofibrous Membranes for High-Efficiency Air Filtration, *ACS Appl.*  
1671 *Mater. Interfaces*. 11 (2019) 43409–43415. doi:10.1021/acsami.9b17205.
- 1672 [159] A.C.C. Bortolassi, S. Nagarajan, B. de Araújo Lima, V.G. Guerra, M.L. Aguiar, V.  
1673 Huon, L. Soussan, D. Cornu, P. Miele, M. Bechelany, Efficient nanoparticles  
1674 removal and bactericidal action of electrospun nanofibers membranes for air  
1675 filtration, *Mater. Sci. Eng. C*. 102 (2019) 718–729.  
1676 doi:10.1016/j.msec.2019.04.094.
- 1677 [160] Q. Li, Y. Xu, H. Wei, X. Wang, An electrospun polycarbonate nanofibrous  
1678 membrane for high efficiency particulate matter filtration, *RSC Adv*. 6 (2016)  
1679 65275–65281. doi:10.1039/C6RA12320A.
- 1680 [161] M. Cao, F. Gu, C. Rao, J. Fu, P. Zhao, Improving the electrospinning process of  
1681 fabricating nanofibrous membranes to filter PM2.5, *Sci. Total Environ*. 666 (2019)  
1682 1011–1021.
- 1683 [162] F.I. Khan, A. Kr. Ghoshal, Removal of Volatile Organic Compounds from  
1684 polluted air, *J. Loss Prev. Process Ind*. 13 (2000) 527–545. doi:10.1016/S0950-  
1685 4230(00)00007-3.
- 1686 [163] Y. Alqaheem, A. Alomair, M. Vinoba, A. Pérez, Polymeric Gas-Separation  
1687 Membranes for Petroleum Refining, *Int. J. Polym. Sci.* 2017 (2017) 1–19.  
1688 doi:10.1155/2017/4250927.
- 1689 [164] M. Bodzek, Membrane Techniques in Air Cleaning, *Polish J. Environ. Stud*. 9  
1690 (2000) 1–12. doi:10.1088/1742-6596/1217/1/012046.
- 1691 [165] K. Kimmerle, C.M. Bell, W. Gudernatsch, H. Chmiel, Solvent recovery from air,  
1692 *J. Memb. Sci*. 36 (1988) 477–488. doi:10.1016/0376-7388(88)80037-1.
- 1693 [166] G. Li, K. Knozowska, J. Kujawa, A. Tonkonogovas, A. Stankevičius, W.  
1694 Kujawski, Fabrication of Polydimethylsiloxane (PDMS) Dense Layer on  
1695 Polyetherimide (PEI) Hollow Fiber Support for the Efficient CO<sub>2</sub>/N<sub>2</sub> Separation  
1696 Membranes, *Polym.* 2021, Vol. 13, Page 756. 13 (2021) 756.  
1697 doi:10.3390/POLYM13050756.
- 1698 [167] G. Rebollar-Perez, E. Carretier, N. Lesage, P. Moulin, Volatile organic compound

- 1699 (VOC) removal by vapor permeation at low VOC concentrations: Laboratory scale  
1700 results and modeling for scale up, *Membranes (Basel)*. 1 (2011) 80–90.  
1701 doi:10.3390/membranes1010080.
- 1702 [168] E.N. Iftekhhar, V. Priesemann, R. Balling, S. Bauer, P. Beutels, A. Calero Valdez,  
1703 S. Cuschieri, T. Czypionka, U. Dumpis, E. Glaab, E. Grill, C. Hanson, P.  
1704 Hotulainen, P. Klimek, M. Kretzschmar, T. Krüger, J. Krutzinna, N. Low, H.  
1705 Machado, C. Martins, M. McKee, S.B. Mohr, A. Nassehi, M. Perc, E. Petelos, M.  
1706 Pickersgill, B. Prainsack, J. Rocklöv, E. Schernhammer, A. Staines, E. Szczurek,  
1707 S. Tsiodras, S. Van Gucht, P. Willeit, A look into the future of the COVID-19  
1708 pandemic in Europe: an expert consultation, *Lancet Reg. Heal. - Eur.* 8 (2021)  
1709 100185. doi:10.1016/j.lanepe.2021.100185.
- 1710 [169] J. Woods, Membrane processes for heating, ventilation, and air conditioning,  
1711 *Renew. Sustain. Energy Rev.* 33 (2014) 290–304. doi:10.1016/j.rser.2014.01.092.
- 1712 [170] Y. Ju, T. Han, J. Yin, Q. Li, Z. Chen, Z. Wei, Y. Zhang, L. Dong, Bumpy  
1713 structured nanofibrous membrane as a highly efficient air filter with antibacterial  
1714 and antiviral property, *Sci. Total Environ.* 777 (2021) 145768.  
1715 doi:10.1016/J.SCITOTENV.2021.145768.
- 1716 [171] A.E. Erickson, D. Edmondson, F.C. Chang, D. Wood, A. Gong, S.L. Levensgood,  
1717 M. Zhang, High-throughput and high-yield fabrication of uniaxially-aligned  
1718 chitosan-based nanofibers by centrifugal electrospinning, *Carbohydr. Polym.* 134  
1719 (2015) 467–474. doi:10.1016/j.carbpol.2015.07.097.
- 1720 [172] X. Zhang, Y. Lu, Centrifugal spinning: An alternative approach to fabricate  
1721 nanofibers at high speed and low cost, *Polym. Rev.* 54 (2014) 677–701.  
1722 doi:10.1080/15583724.2014.935858.
- 1723 [173] L. Persano, A. Camposeo, C. Tekmen, D. Pisignano, Industrial upscaling of  
1724 electrospinning and applications of polymer nanofibers: A review, *Macromol.*  
1725 *Mater. Eng.* 298 (2013) 504–520. doi:10.1002/mame.201200290.
- 1726 [174] Z. Yang, H. Peng, W. Wang, T. Liu, Crystallization behavior of poly( $\epsilon$ -  
1727 caprolactone)/layered double hydroxide nanocomposites, *J. Appl. Polym. Sci.* 116  
1728 (2010) 2658–2667. doi:10.1002/app.
- 1729 [175] B. Duan, C. Dong, X. Yuan, K. Yao, Electrospinning of chitosan solutions in

- 1730 acetic acid with poly(ethylene oxide), *J. Biomater. Sci. Polym. Ed.* 15 (2004) 797–  
1731 811. doi:10.1163/156856204774196171.
- 1732 [176] L. Soffer, X. Wang, X. Zhang, J. Kluge, L. Dorfmann, D.L. Kaplan, G. Leisk,  
1733 Silk-based electrospun tubular scaffolds for tissue-engineered vascular grafts, *J.*  
1734 *Biomater. Sci. Polym. Ed.* 19 (2008) 653–664. doi:10.1163/156856208784089607.
- 1735 [177] H. Souzandeh, Y. Wang, W.H. Zhong, Greenano-filters: Fine nanofibers of  
1736 natural protein for high efficiency filtration of particulate pollutants and toxic  
1737 gases, *RSC Adv.* 6 (2016) 105948–105956. doi:10.1039/c6ra24512a.
- 1738 [178] M.O. Sahto, *Electrospun Nanofibers for Highly Efficient Air Filter Applications*,  
1739 Inovenso Ltd. Co. (2021).
- 1740 [179] K. Graham, M. Ouyang, T. Raether, T. Grafe, B. Mcdonald, P. Knauf, *Polymeric*  
1741 *Nanofibers in Air Filtration Applications*, Fifteenth Annu. Tech. Conf. Expo Am.  
1742 *Filtr. Sep. Soc.* (2002) 9–12.
- 1743 [180] S. Omer, L. Forgách, R. Zelkó, I. Sebe, *Scale-up of Electrospinning: Market*  
1744 *Overview of Products and Devices for Pharmaceutical and Biomedical Purposes*,  
1745 *Pharmaceutics.* 13 (2021). doi:10.3390/pharmaceutics13020286.
- 1746 [181] Y. Liu, L. Zhang, X.-F. Sun, J. Liu, J. Fan, D.-W. Huang, *Multi-jet electrospinning*  
1747 *via auxiliary electrode*, *Mater. Lett.* 141 (2015) 153–156.  
1748 doi:<https://doi.org/10.1016/j.matlet.2014.11.079>.
- 1749 [182] Y. Xu, X. Li, H.-F. Xiang, Q.-Q. Zhang, X.-X. Wang, M. Yu, L.-Y. Hao, Y.-Z.  
1750 Long, *Large-Scale Preparation of Polymer Nanofibers for Air Filtration by a New*  
1751 *Multineedle Electrospinning Device*, *J. Nanomater.* 2020 (2020) 4965438.  
1752 doi:10.1155/2020/4965438.
- 1753 [183] H.-Y. Kim and J.-C. Park, *Conjugate electrospinning devices, conjugate nonwoven*  
1754 *and filament comprising nanofibers prepared by using the same*, US20080102145,  
1755 2008.
- 1756 [184] G. Zheng, J. Jiang, D. Chen, J. Liu, Y. Liu, J. Zheng, X. Wang, W. Li, *Multinozzle*  
1757 *high efficiency electrospinning with the constraint of sheath gas*, *J. Appl. Polym.*  
1758 *Sci.* 136 (2019) 47574. doi:<https://doi.org/10.1002/app.47574>.
- 1759 [185] Y. Zheng, R.H. Gong, Y. Zeng, *Multijet motion and deviation in electrospinning*,  
1760 *RSC Adv.* 5 (2015) 48533–48540. doi:10.1039/C5RA06049D.

- 1761 [186] G. Kim, Y.-S. Cho, W.D. Kim, Stability analysis for multi-jets electrospinning  
1762 process modified with a cylindrical electrode, *Eur. Polym. J.* 42 (2006) 2031–  
1763 2038. doi:<https://doi.org/10.1016/j.eurpolymj.2006.01.026>.
- 1764 [187] H.S. SalehHudin, E.N. Mohamad, W.N.L. Mahadi, A.M. Afifi, Multiple-jet  
1765 electrospinning methods for nanofiber processing: A review, *Mater. Manuf.*  
1766 *Process.* 33 (2018) 479–498. doi:10.1080/10426914.2017.1388523.
- 1767 [188] Z. Zhu, P. Wu, Z. Wang, G. Xu, H. Wang, X. Chen, R. Wang, W. Huang, R. Chen,  
1768 X. Chen, Z. Liu, Optimization of electric field uniformity of multi-needle  
1769 electrospinning nozzle, *AIP Adv.* 9 (2019) 105104. doi:10.1063/1.5111936.
- 1770 [189] Nanospinner 416 Industrial Electrospinning/Spraying Line, (n.d.).
- 1771 [190] H. Niu, T. Lin, Fiber Generators in Needleless Electrospinning, *J. Nanomater.*  
1772 2012 (2012). doi:10.1155/2012/725950.
- 1773 [191] Nanospider™ NS 8S1600U, (n.d.).
- 1774 [192] G. Zheng, J. Jiang, X. Wang, W. Li, J. Liu, G. Fu, L. Lin, Nanofiber membranes  
1775 by multi-jet electrospinning arranged as arc-array with sheath gas for  
1776 electro dialysis applications, *Mater. Des.* 189 (2020) 108504.  
1777 doi:<https://doi.org/10.1016/j.matdes.2020.108504>.
- 1778 [193] A. Ahmed, J. Yin, L. Xu, F. Khan, High-throughput free surface electrospinning  
1779 using solution reservoirs with different radii and its preparation mechanism study,  
1780 *J. Mater. Res. Technol.* 9 (2020) 9059–9072.  
1781 doi:<https://doi.org/10.1016/j.jmrt.2020.06.025>.
- 1782 [194] K. Koenig, K. Beukenberg, F. Langensiepen, G. Seide, A new prototype melt-  
1783 electrospinning device for the production of biobased thermoplastic sub-  
1784 microfibers and nanofibers, *Biomater. Res.* 23 (2019) 10. doi:10.1186/s40824-019-  
1785 0159-9.
- 1786 [195] S. Santoro, I. Vidorreta, I. Coelho, J. Lima, G. Desiderio, G. Lombardo, E.  
1787 Drioli, R. Mallada, J. Crespo, A. Criscuoli, A. Figoli, Experimental Evaluation of  
1788 the Thermal Polarization in Direct Contact Membrane Distillation Using  
1789 Electrospun Nanofiber Membranes Doped With Molecular Probes, *Molecules.* 24  
1790 (2019) 638. doi:10.3390/molecules24030638.
- 1791 [196] J. Avossa, G. Herwig, C. Toncelli, F. Itel, R.M. Rossi, Electrospinning based on

1792 benign solvents: current definitions{,} implications and strategies, Green Chem.  
1793 24 (2022) 2347–2375. doi:10.1039/D1GC04252A.

1794 [197] T.D. Brown, P.D. Dalton, D.W. Hutmacher, Melt electrospinning today: An  
1795 opportune time for an emerging polymer process, Prog. Polym. Sci. 56 (2016)  
1796 116–166. doi:https://doi.org/10.1016/j.progpolymsci.2016.01.001.

1797 [198] H. Zhou, T.B. Green, Y.L. Joo, The thermal effects on electrospinning of  
1798 polylactic acid melts, Polymer (Guildf). 47 (2006) 7497–7505.  
1799 doi:10.1016/j.polymer.2006.08.042.

1800 [199] J. Fang, L. Zhang, D. Sutton, X. Wang, T. Lin, Needleless Melt-Electrospinning of  
1801 Polypropylene Nanofibres, J. Nanomater. 2012 (2012) 382639.  
1802 doi:10.1155/2012/382639.

1803 [200] Y. Shen, S. Xia, P. Yao, R. Hugh Gong, Q. Liu, B. Deng, Structure regulation and  
1804 properties of melt-electrospinning composite filter materials, Fibers Polym. 18  
1805 (2017) 1568–1579. doi:10.1007/s12221-017-7172-1.

1806 [201] A. Figoli, T. Marino, S. Simone, E. Di Nicolò, X.-M. Li, T. He, S. Tornaghi, E.  
1807 Drioli, Towards non-toxic solvents for membrane preparation: a review, Green  
1808 Chem. 16 (2014) 4034. doi:10.1039/C4GC00613E.

1809 [202] D. Lv, M. Zhu, Z. Jiang, S. Jiang, Q. Zhang, R. Xiong, Huang Chaobo, Green  
1810 Electrospun Nanofibers and Their Application in Air Filtration, Macromol. Mater.  
1811 Engeneering. 303 (2018) 1–18. doi:10.1002/mame.201800336.

1812

1813

1814